



Standard Specification for Copper-Beryllium Alloy Wire¹

This standard is issued under the fixed designation B197/B197M; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

This standard has been approved for use by agencies of the U.S. Department of Defense.

1. Scope*

1.1 This specification establishes the requirements for copper-beryllium alloy wire in coils, spools, or other than straight lengths, of any uniform cross section. Copper Alloy UNS Nos. C17200 and C17300² are included.

1.2 Unless otherwise required, Copper Alloy UNS No. C17200 shall be the alloy furnished whenever Specification B197/B197M is specified without any alloy designation.

1.3 The values stated in either inch-pounds or SI units are to be regarded separately as the standard. Within the text, the SI units are shown in brackets. The values stated in each system are not exact equivalents; therefore, each system shall be used independently of the other. Combining values from the two systems may result in nonconformance with the specification.

1.4 The following safety hazard caveat pertains only to the test methods described in this specification:

1.4.1 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

2. Referenced Documents

2.1 ASTM Standards:³

B194 Specification for Copper-Beryllium Alloy Plate, Sheet, Strip, and Rolled Bar

B250/B250M Specification for General Requirements for Wrought Copper Alloy Wire

¹ This specification is under the jurisdiction of ASTM Committee B05 on Copper and Copper Alloys and is the direct responsibility of Subcommittee B05.02 on Rod, Bar, Wire, Shapes and Forgings.

Current edition approved April 1, 2013. Published April 2013. Originally approved in 1945. Last previous edition approved in 2007 as B197/B197M – 07. DOI: 10.1520/B0197_B0197M-07R13.

² The UNS system for copper and copper alloys (see Practice E527) is a simple expansion of the former standard designation system accomplished by the addition of a prefix “C” and a suffix “00.” The suffix can be used to accommodate composition variations of the base alloy.

³ For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard’s Document Summary page on the ASTM website.

B601 Classification for Temper Designations for Copper and Copper Alloys—Wrought and Cast

B846 Terminology for Copper and Copper Alloys

E8 Test Methods for Tension Testing of Metallic Materials

E8M Test Methods for Tension Testing of Metallic Materials [Metric] (Withdrawn 2008)⁴

E112 Test Methods for Determining Average Grain Size

E527 Practice for Numbering Metals and Alloys in the Unified Numbering System (UNS)

3. General Requirements

3.1 The following sections of Specification **B250/B250M** constitute a part of this specification:

- 3.1.1 Terminology,
- 3.1.2 Material and Manufacturer,
- 3.1.3 Chemical Composition,
- 3.1.4 Dimensions and Permissible Variations,
- 3.1.5 Workmanship, Finish, and Appearance,
- 3.1.6 Sampling,
- 3.1.7 Number of Tests and Retests,
- 3.1.8 Specimen Preparation,
- 3.1.9 Test Methods,
- 3.1.10 Significance of Numerical Limits,
- 3.1.11 Inspection,
- 3.1.12 Rejection and Reheating,
- 3.1.13 Certification,
- 3.1.14 Mill Test Report, and
- 3.1.15 Packaging and Package Marking.

3.2 In addition, when a section with a title identical to that referenced in 3.1 above, appears in this specification, it contains additional requirements which supplement those appearing in Specification **B250/B250M**.

4. Terminology

4.1 For definitions of terms related to copper and copper alloys, refer to Terminology **B846**.

4.2 Definitions of Terms Specific to This Standard:

4.2.1 *grain count*—the number of grains per stock thickness.

⁴ The last approved version of this historical standard is referenced on www.astm.org.

*A Summary of Changes section appears at the end of this standard

5. Ordering Information

5.1 Include the following information when placing orders for product under this specification, as applicable:

- 5.1.1 ASTM specification designation and year of issue,
- 5.1.2 Copper (Alloy) UNS No. designation,
- 5.1.3 Temper (Section 7),
- 5.1.4 Dimensions, diameter, or distance between parallel surfaces, and length if applicable,
- 5.1.5 Form of material: cross section such as round, hexagonal, octagonal, oval, trapezoidal, and so forth,
- 5.1.6 How furnished: coils spools, reels, or bucks, and specific lengths with or without ends or stock lengths with or without ends if applicable, and
- 5.1.7 When material is ordered for agencies of the U.S. Government (see Section 15).

5.2 The following options are available and should be specified in the contract or purchase order when required:

- 5.2.1 Type of edge: square corners, round edge, full-rounded edge (see the Edge Contours section in the Dimensions and Permissible Variations Section of Specification **B250/B250M**),
- 5.2.2 Grain size (Section 9.1),
- 5.2.3 Grain count (Section 9.2),
- 5.2.4 Mechanical properties (tensile strength and hardness) (Section 10),
- 5.2.5 Bend test (after precipitation heat treatment) (11.1),
- 5.2.6 Heat identification or traceability details,
- 5.2.7 Special packaging requirements,
- 5.2.8 Certification, and
- 5.2.9 Mill test report.

6. Chemical Composition

6.1 The material shall conform to the chemical composition requirements prescribed in **Table 1** for copper alloy UNS No. designation specified in the ordering information.

6.2 These composition limits do not preclude the presence of other elements. Limits for unnamed elements may be established and analysis required by agreement between the manufacturer or supplier and purchaser.

6.3 Copper is customarily given as remainder, but may be taken as the difference between the sum of all elements analyzed and 100 %.

6.4 When all the elements in **Table 1** are determined, the sum of results shall be 99.5 % min.

TABLE 1 Chemical Requirements

Element	Composition, %	
	Copper Alloy UNS No. C17200	Copper Alloy UNS No. C17300
Beryllium	1.80–2.00	1.80–2.00
Additive elements:		
Nickel + cobalt, min	0.20	0.20
Nickel + cobalt + iron, max	0.6	0.6
Lead	...	0.20–0.6
Aluminum, max	0.20	0.20
Silicon, max	0.20	0.20
Copper	remainder	remainder

7. Temper

7.1 The standard tempers available under this specification and as specified in Practice **B601** are TB00 (solution heat treated), or with varying degrees of cold work TD00 to TD04 to be precipitation heat treated by the user. Also available are products already precipitation heat-treated by the manufacturer, tempers TF00 (AT), TH01 to TH04. These products meet property requirements in **Tables 2 and 3** and generally do not require further heat treatment by the user.

7.2 The pretempered product TL08 shown in **Table 4** is prepared by the manufacturer for special applications.

NOTE 1—Special or nonstandard tempers are subject to negotiation between the supplier and the purchaser.

8. Precipitation Heat Treatment

8.1 The precipitation heat treatment is normally performed by the purchaser after forming. The heat treatment specified herein is applicable to mill products. Other treatment times and temperatures may be preferable for end products made from this material.

8.2 Conformance to the TF00 (AT) through TH04 (HT) specification limits shown in **Tables 2 and 3** for products supplied in the TB00 (A) through TD04 (H) tempers, shall be determined by testing test specimens heat-treated at a uniform temperature of 600 to 625°F [316 to 329°C] for the times shown in **Table 5**.

8.3 Special combinations of properties such as increased ductility, electrical conductivity, dimensional accuracy, endurance life, and resistance to elastic drift and hysteresis in springs may be obtained by special precipitation-hardening heat treatments. The mechanical requirements of **Tables 2 and 3** do not apply to such special heat treatments.

9. Physical Property Requirements

9.1 *Grain Size*—The average grain size of each of two samples of rectangular other than square wire, in thicknesses

TABLE 2 Tensile Strength Requirements for Round, Hexagonal, Octagonal, and Square Wire After Precipitation Heat Treatment (See 11.2)

Temper Designation		Tensile Strength, ^A	
Standard	Former	ksi ^B	MPa
TF00	Precipitation hardened (AT)	160–200 ^C	[1105–1380]
TH01	¼ hard and precipitation heat treated (¼ HT)	175–210 ^C	[1205–1450]
TH02	½ hard and precipitation heat treated (½ HT)	185–215	[1275–1480]
TH03	¾ hard and precipitation heat treated (¾ HT) ^D	190–230	[1310–1585]
TH04	Hard and precipitation heat treated (HT)	195–230	[1345–1585]

^AThese values apply to mill products (see 11.2).

^Bksi = 1000 psi.

^CCorrected editorially.

^DTH03 (¾ HT) condition is generally available up to 0.080 in. [2.0 mm], inclusive, in diameter or distance between parallel surfaces.

TABLE 3 Mechanical Property Requirements^A for Rectangular Other Than Square Wire After Precipitation Heat Treatment (See 11.2)

NOTE 1—Rockwell hardness values apply only to direct determinations, not converted values.

Standard	Temper Designation		Tensile Strength ^A		Rockwell hardness ^B		
	Former		ksi ^C	MPa	C Scale, min	30N Scale, min	15N Scale, min
TF00	Precipitation hardened (AT)		165–190	[1140–1310]	36	56	78
TH01	¼ hard and precipitation heat treated (¼ H)		175–200	[1210–1380]	38	58	79
TH02	½ hard and precipitation heat treated (½ HT)		185–210	[1280–1450]	39	59	79.5
TH04	Hard and precipitation heat treated (HT)		190–215	[1310–1480]	40	60	80

^AThe upper limit in the tensile strength column applies to material thicker than 0.020 in. [0.50 mm].

^BThe thickness of material that may be tested in the case of the Rockwell hardness scales is as follows:

C Scale	0.032 in. and over	[0.80 mm and over]
30N	0.020 to 0.032 in., excl	[0.50 to 0.80 mm, excl]
15N Scale	0.015 to 0.020 in., excl	[0.38 to 0.50 mm, excl]

^Cksi = 1000 psi.

TABLE 4 Tensile Strength Requirements for Round, Hexagonal, Octagonal, and Square Wire After Mill Hardening (Pretempered TL08-Former Designation XHT)

Diameter or Distance Between Parallel Surfaces, in.	Tensile Strength, ksi ^A	Diameter or Distance Between Parallel Surfaces, mm	Tensile Strength, MPa
Over 0.050 to 0.075, excl	140–165	[Over 1.2 to 1.9, excl]	[965–1140]
0.075 to 0.100, excl	120–140	[1.9 to 2.5, excl]	[830–965]
0.100 to 0.114, incl	115–130	[2.5 to 2.9, excl]	[795–895]

^Aksi = 1000 psi.

TABLE 5 Standard Precipitation Heat Treatment Time for Acceptance Test

Temper Designation Before Hardening		Time at 600 to 625°F, h [316–329°C]	
Standard	Former	Round, Hexagonal, Octagonal, and Square Wire	Rectangular Other Than Square Wire
TB00	Solution heat treated (annealed)	3	3
TD01	Quarter-hard	2	2½
TD02	Half-hard	1½	2
TD03	Three-quarter hard	1	2
TD04	Hard	1	2

over 0.010 in. [0.25 mm] taken after precipitation heat treatment (see 8.2), shall not exceed the limits specified in Table 6 when determined in accordance with Test Methods E112 and taken on a plane perpendicular to the direction of rolling or drawing.

9.2 Grain Count:

9.2.1 The grain count of each of two samples of rectangular other than square wire, in thicknesses over 0.004 to 0.010 in. [0.10 to 0.25 mm] inclusive, taken after precipitation heat

treatment (see 8.2), shall not be less than the limits specified in Table 7 when tested in accordance with 9.2.2.

9.2.2 Grain count is the number of grains per stock thickness, averaged for five locations one stock thickness apart. Grain count shall be determined in a plane perpendicular to the direction of rolling or drawing.

10. Property Requirements

10.1 The property requirement basis for acceptance or rejection for product in all forms and tempers is listed in the Tables as follows:

10.1.1 For round, hexagonal, octagonal, and square wire:

10.1.1.1 In the solution heat-treated, and solution heat-treated and cold worked conditioning—Table 8,

10.1.1.2 After precipitation heat-treatment—Table 2,

10.1.1.3 In the pretempered (mill-hardened) condition—Table 4.

10.1.2 For rectangle other than square wire:

10.1.2.1 Rockwell hardness shall be the basis of acceptance or rejection for wire 0.015 in. (0.040 mm) thick or over unless otherwise specified—Table 9.

10.1.2.2 For wire less than 0.015 in. (0.40 mm), or when agreement on hardness tests cannot be reached, the tensile strength requirements shall apply.

TABLE 6 Grain Size Requirements for Rectangular Other Than Square Wire

Thickness, in.	Maximum Average Grain Size, mm	Thickness, mm
Over 0.010 to 0.030, incl	0.035	[Over 0.25 to 0.75, incl]
Over 0.030 to 0.090, incl	0.045	[Over 0.75 to 2.30, incl]
Over 0.090 to 0.188, incl	0.060	[Over 2.3 to 4.8, incl]

TABLE 7 Grain Count Requirements for Rectangular Other Than Square Wire

Thickness, in.	Minimum Number of Grains	Thickness, mm
Over 0.004 to 0.006, incl	6	[Over 0.10 to 0.15, incl]
Over 0.006 to 0.008, incl	7	[Over 0.15 to 0.20, incl]
Over 0.008 to 0.010, incl	8	[Over 0.20 to 0.25, incl]

TABLE 8 Tensile Strength Requirements for Round, Hexagonal, Octagonal, and Square Wire

Standard	Temper Designation		Tensile Strength,	
	Former		ksi ^A	MPa
TB00	Solution heat treated (annealed) (A)		58–78	[400–540]
TD01	Quarter-hard (¼ H)		90–115	[620–795]
TD02	Half-hard (½ H)		110–135	[760–930]
TD03	Three-quarter hard ^B (¾ H)		130–155	[895–1070]
TD04	Hard (H)		140–165	[965–1140]

^Aksi = 1000 psi.

^BTD03 (¾ H) and TD04 (H) tempers are generally available up to 0.080 in. [2.0 mm], inclusive, in diameter or distance between parallel surfaces.

10.1.2.3 In the solution heat-treated and solution heat-treated and cold-worked condition—[Table 9](#).

10.1.2.4 After precipitation heat-treatment—[Table 3](#).

11. Performance Requirements

11.1 Bend Tests Requirements:

11.1.1 Round, hexagonal, octagonal, and square wire in tempers shown in [Table 8](#) shall withstand being bent cold through five successive turns on a radius equal to the diameter or distance between parallel surfaces of the wire.

11.1.1.1 The specimens shall not develop cracks visible to the unaided eye.

11.2 When specified (see [5.2.5](#)), rectangular other than square wire after precipitation heat treatment, according to [Table 5](#) and having dimensions of 0.004 to 0.020 in. [0.10 to 0.50 mm], inclusive in thickness, and having a width of at least four times its thickness, shall conform to the requirements specified in [Table 10](#) when tested in accordance with [14.2](#).

12. Dimensions and Permissible Variations

12.1 The dimensions and tolerances for material covered by this specification shall be as specified in the current edition of Specification [B250/B250M](#), with particular reference to the Dimensions and Permissible Variations Section and the following tables of that specification:

12.2 *Diameter or Distance Between Parallel Surfaces*—See [6.2](#), [Table 2](#).

12.3 *Thickness*⁵—See [6.3](#), [Table 4](#),

⁵ Applicable to flat (rectangular and square) wire only.

12.4 *Width*⁵—See [6.4](#), [Table 6](#),

12.5 *Length*⁵—See [6.5](#), [Tables 7](#) and [8](#),

12.6 *Straightness*⁵—See [6.6](#), [Table 9](#).

13. Specimen Preparation

13.1 Tension test specimens, when required, shall be prepared in a full cross-section area if practicable. Full cross-section or machined specimens shall be as specified in Test Methods [E8](#) and [E8M](#).

NOTE 2—Mechanical property data determined on other than round cross section, for sizes under 0.125 in. [3.2 mm], may be compromised and be inaccurate due to the stress riser effect on the corner.

14. Test Methods

14.1 *Chemical Analysis*—In case of dispute, the test method in Specification [B194](#) Annex shall be used for determining chemical requirements for the elements and ranges shown in [Table 1](#).

14.2 *Bend Test*—Five specimens of any convenient length that have been precipitation heat treated in accordance with [Table 5](#), shall be clamped firmly between a flat jaw and test radius, as shown in [Fig. 1](#). The test radius shall be within $\pm 6\%$ of the specimen thickness up to 0.010 in. [0.25 mm], and within $\pm 4\%$ of the specimen thickness 0.010 in. [0.25 mm] and over. The test specimen shall be bent approximately 90 degrees around the test radius, using a tangential wiping motion with adequate radial pressure to ensure continuous contact between the specimen and the test radius. To pass the bend test, at least four out of five, and at least 80 % of the total specimens tested from a lot must withstand the 90 degree bend without visible cracks or fractures when observed in the full 90 degree bend position.

15. Orders for U.S. Government Agencies

15.1 Orders for agencies of the U.S. Government shall conform to the special government requirements stipulated in the Supplement Requirements Section in Specification [B250/B250M](#).

16. Keywords

16.1 copper-beryllium; wire

TABLE 9 Mechanical Property Requirements for Rectangular Other Than Square Wire

NOTE 1—Hardness values shown apply only to direct determinations, not converted values.

Standard	Temper Designation Former	Tensile Strength		Elongation ^A in 2 in. [50 mm], min, %	Rockwell Hardness ^B		
		ksi ^C	MPa		B Scale	30T Scale	15T Scale
TB00	Solution heat treated (annealed) (A)	60–78	[410–510]	35	45–78	46–67	75–85
TD01	Quarter-hard (¼ H)	75–88	[510–610]	10	68–90	62–75	83–89
TD02	Half-hard (½ H)	85–100	[590–690]	5	88–96	74–79	88–91
TD04	Hard (H)	100–120	[690–830]	2	96–102	79–83	91–94

^AElongation requirement applies only to wire 0.004 in. [0.50 mm] and thicker.

^BThe thickness of material that may be tested in the case of the Rockwell hardness scales is as follows:

B Scale	0.032 in. and over	[0.80 mm and over]
30T Scale	0.020 to 0.032 in., excl	[0.50 to 0.80 mm, excl]
15T Scale	0.015 to 0.020 in., excl	[0.38 to 0.50 mm, excl]

^Cksi = 1000 psi.

TABLE 10 Bend Test Requirements for Rectangular Other Than Square Wire

Standard	Temper Designation Former	Test Radius ^A
TH01	¼ hard and precipitation heat treated (¼ HT)	6 <i>t</i>
TH02	½ hard and precipitation heat treated (½ HT)	9 <i>t</i>
TH04	Hard and precipitation heat treated (HT)	15 <i>t</i>

^AThe *t* refers to the measured average stock thickness to be tested.

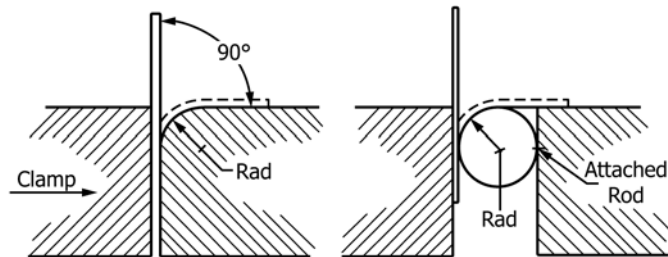


FIG. 1 Methods for Clamping Specimen to Radius for Bend Test

SUMMARY OF CHANGES

Committee B05 has identified the location of selected changes to this standard since the last issue B197/B197M-01) that may impact the use of this standard. (Approved Oct. 1, 2007.)

(1) In this five-year review there were no technical changes, only some editorial changes to some metric values and one temper typo correction.

(2) Corrected Chemistry in Table 1 from Lead 0.60 to 0.6 to conform to CDA limits.

 **B197/B197M – 07 (2013)**

ASTM International takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.

This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.

This standard is copyrighted by ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (www.astm.org). Permission rights to photocopy the standard may also be secured from the Copyright Clearance Center, 222 Rosewood Drive, Danvers, MA 01923, Tel: (978) 646-2600; <http://www.copyright.com/>