



Designation: D1042 – 12 (Reapproved 2017)

Standard Test Method for Linear Dimensional Changes of Plastics Caused by Exposure to Heat and Moisture¹

This standard is issued under the fixed designation D1042; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

1. Scope

1.1 This test method is designed to provide a means for measuring in plastic specimens the dimensional changes such as shrinkage or expansion, developed under specific heat and water conditionings.

1.2 The values stated in SI units are to be regarded as standard. The values given in parentheses are mathematical conversions to inch-pound units that are provided for information only and are not considered standard.

1.3 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

NOTE 1—There is no known ISO equivalent to this standard.

1.4 *This international standard was developed in accordance with internationally recognized principles on standardization established in the Decision on Principles for the Development of International Standards, Guides and Recommendations issued by the World Trade Organization Technical Barriers to Trade (TBT) Committee.*

2. Referenced Documents

2.1 *ASTM Standards:*²

D883 Terminology Relating to Plastics

D5947 Test Methods for Physical Dimensions of Solid Plastics Specimens

3. Terminology

3.1 *Definitions:* Definitions of terms applying to this test method appear in Terminology D883.

¹ This test method is under the jurisdiction of ASTM Committee D20 on Plastics and is the direct responsibility of Subcommittee D20.50 on Durability of Plastics. Current edition approved Aug. 1, 2017. Published August 2017. Originally published as D1042 – 49T. Last previous edition D1042 – 12. DOI: 10.1520/D1042-12R17.

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

4. Significance and Use

4.1 This test method is intended only as a convenient test method for measurement of linear dimensional changes in plastics subjected to defined conditions of test as outlined in Sections 7 and 8.

5. Apparatus

5.1 *Scriber*, so constructed that two sharp needle points are rigidly separated by 100 ± 0.2 mm. The scriber, as shown in Fig. 1, consists of two sharp steel needles, approximately 1.5 mm in diameter. The needles are to be inserted in drilled holes with their axes parallel to each other and perpendicular to and intersecting the long axis of a stainless steel rigid rod or bar stock, 125 ± 5 mm in length. The needles' points shall extend 6 ± 2 mm beyond the supporting rod and are held in position by setscrews inserted through the ends of the rod. The scriber shall be calibrated by scribing an arc onto an unconditioned sample and measuring this initial scribed distance with a calibrated caliper to the nearest 0.1 mm. Thickness of arc lines shall not exceed 0.02 mm.

NOTE 2—Phonograph needles may be used as a satisfactory scriber.

5.2 *Measuring Microscope*, having a magnification of at least 20 \times and graduated to have a resolution of 0.01 mm.

NOTE 3—For more precise measurements, a micrometer microscope should be used.

5.3 *Caliper, 6-in.*, with a readability of 0.01 mm and an illuminated desk magnifier, 1.75 \times to 2.0 \times to assist with the placement of the caliper points onto the scribed lines

5.4 *Beaker*, having a suitable size for the number of specimens to be evaluated and is constructed of a material that is stable under the test conditions.

5.5 *Room or Conditioning Chamber*, capable of being maintained at $23 \pm 2^\circ\text{C}$ and $50 \pm 10\%$ RH.

5.6 *Conditioning Oven*, full draft air-circulating oven, capable of being maintained within $\pm 2^\circ\text{C}$ of the set temperature.

5.7 *Absorbent Material*, cloth or paper suitable for drying.

6. Test Specimens

6.1 Specimens shall not be less than 110 mm in length in the direction of test. The preferred specimen size is 125 ± 5 mm

*A Summary of Changes section appears at the end of this standard

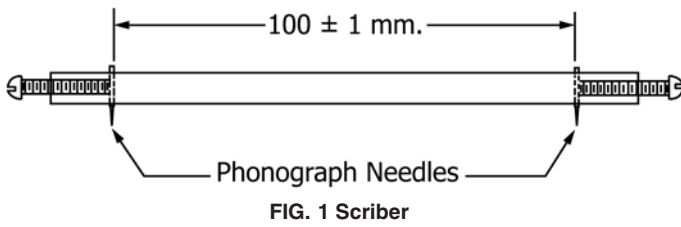


FIG. 1 Scribe

in length by 13 ± 0.5 mm wide by $3.0 (-0.0 + 0.2)$ mm thick. Refer to Test Method D5947 for guidance on measuring physical dimensions of solid plastic specimens.

6.2 Three specimens shall be tested for each conditioning.

6.3 Individual specimens shall be positioned vertically in the specified environment.

NOTE 4—A wire hook inserted in a hole drilled in one end of the specimen has been found acceptable.

7. Conditioning and Exposure

7.1 Preconditioning

7.1.1 Unless otherwise specified in the appropriate material specification, precondition specimens at $23 \pm 2^\circ\text{C}$ and $50 \pm 10\%$ relative humidity for a minimum of 40 h prior to initial scribing.

NOTE 5—If moisture equilibrium is required prior to preconditioning, refer to the specific material specifications.

7.1.2 After removal from the pre-conditioning environment, specimens shall be tested within 30 min.

7.2 Method A—Water Immersion

7.2.1 Specimens shall be immersed in water maintained at $23 \pm 2^\circ\text{C}$ for 168 ± 1 h.

7.2.2 The specimens shall be wiped dry with the absorbent cloth after removal from the water and tested within 3 min.

7.3 Method B—Oven Conditioning

7.3.1 Specimens shall be conditioned in an oven at $70 \pm 2^\circ\text{C}$ for 25 ± 1 h.

7.3.2 After removal from the oven, the specimens shall be tested within 3 min.


7.4 Other conditionings for specific service conditions can be used if agreed upon by all parties.

7.5 Conduct tests in a standard laboratory atmosphere of $23 \pm 2^\circ\text{C}$ and $50 \pm 10\%$ relative humidity.

8. Procedure

8.1 Immediately following the preconditioning, scribe an arc of 100-mm radius on the surface of the test specimen. Press one needle firmly into the specimen to form a center for this and subsequent measurements. The other needle scribes the arc that is used as a reference for all subsequent measurements (see Fig. 2). Draw the arcs smoothly, using a pressure consistent with the surface hardness and test conditions to which the specimen is subjected. It is desirable to lightly scratch the surface with the needle so that a sharp, clear arc is defined.

NOTE 6—A contrasting colored, permanent type marker may be used on the surface of the specimen, in the area of the scribe to aid in defining a sharp, clear arc.

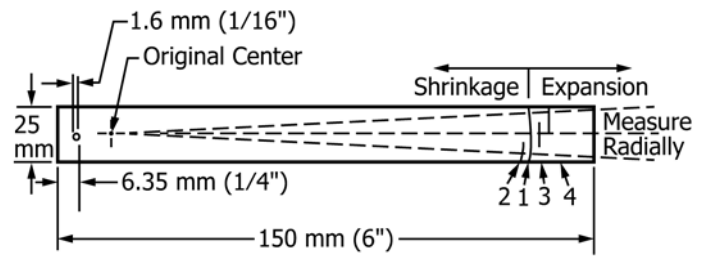

- 1—Original arc
- 2—After 37.7°C (100°F) and 100 % humidity
- 3—After 60°C (140°F)
- 4—Final conditioning

FIG. 2 Scribing Test Specimens for Measurement

8.2 After conditioning, reinsert one needle in the original center and draw a short arc with the other. Measure the distance (D_B) between the original arc and the new arc with either a caliper or the microscope. Measure the separation of the arcs between corresponding positions, for example, center to center.

8.3 If the test specimen is not flat, flatten it by pressing or clamping it against a plane surface before scribing the arcs and making the measurements. In no case shall the specimen be clamped or otherwise confined during the period of exposure to accelerated service conditions.

9. Calculation and Measurement

9.1 Measure the distance between arcs to the nearest 0.01 mm.

9.2 Determine the amount of linear expansion or shrinkage by the following:

$$L_C = D_B / D_I \times 100 \quad (1)$$

where:

L_C = percent of linear change,

D_B = distance between the scribed arcs, that is, expansion or shrinkage, and

D_I = initial scribed distance (100 mm).

10. Precision and Bias³

10.1 This test method is in use by a limited number of D20.50 members. Subcommittee D20.50 was not able to locate a sufficient number of laboratories willing to conduct a round robin, for the purpose of developing an acceptable Precision and Bias statement. However, repeatability conducted on six materials was developed by one laboratory. Results are as follows:

TABLE Method A—Water Conditioning

Material	Thick. (mm)	Exp. or Shr.	Spec. 1 (mm)	Spec. 2 (mm)	Spec. 3 (mm)	AVG (mm)	STD DEV	% CH (L_C)
PA 66	3.10	Expansion	0.108	0.114	0.091	0.104	0.012	0.104
PP	3.00	Shrinkage	0.059	0.064	0.072	0.065	0.007	0.065
ABS	2.98	Expansion	0.119	0.308	0.131	0.186	0.106	0.186
PC	3.15	Shrinkage	0.051	0.067	0.138	0.085	0.046	0.085
PS	3.10	Shrinkage	0.054	0.072	0.065	0.064	0.009	0.064
PMMA	2.98	Expansion	0.056	0.032	0.076	0.055	0.022	0.055

³ To participate in the development of precision and bias data, contact the staff manager of ASTM Committee D20 at ASTM Headquarters.

TABLE Method B—Oven Conditioning

Material	Thick. (mm)	Exp. or Shr.	Spec. 1 (mm)	Spec. 2 (mm)	Spec. 3 (mm)	AVG (mm)	STD DEV	% CH (L_C)
PA 66	3.10	Shrinkage	0.059	0.064	0.078	0.067	0.010	0.067
PP	3.00	Shrinkage	0.169	0.171	0.158	0.166	0.007	0.166
ABS	2.98	Shrinkage	0.150	0.185	0.128	0.154	0.029	0.154
PC	3.15	Shrinkage	0.250	0.222	0.232	0.235	0.014	0.235
PS	3.10	Shrinkage	0.223	0.268	0.321	0.271	0.049	0.271
PMMA	2.98	Shrinkage	0.170	0.189	0.147	0.169	0.021	0.169

11. Report

11.1 The test report shall include the following information:

11.1.1 A reference to this standard;

11.1.2 Date of testing;

11.1.3 A statement that test results relate only to the behavior of the test specimens under the conditions of this test;

11.1.4 Identification of the material tested, including the manufacturer, designation, type of material, the specimen orientation with respect to any anisotropy, and anything unique to the material;

11.1.5 Dimensions of the specimen;

11.1.6 Method of conditioning: A, B, or other;

11.1.7 Method of measurement: either caliper or microscope;

11.1.8 Distance (D_B) between the arcs after each conditioning; and

11.1.9 Percent linear expansion or shrinkage (L_C).

12. Keywords

12.1 accelerated service conditions; linear dimensional changes; plastics

ASTM International takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.

This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.

This standard is copyrighted by ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (www.astm.org). Permission rights to photocopy the standard may also be secured from the Copyright Clearance Center, 222 Rosewood Drive, Danvers, MA 01923, Tel: (978) 646-2600; http://www.copyright.com/