

# Standard Practice for Core Sampling of Raw Wool in Packages for Determination of Percentage of Clean Wool Fiber Present<sup>1</sup>

This standard is issued under the fixed designation D1060; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon  $(\varepsilon)$  indicates an editorial change since the last revision or reapproval.

#### 1. Scope

- 1.1 This practice for sampling covers a procedure for obtaining samples from lots of grease, pulled, or scoured wool or related animal fibers in bales or bags for the determination of the clean wool fiber present by a procedure similar to that described in Test Method D584.
- 1.2 This practice provides a description of suitable core sampling equipment, the sampling procedure, and the method for determining the number of packages to be bored and the number of cores to be taken from each sampled package.
- 1.3 Reliable estimates are given for the standard deviation of the percentage clean wool fiber present between packages and within packages for lots of many types of raw wool.
- 1.4 The values stated in inch-pound units are to be regarded as standard. The values given in parentheses are mathematical conversions to SI units that are provided for information only and are not considered standard.
- 1.5 This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.

#### 2. Referenced Documents

2.1 ASTM Standards:<sup>2</sup>

D123 Terminology Relating to Textiles

D584 Test Method for Wool Content of Raw Wool—Laboratory Scale

E105 Practice for Probability Sampling of Materials

E122 Practice for Calculating Sample Size to Estimate, With Specified Precision, the Average for a Characteristic of a Lot or Process

### D4845 Terminology Relating to Wool

#### 3. Terminology

- 3.1 For all terminology relating to D13.13, Wool and Wool Felt, refer to Terminology D4845.
- 3.1.1 The following terms are relevant to this standard: clean wool fiber present, core and raw wool.
- 3.2 For definitions of other textile terms used in this practice, refer to Terminology D123.

#### 4. Summary of Practices

4.1 The lot is core sampled in accordance with one of a series of equivalent schedules based on estimates of variability of the percentage clean wool fiber present and on the required level of precision. A set of packages of wool is taken as a lot sample. From each package in the lot sample, a fixed number of cores of wool is drawn to be used as a laboratory sample. Guidance in the selection of the most economical of the equivalent schedules is provided.

#### 5. Significance and Use

- 5.1 Core sampling is widely accepted, when applicable, for obtaining a laboratory sample representative of the clean wool fiber present in a lot of packaged raw wool.
- 5.2 If the wool is so loosely packed that a core cannot be cut, or if it is so highly compressed that the sampling tool cannot readily penetrate into the package to the required depth and in the required direction, core sampling is not applicable. The density of wool in most types of commercial packages is suitable for sampling by this method.
- 5.3 The procedure described in this practice is adapted to the application of statistical methods for estimating the size of sample required to achieve a required level of sample precision at minimum cost.


Note 1—The basic sampling equipment, operating procedure, and statistical approach used in this practice have been adapted for sampling lots of wool for the determination of other properties that are not affected by boring, such as average fiber diameter, and for sampling lots of other bulk fibers in packages.

<sup>&</sup>lt;sup>1</sup> This practice is under the juristiction of ASTM Committee D13 on Textiles and is the direct responsibility of Subcommittee D13.13 on Wool and Felt.

Current edition approved June 1, 2010. Published June 2010. Originally approved in 1949 . Last previous edition approved in 2005 as D1060-96 (2005). DOI: 10.1520/D1060-10.

<sup>&</sup>lt;sup>2</sup> For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.



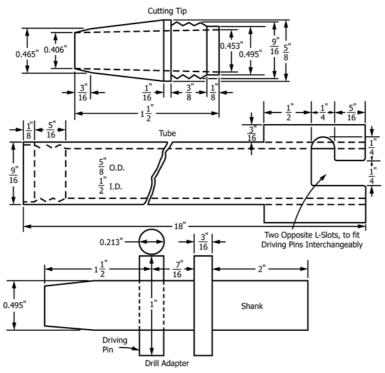

(Metric equivalents may be calculated by multiplying inches by 25.4 to obtain equivalent dimensions in millimetres.)

FIG. 1 Small Diameter Wool Sampling Tool (United States Customs Service)

#### 6. Apparatus

- 6.1 Sampling Tool<sup>3</sup>—A tube equipped with a cutting edge, together with a drill, hammer, press, or similar device, and accessories. The tube must be capable of penetrating the required distance (see 7.2) into a package of wool and cutting a core therefrom, which core must be retained substantially unchanged within the tube during its withdrawal from a package.
- 6.1.1 Fig. 1 illustrates the design of a recommended type of rotatable small-diameter wool sampling tube.
- 6.1.2 Sampling tubes in common use range from approximately  $\frac{1}{2}$  to 2 in. (13 to 50 mm) in diameter, and from 10 to 40 in. (250 to 1000 mm) in length.
- 6.1.3 Some types of sampling tubes are equipped with receptacles at the rear of the tube.
- 6.1.4 Drills of  $\frac{1}{2}$  hp (375 w) rotating at 200 to 550 rpm (3.3 to 10 rps), have been found to be satisfactory.
- 6.1.5 A toothed cutting edge on a rotating tube of small diameter, instead of the smooth edge illustrated in Fig. 1, is acceptable provided that for any specific design it has been shown that a bias is not introduced thereby. The absence of bias in samples obtained with a rotating 2-in. (50 mm) diameter tube with a toothed cutting edge has been demonstrated.

6.2 Sample Container—A container with closure of such material and so constructed that a sample stored therein will not show a material change in its moisture content during the interval between sampling and weighing the sample for test.

## 7. Sampling Procedure

- 7.1 *Time of Sampling*—Take the sample at or about the time the lot is weighed.
- 7.2 Depth of Penetration—Penetrate a bale of wool with the sampling tube to a depth such that substantially all parts of the package can be reached. Maintain the same depth of penetration for each core taken from a given lot.
  - 7.3 Location of Borings:
- 7.3.1 Consider a package as composed of eight sections approximately equal in volume, defined by top or bottom, front or back, left or right.
- 7.3.2 Alternate the location of boring in such a fashion that the total composite sample will consist of approximately the same number of cores from each section of the packages.
- 7.3.3 If the packages have been compressed in a baling press, enter a package through a compression surface and in a direction normal to that surface.
- 7.4 Whenever there is danger that loose sand or other material may drop out of the tube during or after boring, so position the package that the direction of boring will be horizontal.

<sup>&</sup>lt;sup>3</sup> The sole source of supply of the apparatus known to the committee at this time is Yocom-McColl Testing Laboratories, Inc., 540 Elk Place, Denver, CO 80216. If you are aware of alternative suppliers, please provide this information to ASTM Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, <sup>1</sup> which you may attend.

7.5 Just before entering a sampling tube into a package of wool, cut the covering in such a way that none of the covering material fibers become mixed with the core or with the wool in the package.

7.6 Immediately upon withdrawal of the tube after boring, extrude the core directly into the sample container or the intermediate receptacle (6.1.3) without loss of material or unnecessary exposure to atmospheric conditions that may result in a change in the moisture content of the core.

## 8. Size of Sample<sup>4</sup>

8.1 *Variance of Sample Mean*—If a sample consists of k cores from each of n packages from a lot of N packages of raw wool, and the  $n \times k$  cores are composited into a single sample on which m tests for percent clean wool fiber present are made, then the variance of the mean of the observations is given using Eq. 1 (Notes 2 and 3):

$$\sigma_{x}^{2} = \frac{\sigma_{b}^{2}}{n} \times \frac{N-n}{N} + \frac{\sigma_{w}^{2}}{n \times k} + \frac{\sigma_{t}^{2}}{m}$$

$$= \sigma_{s}^{2} + \frac{\sigma_{t}^{2}}{m}$$
(1)

where:

 $\sigma_{\rm r}^2$  = variance of the mean of the m observations,

 $\sigma_b^2$  = variance for percent clean wool fiber present between packages within the lot,

 $\sigma_w^2$  = average variance for percent clean wool fiber present of cores within packages of the lot,

 $\sigma_t^2$  = variance of observations on a homogeneous sample,

 $\sigma_s^2$  = variance for percent clean wool fiber present for the sample, as defined by Eq 1,

n = number of packages selected at random from the lot from which cores are taken,

N = number of packages in the lot,

k = number of cores taken from each of the n packages, and

m = number of observations made on the composite sample.

Note 2—Uniform mass of packages and of cores are assumed. If the departure from uniformity is such that a material error would be introduced by this assumption, proportional compositing must be adhered to.

Note 3—The factor (N-n)/N is the correction for sampling from a finite population. A corresponding correction is generally not necessary for cores and tests.

8.2 *Number of Cores*—Unless otherwise agreed upon, as when specified in an applicable material specification, take a number of cores such that  $\sigma_s^2$  will be 0.2603.

Note 4—0.2603 is the value calculated from  $(1.0/1.960)^2$ 

where:

1.0 = allowable variation of the percent clean wool fiber present of the composite sample, and

1.960 = value of Student's t for infinite degrees of freedom, two-sided limits, and a 95 % probability level.

8.2.1 Reliable Estimates of Variances Available—When reliable estimates of  $\sigma_b^2$  and  $\sigma_w^2$  are available, determine the required number of packages based on a specific number of cores per package using Eq 2 or Table 1:

$$n = N \left( s_w^2 + k s_h^2 \right) / \left[ 0.2603 \, kN + k s_h^2 \right] \tag{2}$$

where:

n = number of packages to be selected from the lot for coring (rounded upward to a whole number),

N =

k = number of cores to be taken from each selected package (Note 5),

 $s_w$  = reliable estimate of the standard deviation for percent clean wool fiber present of cores within packages of a lot of similar packaged raw wool (Note 6),

 $s_b$  = reliable estimate of the standard deviation for percent clean wool fiber present between packages within a lot of similar packaged raw wool (Note 6), and

0.2603 = value defined in Note 4.

Note 5—Any convenient value of k may be used, but the value of k calculated using Eq 3 and rounding to the nearest whole number will give the most economical sample:

$$k = (s_w^2 \times B/s_h^2 \times C)^{\frac{1}{2}}$$
 (3)

where:

B = average cost of selecting and positioning a package for coring, and

C = average cost of taking and handling a core, and the other terms are defined in the legend for Eq 2.

Note 6—Estimates of the variances are best based on data obtained in investigations using analysis of variance techniques for lots of similar packaged raw wool. The estimates listed in Table A1.1 were so obtained. Estimates may also be based on records in the user's laboratory if the plan for sampling and testing described in STP 114<sup>5</sup> has been followed. For testing that does not involve a dispute between the purchaser and the supplier, variances may be estimated as specified in Practice E122.

8.2.2 No Reliable Estimates of Variances Available—When no reliable estimates of  $\sigma_b^2$  and  $\sigma_w^2$  are available, determine the required number of packages based on a specific number of cores per package using Eq 2 or Table 1 and  $s_w = s_b = 5.0$  percentage points. These estimates of variability are somewhat larger than the variability usually found in practice and will usually require a larger number of cores than when reliable estimates of variability are available.

## 9. Sampling Schedules

9.1 For convenience, Table 1 gives the values of n calculated by Eq 2 for selected pairs of values of  $s_w$  and  $s_b$  and for selected lot sizes, N, and numbers of cores per package, k, for an allowable variation of  $\pm 1.0$  % clean wool fiber present at a probability level of 95 %.

#### 10. Keywords

10.1 sampling; wool content

<sup>&</sup>lt;sup>4</sup> For background information, see the paper by Louis Tanner and W. Edwards Deming, "Some Problems in the Sampling of Bulk Materials," *Proceedings*, ASTM, Vol 49, 1949, p. 1181 and ASTM Practice E105.

<sup>&</sup>lt;sup>5</sup> Symposium on Bulk Sampling, ASTM STP 114, ASTM, 1952.



TABLE 1 Values of n for an Allowable Variation of ± 1.0 % Clean Wool Fiber Present (0.86 % Wool Base) at a Probability Level of 95 % for Selected Values of  $s_{w}$ ,  $s_{b}$ , and k

Number of Number of Packages in Lot, N												
		Cores per										
s <sub>w</sub>	S <sub>b</sub>	Sampled	25	50	75	100	150	200	300	500	750	1000
		Package, k						es to Be Sa	•			
1.0	1.0	1	7	8	8	8	8	8	8	8	8	8
1.0 1.0	1.5 2.0	1 1	10 12	11 15	12 17	12 17	12 18	12 18	13 19	13 19	13 19	13 19
1.0	2.5	1	15	19	22	23	24	25	26	27	27	28
1.0	3.0	1	17	23	27	29	32	33	35	36	37	38
1.0	3.5	1	18	27	32	35	39	43	44	47	48	49
1.0	4.0	1	19	30	36	41	47	50	55	59	61	62
1.0	4.5	1	20	32	40	46	54	59	65	71	74	76
1.0	5.0	1	21	35	44	51	61	68	76	84	89	92
1.5 1.5	1.0 1.5	1	11 13	12 15	12 16	13 16	13 17	13 17	13 17	13 17	13 18	13 18
1.5	2.0	1	15	19	20	21	22	23	23	24	24	24
1.5	2.5	1	17	23	25	27	29	30	31	32	32	32
1.5	3.0	1	19	26	30	33	36	37	39	41	42	42
1.5	3.5	1	20	29	35	38	43	46	49	51	53	54
1.5	4.0	1	21	32	39	44	50	54	59	63	65	67
1.5 1.5	4.5 5.0	1	21 22	34 36	43 46	49 54	57 64	63 71	69	75 88	79 93	81 96
2.0	1.0	1	17	18	19	54 19	19	19	80 19	20	20	20
		2	10	11	11	12	12	12	12	12	12	12
2.0	1.5	1	18	21	22	23	23	24	24	24	24	24
		2	13	14	15	16	16	16	16	17	17	17
2.0	2.0	1	20	24	26	27	28	29	30	30	31	31
0.0	0.5	2	15	18	20	20	21	22	22	23	23	23
2.0	2.5	1 2	21 17	27 22	30 25	32 26	34 28	36 29	37 30	38 31	39 31	39 31
2.0	3.0	1	21	30	35	38	41	43	45	47	48	49
		2	18	25	29	32	35	37	38	40	41	41
2.0	3.5	1	22	33	39	43	48	51	54	58	59	60
		2	19	29	34	38	42	45	48	51	52	53
2.0	4.0	1	23	35	43	48	55	59	64	69	72	73
2.0	4.5	2 1	20 23	32 37	39 46	43 53	50 62	53 68	58 74	62 81	64 85	66 87
2.0	4.5	2	23 21	34	40	49	57	62	68	74	78	80
2.0	5.0	1	24	39	49	57	68	76	85	94	99	102
		2	22	36	46	53	64	71	79	88	92	95
2.5	1.0	1	25	26	27	27	28	28	28	28	28	28
		2	14	15	16	16	16	16	16	16	16	16
2.5	1.5	1 2	25 16	28 18	30	31 20	31	32 20	32 21	33 21	33 21	33 21
2.5	2.0	1	25	31	19 33	35	20 36	37	38	39	39	39
2.0	2.0	2	17	21	23	24	25	26	27	27	27	27
2.5	2.5	1	25	33	37	39	42	43	45	46	47	47
		2	19	25	28	30	32		34	35	35	36
2.5	3.0	1	25	35	41	44	48	50	53	55	57	57
0.5	2.5	2 1	20	28 37	32	35	38	40	42	44 65	45 67	46
2.5	3.5	_	25 21	31	44 37	49 41	55 45	58 48	62 52	65 54	67 56	68 57
2.5	4.0	2 1	21 25	39	37 47	53	45 61	66	52 71	54 77	56 80	57 81
		2	22	33	41	46	53	57	61	66	68	70
2.5	4.5	1	25	40	50	58	67	74	81	89	93	95
		2	22	36	45	51	60	65	72	78	82	84
2.5	5.0	1	25	42	53	62	74 66	82	91	101	107	110
		2 2	23 23	37 37	48 48	56 56	66 66	73 73	82 82	90 90	96 96	99 99
3.0	1.0	1	В	36	37	37	38	38	38	39	39	39
		2	19	20	21	21	21	21	21	21	22	22
3.0	1.5	1	В	37	39	40	41	42	43	43	43	43
		2	20 B	23	24	24	25	25	26	26	26	26
3.0	2.0	1		39	42	44	46	47	48	49	49	50
3.0	2.5	2 1	21 B	25 40	28 45	29 48	30 51	31 53	32 55	32 56	32 57	33 58
0.0	۷.۵	2	22	28	32	34	36	37	39	40	41	41
3.0	3.0	1	В	41	48	52	57	59	63	65	67	67
		2	22	31	36	39	43	45	47	49	50	51
3.0	3.5	1	В	43	51	56	63	67	71	75	77	78
0.0	4.0	2	23 B	34	40	44	49	53	56	59	61	62
3.0	4.0	1		44 36	53 44	60 49	69 56	74 61	80 66	86 71	89 73	91 75
3.0	4.5	2 1	23 B	36 44	56	49 64	56 74	61 81	90	98	73 102	75 105
0.0	7.0	2	24	38	47	54	63	69	76	83	87	89



TABLE 1 Continued

Number of Park   Park			N 1 6		IA	DLE I	onunuea						
Sampled   Samp			Number of							-			
Number of Processings   Numb	$s_w$	s <sub>b</sub>	•	25	50	75	100	150	200	300	500	750	1000
2							Number	of Package	es to Be Sar	mpled, n			
10	3.0	5.0	1	В	45	58	67	80	89	99	110	116	120
Section   Sect				24									
1.5	3.5	1.0		В	48								
1.5													
1.5													
1.0	0.5	1.5		14 <i>B</i>									
1	3.5	1.5											
3.5   2.0   1													
3.5				16									
1	3.5	2.0			48	52	55	57	58	60	61	62	
3.5													
3.5													
2	2.5	0.5											
1	3.5	2.5											
3.5													
3.5 3.0 1													
3	3.5	3.0	1	В			61						
3.5													
3.5													
2	0.5	0.5		20 B									
1	3.5	3.5											
1													
3.5													
3 23 35 43 48 55 60 65 69 72 73  4 22 33 41 46 52 57 61 66 68 69  3.5 4.5 1 8 49 62 71 83 90 100 109 114 116  2 25 40 50 57 67 73 81 88 92 95  4 222 36 44 51 59 65 72 78 82 84  3.5 5.0 1 8 49 63 73 88 97 109 121 127 131  2 25 41 53 61 73 88 97 109 121 127 131  3 24 39 49 67 69 76 85 94 100 102  4 223 37 46 65 67 69 76 85 94 100 102  4 223 37 48 55 66 73 82 91 96 99  4.0 1.0 1 8 8 8 97 109 121 127 131  2 8 8 97 109 121 127 131  3 24 39 49 67 69 76 85 94 100 102  4 23 37 48 55 66 73 82 91 96 99  4.0 1.0 1 8 8 9 63 73 88 97 109 121 127 131  4 18 8 9 8 63 63 64 65 65 65 65 66 66 66 66 66 66 66 66 66	3.5	4.0											
3.5			2	25									
2 25 40 50 57 67 73 81 88 92 95 95 87 83 83 89 97 83 81 88 92 95 95 85 85 85 85 85 85 85 85 85 85 85 85 85							48				69		
2 25 40 50 57 67 73 81 88 92 95 95 87 83 83 89 97 83 81 88 92 95 95 85 85 85 85 85 85 85 85 85 85 85 85 85				22									
1	3.5	4.5											
$\begin{array}{c ccccccccccccccccccccccccccccccccccc$													
2													
2	3.5	5.0		<i>B</i>									
100   102   102   103   104   105   106   106   107   107   108   109   109   100	0.0	0.0											
4.0													
1				23		48	55	66	73	82	91	96	99
1.5	4.0	1.0											
$ \begin{array}{c ccccccccccccccccccccccccccccccccccc$													
4.0													
2	4.0	1.5		B B	10 B								
$ \begin{array}{c ccccccccccccccccccccccccccccccccccc$	4.0	1.5		В	34								
4.0       2.0       1       B       B       64       67       70       72       74       75       76       76         2       B       36       39       40       42       43       44       45       46       46         4       20       24       26       27       28       29       30       30       31       31         4.0       2.5       1       B       B       65       69       74       77       80       82       83       84         4       2.5       1       B       B       65       69       74       77       80       82       83       84         4       2.1       27       30       32       34       36       39       40       42       43       44       44         4.0       3.0       1       B       B       66       72       79       82       87       90       92       93         4.0       3.0       1       B       B       66       72       79       82       87       90       92       93         4.0       3.5       1       B       B				22									
1.0			4			22	23	23	24	24	24	24	24
3 23 28 30 32 33 34 35 35 36 36 36 36 36 36 36 36 36 36 36 36 36	4.0	2.0											
4.0			2										
4.0			3	23	28	30	32	33		35			36
4.0         3.0         1 <td>4.0</td> <td>2.5</td> <td>1</td> <td>20 B</td> <td>24 B</td> <td>20 65</td> <td></td> <td></td> <td></td> <td></td> <td></td> <td></td> <td></td>	4.0	2.5	1	20 B	24 B	20 65							
$ \begin{array}{c ccccccccccccccccccccccccccccccccccc$	4.0	2.5				42							
4 21 27 30 32 34 36 37 38 39 39 49 40 4.0 3.0 1 8 8 8 94 100 103 104 4.0 3.5 1 8 8 8 95 103 110 114 116 4 10 4.5 4.5 4.5 4.5 4.5 4.5 4.5 4.5 4.5 4.5				23									
2			4	21	27	30						39	
3 24 33 38 41 45 47 50 52 53 54 4 21 30 35 38 41 43 45 47 48 49 4.0 3.5 1 B B B 67 74 83 88 94 100 103 104 2 B 41 48 53 60 63 68 72 74 75 3 24 35 42 46 52 55 59 62 64 65 4 22 33 39 43 48 51 54 58 59 60 4.0 4.0 1 B B B 68 77 88 95 103 110 114 116 2 B 42 51 58 66 71 77 83 86 87 3 24 37 46 61 69 63 69 73 76 78 4 23 35 43 48 55 59 64 69 72 73 4.0 4.5 1 B B B 69 79 92 101 111 121 127 130 4 54 58 59 60 4 69 72 73 4.0 4.5 1 B B B 69 79 92 101 111 121 127 130 5 6 65 71 79 86 90 92 101 5 6 65 71 79 86 90 92 101 5 7 7 7 7 83 87 94 99 101 6 7 8 7 8 7 94 99 101 7 8 7 8 7 94 99 101 7 8 8 7 94 99 101 7 8 8 7 94 99 101 8 8 8 95 70 81 97 107 120 133 140 144	4.0	3.0						79					93
$ \begin{array}{c ccccccccccccccccccccccccccccccccccc$			2			45							
$ \begin{array}{c ccccccccccccccccccccccccccccccccccc$				24	33	38							54
$ \begin{array}{c ccccccccccccccccccccccccccccccccccc$	4.0	2.5		21 B	30 B	35 67							49
3 24 35 42 46 52 55 59 62 64 65 4 22 33 39 43 48 51 54 58 59 60 4.0 4.0 1 1	4.0	3.5		В									
4.0 4.0 4.0 1 B B B 68 77 88 95 103 110 114 116 2 B B 42 51 58 66 71 77 83 86 87 3 24 37 46 61 69 63 69 73 76 78 4.0 4.5 1 B B 69 79 92 101 111 121 127 130 2 B 43 54 62 72 79 87 94 99 101 3 24 39 49 56 65 71 79 86 90 92 4 23 37 46 53 62 68 74 81 85 87 4.0 5.0 5.0 1 B B B 70 81 97 107 120 133 140 144			3										
4.0 4.5 1 B 42 51 58 66 71 77 83 86 87 40 4.5 4 23 35 43 48 55 59 64 69 72 73 40 4.5 4 23 35 44 62 72 79 87 94 99 101 3 24 39 49 56 65 71 79 86 90 92 4.0 4.0 5.0 1 B B B 70 81 97 107 120 133 140 144			4	22	33	39					58		
4.0     4.5     1     8     42     51     58     66     71     77     83     86     87       4.0     23     35     43     48     55     59     64     69     72     73       4.0     4.5     1     8     8     69     79     92     101     111     121     127     130       2     8     43     54     62     72     79     87     94     99     101       3     24     39     49     56     65     71     79     86     90     92       4     23     37     46     53     62     68     74     81     85     87       4.0     5.0     1     8     8     70     81     97     107     120     133     140     144	4.0	4.0	1		В	68				103	110		116
3 24 37 46 61 69 63 69 73 76 78 4 23 35 43 48 55 59 64 69 72 73 4.0 4.5 1 B B 69 79 92 101 111 121 127 130 2 B 43 54 62 72 79 87 94 99 101 3 24 39 49 56 65 71 79 86 90 92 4 23 37 46 53 62 68 74 81 85 87 4.0 5.0 1 B B 70 81 97 107 120 133 140 144			2			51				77	83	86	87
4.0 4.5 1 B B 69 79 92 101 111 121 127 130 2 B 43 54 62 72 79 87 94 99 101 3 24 39 49 56 65 71 79 86 90 92 4 23 37 46 53 62 68 74 81 85 87 4.0 5.0 1 B B 70 81 97 107 120 133 140 144				24									78
2 B 43 54 62 72 79 87 94 99 101 3 24 39 49 56 65 71 79 86 90 92 4 23 37 46 53 62 68 74 81 85 87 4.0 5.0 1 B B 70 81 97 107 120 133 140 144				23	35								
3 24 39 49 56 65 71 79 86 90 92 4 23 37 46 53 62 68 74 81 85 87 4.0 5.0 1 <sup>B</sup> <sup>B</sup> 70 81 97 107 120 133 140 144	4.0	4.5						92					
4 23 37 46 53 62 68 74 81 85 87 4.0 5.0 1 <sup>B</sup> <sup>B</sup> 70 81 97 107 120 133 140 144			2										101
· · · · · · · · · · · · · · · · · · ·				23									
· · · · · · · · · · · · · · · · · · ·	4.0	5.0			В								
	-				44								



TABLE 1 Continued

		N. I. C		17	DLE I	onunuea			,			
		Number of Cores per						kages in Lo	-			
s <sub>w</sub>	s <sub>b</sub>	Sampled	25	50	75	100	150	200	300	500	750	1000
		Package, k				Number	of Package	es to Be Sa	mpled, n			
		3	25	40	52	60	72	79	89	98	104	107
		4	24	39	49	57	68	76	85	94	99	102
4.5	1.0	1	В	В	В	79	80	81	81	82	82	82
		2	В	40	41	42	42	42	43	43	43	43
		3	В	28	29	29	30	30	30	30	30	30
4.5	1.5	4 1	21 B	22 B	23 B	23 80	23	23	23	24	24	24
4.5	1.5	2	В	41	43	80 44	82 45	83 46	85 47	85 47	86 47	86 48
		3	В	30	32	32	33	34	34	34	35	35
		4	21	24	26	26	27	27	28	28	28	28
4.5	2.0	1	В	В	В	81	85	87	89	91	92	92
		2	В	42	46	48	50	51	52	53	54	54
		3	В	32	35	36	38	39	40	41	41	41
4 E	0.5	4 1	22 B	27 B	29 B	31 83	32	33	34	34	35	35
4.5	2.5	2	В	43	48	51	88 55	91 57	95 59	98 61	99 61	100 62
		3	В	34	38	41	44	45	47	48	49	49
		4	23	30	33	36	38	39	41	42	43	43
4.5	3.0	1	В	В	В	84	92	96	101	106	108	109
		2	В	44	51	55	60	63	66	69	71	72
		3	В	36	42	45	50	52	55	57	58	59
		4	23 B	32 B	37	41	44	47	49	41	52	53
4.5	3.5	1	В		B	85	96	102	108	115	118	120
		2 3	В	45	53	59 50	66	70 60	75 64	79 67	81	83
		3 4	24	38 35	45 41	46	56 51	54	64 58	67 61	69 63	70 64
4.5	4.0	1	B	В	B	87	99	107	116	125	129	132
1.0	1.0	2	В	46	56	63	72	77	84	90	93	95
		3	В	40	49	55	62	67	73	78	81	83
		4	24 B	37	45	51	58	62	68	73	75	77
4.5	4.5	1		В	В	88	103	113	124	135	141	145
		2	В	46	58	66	77	85	93	101	106	109
		3	B	41	51	59	69	75	83	90	94	97
4.5	5.0	4 1	24 <i>B</i>	39 B	48 <i>B</i>	55 89	65 106	71	78 132	85 146	89 155	91
4.5	5.0	2	В	47	60	69	83	118 92	103	146 114	155 120	159 124
		3	В	42	54	63	75	83	93	103	109	112
		4	24	40	51	59	71	79	88	97	103	106
5.0	1.0	1	В	В	В	97	98	98	99	100	100	100
		2	В	49	50	50	51	51	52	52	52	52
		3	В	34	35	35	35	36	36	36	36	36
		4	25 B	26 B	27 B	27	28	28	28	28	28	28
5.0	1.5	1 2	В			97	99	101	102	103	104	104
		3	В	49 35	51 37	53 38	54 39	55 39	56 40	56 40	57 51	57 41
		4	25	28	30	31	31	32	32	33	33	33
5.0	2.0	1	В	В	В	97	102	104	106	109	110	110
		2	В	49	53	55	58	59	61	62	63	63
		3 4	В	37	40	42	43	44	46	46	47	47
		4	25 B	31 B	33 B	35	36	37	38	39	39	39
5.0	2.5	1	В			97	104	108	112	115	117	118
		2	В	49 38	55	59 46	63	65 51	67	69	70 55	71 55
		3 4			43	39	49 42	43	52 45	54 46	55 47	55 47
5.0	3.0	1	25 B	33 B	37 B	98	107	112	118	123	125	127
0.0	0.0	2	В	49	57	62	68	71	75	78	79	80
		3	В	40	46	50	55	57	60	63	64	65
		4	25 B	35 B	41 B	44	48	50	53	55	57	57
5.0	3.5	1	В			98	109	116	124	131	135	137
		2	В В	49	59	65	73	77	83	87	90	91
		3		41	49	54	61	65	69	73	75 07	76
F 0	4.0	4 1	25 B	37 B	44 <i>B</i>	49 98	55	58 121	62	65 141	67 146	68 140
5.0	4.0	1 2	В	50	61	98 68	112 78	121 84	131 91	141 98	146 102	149 104
		3	В	42	52	58	78 67	72	78	98 84	87	89
		4		39	47	53	61	66	71	77	80	81
5.0	4.5	1	25 B	39 B	47 B	98	115	126	139	151	158	162
	-	2	В	50	62	71	83	91	100	109	114	117
		3	В	43	54	62	73	80	88	96	100	102
		4	25 B	40	50	58	68	74	81	89	93	95
5.0	5.0	1	В В	В	В	98	118	130	146	162	171	176
		2	В	50	64	74	88	98	110	121	128	132



TABLE 1 Continued

		N. I. C			DLE I C	onunuea						
		Number of Cores per						kages in Lo	-			
s <sub>w</sub>	s <sub>b</sub>	Sampled	25	50	75	100	150	200	300	500	750	1000
		Package, k				Number	of Package	es to Be Sar	mpled, n			
		3	В	44	57	66	79	87	98	108	114	117
		4	25	42	53	62	74	82	91	101	107	110
5.5	1.0	1	В	В	В	В	118	118	119	120	120	120
		2	В	В	59	60	61	61	62	62	62	62
		3	В В	40	41	42	42	42	43	43	43	43
		4 5	24	31	32	32 27	33	33	33	33 27	33 27	33
		6	21	26 22	26 23	27	27 23	27 23	27 23	24	24	27 24
5.5	1.5	1	B	В	В	В	119	120	122	123	124	124
		2	В	В	60	62	64	64	65	66	66	67
		3	В	41	43	44	45	46	47	47	47	47
		4	В	33	34	35	36	37	37	38	38	38
		5	24	28	29	30	31	31	31	32	32	32
5.5	2.0	6 1	21 <i>B</i>	24 <i>B</i>	26 B	26 <sub>B</sub>	27 120	27 123	28 126	28 128	28 129	28 130
5.5	2.0	2	В	В	61	64	67	69	70	72	72	73
		3	В	42	45	47	50	51	52	53	54	54
		4	В	34	37	39	41	42	43	44	44	44
		5	24	30	33	34	36	36	37	38	38	39
		6	22 B	27	29	31	32	33	34	34	35	35
5.5	2.5	1	В	В В	В	В	121	126	130	134	136	137
		2	В		63	67	71 55	74 57	77 50	79	80	81
		3 4	В	43 36	48 41	51 43	55 46	57 48	59 50	60 51	61 52	62 52
		5	25	32	36	39	41	43	44	46	46	47
		6	23	30	33	35	38	39	41	42	43	43
5.5	3.0	1	В	В	В	В	123	129	136	142	145	146
		2	В	В	64	69	76	80	84	87	89	90
		3	В В	44	51	55	60	63	66	69	71	71
		4		38	44	48	52	55	58	60	61	62
		5 6	25 23	35 32	40 37	43 41	47 44	50 46	52 49	55 51	56 52	56 53
5.5	3.5	1	23 B	B	В	B	125	133	142	150	154	156
0.0	0.0	2	В	В	65	72	81	86	91	97	99	101
		3	В	45	53	59	66	70	75	79	81	82
		4	В	40	47	52	58	62	66	70	72	73
		5	25	37	44	48	54	57	61	65	67	68
	4.0	6	24 <i>B</i>	35 B	41 <i>B</i>	46 B	51	54	58	61	63	64
5.5	4.0	1 2	В	В	66	75	127 85	136 92	148 100	159 107	165 111	168 113
		3	В	45	56	63	72	77	84	90	93	95
		4	В	41	50	57	65	70	76	81	84	86
		5	25	38	47	53	61	65	71	76	79	80
		6	24	37	45	51	58	62	68	72	75	77
5.5	4.5	1	В В	В В	В	В	128	140	155	168	176	180
		2	В		67	77	90	98	108	118	124	127
		3	В	46	58 53	66 61	77 71	84 77	93	101	106	109
		4	25	42 40	53 50	61 57	71 67	77 73	85 81	93 88	97 92	100 94
		5 6	24 B	39 B	48 B	55	64	70	78	85	89	91
5.5	5.0	1			В	В	130	144	161	179	189	194
		2	В	В	68	79	94	105	117	130	137	141
		3	В В	47	60	69	83	92	103	114	120	123
		4		43	55	64	77	85	95	105	111	115
		5 6	25	41 40	53 51	61 59	73 71	81 78	91 88	101 97	106 103	109
6.0	1.0	1	24 B	40 B	51 B	39 B	139	140	141	142	142	106 142
0.0	1.0	2	В	В	70	71	72	72	73	73	73	73
		3	В	47	48	49	49	49	50	50	50	50
		4	В	36	37	37	38	38	38	39	39	39
		5	В	30	30	31	31	31	32	32	32	32 27
		6	24 B	25	26	26	27	27	27	27	27	27
6.0	1.5	1	В В	В В	B 70	В	139	141	143	145	146	146
		2	В		70	72	74 50	75 50	76 54	77	77 55	78 55
		3 4	В	47 37	50	51 40	52 41	53	54 42	54 42	55 43	55 43
		4 5	В	37 31	39 33	40 34	41 35	42 35	43 36	43 36	43 36	43 36
		6	24	28	29	30	30	31	31	32	32	32
6.0	2.0	1	В	В	29 B	В	140	143	147	150	151	152
-	-	2	В	В	71	74	77	79	81	82	83	84
		3	В	48	52	54	56	58	59	60	61	61
		4	В	39	42	44	46	47	48	49	49	50

TABLE 1 Continued

Number of Packages in Le							in Lot, N						
s <sub>w</sub>	s <sub>b</sub>	Cores per Sampled	25	50	75	100	150	200	300	500	750	1000	
		Package, k				Number	of Package	es to Be Sa	mpled, n				
		5	В	33	36	38	40	40	41	42	43	43	
		6	24	30	32	34	35	36	37	38	38	38	
6.0	2.5	1	В	В	В	В	140	145	151	155	158	159	
		2	В	В	71	76	81	84	87	89	91	91	
		3	В	48	54	57	61	63	65	67	68	69	
		4	В	40	45	48	51	53	55	56	57	58	
		5	В	35	40	42	45	47	48	50	51	51	
		6	25	32	36	38	41	43	44	45	46	46	
6.0	3.0	1	В	В	В	В	141	148	156	162	166	168	
		2	В	В	71	78	85	89	94	98	100	101	
		3	В	48	56	60	66	69	73	76	78	78	
		4	В	41	48	52	57	59	63	65	67	67	
		5	В	37	43	47	51	54	56	59	60	6	
		6	25	35	40	43	47	50	52	54	56	56	
6.0	3.5	1	В	В	В	В	142	151	161	170	175	178	
		2	В	В	72	80	89	95	101	107	110	111	
		3	В	48	58	64	71	76	81	86	88	89	
		4	В	43	51	56	63	67	71	75	77	78	
		5	В	39	46	51	57	61	65	69	71	72	
		6	25	37	44	48	54	57	61	65	66	767	
6.0	4.0	1	В	В	В	В	142	153	166	178	185	189	
		2	В	В	72	81	93	100	109	117	121	124	
		3	В	49	60	67	77	83	90	96	100	102	
		4	В	42	53	60	69	74	80	86	89	9.	
		5	В	40	49	56	64	69	74	80	83	84	
		6	25	38	47	53	60	65	71	76	79	80	
6.0	4.5	1	В	В	В	В	143	156	172	187	196	20	
		2	В	В	73	83	97	106	117	128	134	137	
		3	В	49	61	70	82	90	99	108	113	115	
		4	В	44	56	64	74	81	90	98	102	10	
		5	В	42	52	60	70	76	84	92	96	98	
		6	25	40	50	57	67	73	81	88	92	94	
6.0	5.0	1	В	В	В	В	143	159	178	197	208	214	
		2	В	В	73	85	101	112	126	139	147	15	
		3	В	49	63	73	87	96	108	120	126	130	
		4	В	44	58	67	80	89	99	110	116	120	
		5	В	43	55	64	76	84	94	104	110	113	
		6	25	41	53	61	73	81	9	100	106	109	

<sup>&</sup>lt;sup>A</sup> Calculated using Eq 2.

#### ANNEX

(Mandatory Information)

## A1. CLASSIFICATION OF WOOLS FOR SAMPLING PURPOSES

A1.1 Committee studies have shown that the values for  $s_w$  and  $s_b$  listed in Table A1.1 are good estimates of the average values for lots of several types of packaged wool as they appeared in the commerce of the United States of America early in 1964, provided the packages comprising the lot conformed to the following conditions:

A1.1.1 Each package was uniformly and randomly packed.

A1.1.2 All packages were undamaged (Note A1.1), of the same kind (bales or bags), and of approximately the same dimensions and mass, within usual commercial limits.

A1.1.3 All packages contained the same kind of wool or hair (sheep, goat, camel, alpaca, and so forth), from the same geographic area, of the same general character (apparel or carpet type, fleece, matchings, crutchings, and so forth), and in the same general condition (grease, scoured, washed, pulled, and so forth).

Note A1.1—The data given in Table A1.1 would not be applicable to lots containing packages materially damaged by water, oil, or other agent unless these packages were first removed from the lot for separate evaluation. Normally soiled or torn coverings of themselves do not indicate material damage for sampling purposes.

<sup>&</sup>lt;sup>B</sup> The specified allowable variation cannot be obtained with this number of cores, *k*, per package.

TABLE A1.1 Estimates of s<sub>w</sub> and s<sub>b</sub> for Precentage Clean Wool Fiber Present of Lots<sup>A</sup> of Packaged Wool of Several Types

Classification	$s_w$	$s_b$	Classification	$s_w$	$s_b$
A. Apparel Wool, Foreign:		•	C. Carpet Wool:		
(1) Greasy, not burry:			(1) Washed or greasy, not burry:		
Argentine	2.5	2.5	Aleppo	3.0	2.5
Australia <sup>B</sup>	1.5	4.0	B.A.	3.5	2.5
Brazil	2.5	2.5	Blackface	4.0	3.5
Canada	4.5	2.0	Indian (other than Vicanere):		
Chile	2.0	5.0	White	2.5	1.5
Peru, wool	2.5	2.5	Colored	3.5	3.0
Peru, alpaca	3.0	1.5	Iran	3.5	3.5
New Zealand	1.5	4.0	Iraq	3.5	2.0
South Africa	1.5	4.0	New Zealand crutchings	3.5	5.0
Uruguay	3.0	1.5	Pakistan	2.0	5.0
(2) Pulled, not burry:			Vicanere	3.0	2.5
Slight lime, all types	1.5	1.5	(2) Washed or greasy, burry:		
Heavy lime, all types	2.5	2.5	5 to 10 % burr, scoured basis	increase correspo	nding" not burry" $s_w$
(3) Scoured, not burry:				by 1.0	
Well scoured, all types	1.0	1.0	Over 10 % burr, scoured basis	increase correspo	nding" not burry" $s_w$
Poorly scoured, all types	1.5	1.5		by 2.0	
(4) Burry:			(3) Pulled or colored	same as washed	or greasy, burry, 5
5 to 10 % burr, scoured basis	increase correspond 1.0	ling "not burry" $s_W$ by		to 10 %	
Over 10 % burr, scoured basis	increase correspond	ling "not burry" $s_{W}$ by	Scoured, not burry:		
	2.0		Well scoured, all types	1.0	1.0
B. Apparel Wool, Domestic:			Poorly scoured, all types	1.5	1.5
(1) Original bags, ungraded	4.5	2.0	(5) Scoured; burry:		
(2) Territory wool, graded <sup>C</sup>	4.5	2.0	5 to 10 % burr	2.5	1.5
(3) Fleece wools, graded <sup>C</sup>	5.0	2.0	Over 10 % burr	3.5	1.5

A For restrictions on the packages that may be included in a lot to which the estimates apply, see A1.1.1 – A1.1.3.

ASTM International takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.

This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.

This standard is copyrighted by ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (www.astm.org). Permission rights to photocopy the standard may also be secured from the Copyright Clearance Center, 222 Rosewood Drive, Danvers, MA 01923, Tel: (978) 646-2600; http://www.copyright.com/

<sup>&</sup>lt;sup>B</sup> A study conducted in 1971 confirmed these estimates. A copy is available from ASTM Headquarters, 100 Barr Harbor Drive, West Conshohocken, PA 19428. Request Research No. RR:D13-1044.

<sup>&</sup>lt;sup>C</sup> Studies conducted in 1972 to 1974 indicated that these estimates are also applicable to compressed bales weighing approximately 454 kg (1000 lb). A copy is available from ASTM Headquarters, 100 Barr Harbor Drive, West Conshohocken, PA 19428. Request Research No. RR:D13-1044.