



Designation: D2065 – 03 (Reapproved 2017)

Standard Test Method for Determination of Edge Performance of Composite Wood Products Under Surfactant Accelerated Moisture Stress¹

This standard is issued under the fixed designation D2065; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

1. Scope

1.1 This test method is intended to serve as a means for measurement of swelling and cracking of the coated or uncoated edge of a composite wood substrate that has been subjected to wetting by a test solution containing surface active agent.

1.2 The values stated in SI units are to be regarded as the standard. The values given in parentheses are for information only.

1.3 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

1.4 *This international standard was developed in accordance with internationally recognized principles on standardization established in the Decision on Principles for the Development of International Standards, Guides and Recommendations issued by the World Trade Organization Technical Barriers to Trade (TBT) Committee.*

2. Referenced Documents

2.1 *ASTM Standards:*²

[D661 Test Method for Evaluating Degree of Cracking of Exterior Paints](#)

[E177 Practice for Use of the Terms Precision and Bias in ASTM Test Methods](#)

[E691 Practice for Conducting an Interlaboratory Study to Determine the Precision of a Test Method](#)

3. Terminology

3.1 *Definitions of Terms Specific to This Standard:*

¹ This test method is under the jurisdiction of ASTM Committee D01 on Paint and Related Coatings, Materials, and Applications and is the direct responsibility of Subcommittee D01.52 on Factory Coated Wood Products.

Current edition approved July 1, 2017. Published July 2017. Originally approved in 1991. Last previous edition approved in 2011 as D2065 – 03 (2011). DOI: 10.1520/D2065-03R17.

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

3.1.1 *crack rating, n*—a numerical value on a scale from 1 to 10, with 10 representing no evidence of cracking of the edge (see Test Method [D661](#)).

3.1.2 *composite wood products, n*—boards or other structural or decorative materials manufactured from wood fibers, flakes or strands and various resin binders consolidated under heat, or pressure, or both.

4. Summary of Test Method

4.1 A surfactant solution is placed in a tray that contains a sponge. A preweighed and calipered panel with a coated edge is placed with the edge in contact with the surfactant saturated sponge for 2 h. The exposed panel is blotted dry, reweighed, recalipered, and inspected for edge cracking. Percentage weight and thickness changes are calculated and recorded. Edge cracking is rated in accordance with Test Method [D661](#) and recorded.

5. Significance and Use

5.1 This test method provides a measure of the dimensional stability and integrity of the coated edge of various composite wood products under accelerated moisture stress. It is widely used as an indicator or predictor of the anticipated performance of composite wood products during exterior exposure. It may be used for developmental evaluation of coatings, substrates, or both. It may also be useful for quality control or monitoring of the production of coated or uncoated composite wood products.

6. Apparatus

6.1 *Wide Flat Tray or Pan*, suitable to contain the required number of sponges and test boards. The sides must be high enough to safely contain at least 6 mm (¼ in.) of solution.

6.2 *Rack or Holder*, suitable to support the required number of test boards at the nominal 60° angle.

6.3 *Micrometer or Vernier Caliper*, of sufficient capacity for the board thickness to be measured and capable of 0.1 mm accuracy.

6.4 *Balance*, with sufficient capacity (typically 400 g) and 0.01 g accuracy.

6.5 *Suitable Saw*, for cutting of samples.

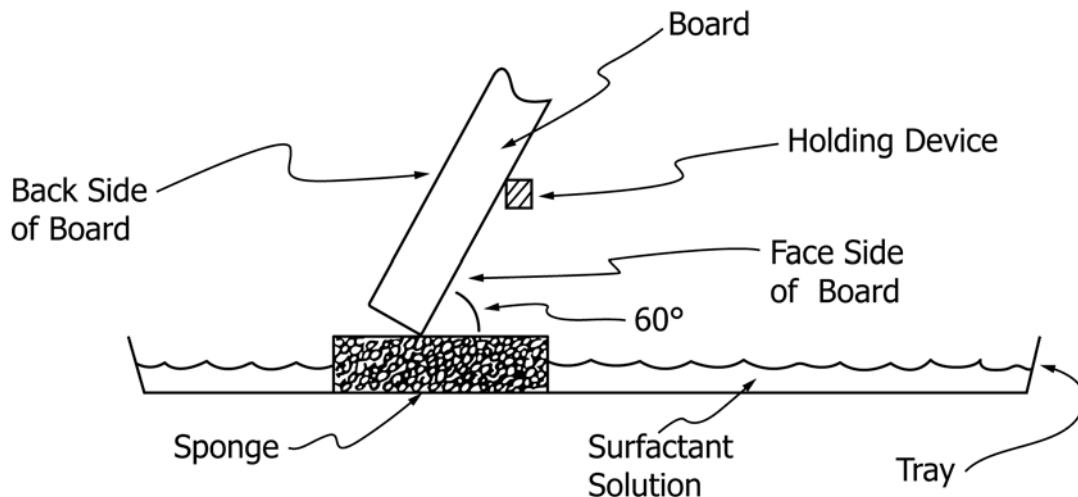


FIG. 1 Test Apparatus Side View

6.6 *Common Household Cellulose Sponges*, cut to suitable size.

7. Materials

7.1 A sufficient supply of test solution.

7.2 Appropriately identified test boards cut to proper size.

8. Hazards

8.1 When using saws, wear goggles, dust mask, and use proper machine safeguards to prevent injury.

9. Procedure

9.1 See Fig. 1.

9.2 Make the required test solution.³ Pour solution into the tray to saturate all sponges, and allow to reach room temperature. A 6-mm (1/4-in.) depth of solution in the tray works well.

9.3 Cut board specimens to a suitable size. A 10.2-cm (4-in.) by 12.7-cm (5-in.) size has been found to be convenient. The 10.2-cm (4-in.) dimension should be the coated edge. Preparation of triplicate specimens is recommended.

9.4 Measure thickness of the samples along the edge to be tested. Three measurements at 2.54-cm (1-in.) intervals (Fig. 2) are recommended for a 10.2-cm (4-in.) specimen. Record results.

9.5 Weigh the samples to the nearest 0.01 g and record.

9.6 Place boards in the tray on sponges as noted in Fig. 1. If coated edges are to be tested, note that the sponges must be narrower than the length (nominally 10.2 cm or 4 in.) of the contacting coated edges to prevent contact of the solution with the uncoated edges of the samples. Sponges 9.0-cm (3.5-in.) wide have been used successfully. For the same reason, the

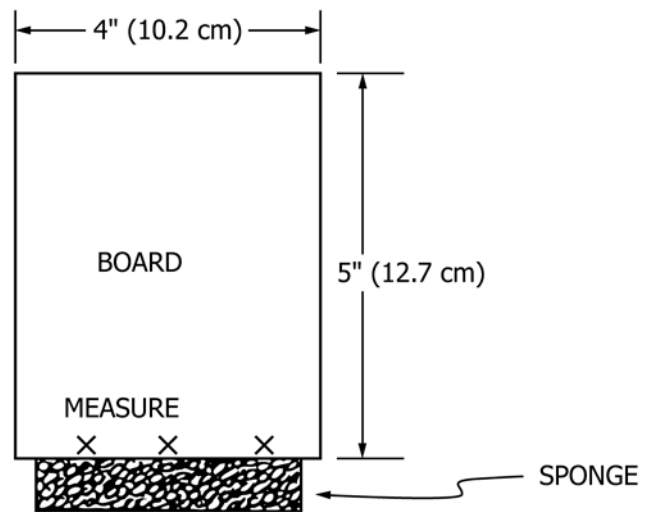


FIG. 2 Specimen Dimensions

coated face of the board must rest against the sponge at a 60° angle to prevent contact of the solution with the uncoated back of the board.

9.7 The test duration is 2 h. After 2 h, remove the boards and blot the edges dry with paper towels.

9.8 Observe and record changes as follows:

9.8.1 Visually inspect the edges for cracks and record the crack rating in accordance with Test Method D661. Repeat the observation 48 h later.

9.8.2 Remeasure the thickness of the boards at the same spots measured in 4.4. Record the percent change at each spot,

9.8.3 Reweigh the boards and record the weight gain and percent weight gain, and

9.8.4 Calculate averages and standard deviations for the percent thickness change and percent weight gain.

10. Precision and Bias

10.1 *Precision*—An interlaboratory study of Composite Wood Product surfactant accelerated moisture stress was conducted in accordance with Practice E691 in seven laboratories

³ Common test solutions such as 1.0 % of an ethoxylated alkylphenol, nonionic with hydrophile lipophile balance (HLB) of 13.5 is made using warm, (over 120°F (49°C)), distilled, or deionized water. Historically, Triton X-100 has been used, but with this revision Turgitol 15-S-9 was used. Refer to *McCutcheon's Emulsifiers and Detergents*, 1996, McCutcheon Publishing Co., 175 Rock Rd., Glen Rock, NJ 07452.

TABLE 1 Interlaboratory Study

Material	Average	Repeatability, Standard Deviation, Sr	Reproducibility, Standard Deviation, SR	Repeatability Limit, Y	Reproducibility Limit, R
A	12.8886	2.0878	5.8050	5.8458	16.2540
B	9.7200	0.6498	3.5835	1.8195	10.0338
C	16.8257	2.1491	7.4174	6.0175	20.7688
D	9.1943	2.0814	6.2392	5.8279	17.4696
E	14.3286	2.0616	5.4152	5.7724	15.1626
F	11.8229	3.7899	6.3353	10.6117	17.7389

with five materials, with each laboratory obtaining six test results for each material (see [Table 1](#)).

10.1.1 The terms repeatability limit and reproducibility limit in [Table 1](#) are used as specified in Practice [E177](#).

10.2 *Bias*—Since there is no accepted reference material, method, or laboratory suitable for determining the bias for the procedure in this test method, no statement on bias is being made.

11. Keywords

11.1 accelerated moisture stress; detergent test; wood or composite-wood

ASTM International takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.

This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.

This standard is copyrighted by ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (www.astm.org). Permission rights to photocopy the standard may also be secured from the Copyright Clearance Center, 222 Rosewood Drive, Danvers, MA 01923, Tel: (978) 646-2600; http://www.copyright.com/