



# Standard Test Method for Adequacy of Fusion of Extruded Poly(Vinyl Chloride) (PVC) Pipe and Molded Fittings by Acetone Immersion<sup>1</sup>

This standard is issued under the fixed designation D2152; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon ( $\epsilon$ ) indicates an editorial change since the last revision or reapproval.

## 1. Scope\*

1.1 This test method covers the determination of the adequacy of fusion of extruded rigid poly(vinyl chloride) (PVC) pipe and molded fittings as indicated by reaction to immersion in anhydrous acetone.

1.2 The values stated in inch-pound units are to be regarded as the standard except where instruments are calibrated in SI units.

1.3 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.* Specific hazards statements are given in [Annex A1](#).

## 2. Referenced Documents

- 2.1 *ASTM Standards:*<sup>2</sup>  
[D618 Practice for Conditioning Plastics for Testing](#)

## 3. Significance and Use

3.1 This test method is applicable only for distinguishing between inadequately fused and adequately fused PVC. The difference between thermally degraded and adequately fused PVC cannot be detected by this test method. Acetone immersion is not a substitute for burst, impact, or other physical or chemical tests on PVC pipe or fittings and it, therefore, shall not be used as the only test specification for purchasing of PVC pipe and fittings. This test only detects inadequate fusion and does not determine the over-all quality of the PVC pipe or fittings.

<sup>1</sup> This test method is under the jurisdiction of ASTM Committee F17 on Plastic Piping Systems and is the direct responsibility of Subcommittee F17.25 on Vinyl Based Pipe.

Current edition approved May 1, 2013. Published June 2013. Originally approved in 1963T. Last previous edition approved in 2010 as D2152 – 95(2010). DOI: 10.1520/D2152-13.

<sup>2</sup> For referenced ASTM standards, visit the ASTM website, [www.astm.org](http://www.astm.org), or contact ASTM Customer Service at [service@astm.org](mailto:service@astm.org). For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

3.2 This test method is useful in determining whether inadequate fusion contributed to failure of PVC pipe or fittings in other physical or chemical tests, or in service.

3.3 This test method is useful in evaluating the adequacy of PVC fusion obtained in process or materials trials.

3.4 This test method determines adequacy of fusion on a single, relatively small specimen. This test method requires the use of a hazardous reagent which must be properly handled and disposed. Therefore, this test method may not be cost-effective to employ as a routine quality control test.

## 4. Apparatus

4.1 *Container*—Either individual, sealable containers for each specimen or one large, airtight container capable of holding several specimens without touching one another.

4.2 *Hydrometer and Cylinder*—Precision hydrometer, graduated in thousandths, with a minimum range of 0.780 to 0.790 g/mL and a cylinder large enough to immerse the hydrometer.

4.3 *Thermometer*—ASTM 12C total immersion thermometer, range from  $-20^{\circ}\text{C}$  to  $102^{\circ}\text{C}$  accurate to  $0.2^{\circ}\text{C}$ , or equivalent.

## 5. Reagent

5.1 *Acetone*—American Chemical Society Reagent Grade, having a maximum density of 0.7857 g/mL at  $25^{\circ}\text{C}$ .

NOTE 1—See [Annex A1](#) for the safety and health precautions to be used with acetone.

5.2 Prior to conducting the test, check the density of the acetone with a precision hydrometer to determine its dryness. If the density of the acetone is greater than 0.7890 g/mL at  $23^{\circ}\text{C}$ , (corresponding to approximately 1 % water by mass (see [Fig. X1.1](#))), use fresh acetone or dry the wet acetone with a drying agent. Recheck the density of the fresh or dried acetone before using.

NOTE 2—Wet acetone can be dried by thoroughly agitating it with at least 15 g of anhydrous calcium sulfate ( $\text{CaSO}_4$ ) for each gram of water present.

NOTE 3—The presence of water in the acetone reduces its sensitivity to differences in the degree of fusion of rigid poly(vinyl chloride) (PVC). It is important to dry the acetone properly and conduct the test in a sealed

\*A Summary of Changes section appears at the end of this standard

container, because acetone rapidly absorbs moisture from the atmosphere.

NOTE 4—Round-robin testing between four laboratories showed that test results are not significantly altered with up to 2 % water by weight in the acetone.

## 6. Sampling

6.1 Specimens shall be taken from individual pipe sections, fittings, or remnant portions of pipe or fittings. Specimens shall be taken from locations which are to be evaluated for adequacy of fusion, or immediately adjacent to them.

6.2 The number of individual specimens to be tested and their locations shall be chosen to be representative of the pipe or fittings being evaluated for adequacy of fusion.

## 7. Test Specimens

7.1 *Size of Specimen*—Specimen shall be a size that is convenient to immerse in the test container but not less than ½ in. (13 mm) in height. For small diameter pipe, the specimen shall be a complete circumferential section of the pipe. For large diameter pipe, the specimen shall be a full pipe section but it may be cut into smaller pieces to facilitate testing. Small molded parts shall be immersed as a single item. For large molded fittings, the specimen shall be a complete circumferential section which may be cut into segments before being immersed. If the pipe or fitting to be evaluated has fractured or fragmented in other tests or in service, specimens of any shape and size may be tested.

7.2 *Specimen Preparation*—For pipe having a wall thickness greater than 0.125 in. (3.2 mm) the wall thickness shall be reduced to allow testing of the entire wall thickness of the specimen at six or more intervals around the circumference of one end of the specimen. The mid-wall surface exposed for testing shall be from the interior wall surface to the exterior wall surface at a minimum of 45 degrees from the square cut on the end of the pipe as shown in Fig. 1. Removal shall be effected by filing, wet sanding, or other means that will minimize localized heating of the surface. It is not necessary to reduce the wall thickness on molded fittings.

## 8. Conditioning

8.1 Unless otherwise specified, condition the specimens in air for 1 h at  $23 \pm 2^\circ\text{C}$  ( $73.4 \pm 3.6^\circ\text{F}$ ) prior to testing. The




FIG. 1 Specimen Preparation

specimens shall not be conditioned in water because of the effect water has on the acetone. For referee purposes conditioning shall be in accordance with Procedure A of Practice D618.

## 9. Procedure

9.1 Conduct the tests in a Standard Laboratory Atmosphere of  $23 \pm 2^\circ\text{C}$  unless otherwise specified.

9.2 Place sufficient dried acetone into the container to ensure complete immersion of the specimen.

9.3 Place the test specimen in the acetone, seal the container, and do not agitate. Allow specimen to stand immersed for 20 min.

9.4 After 20 min, remove the specimen from the container and inspect for signs of attack.

9.5 Attack is described as a lifting, raising, or removing, or both, of any material outside surface, inside surface, or mid-wall, of the specimen. Swelling or softening of the test specimen shall not be considered attack.

## 10. Fusion Criteria

10.1 At least 50 % attack of the inside, outside, or mid-wall surface or at least 10 % attack on more than one surface shall be considered to be indicative of inadequate fusion.

## 11. Report

11.1 The report shall include the following:

11.1.1 Complete identification of the PVC compound,

11.1.2 Production code number of the pipe or fittings,

11.1.3 Nominal dimensions of the pipe or fittings,

11.1.4 Observations after 20 min immersion shall be reported indicating attack or no attack,

11.1.5 The area attacked, inside, outside, or mid-wall, and the estimated percentage of that area attacked, and

11.1.6 Date of test.

## 12. Precision and Bias

12.1 This test method is subjective, based on operator judgement. Therefore a statement on precision and bias is not applicable.

## 13. Keywords

13.1 acetone; fusion; pipe; poly(vinyl chloride); PVC

(Mandatory Information)

**A1. RECOMMENDED SAFETY PRECAUTIONS TO BE USED WITH ACETONE**

**A1.1 Safety Requirements:**

A1.1.1 No source of ignition is to be permitted where acetone is used.

A1.1.2 Dispense acetone only from approved safety containers.

A1.1.3 Dispose of used acetone, or acetone-impregnated cloths only in an approved safety waste receptacle.

A1.1.4 Avoid prolonged breathing of acetone. Use acetone only in a well ventilated area.

A1.1.5 Use proper eye protection such as chemical-worker’s goggles or a face shield when handling acetone.

A1.1.6 Avoid prolonged exposure to the skin. If prolonged exposure to the skin cannot be avoided, use protective clothing.

**A1.2 Health Hazards:**

A1.2.1 Acetone is a mild irritant to eyes, nose and throat but only minor residual injury will occur if no medical treatment is given.

A1.2.2 Prolonged or continuous exposure of acetone to the skin may cause acute or chronic dermatitis. Exposed skin areas should be washed and dried. Consult a physician if a rash develops.


**A1.3 Fire Hazard:**

A1.3.1 Acetone is a very flammable liquid having a flash point of  $-18^{\circ}\text{C}$  ( $0^{\circ}\text{F}$ ). Use dry chemical, alcohol foam, or carbon dioxide to fight a fire. Use water to keep fire-exposed containers cool or to wash away or dilute spills which have not ignited.

**APPENDIX**

(Nonmandatory Information)

**X1. DENSITY OF ACETONE VERSUS PERCENT WATER AT FOUR TEMPERATURES**

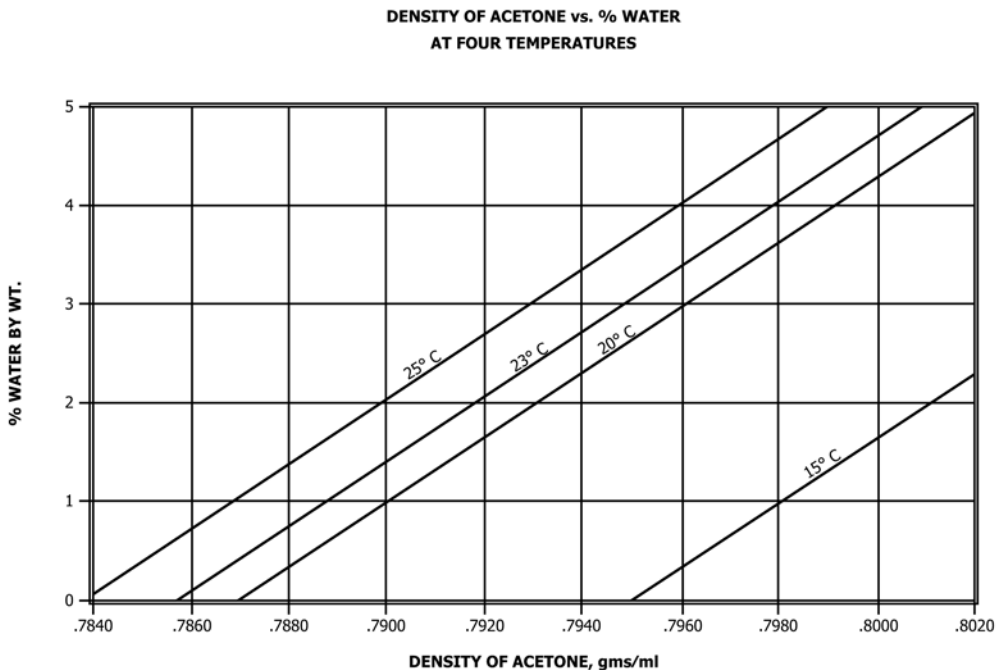

**FIG. X1.1 Density of Acetone versus Percent Water at Four Temperatures**

**SUMMARY OF CHANGES**

Committee F17 has identified the location of selected changes to this standard since the last issue (D2152 – 95(2010)) that may impact the use of this standard.

(1) 7.2 was revised.

(2) Fig. 1 was added.

*ASTM International takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.*

*This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.*

*This standard is copyrighted by ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (www.astm.org). Permission rights to photocopy the standard may also be secured from the Copyright Clearance Center, 222 Rosewood Drive, Danvers, MA 01923, Tel: (978) 646-2600; <http://www.copyright.com/>*