



Standard Test Method for Column Crush Properties of Blown Thermoplastic Containers¹

This standard is issued under the fixed designation D2659; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

1. Scope*

1.1 This test method covers the determination of mechanical properties of blown thermoplastic containers, whether blown commercially or in the laboratory, loaded under columnar crush conditions at a constant rate of compressive deflection.

NOTE 1—Although this test method was developed specifically for blow-molded containers, the general procedure can also be applied to containers of suitable geometries produced by other means, for example, thermoforming, injection molding, etc.

1.2 The values stated in SI units are to be regarded as the standard.

NOTE 2—There is no known ISO equivalent to this standard.

1.3 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

2. Referenced Documents

2.1 *ASTM Standards:*²

- D618 Practice for Conditioning Plastics for Testing
- D883 Terminology Relating to Plastics
- D4976 Specification for Polyethylene Plastics Molding and Extrusion Materials
- E4 Practices for Force Verification of Testing Machines
- E83 Practice for Verification and Classification of Extensometer Systems

3. Terminology

3.1 *Definitions*—For definitions of terms used in this test method and associated with plastics issues refer to the terminology contained in ASTM D883.

¹ This test method is under the jurisdiction of ASTM Committee D20 on Plastics and is the direct responsibility of Subcommittee D20.19 on Film, Sheeting, and Molded Products.

Current edition approved May 1, 2016. Published May 2016. Originally approved in 1967. Last previous edition approved in 2011 as D2659 - 11. DOI: 10.1520/D2659-16.

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

3.2 Definitions of Terms Specific to This Standard:

3.2.1 *apparent crushing stiffness*—the ratio of the crushing load to the corresponding deflection at a point on the linear portion of the crushing load deflection curve (expressed in newtons per metre (or pounds per inch)).

3.2.2 *column*—a compression member that is axially loaded.

3.2.3 *crushing load at failure*—the crushing load applied to a blown thermoplastic container that produces a failure by fracture or parting of the material in any portion of said container (expressed in kilograms (or pounds)).

3.2.4 *crushing yield load*—the first load at which an increase of deflection occurs with no increase in load in a compressive crushing test (expressed in units of kilograms (or pounds) of load).

NOTE 3—In some cases, usually as a result of design or styling features, or both, of a specific container, multiple values of the crushing yield load are observed, that is, a small deflection occurs with no increase or with a decrease in the crush load, followed by resumption of the normal crush load change with deflection. This phenomenon cannot be ignored in the evaluation of the column crush properties of a blown thermoplastic container, since it can be a very useful designated failure point for the application under consideration. The load at which this abrupt change occurs can be chosen as a crushing yield load for study. In such a case, the report of results should be accompanied by a proper description of the crushing yield load selected.

3.2.5 *deflection at crushing yield load*—the decrease in length of the container specimen produced at the crushing yield load along the center line of testing (axis of crushing, see Fig. 1) (expressed in millimetres (or inches)).

3.2.6 *gage length*—the original length of that portion of the specimen over which strain or change in length is determined.

4. Significance and Use

4.1 Column crush tests only provide information about the crush properties of blown thermoplastic containers when employed under conditions approximating those under which the tests are conducted.

4.2 The column crush properties include the crushing yield load, deflection at crushing yield load, crushing load at failure, and apparent crushing stiffness. Blown thermoplastic containers made from materials that possess a low order of ductility can fail in crushing by brittle fracture. In such cases, the

*A Summary of Changes section appears at the end of this standard

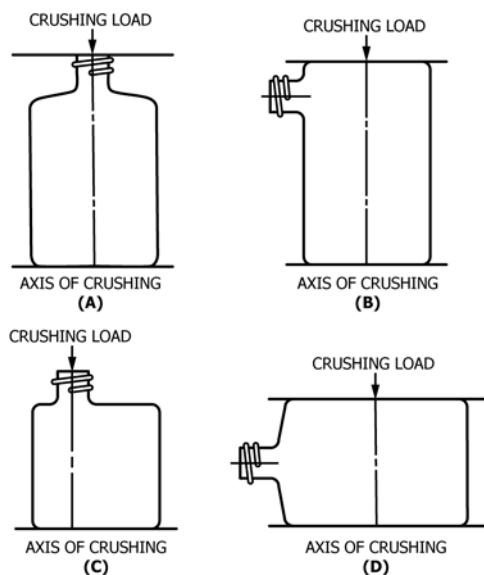


FIG. 1 Typical Crushing Axes

crushing yield load is equivalent to the crushing load at failure. Blown thermoplastic containers made of ductile materials do not always exhibit a crushing load at failure although they will normally provide a crushing yield load value.

4.3 Column crush tests provide a standard method of obtaining data for research and development, applications, design, quality control, acceptance or rejection under specifications, and special purposes. The tests cannot be considered significant for engineering design in applications differing widely from the load - time scale of the standard test. Such applications require additional tests such as impact, creep, and fatigue.

5. Apparatus

5.1 *Testing Machine*—Any suitable testing machine capable of control of constant-rate-of-crosshead movement and comprising essentially the following:

5.1.1 *Drive Mechanism*—A drive mechanism imparting the crosshead movable member of a uniform, controlled velocity with respect to the fixed member, this velocity to be regulated as specified in Section 9.

5.1.2 *Load Indicator*—A load-indicating mechanism capable of showing the total crushing load carried by the test specimen. The mechanism shall be essentially free from inertia-lag at the specified rate of testing and shall indicate the crushing load with an accuracy of $\pm 1\%$. The accuracy of the testing machine shall be verified at least once a year, in accordance with Practices E4.

5.2 *Extensometer*—A suitable instrument for determining the distance between the two surfaces of load application on the test specimen at any time during the test. It is desirable that this instrument automatically record this distance, or any change in it as a function of the crushing load on the test specimen. The instrument shall be essentially free of inertia-lag at the specified rate of loading and shall conform to the requirements for a Class B-2 extensometer, as defined in Practice E83.

5.3 *Load Application Fixtures*—A means shall be provided to apply the crushing load to the specimen such as a stationary and moveable parallel platens. The fixtures shall be of sufficient rigidity to prevent fixture deformation due to the applied crushing load.

NOTE 4—In the event that the bearing surface of the blown thermoplastic container deviates noticeably from the parallel relationship, the construction and use of a suitable testing jig will be necessary. This jig shall be attached to that crosshead member of the testing machine that contacts the nonparallel surface of the container. In the event of slippage on the machine crushing surfaces, a nonslip material such as masking tape can be applied to the slipping member of the testing machine.

6. Test Specimens

6.1 The specimens for testing shall be the blown thermoplastic container under investigation. The specimens must be free of obvious defects such as rocker bottoms or bent necks, unless such defects constitute a variable to be studied. The surfaces of the container that bear on the fixed and movable members of the testing machine shall be parallel to each other.

7. Conditioning

7.1 *Conditioning*—Condition the test specimens in accordance with Procedure A of Practice D618 unless otherwise specified by contract or the relevant ASTM material specification. Temperature and humidity tolerances shall be in accordance with Section 7 of Practice D618 unless specified differently by contract or material specification.

7.2 *Test Conditions*—Conduct tests at the same temperature and humidity used for conditioning with tolerances in accordance with Section 7 of Practice D618 unless otherwise specified by contract or the relevant ASTM material specification.

NOTE 5—Alternatively, blown thermoplastic container test specimens that are made of materials known to be insensitive to changes of relative humidity, can be conditioned at the Standard Laboratory Temperature of $23 \pm 2^\circ\text{C}$ ($73.4 \pm 3.6^\circ\text{F}$) for a period of 24 h, unless otherwise specified.

8. Number of Test Specimens

8.1 At least 20 specimens shall be tested for each sample on any given axis of crushing. If more than one axis of crushing is to be studied, at least 20 specimens shall be tested for each axis.

8.2 Specimens that fail at some obvious fortuitous flaw shall be discarded and retests made on additional specimens, unless such flaws constitute a variable to be studied. The data shall be discarded and the number of rejected specimens noted.

9. Speed of Testing

9.1 Speed of testing shall be the relative rate of motion of the fixed and movable members of the testing machine during the test. Rate of motion of the movable member, when the machine is running idle, can be used if it can be shown that the resulting speed of testing is within the limits of variation allowed.

9.2 The speed of testing shall be constant within $\pm 10\%$.

9.3 The speed of testing shall be chosen in the range from 12.5 mm (0.50 in.)/min to 50.0 mm (2.0 in.)/min.

NOTE 6—Round-robin tests have shown that precision of measurements is less than satisfactory when testing speeds less than 12.5 mm (0.50 in.)/min or more than 50.0 mm (2.0 in.)/min were employed for a limited number of blown thermoplastic container styles and designs. Lower or higher testing speeds are acceptable if it can be shown that the precision of the resulting measurements is satisfactory.

NOTE 7—A testing speed of 25.0 ± 2.5 mm (1.0 ± 0.1 in.)/min has been found useful. It is desirable, however, that several speeds of testing be evaluated when a new blown thermoplastic container is to be studied, since performance behavior can be affected by different testing speeds.

10. Procedure

10.1 Place the test specimen between the fixtures of the testing machine, taking care to align the axis of crushing with the center line of the movable fixture and to ensure that the bearing surfaces of the test specimen are parallel to the bearing surfaces of the stationary and movable fixtures. Ensure adequate venting to allow equalization of air pressure during the crushing test (see Note 8). Adjust the movable fixture of the testing machine until it just contacts the top of the test specimen.

10.2 Carefully select the axis of crushing so as to provide measurements along the desired blown thermoplastic container center line. Fig. 1 shows typical axes of crushing selections.

NOTE 8—Round-robin tests have shown that pressure changes within a sealed blown thermoplastic container during column crush tests will change the values obtained. If the seal is not consistent, the accuracy and precision of the measurement will be adversely affected. Furthermore, testing of sealed specimens can result in explosive failure, so that testing is not recommended without proper safeguards. Thus, venting of the specimens is necessary, not only to ensure accuracy and precision of measurements, but, also, as a safety precaution, and to ensure a correct basis for obtaining comparable measurement data. In the case of (a) and (c) in Fig. 1, this can be accomplished by allowing the container opening to remain unsealed and drilling a hole in the testing machine member that bears on this opening.

10.3 If the crushing yield load data only are desired, proceed as follows:

10.3.1 Set the speed control at the desired speed of testing and start the machine.

10.3.2 Record the load carried by the specimen as defined in 3.2 and the location of the yield or failure of the specimen.

10.4 If crush load - deflection data are desired, proceed as follows:

10.4.1 Attach or adjust the extensometer, or both.

10.4.2 Set the speed control at the desired speed of testing and start the machine.

10.4.3 Record crush loads and corresponding deflection at appropriate intervals of deflection, or, if the test machine is equipped with an automatic recording device, record the crush load - deflection curve to the desired end point. In either case, also record the location of the yield or failure of the specimen.

11. Calculation

11.1 *Crushing Yield Load*—Determine the crushing yield load by observation of that point on the crush load - deflection curve at which an increase in deflection occurs without an increase in crush load. Express the result in kilograms (or pounds) and report to three significant figures.

11.2 *Crushing Load at Failure*—Determine the crushing load at failure by observation of that point on the crush load -

deflection curve that corresponds to the failure by fracture or parting of the material. Express the results in kilograms (or pounds) and report to three significant figures.

11.3 *Deflection at Crushing Yield Load*—Determine the deflection at crushing yield load by observation of the decrease in length produced in gage length of the specimen at the crushing yield load. Express the results in millimetres (or inches) and report the result to three significant figures.

11.4 *Apparent Crushing Stiffness*—Calculate the apparent crushing stiffness by selecting any point on the initial straight line portion of the crush load - deflection curve and dividing the crush load at this point by the corresponding deflection. Express the results in newtons per metre (or pounds per inch) and report to three significant figures.

11.5 If the crushing load-deflection curve exhibits a non-linear response, this shall be reported in accordance with 12.1.11.

11.6 For each sample of at least 20 test specimens, calculate to three significant figures the arithmetic mean of all values obtained and report as the “average value” for the particular property in question.

11.7 For each lot of samples tested, calculate the standard deviation (estimated) as follows and report to two significant figures.

$$s = \sqrt{(\sum X^2 - n\bar{X}^2)/(n - 1)} \quad (1)$$

where:

s = estimated standard deviation,

X = value of a single observation,

n = number of observations, and

\bar{X} = arithmetic mean of the set of observations.

12. Report

12.1 Report the following information:

12.1.1 Complete identification of the blown thermoplastic container tested, such as type, source, manufacturer, form, and previous history,

12.1.2 Purpose of test,

12.1.3 Conditioning procedure used,

12.1.4 Atmospheric conditions in test room,

12.1.5 Description of axis of crushing used,

12.1.6 Number and weight of specimens, average value, and standard deviation,

12.1.7 Speed of testing,

12.1.8 Crushing yield load, average value, and standard deviation,

12.1.9 Crushing strength at failure, average value, standard deviation, and description of failure,

12.1.10 Deflection at crushing yield point, average value, and standard deviation,

12.1.11 Apparent crushing stiffness, average value, and standard deviation, as well as specification at the point chosen in the case of a crush load - deflection curve that is nonlinear,

12.1.12 Description of the yield or any other failure phenomenon of the specimen, and

12.1.13 Date of test.

13. Precision and Bias

13.1 The between-laboratories *reproducibility* of this test method was determined on a 2015-cm³ (68-oz) cylindrical container (capacity measured to overflow), weighing approximately 70 g made from a Class 3 polyethylene plastic (Specification **D4976**). The speed of testing was 25.4 mm/min. The sample size was 20 containers. The containers were made in a single laboratory from a single mold and tested in five different laboratories. The average values and between-laboratories standard deviations obtained were:

	<i>X</i>	<i>s</i>
Crushing yield load, kg (lb)	35.1 (77.4)	1.68 (3.7)
Deflection at crushing yield load, mm (in.)	8.941 (0.352)	0.787 (0.031)
Apparent crushing stiffness, N/m (lb/in.)	55.7 (493)	3.6 (32)

13.2 The within-laboratory *repeatability* of this test method gave similar results on bottles made from the same mold and the same raw material.

13.3 These containers did not exhibit crushing strength at failure.

13.4 Since there is no accepted reference method for this test method, the bias of this test method cannot be determined.

14. Keywords

14.1 crush properties; plastic containers

SUMMARY OF CHANGES

Committee D20 has identified the location of selected changes to this standard since the last issue (D2659 - 11) that may impact the use of this standard. (May 1, 2016)

- | | |
|--|---|
| <ul style="list-style-type: none"> (1) Added reference to ASTM D883. (2) Added 3.2 Definition of Terms Specific to this Standard. (3) Added 3.1.5 to define column. (4) Added 3.1.6 to define gage length. (5) Added 5.3 Load application fixtures. (6) Moved Note 4 up from Section 6, Test Specimens, to under 5.3, Load application fixtures. | <ul style="list-style-type: none"> (7) Revised wording in 7.1 and 7.2 to reference D618 instead of listing the actual conditioning requirements. (8) Removed 10.1 which requires the determination of the test specimen weight as it is not used in the procedure nor calculations. (9) Replaced the term “member” with “fixture” to be consistent with the addition of load application fixtures in 5.3, Apparatus. |
|--|---|

ASTM International takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.

This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.

This standard is copyrighted by ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (www.astm.org). Permission rights to photocopy the standard may also be secured from the Copyright Clearance Center, 222 Rosewood Drive, Danvers, MA 01923, Tel: (978) 646-2600; http://www.copyright.com/