



Standard Test Method for Wear Rate and Coefficient of Friction of Materials in Self- Lubricated Rubbing Contact Using a Thrust Washer Testing Machine¹

This standard is issued under the fixed designation D3702; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

1. Scope

1.1 This test method covers the determination of wear rate and coefficient of friction for self-lubricated materials in rubbing contact by a testing machine² that utilizes a thrust washer specimen configuration.

NOTE 1—This machine may also be used to measure coefficient of friction.

1.2 The values in SI units are to be regarded as the standard. In cases where materials, products, or equipment are available only in inch-pound units, SI values in parentheses are for information only.

1.3 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

2. Terminology

2.1 Definitions:

2.1.1 *coefficient of friction, μ or f —in tribology*—the dimensionless ratio of the friction force (F) between two bodies to the normal force (N) pressing these bodies together.

$$\mu \text{ or } f = (F/N) \quad (1)$$

2.1.1.1 *Discussion*—A distinction is often made between static coefficient of friction and kinetic coefficient of friction.

2.1.2 *wear*—damage to a solid surface, generally involving progressive loss of material, due to relative motion between that surface and a contacting substance or substances.

¹ This test method is under the jurisdiction of ASTM Committee D02 on Petroleum Products, Liquid Fuels, and Lubricants and is the direct responsibility of Subcommittee D02.L0.05 on Solid Lubricants.

Current edition approved May 1, 2014. Published July 2014. Originally approved in 1978. Last previous edition approved in 2009 as D3702–94 (2009). DOI: 10.1520/D3702-94R14.

² An example known to the committee at this time is the Falex Multispécimen Test Machine, available from Falex Corp., 1020 Airpark Drive, Sugar Grove, IL 60554. This manufacturer recommends a maximum test load of 808 lb (367 kg). If you are aware of alternative suppliers, please provide this information to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee,¹ which you may attend.

2.1.3 *wear rate*—the rate of material removal or dimensional change due to wear per unit of exposure parameter; for example, quantity of material removed (mass, volume, thickness) in unit distance of sliding or unit time.

2.2 Definitions of Terms Specific to This Standard:

2.2.1 *torque*—reaction of a tendency to turn due to friction forces between specimens traveling in a circular path. It is the product of a restraining force and the radius at which it acts to balance the frictional torque.

3. Summary of Test Method

3.1 The test machine is operated with a test specimen rotating under load against a stationary steel washer. Each test consists of break-in for 40 h followed by a selected test duration, each at the same selected normal load and speed. Load is obtained by application of dead weights to the 10:1 lever arm. The contact area is 1.29 cm² (0.20 in.²). The mean rubbing velocity is related to spindle rotational speed: 1 rpm = 0.0848 m/min (0.278 ft/min).

3.2 The thickness change of the test specimen and torque during test are measured for each test.

3.3 Wear rate in centimetres per hour (inches per hour) and coefficient of friction is reported.

4. Significance and Use

4.1 This test method is used to determine the equilibrium rate of wear and coefficient of friction of materials in rubbing contact under useful operating conditions, that is, combinations of pressure and velocity that fall below the PV (pressure \times velocity) limit of the test material. The user of this test method should determine to his own satisfaction whether the results of this test procedure correlate with field performance or other bench test machines. If the test conditions are changed, the wear rates may change and the relative value of one material with respect to another may also change.

4.2 Test conditions may be selected from **Table 1**.

4.3 The precision of wear measurement is relatively independent of test duration or amount of wear, but the precision of wear rate (calculation) improves with test duration and amount of wear. It is generally believed that useful wear rate precision

TABLE 1 Test Conditions^A

Rotational speed, rpm	Rubbing Velocity, ft/min (m/min)	Load, lb (kg), to Obtain PV, psi × ft/min (kg/cm ² × m/min) at Selected Speeds			
		PV ₁ 1250 (26.8)	PV ₂ 2500 (53.6)	PV ₃ 5000 (107.1)	PV ₄ 10 000 (214.3)
36	10 (3.05)	25.0 (11.3)	50.0 (22.7)	100 (45.4)	200 (90.7)
180	50 (15.2)	5.0 (2.3)	10.0 (4.5)	20.0 (9.1)	40.0 (18.1)
900	250 (76.2)	1.0 (0.5)	2.0 (0.9)	4.0 (1.8)	8.0 (3.6)

^A For many applications a wear rate exceeding 1.0×10^{-5} in./h (2.5×10^{-7} m/h) is considered excessive. Typical wear rates for some commonly used materials at different PV levels are:

Acetal homopolymer at PV ₁ :	5×10^{-6} to 1×10^{-5} in./h (1.3×10^{-7} to 2.5×10^{-7} m/h)
Acetal homopolymer at PV ₂ :	1×10^{-5} to 3×10^{-5} in./h (2.5×10^{-7} to 7.5×10^{-7} m/h)
22 % PTFE-filled acetal homopolymer at PV ₂ :	3×10^{-6} to 6×10^{-6} in./h (7.5×10^{-8} to 1.5×10^{-7} m/h)
Polyamide (Type 6-6) at PV ₂ :	1×10^{-5} to 5×10^{-5} in./h (2.5×10^{-7} to 1.3×10^{-6} m/h)
15 % graphite filled polyimide resin at PV ₃ :	1×10^{-5} to 2×10^{-5} in./h (2.5×10^{-7} to 5×10^{-7} m/h)

requires the selection of a test duration sufficient to produce 0.1 mm (0.004 in.) of wear. Test durations will often be in the 50 to 4000-h range.

5. Apparatus

5.1 *Falex Multispecimen Test Machine*, Fig. 1, shown schematically in Fig. 2 and described in Annex A1.

5.2 *Test Specimen or Rotating Wafer*, shown in Fig. 3.

5.3 *Stationary Washer*, AISI C-1018 steel, shown in Fig. 4. The surface finish should be 16 ± 2 µin. AA, the hardness Rc 20 ± 5 .

5.4 *Micrometer* (Note 4), capable of measuring to the nearest 0.003 mm (0.0001 in.).

6. Reagents and Materials

6.1 *Solvent*, safe, non-film forming, nonchlorinated.

NOTE 2—Petroleum distillates, formerly used as solvents, have been eliminated due to possible toxic effects. Each user should select a solvent that can meet applicable safety requirements and thoroughly clean machine parts.

6.2 Appropriate reagents for cleaning the test specimen as recommended by the manufacturer of the test material.

7. Preparation of Apparatus

7.1 Measure the finish of the steel mating surface perpendicular to the finishing direction.

7.2 Before each test, thoroughly clean the steel washer and both specimen holders using the solvent per 5.1.

NOTE 3—Remove all solvents from the washer before testing.

7.3 Clean the test specimen as recommended by the manufacturer of the test material.

7.3.1 Store cleaned test specimens prior to testing in a glass jar.

7.3.2 Following the cleaning, do not handle the test specimens with bare hands. It is recommended that clean cotton gloves or clean tweezers or tongs be used.

NOTE 4—Check compatibility of the test specimen cleaning procedure and reagents with the specific material to be tested.

7.4 Preset the speed control to provide the desired speed as measured in revolutions per minute using the built-in tachometer. Refer to Table 1 to convert the specified velocity to revolutions per minute.

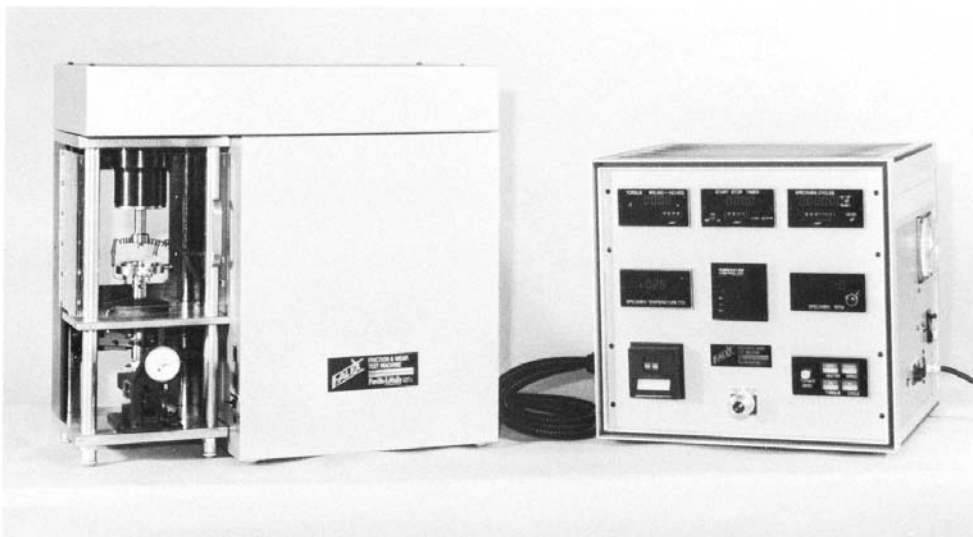


FIG. 1 The Falex Multispecimen Test Machine

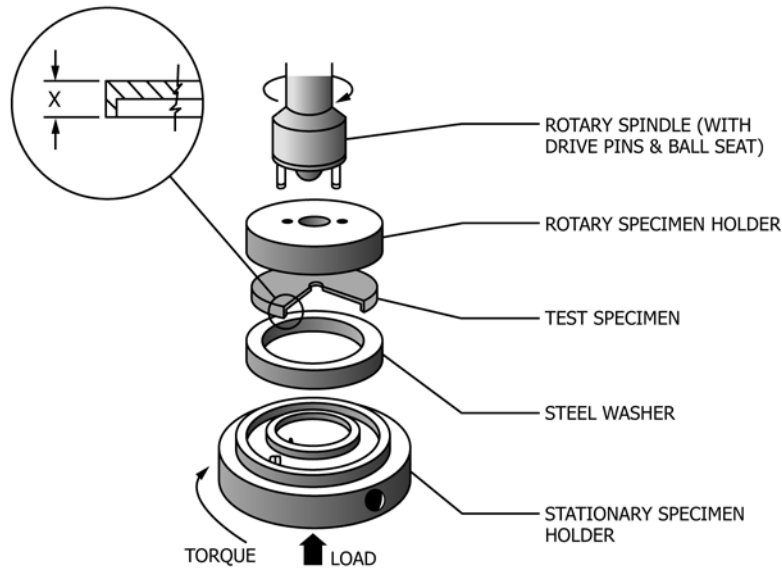


FIG. 2 Thrust Washer Test Specimen Arrangement

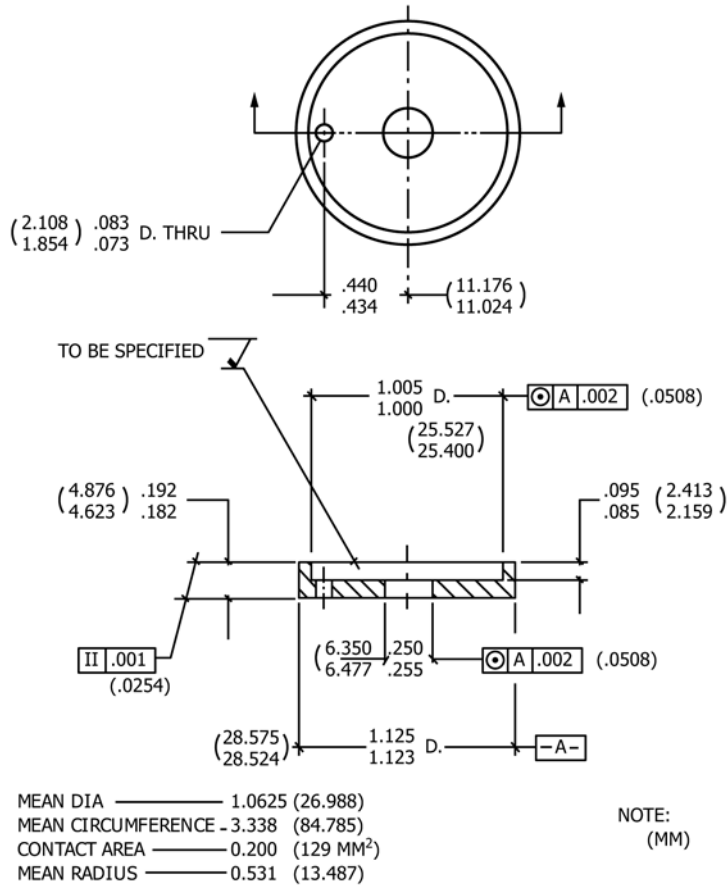


FIG. 3 Rotating Test Specimen

7.5 Install the test specimen in the upper specimen holder with the bolt and washer provided. Torque the bolt to

$$2.8 \pm 0.6 \text{ J } (25 \pm 5 \text{ in.}\cdot\text{lbf}) \quad (2)$$

7.6 Place the steel washer in the lower specimen holder.

7.7 Balance the load lever arm with the bale rod attached.

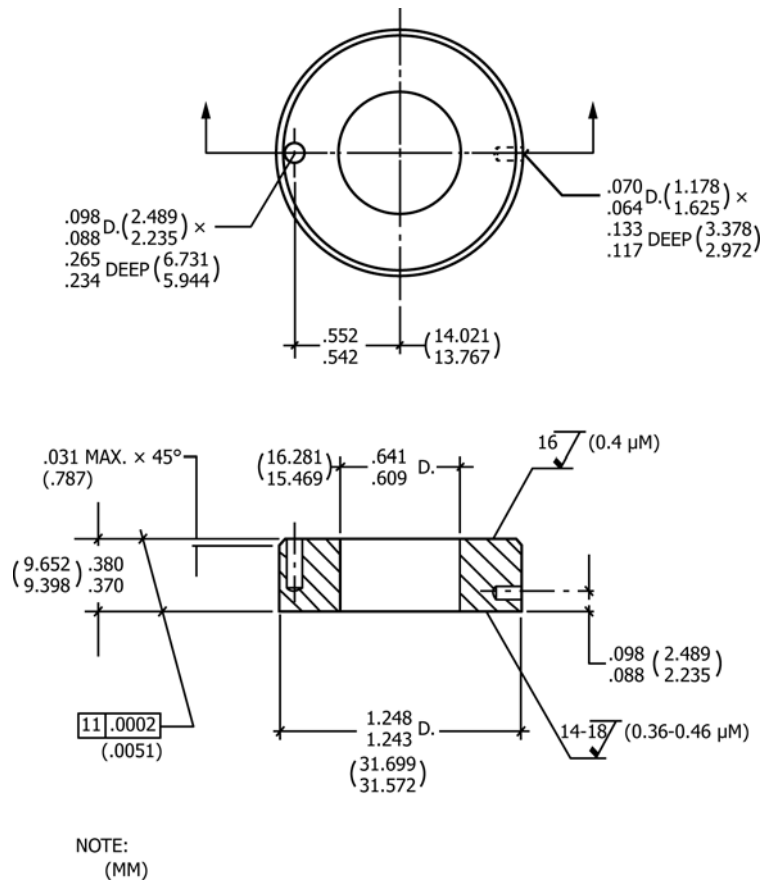


FIG. 4 Stationary Steel Washer Specimen

7.8 Mount the test specimen together with its specimen holder in the rotary spindle so that the drive pins of the spindle are inserted in the drive pin holes of the specimen holder and the specimen holder is free to pivot on the ball seat.

7.9 Determine the dead weight, w , to be applied to the bale rod as follows:

$$W = \frac{F}{10} \quad (3)$$

where:

F = normal force.

7.10 If coefficient of friction is to be determined, check calibration of torque meter and adjust, if required, according to equipment manufacturer's instructions.

NOTE 5—Calibrate torque meter such that the anticipated test torque is approximately two-thirds of calibration value.

NOTE 6—A chart recorder can be used to continuously record torque throughout the test. Zero and span the recorder according to the manufacturer's instructions.

8. Procedure

8.1 With the specimens and bale rod in position, gently apply the appropriate weight to the bale rod.

8.2 Turn on the machine.

8.3 When the prescribed break-in interval duration (40 h) has been completed, stop the machine, remove the weights

from the bale rod and carefully lower the stationary specimen holder to its lowest position.

8.4 Remove the test specimen together with its specimen holder and clean with a lint-free wiper.

8.5 Condition the specimens for a minimum of 1 h at room temperature prior to measuring thickness.

8.6 Measure the thickness of the test specimen together with its specimen holder at four places, 90° apart. Mark the test specimen (inside the raised test surface) so subsequent measurements can be made at the same places.

8.7 Balance the load lever arm with the bale rod attached.

8.8 Mount the test specimen together with its specimen holder in the rotary spindle so that the drive pins of the spindle are inserted in the drive pin holes of the specimen holder and the specimen holder is free to pivot on the ball seat.

8.9 With the specimens and bale rod in position, gently apply the appropriate weight to the bale rod.

8.10 Turn on the machine and chart recorder if torque is to be recorded.

8.11 When the prescribed test interval duration has been completed, stop the machine, remove the weights from the bale rod, and carefully lower the stationary specimen holder to its lowest position.

8.12 Remove the test specimen together with its specimen holder and clean with a lint-free wiper.

8.13 Condition the specimens for a minimum of 1 h at room temperature prior to measuring thickness.

8.14 Measure the thickness of the test specimen together with its specimen holder at the same four places, 90° apart, previously marked.

9. Calculation

9.1 *Wear:*

9.1.1 Record the (four) thickness measurements for the test specimen before and after test, and actual test duration in hours.

9.1.2 Calculate the wear rate as follows:

$$WR = \frac{(X_{1a} + X_{1b} + X_{1c} + X_{1d}) - (X_{2a} + X_{2b} + X_{2c} + X_{2d})}{4T} \quad (4)$$

where:

- WR = wear rate, in./h (m/h),
- X = thickness, in., (m), and
- T = test duration, h.

9.1.3 Subscripts 1a, 1b, 1c, and 1d are the initial four thickness measurements taken 90° apart on the upper rotating specimen. Subscripts 2a, 2b, 2c, and 2d are the corresponding final thickness measurements.

9.2 *Coefficient of Friction:*

9.2.1 Calculate the coefficient of friction from the torque values as follows:

$$f = T/rW \quad (5)$$

where:

- f = coefficient of friction,
- T = specimen torque, N·m (lb·in.),
- r = test specimen radius, 13.49 mm (0.531 in.), and
- W = normal force, kg (lb).

10. Precision and Bias

10.1 *Precision*—The precision³ of this test method for wear as determined by the statistical examination of interlaboratory test results is as follows:

10.1.1 *Repeatability*—The difference between successive results obtained by the same operator with the same apparatus under constant operating conditions on identical test material would, in the long run, in the normal and correct operation of the test method exceed the following values only in one case in twenty.

$$0.019 \text{ mm (0.00075 in.)} \quad (6)$$

10.1.2 *Reproducibility*—The difference between two single and independent results obtained by different operators working in different laboratories on identical test material would, in the long run, exceed the following values only in one case in twenty.

$$0.030 \text{ mm (0.00118 in.)} \quad (7)$$

10.2 The tests on which the precision statement is based were all conducted at PV₃, with 180 rpm used in round robin 1, 2a, and 3, and 720 rpm in round robin 2b. Test durations were 100 h, except for round robin 1 where they ranged from 118 to 313 h. Wear in 100 h round robins averaged 0.00027 to 0.00049 in., and in no test did wear exceed 0.0017 in.

10.3 *Bias*—Since there is no accepted reference material suitable for determining the bias for the procedure for measuring wear rate, bias has not been determined.

11. Keywords

11.1 coefficient of friction; self-lubricated; torque; wear; wear-rate

³ Supporting data have been filed at ASTM International Headquarters and may be obtained by requesting Research Report RR:D02-1054.

ANNEX

(Mandatory Information)

A1. DESCRIPTION OF THE THRUST WASHER TESTING MACHINE (Fig. 1)


A1.1 Dead weights are attached to a bale rod, and act through a 10:1 lever arm to load the stationary (lower) washer axially upward against a rotating (upper) test specimen. The lever arm may be balanced to compensate for the weight of the stationary washer. Optional controlled pneumatic loading systems are available to replace applications of dead weight.

A1.2 The rotary spindle is driven by a variable-speed dc motor with feed back speed control, controlled by a 10-turn potentiometer, acting through dual-range step pulleys. Typical spindle speed range is 10 to 7200 rpm. A built-in tachometer

provides speed indication. An elapsed time indicator with reset feature to indicate motor running time should be included.

A1.3 In rotation at motion, torque is indicated throughout the test by a digital indicator.

A1.4 Optional features include an assortment of torque measurement devices; apparatus for the application, control, and readout of various test environment conditions; and devices to accommodate alternative test sample configurations.

 **D3702 – 94 (2014)**

ASTM International takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.

This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.

This standard is copyrighted by ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (www.astm.org). Permission rights to photocopy the standard may also be secured from the Copyright Clearance Center, 222 Rosewood Drive, Danvers, MA 01923, Tel: (978) 646-2600; <http://www.copyright.com/>