



Designation: D3882 – 08 (Reapproved 2016)^{ε1}

Standard Test Method for Bow and Skew in Woven and Knitted Fabrics¹

This standard is issued under the fixed designation D3882; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ε) indicates an editorial change since the last revision or reapproval.

^{ε1} NOTE—The tolerances in 10.1 and 10.2 were corrected editorially in May 2017.

1. Scope

1.1 This test method covers the determination of bow and skew of filling yarns in woven fabrics and the courses in knitted fabrics.

1.2 This test method can also be used to measure the bow and skew of printed geometric designs.

1.3 The values stated in either SI units or inch-pound units are to be regarded separately as standard. The values stated in each system may not be exact equivalents; therefore, each system shall be used independently of the other. Combining values from the two systems may result in non-conformance with the standard.

1.4 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

1.5 *This international standard was developed in accordance with internationally recognized principles on standardization established in the Decision on Principles for the Development of International Standards, Guides and Recommendations issued by the World Trade Organization Technical Barriers to Trade (TBT) Committee.*

2. Referenced Documents

2.1 *ASTM Standards:*²

[D123 Terminology Relating to Textiles](#)

[D1776 Practice for Conditioning and Testing Textiles](#)

[D2904 Practice for Interlaboratory Testing of a Textile Test](#)

¹ This test method is under the jurisdiction of ASTM Committee D13 on Textiles and is the direct responsibility of Subcommittee D13.60 on Fabric Test Methods, Specific.

Current edition approved July 1, 2016. Published July 2016. Originally approved in 1980. Last previous edition approved in 2012 as D3882 – 08(2012)^{ε1}. DOI: 10.1520/D3882-08R16E01.

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

[Method that Produces Normally Distributed Data \(Withdrawn 2008\)](#)³

[D2906 Practice for Statements on Precision and Bias for Textiles \(Withdrawn 2008\)](#)³

[D3990 Terminology Relating to Fabric Defects](#)

3. Terminology

3.1 For all terminology related to Fabric Defects see Terminology [D3990](#).

3.2 The following terms are relevant to this standard: bow, double bow, double hooked bow, double reverse bow, hooked bow, knitted fabric, skew, standard atmosphere for testing textiles.

3.3 For definitions of all other textile terms see Terminology [D123](#).

4. Summary of Test Method

4.1 *Bow*—A straightedge is placed across the fabric between two points at which a marked filling yarn, knitting course, designated printed line, or designated design meets the two selvages or edges. The greatest distance between the straightedge and the marked filling line, knitting course, designated printed line, or designated design is measured parallel to the selvage.

4.2 *Skew*—The straight-line distortion of a marked filling yarn, knitting course, designated printed line, or designated design is measured from its normal perpendicular to the selvage or edge.

5. Significance and Use

5.1 This test method is considered satisfactory for acceptance testing of commercial shipments.

5.1.1 If there are differences of practical significance between reported test results for two laboratories (or more), comparative tests should be performed to determine if there is a statistical bias between them, using competent statistical

³ The last approved version of this historical standard is referenced on www.astm.org.

assistance. As a minimum, the test samples to be used are as homogeneous as possible, are drawn from the material from which the disparate test results were obtained, and are randomly assigned in equal numbers to each laboratory for testing. Other fabrics with established test values may be used for this purpose. The test results from the two laboratories should be compared using a statistical test for unpaired data, at a probability level chosen prior to the testing series. If a bias is found, either its cause must be found and corrected, or future test results must be adjusted in consideration of the known bias.

5.2 Individual rolls are normally accepted or rejected on the basis of the maximum amount of bow or skew in a specific roll of fabric. The average bow or skew in a roll or lot or the range of bow or skew in a roll may be determined but are not normally used in the trade for acceptance or rejection.

5.3 Bow or skew can be induced during fabric manufacturing, dyeing, tentering, finishing, or other operations where a potential exists for uneven distribution of tensions across the fabric width. Bow and skew are more visually displeasing in colored, patterned fabrics such as plaids and horizontal stripes rather than in solid colors because the contrast makes the distortion more prominent. These defects may cause sewing problems in such fabrics and draping problems in finished products. In some cases, a specified amount of skew is needed, for example, to prevent twisting of pant legs made of twill fabric. Matching plaids from distorted patterns may create serious problems for the garment manufacturer or home sewer. Wavy or sharp breaks in the bow line are more detrimental to the appearance of small parts of a garment (such as collars, pockets, and so forth) than a gradual slope from a straight line.

5.3.1 Automotive interior textiles used for seat bolsters, cushions, headrests and door panels may be susceptible to bow and skew, especially when visually patterned fabrics are joined or mated to a straight edge surface.

6. Apparatus

6.1 *Measuring Stick or Steel Tape*, graduated in 1-mm ($\frac{1}{16}$ -in.) divisions and longer than the width of the fabric that is to be measured.

6.2 *Rigid Straightedge or t-square*, longer than the width of the fabric that is to be measured.

6.3 *Flat Surface*, of sufficient length to unroll or unfold the fabric (see 6.4).

6.4 *Fabric Inspection Table* (Optional), to unroll and roll fabric rolls or unfold and fold fabric bolts with sufficient lighting that provides transmitted light from underneath the fabric to make the defect more clearly visible.

7. Sampling and Test Specimens

7.1 *Primary Sampling Unit*—Consider rolls or bolts of fabric or fabric components of fabricated systems to be the primary sampling unit, as applicable.

7.2 *Laboratory Sampling Unit*—As a laboratory sampling unit take the entire roll or bolt after removing a first 1-mm (1-yd) length. For fabric components of fabricated systems, use the entire system.

7.3 *Test Specimens*—As test specimens, select 3 test areas from each laboratory sampling unit. Exclude the first and last fifth of the roll or bolt or piece length. Select test areas at random but no closer to one another than one fifth of the roll or bolt or piece length.

7.3.1 *Optical test specimens*—Select 3 test areas from each sampling unit. Exclude the first and last 10 m (11 yd) of a roll and test random areas within the roll.

7.3.1.1 Cut pieces that are at least 400 mm (16 in.) in width can be measured for bow and skew.

8. Conditioning

8.1 Condition the test specimens to moisture equilibrium for testing in the standard atmosphere for testing textiles in accordance with Practice **D1776** or, if applicable, in the specified atmosphere in which the testing is to be performed.

8.1.1 When full rolls or bolts of fabric cannot be properly conditioned in a reasonable time with available facilities, perform the test without conditioning and report the actual condition prevailing at the time of the test. Such results may not correspond with the results obtained when testing conditioned specimens at the standard atmosphere for testing textiles.

9. Procedure

9.1 Test the test specimens in the standard atmosphere for testing textiles in accordance with Section 8.

9.2 Handle the test specimens carefully to avoid altering the natural state of the material.

9.3 Lay the fabric on a smooth, horizontal surface without tension in any direction or use the optional fabric inspection table.

9.4 *Bow*:

9.4.1 Measure the bow in three places spaced as widely as possible along the length of the fabric or along a minimum of 1 m (1 yd). If possible, make no measurement closer to the ends of the roll or piece of fabric than 1 m (1 yd).

9.4.2 Follow a distinctive color yarn or pattern line across the width of the fabric. Trace one filling yarn, knitting course, or printed line across the full width of the fabric using a soft pencil or suitable marker.

9.4.3 Place a rigid straightedge across the fabric connecting the points at which the distinctive color yarn or pattern line, or marked yarn meets the two selvages or edges.

9.4.4 Measure the distance along the straightedge between the two selvages or edges to the nearest 1 mm ($\frac{1}{16}$ in.) and record as the baseline distance (BL).

9.4.4.1 For certain end uses where several narrow panels are sewn in a garment, it will be necessary to measure the bow across a narrower distance than the total width of the fabric, for example, a width of 38 cm (15 in.). This distance is used as the fabric width when calculating the bow.

9.4.4.2 For automotive or other applications where narrow panels or cut pieces are used, it will be necessary to measure bow across a narrower distance than across the full width of the fabric, for example, a width of 400 mm (16 in.). Use this distance as the fabric width when calculating bow.

9.4.5 Measure the greatest distance parallel to the selvages or edges between the straightedge and the distinctive color yarn or pattern line, or marked yarn to the nearest 1 mm (¹/₁₆ in.) and record as the bow distance (*D*) including the type. (See Fig. 1).

9.4.5.1 If double bow is evident, measure and record both distances.

NOTE 1—Fig. 1 represents typical examples of bows in a fabric that do not have any skew. Many variations in the shape or deepest portion of the arc can occur in actual fabrics. No provision is made to measure bow in the presence of skew.

9.4.5.2 When measuring narrow panels, for example, 400 mm (16 in.), measure the bow across the width from left to right in 400 mm (16 in.) increments. For example, measure full width units, 400 mm (16 in.). On the right side align with the right selvage and measure a 400 mm (16 in.) section. These measurements may overlap with some of the previously measured sections.

9.5 Skew:

9.5.1 Measure the skew in three places spaced as widely as possible along the length of the fabric or along a minimum of 1 m (1 yd). If possible, make no measurement closer to the ends of the roll or piece of fabric than 1 m.

9.5.2 Follow a distinctive color yarn or pattern line across the width of the fabric. Trace one filling yarn, knitting course, or printed line across the full width of the fabric using a soft pencil or suitable marker (Line AC if right-hand skew, Line DC if left-hand skew).

9.5.3 Place a rigid straight edge or t-square across the fabric width perpendicular to the selvage or edge such that it coincides with the lower point on the fabric at which the distinctive color yarn or pattern line, or marked yarn meets one of the selvages or edges (Line BC).

9.5.4 Measure the distance along the straightedge or t-square between the two selvages or edges (Line BC) to the nearest 1 mm (¹/₁₆ in.) and record as the fabric width (*W*). (See Fig. 2.)

9.5.4.1 For automotive or other applications where narrow panels or cut pieces are used, it will be necessary to measure skew across a narrower distance than across the full width of fabric, for example, a width of 400 mm (16 in.). Use this distance as the fabric width when calculating skew.

9.5.5 Measure the distance parallel to the selvages or edges between the straightedge and the distinctive color yarn or pattern line, or marked yarn to the nearest 1 mm (¹/₁₆ in.) (Line AB, or BD) and record including the skew direction, right-hand “Z,” left hand “S,” and whether evident on the face or back of the fabric. (See Fig. 2.)

NOTE 2—Fig. 2 represents a schematic drawing of typical skew; variations may occur in actual fabric. Examination of Fig. 2 will show that the skew in a fabric will be consistently categorized as left-hand (or right-hand) regardless whether the fabric is being fed from the top or bottom roll of the viewing frame or whether the direction of skew is measured from the right or left selvage or side, provided either the face or back of the fabric is being viewed.

10. Calculation

10.1 Bow, Individual Measurements—Calculate the maximum bow of individual specimens to the nearest 0.1 % or nearest 1 mm (¹/₁₆ in.) using Eq 1.

$$\text{Bow, \%} = 100(D/BL) \tag{1}$$

$$\text{or Bow, mm (in)} = D$$

where:

D = maximum bow distance, mm (in.), (from 9.4.5), and
BL = baseline distance, mm (in.), (from 9.4.4).

10.1.1 If double bow is present, calculate the larger of the two bows.

10.2 Skew, Individual Measurements—Calculate the skew of individual specimens to the nearest 0.1 % or 1 mm (¹/₁₆ in.) using Eq 2 or Eq 3, as applicable.

$$\text{Skew, \% , right - hand} = 100(AB)/BC \tag{2}$$

$$\text{Skew, \% , left - hand} = 100(BD)/BC \tag{3}$$

$$\text{or Skew, mm (in)} = AB \text{ or } BD$$

where:

AB = skew distance, right hand, mm (in.), (from 9.5.5),
BD = skew distance, left hand, mm (in.), (from 9.5.5), and
BC = width of fabric, mm (in.), (from 9.5.4).

11. Report

11.1 Report that the skew or bow were determined as directed in Test Method D3882. Describe the material or product sampled and the method of sampling used.

11.2 Report the following information for each laboratory sampling unit:

11.2.1 Bow:

11.2.1.1 Individual bow in units of measurement or percent,

11.2.1.2 Maximum bow in units of measurement or percent,

11.2.1.3 Fabric width, and

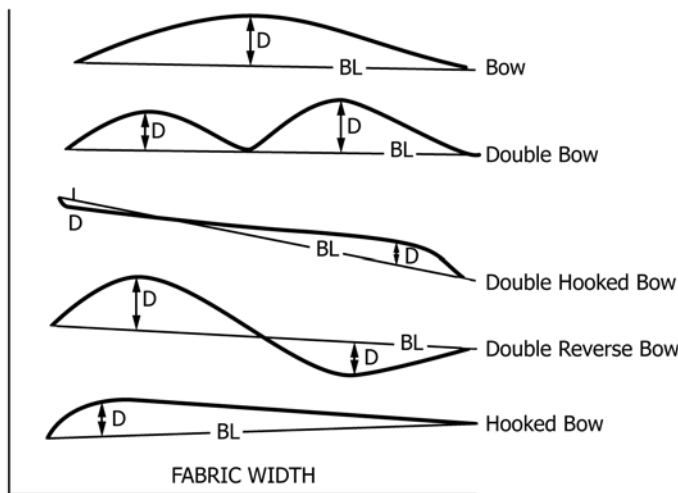


FIG. 1 Typical Bow Conditions

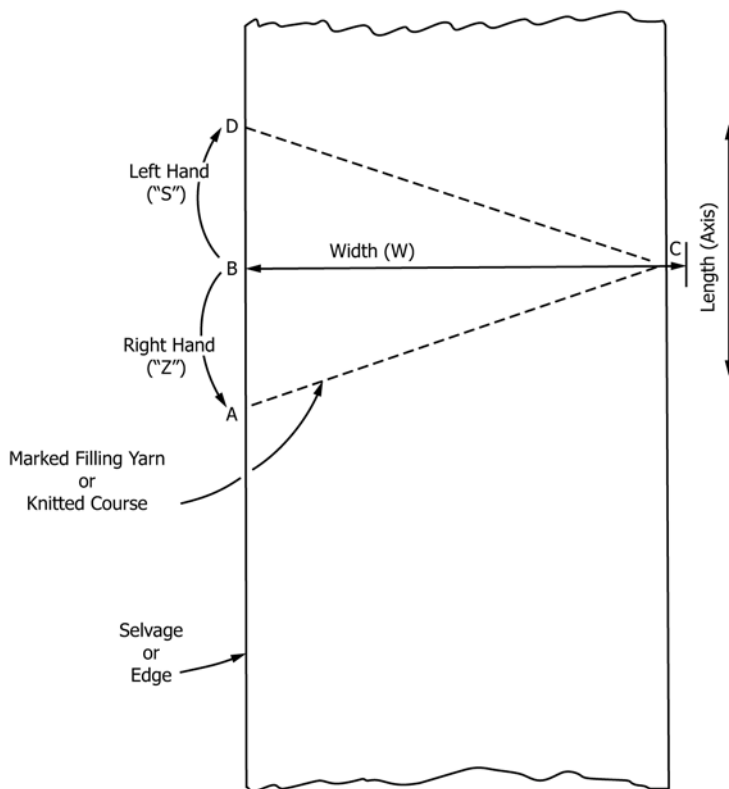


FIG. 2 Typical Skew Conditions

11.2.1.4 Type of bow observed, for example, double bow, double reverse bow, double hooked bow, hooked bow, or other variation.

11.2.2 Skew:

11.2.2.1 Individual skew in units of measurements and percent,

11.2.2.2 Maximum skew in units of measurements and percent,

11.2.2.3 Fabric width,

11.2.2.4 Direction of skew, right-hand “Z,” left-hand “S,” and

11.2.2.5 Side of fabric where skew was observed, face or back.

11.3 The actual temperature, in degrees °C (°F) and relative humidity (%) conditions prevailing at the time of the test.

11.3.1 Report the pretest conditioning environment, temperature in degrees °C (°F) and relative humidity (%).

12. Precision and Bias

12.1 Summary—In comparing two averages of three determinations when using the procedures in this test method, the differences should not exceed the single-operator precision values shown in Table 1 for the respective number of tests in 95 out of 100 cases when all the observations are taken by the same well-trained operator using the same piece of equipment and specimens randomly drawn from the sample of material. Larger differences are likely to occur under all other circumstances.

TABLE 1 Critical Differences, 95 % Probability Level, for Bow and Skew for the Conditions Noted

Property	Number of Observations in Each Average	Critical Differences for the Conditions Noted ^A , %		
		(Single-Operator) Precision	(Within-Laboratory) Precision	(Between-Laboratory) Precision
Bow	1	0.80	0.80	0.80
	3	0.46	0.46	0.46
	6	0.33	0.33	0.33
	12	0.23	0.23	0.23
	24	0.16	0.16	0.16
Skew	1	2.99	2.99	3.18
	3	1.73	1.73	2.04
	6	1.22	1.22	1.63
	12	0.86	0.86	1.38
	24	0.61	0.61	1.24

^A The critical differences for Table 1 were calculated using $t = 1.960$, which is based on infinite degrees of freedom.

12.2 Interlaboratory Test Data⁴—An interlaboratory test was run in 1981 in which randomly drawn specimens of three materials were tested in each of three laboratories for fabric bow and in each of four laboratories for fabric skew. Two operators in each laboratory each tested two specimens of each material for bow and skew using Test Method D3882. The precision statement is based upon a testing plan described in Practices D2904 and D2906. The three fabrics were: (1) 65 % polyester/35 % cotton plaid approximately 3.9 oz/yd² (2) 50 %

⁴ Supporting data are available from ASTM Headquarters. Request RR: D-13-1070.

polyester/50 % cotton fancy weave of 3.8 oz/yd², and (3) 100 % cotton denim of approximately 15.2 oz/yd². Fabric bow ranged from 1.7 to 2.6 % for Fabric A, 0.6 to 2.3 % for Fabric B, and 0.9 to 1.2 % for Fabric C. Skew ranged from 3.6 to 8.2 % for Fabric A, 8.2 to 12.3 % for Fabric B, and 5.4 to 7.4 % for Fabric C. The components of variance for bow and skew expressed as standard deviations were calculated to be the values listed in **Table 2**.

12.3 *Precision*—For the components of variance reported in **Table 1**, two averages of observed values should be considered

TABLE 2 Components of Variance Expressed as Standard Deviations^A

Properties	Components of Variance Expressed as Standard Deviations ^A , %		
	Repeatability		Reproducibility
	(Single-Operator) Component	(Within-Laboratory) Component	(Between-Laboratory) Component
Bow	0.289	0.000	0.000
Skew	1.079	0.000	0.390

^A The square roots of the components of variance are being reported to express the variability in the appropriate units of measure rather than as the squares of those units of measure.

significantly different at the 95 % probability level if the difference equals or exceeds the critical differences listed in **Table 1**.

NOTE 3—The tabulated values of the critical differences should be considered to be a general statement, particularly with respect to between-laboratory precision. Before a meaningful statement can be made about two specific laboratories, the amount of statistical bias, if any, between them must be established, with each comparison being based on recent data obtained on specimens taken from a lot of material of the type being evaluated so as to be as nearly homogeneous as possible and then randomly assigned in equal numbers to each of the laboratories.

NOTE 4—Since the interlaboratory test included only three laboratories for bow and four laboratories for skew, estimates of between laboratory precision may be either underestimated or overestimated to a considerable extent and should be used with special caution.

12.4 *Bias*—The procedure of this test method produces a test value that can be defined only in terms of a test method. There is no independent, referee method by which bias may be determined. This test method has no known bias.

13. Keywords

13.1 bow; knitted fabric; skew; woven fabric

ASTM International takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.

This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.

This standard is copyrighted by ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (www.astm.org). Permission rights to photocopy the standard may also be secured from the Copyright Clearance Center, 222 Rosewood Drive, Danvers, MA 01923, Tel: (978) 646-2600; http://www.copyright.com/