



Standard Test Method for Entanglements in Untwisted Filament Yarns by Needle Insertion¹

This standard is issued under the fixed designation D4724; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

1. Scope

1.1 This test method covers two options for the measurement of entanglements in untwisted filament yarns using needle insertion options for instrument (A) and manual (B) techniques.

1.2 The values stated in either SI or inch-pound units (in parentheses) are to be regarded separately as standard. The values stated in each system may not be exact equivalents; therefore, each system must be used independently of the other without combining values in any way.

1.3 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

2. Referenced Documents

2.1 *ASTM Standards:*²

[D123 Terminology Relating to Textiles](#)

[D1776 Practice for Conditioning and Testing Textiles](#)

[D2258 Practice for Sampling Yarn for Testing](#)

[D4849 Terminology Related to Yarns and Fibers](#)

3. Terminology

3.1 *Definitions:*

3.1.1 For definitions of terms relating to yarns and fibers, refer to Terminology [D4849](#).

3.1.1.1 The following terms are relevant to this standard: entanglement, filament yarn.

¹ This test method is under the jurisdiction of ASTM Committee [D13](#) on Textiles and is the direct responsibility of Subcommittee [D13.58](#) on Yarns and Fibers.

Current edition approved Jan. 1, 2011. Published January 2011. Originally approved in 1999. Last previous edition approved in 2010 as D4724–10. DOI: 10.1520/D4724-11.

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

3.2 For definitions of other textile terms used in this test method, refer to Terminology [D123](#).

4. Summary of Test Method

4.1 A summary of each option is in the section for that option.

5. Significance and Use

5.1 Option 1 of this test method for the determination of the degree of untwisted filament yarn entanglement, as measured instrumentally, is used for acceptance testing of commercial shipments; however, caution is advised because information on between-laboratory precision is lacking. Comparative tests, as directed in [5.1.1](#), may be advisable.

5.1.1 If there are differences of practical significance between the reported test results for two or more laboratories, comparative tests should be performed by those laboratories to determine if there is a statistical bias between them, using competent statistical assistance. As a minimum, samples used for each comparative test should be as homogeneous as possible, drawn from the same lot of material as the samples that results in disparate results during initial testing, and randomly assigned in equal numbers to each laboratory. Other fabrics with established test values may be used for this purpose. The test results from the laboratories involved should be compared appropriate statistical analysis and a probability level chosen by the two parties before testing begins, at a probability level chosen prior to the testing series. If a bias is found, either its cause must be found and corrected or future test results must be adjusted in consideration of the known bias.

5.2 Option 2 for this test method is intended for use when the supply of yarn is limited.

5.3 The instrumental option of this test method is based on the total randomization of the entanglements in the yarn; therefore, the distance measured between the point of insertion of a pin in the middle of the yarn and the point at which an entanglement is encountered, by movement of the yarn or the

pin until it is stopped at a preset level of force, is representative of the distance between two entanglements at some location in the yarn.

5.4 Entanglements are used frequently instead of twist to ensure the integrity of filament yarns. Such entanglements generally give somewhat less protection during weaving or knitting than twist, but with proper care, will perform quite satisfactorily.

6. Sampling and Test Specimens

6.1 *Primary Sampling Unit*—Consider shipping containers of yarn to be the primary sampling unit.

NOTE 1—A realistic specification or other agreement between the purchaser and the supplier requires taking into account the variability between shipping containers, packages within a shipping container, and successive lengths from a package to provide a plan that, at the specified level for the property of interest, has a meaningful producer’s risk, consumer’s risk, acceptable quality level, and limiting quality level.

6.2 *Laboratory Sample Unit*—For each primary sampling unit, take laboratory sampling units as directed in Practice **D2258**. Do not rewind or transfer material from packages taken from shipping containers to another packages.

6.3 *Test Specimen*—For acceptance testing, use laboratory units as a source of specimens. Make 20 observations on each laboratory sampling unit.

7. Conditioning

7.1 *Preparation of Test Package*—Before preconditioning or conditioning the test package, remove at least 100 m or 110 yds of yarn from the test package to avoid testing nonrepresentative yarn.

7.2 *Preconditioning*—Normally, preconditioning is not necessary unless the test packages are received with higher than the normal moisture level. If preconditioning is necessary, treat the packages as directed in Practice **D1776**.

7.3 *Conditioning*—Condition the test packages as directed in Practice **D1776**.

OPTION 1—INSTRUMENTAL MEASUREMENT OF THE DEGREE OF ENTANGLEMENT OF UNTWISTED FILAMENT YARN

8. Summary of Option

8.1 A yarn is passed at constant speed and constant pretension through the thread path of the instrument. After a required yarn length has run through, the yarn is pierced by a needle, and advanced automatically until a preset needle tension is attained. Then, the needle is withdrawn, and the yarn length from insertion to this critical point is measured automatically. This cycle of yarn advance, piercing by the needle, and length measurement is repeated for a predetermined number of times. The individual measured pulled yarn lengths and the total of these yarn lengths are automatically recorded.

9. Apparatus

9.1 *Automatic Needle Pull Entanglement Testers*, rapid automatic pin insertion detector (RAPID)³ and Rothschild automatic yarn entanglement testers NPT.³

9.2 *Standard Laboratory Weights*, ranging from 1 to 100 g.

9.3 *Stopwatch*, with 1/5-s divisions.

9.4 *Speed Indicator*, tachometer, 0 to 1000 rpm range.

9.5 *Magnetic Whorl Tensioning Device*, optional.

10. Procedure

10.1 Test the yarn in the standard atmosphere for testing textiles, as directed in Practice **D1776**.

10.2 Calibrate the entanglement tester and tensiometer as prescribed by the instrument manufacturer.

10.3 Mount the test package on a suitable holder.

10.4 *Yarn Pretension*—Calculate the pretension by using one of the equations below:

$$YP (g) = (D \wedge 0.5) 0.75 \quad (1)$$

$$YP (cN) = (T \wedge 0.5) * 0.70 \quad (2)$$

10.5 *Trip Level Tension*—Calculate the trip level by using one of the equations below:

$$TLT(g) = (D \wedge 0.35) * 3.5 \quad (3)$$

$$TLT (cN) = (T \wedge 0.35) * 3.31 \quad (4)$$

where:

YP = Yarn pretension,
TLT = trip level tension, c/tex (gf/d),
T = linear density, tex,
D = linear density, denier, and
F = filament count.

10.6 Set the RAPID instrument as follows:

10.6.1 *Measuring Speed*—10–20 m/min.

10.6.2 *Observations/Package*—20.

10.6.3 *No-Show Length*—Refer to the manufacturer’s manual.

10.6.4 Present the loose end of the yarn to the inlet gun (see **Fig. 1**). The instrument will string up, automatically strip some yarn, start the measurement cycle, and discard the tested yarn to waste.

10.6.4.1 If there is no entanglement in the “No-Show” length, the instrument will do the following:

(1) If the “Pin Miss Ignored Limit” has not been exceeded, rotate the pinwheel, reinsert the needle in the yarn, and continue testing. The test is aborted and a “No-Show” recorded.

(2) If the “Pin Miss Ignored Limit” has been exceeded, enter a “Freeze” state and request confirmation of pin insertion. The operator will restart the test if the pin did not pierce the yarn (increasing the “Pin Miss Count” by 1, or the operator will acknowledge pin piercing by pressing the “Confirm” button designating this a true no entanglement section, which adds the length to the results.

³ Apparatus is commercially available.

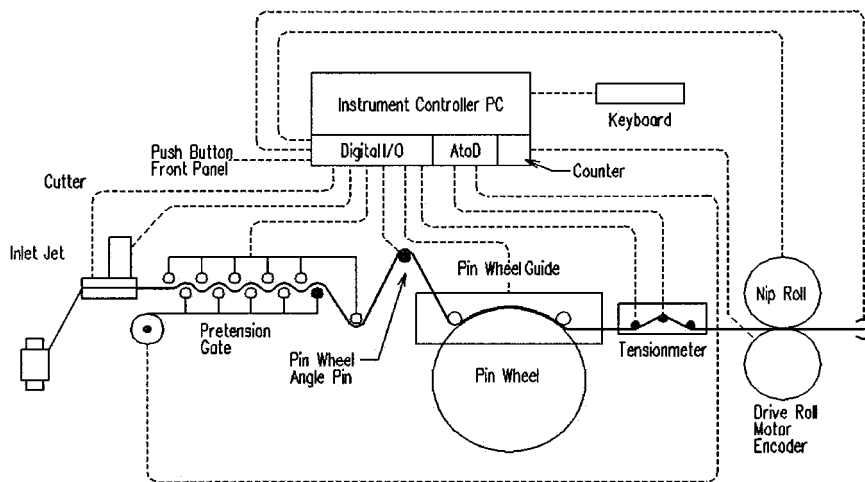


FIG. 1 Yarn String-Up Diagram for Rapid Automatic Pin Insertion Detector (RAPID)

10.7 Set the Rothschild instrument as follows:

10.7.1 *Measuring Speed*—10–20 m/min.

10.7.2 *Forwarding Time*—5 s.

10.7.3 *Observations/Package (decade counter)*—20.

10.7.4 *No-Show Length*—500 mm or as specified by user.

This is an optional setting and the length should be established based on the product or end-use of the product.

10.7.5 Feed the yarn from the package through the pretension device. The yarn then is threaded across the needle piercing section and through the measuring head. Then, yarn goes to a yarn speed roll and is taken up to the “Take-up” wheel (see Fig. 2) or can bypass the “Take-up” wheel and go into the aspirator after the yarn speed roll, to prevent buildup on the take-up wheel. The software initializes a specified length for stripping and starts the test.

10.7.5.1 If there is no entanglement in the “No-Show” length, the instrument will do the following:

(1) Stop the yarn and withdraw the needle.

(2) Record a “No-Show” in the software (and on the printout).

(3) Reinsert the needle into the yarn and wind until a node (entanglement) is detected.

(4) The first entanglement after a “No-Show” is ignored.

(5) The needle is withdrawn, and the yarn is advanced the specified length of the entanglement and is reinserted into the yarn and the test continues. This is to ensure that an accurate reference between entanglement is established.

10.7.6 Remove the yarn from the take-up wheel frequently to avoid excessive waste build-up. Use care if a sharp blade is used. To avoid any build-up, the yarn may be placed in the aspirator after the last wrap on the “Yarn speed roll.”

11. Calculations

11.1 In the following way the tester computer will calculate the average number of entanglements per metre using:

The total count of entanglements measured must equal 100.

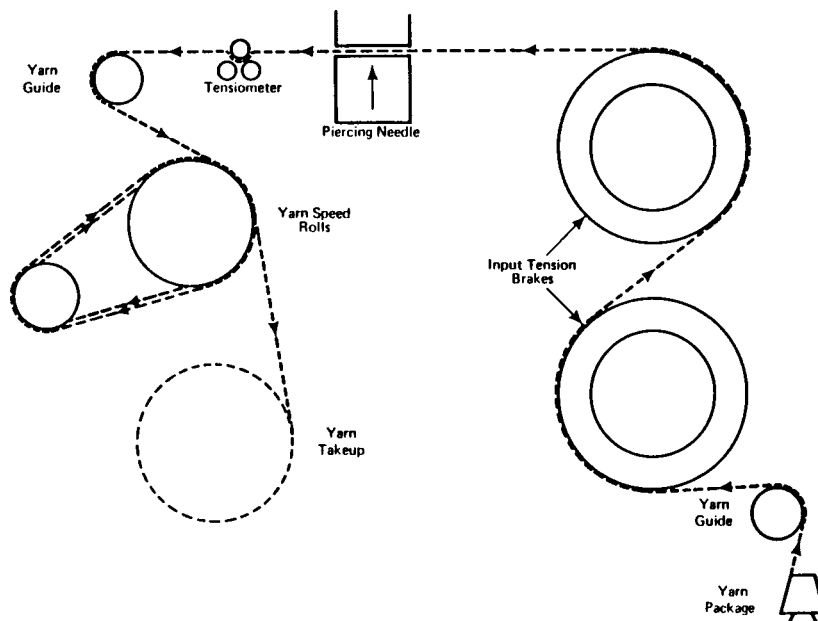


FIG. 2 Yarn String-Up Diagram for Rothschild Needle Insertion Entanglement Apparatus

The Distances between Entanglements (DE) must be recorded individually.

The average Distance between Entanglements (DE_{avg}) is calculated using Eq 5:

$$DE_{avg} = \frac{\sum_{i=1}^{100} DE_i}{100} \quad (5)$$

The standard deviation in this average value is calculated using Eq 6:

$$DE_{stdev} = \sqrt{\frac{\sum_{i=1}^{100} (DE_i - DE_{avg})^2}{99}} \quad (6)$$

The average number of entanglements per meter (EPM) is calculated using Eq 7:

$$EPM = \frac{1}{DE_{avg}} \quad (7)$$

The standard deviation in the average number of entanglements is calculated using Eq 8:

$$EPM_{stdev} = \frac{DE_{stdev}}{(DE_{avg})^2} \quad (8)$$

The half length of the 95% confidence interval (CI95) is calculated using Eq 9:

$$CI95 = t \cdot \frac{2}{\sqrt{n}} \approx 0.2 \cdot s \quad (9)$$

where:

DE = Distance between Entanglements, and

EPM = average number of entanglements/m.

11.2 Calculate the average entanglements/m for the lot.

12. Report

12.1 State that the packages were tested as directed in Option 1 of Test Method D4724. Describe the material or product sampled and the method of sampling used.

12.2 The report shall include the following information:

12.2.1 Nominal linear density.

12.2.2 Pretension level used.

12.2.3 Trip level tension used.

12.2.4 Measuring speed.

12.2.5 Transport time.

12.2.6 The distances between entanglements for each specimen.

12.2.7 No show distance and any no shows encountered for each specimen.

12.2.8 The EMC for each package and the average for the lot.

12.2.9 The instrument used.

12.2.10 Any modifications to the test.

OPTION 2—MANUAL MEASUREMENT OF DEGREE OF FILAMENT ENTANGLEMENT

13. Summary of Option

13.1 A stationary needle is inserted in the yarn. A hook is placed in the same opening made by the needle. The hook is

attached to one end of a flexible cord and a tensioning weight to the other end of the cord. The weight is allowed to drop vertically and gradually until the hook is stopped by an entanglement in the yarn. The needle is then moved in the opposite direction along the length of the specimen until it encounters another entanglement. The distance between the hook and needle is recorded as the distance between entanglements. See Fig. 3.

14. Apparatus

14.1 *Weight*, 2.5 ± 0.01 g.

14.2 *J-Shaped Hook*, approximately 25 mm long.

14.3 *Cord, or thread*, flexible, No. 50 cotton.

14.4 *Illuminated Magnifier*³, with a lens capable of 3x to 10x magnifications.

14.5 *Horizontal Test Board*, equipped with a sliding metric scale, movable black plastic perforated card 25 by 75 by 1.6 mm (1.0 by 3.0 by 1/16 in.), and yarn clamp.

14.6 *Air Jet Suction*.

14.7 *Pick Needle*.

14.8 *Tensiometer*.

15. Procedure

15.1 Test the yarn in the standard atmosphere for testing textiles, as directed in Practice D1776.

15.2 Place the yarn package on a suitable stand under the table supporting the test apparatus.

15.3 Feed the yarn through the test apparatus.

15.4 Open the main air valve completely for the air jet suction device and strip off the outside layer of yarn.

15.5 Attach the J-hook to one end of the cord, or thread, and feed the other end through the guide at the left side of the test board. Cut the cord to a length that allows it to hang at least 750 mm above the floor. Attach the weight to the free end of the cord.

15.6 Adjust tension on the yarn to 0.1 cN (0.01 gf/d) using a valve at the air jet. Do this while the air jet is pulling against the yarn that is held stationary by a clamp on the right side of the test board.

15.7 Place the magnifier over the control test area.

15.8 Slide the plastic card under the yarn.

15.9 Push the pick needle through the center of the yarn and make an opening wide enough for the J-hook. Extend the pick needle into a hole in the card.

15.10 Insert the hook into the opening next to the pick needle and let the hook move gently to the left until it catches on an entanglement (hard node) and its mass holds it in the yarn.

15.11 With the pick needle still in the yarn, pull it from the card and gently move it to the right until resistance due to another entanglement (hard node) is encountered.

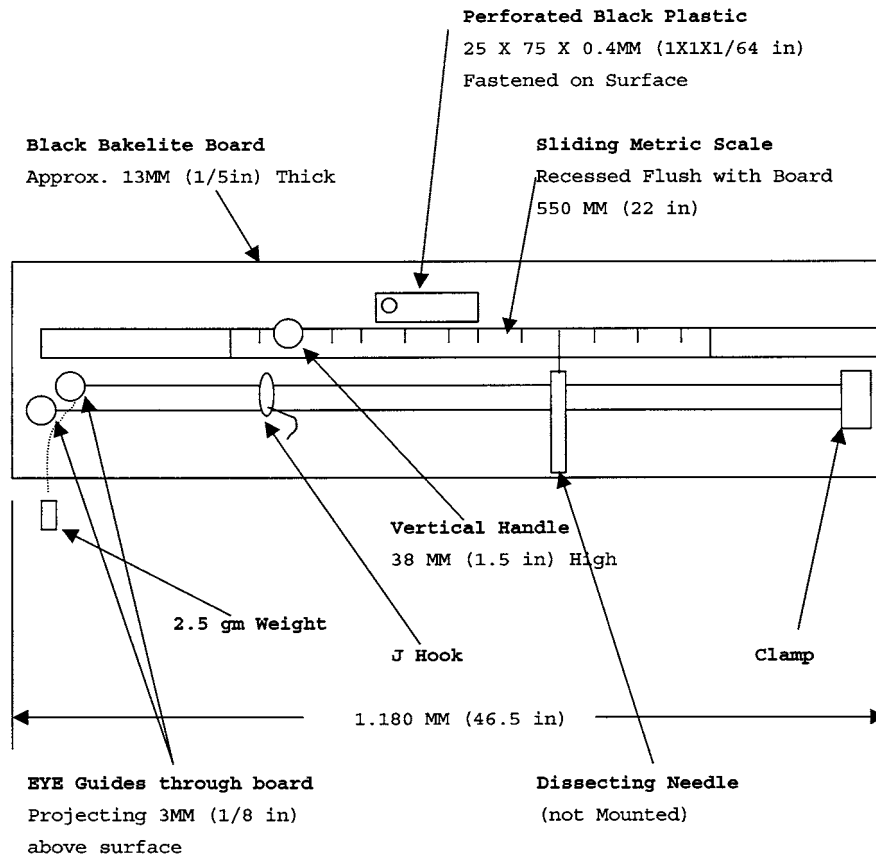


FIG. 3 Entanglement Tester (Manual Method)

15.12 Move the card out of the way, measure the distance between the hook, and pick needle (two entanglements) to the nearest mm.

15.13 Remove the hook and pick needle, open the clamp and allow yarn to pass through the air jet for approximately 10 s.

15.14 Repeat 15.5-15.13 until 20 observations have been made on each test package.

16. Calculation

16.1 Calculate the average distance between entanglements for each package to the nearest millimetre.

16.2 Calculate the entanglements/m for each package to the nearest 0.1 unit using Eq 10:

$$EPM = 1000/L \quad (10)$$

where:

EPM = entanglements/m,
1000 = number of mm/m, and
L = average distance between entanglements in mm.

16.3 Calculate the average entanglements/m for all the packages.

17. Report

17.1 State that the test packages were tested as directed in Option 2 of Test Method D4724. Describe the materials or products sampled and the method of sampling used.

17.2 The report shall include the following information for the laboratory sampling unit and for the lot as applicable to a material specifications or contract order:

17.2.1 Normal linear density.

17.2.2 Yarn tension.

17.2.3 Number of observations, if more than 20.

17.2.4 Entanglement value for each package and the average for all the packages.

18. Precision and Bias

18.1 *Summary*—See Table 1 for Probability values. In comparing two rates of entanglements/m, the entanglements measured over the same length of opportunity should be compared using the critical difference in Table 2. If the rates of entanglements include bias due to systematic sampling or testing errors, the critical differences in Table 2 will be overly optimistic. When the two counts being compared are measured over difference lengths, Table 2 is no longer valid and help should be sought from a competent statistician.

18.2 *Interlaboratory Test Data*—A interlaboratory test was run in 1997 in which randomly drawn samples of five materials were tested in each of four laboratories. Each laboratory used two operators, each of whom tested two specimens of each material. Since the data represents counts, components of variance were not calculated. Instead, the data was analyzed by nonparametric statistical methods to determine bias and interactions among laboratories and operators.

TABLE 1 Values of Student's *t* for One-Sided and Two-Sided Limits and the 95 % Probability^A

df	One-Sided	Two-Sided	df	One-Sided	Two-Sided	df	One-Sided	Two-Sided
1	6.314	12.706	11	1.796	2.201	22	1.717	2.074
2	2.920	4.303	12	1.782	2.179	24	1.711	2.064
3	2.353	3.182	13	1.771	2.160	26	1.706	2.056
4	2.132	2.776	14	1.761	2.145	28	1.701	2.048
5	2.015	2.571	15	1.753	2.131	30	1.697	2.042
6	1.943	2.447	16	1.746	2.120	40	1.684	2.021
7	1.895	2.365	17	1.740	2.110	50	1.676	2.009
8	1.860	2.306	18	1.734	2.101	60	1.671	2.000
9	1.833	2.262	19	1.729	2.093	120	1.658	1.980
10	1.812	2.228	20	1.725	2.086	—	1.645	1.960

^AValues in this table were calculated using Hewlett Packard HP 67/97 Users' Library Programs 03848D, "One-Sided and Two-Sided Critical Values of Student's *t*" and 00350D, "Improved Normal and Inverse Distribution." For values at other than the 95 % probability level, see published tables of critical values of Student's *t* in any standard statistical test (2), (3), (4), and (5).

TABLE 2 Values of *b* for Critical Differences in Entanglement Counts, *a* and *b*, for Two-Sides Tests at a the 95 % Probability Level

<i>r=a+b</i>	<i>b</i>	<i>r=a+b</i>	<i>b</i>	<i>r=a+b</i>	<i>b</i>	<i>r=a+b</i>	<i>b</i>
8	0	24	6	39	12	53	18
11	1	27	7	41	13	55	19
14	2	29	8	43	14	57	20
16	3	32	9	46	15	60	21
19	4	34	10	48	16	62	22
22	5	36	11	50	17	64	23

NOTE 2—Because the interlaboratory tests included only four laboratories, estimates of between laboratory precision may be underestimated to a considerable extent and should be used with special caution.

18.3 *Critical Differences*—Two rates of entanglements measured over the same test length should be considered significantly different at the 95 % probability level, if the smallest rates is less then or equal to the tabulated value of *b* in **Table 2**.

18.4 *Bias*—The procedure of this test method produces a test value that cannot be defined only in terms of a test method. There is no independent, referee method by which bias may be determined. This test method has no know bias.

19. Keywords

19.1 entanglement; yarn

ASTM International takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.

This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.

This standard is copyrighted by ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (www.astm.org). Permission rights to photocopy the standard may also be secured from the ASTM website (www.astm.org/COPYRIGHT/).