



Standard Test Method for Permeability of Leather to Water Vapor¹

This standard is issued under the fixed designation D5052; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

This standard has been approved for use by agencies of the U.S. Department of Defense.

1. Scope

1.1 This test method covers the determination of the permeability of leather to water vapor by measuring the rate at which water vapor passes through a test specimen. This test method does not apply to wet blue.

1.2 The values stated in either inch-pound or SI units are to be regarded separately as standard. The values stated in each system may not be exact equivalents, therefore, each system shall be used independently of the other. Combining values from the two systems may result in nonconformance with the standard.

1.3 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

2. Referenced Documents

2.1 *ASTM Standards:*²

D1610 Practice for Conditioning Leather and Leather Products for Testing

3. Summary of Test Method

3.1 In this test method the water vapor permeability is measured after the test specimen is exposed to moist air on one side and dry air on the other side.

4. Significance and Use

4.1 This test method is intended for use on all types of leathers.

4.2 Water vapor permeability is one of several factors contributing to the relative comfort of footwear, handwear, and garments.

¹ This test method is under the jurisdiction of ASTM Committee D31 on Leather and is the direct responsibility of Subcommittee D31.07 on Physical Properties

Current edition approved Oct. 1, 2010. Published November 2010. Originally approved in 1990. Last previous edition approved in 2005 as D5052 - 00 (2005). DOI: 10.1520/D5052-00R10.

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

5. Apparatus

5.1 *Analytical Balance*, accurate to 0.001 g.

5.2 *Permeability Apparatus*, as shown in Fig. 1. It shall consist of an aluminum cup having approximately the dimensions shown in Fig. 2 and a template, 1/8 in. thick and 2.225 ± 0.025 in. in diameter [area is 0.0025 m^2 , or 25 cm^2], made of brass or other non-corrosive metal.

5.3 *Steel Stamping Die*, 2.75 ± 0.1 in. in diameter.

5.4 *Constant Temperature and Humidity Chamber*, which may be either a laboratory, a cabinet, or a chamber with circulated air maintained at standard condition ($23 \pm 1^\circ\text{C}$ and $50 \pm 4\%$ relative humidity).

5.5 *Fan*, capable of maintaining an air-flow over the surface of the *Permeability Apparatus* at a velocity of at least 500 ft/min [254 m/s].

6. Reagents and Materials

6.1 *Desiccant*, consisting of fresh 8 mesh anhydrous calcium chloride.

6.2 *Microcrystalline Wax*, with a melting point of 70°C or lower.

7. Procedure

7.1 All specimens shall be conditioned as prescribed in Practice D1610. Conditioning other than as prescribed shall be noted in the results.

7.2 Fill the aluminum cup with the desiccant to a height between 1/8 and 1/4 in. [3.2 to 6.4 mm] below the level of the rim, as shown in Fig. 1. Leave enough space so that shaking of the dish, which must be done after each weighing, will mix the desiccant. Place the specimen, with the grain side downward, over the desiccant and center with the cup. Place the template flat on the specimen and center as nearly as possible with the cup. Apply a slight pressure to the template to ensure good contact between the rim of the cup, the specimen, and the template around the entire rim. Fill the groove formed by the lip of the cup and the edge of the template with melted wax that is allowed to harden before the template is removed. (The removal of the template from the hardened wax is facilitated by

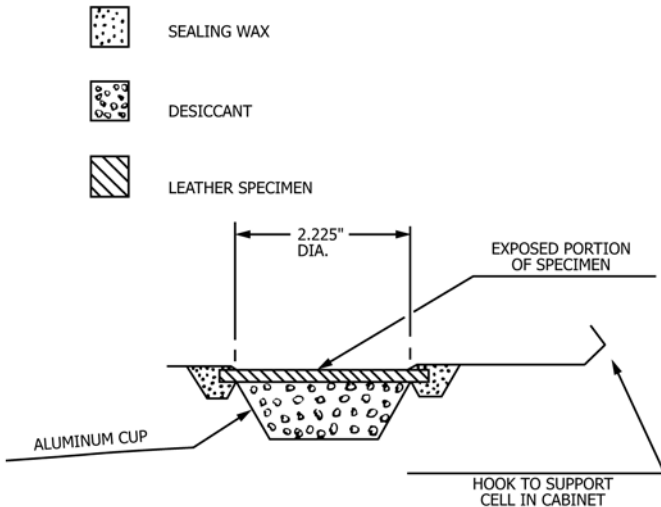


FIG. 1 Permeability Apparatus

applying a coat of petroleum jelly to the edge and chilling the template prior to use.)

7.3 Place the complete assembly in the constant temperature and humidity chamber, specimen side up. Adjust the air flow so that the velocity over the specimen shall be at least 500 ft/min [254 m/s]. At the end of 1 h, weigh the assembly to the nearest 0.001 g. This will be considered the “initial weight.” Shake the assembly after weighing to redistribute the surface of the desiccant. (The assembly shall preferably be weighed in the constant temperature and humidity chamber. If this is not possible, the assemblies can be removed and weighed one at a time, provided they are returned to the chamber in 2 min or less.) Weigh the assembly at 1-h intervals shaking the assembly after each weighing until three or more successive weighings show weight increases that are equal within 0.02 g. (The weighing intervals can be extended longer for specimens with low permeability.) Total time should be no less than 4 h and not more than 24 h. The last weighing will be recorded as the “final weight.”

8. Calculation

8.1 Calculate the permeability to water vapor of the test specimen by one of the following equations:

$$P = \frac{I}{AT} \quad (1)$$

where:

P = water vapor permeability in grams per square centimetre per hour,

I = increase in weight in grams in total time,

A = area of the exposed specimen in square centimetres (normally 25), and

T = total time of exposure in hours between initial and final weighings.

OR

$$P = \frac{I}{AT} \quad (2)$$

where:

P = water vapor permeability in grams per square centimetre per 24 h (day),

I = increase in weight in grams in total time multiplied by 24,

A = area of the exposed specimen in square metres (normally 0.0025), and

T = total time of exposure in hours between initial and final weighings.

9. Report

9.1 The average of the results obtained from the test specimens shall be the water vapor permeability of the sample.

10. Precision and Bias

10.1 This test method is adopted from the procedures of the American Leather Chemists Association³ where it has long been in use and where it was approved for publication before the inclusion of precision and bias statements were mandated. The original interlaboratory test data is no longer available. The user is cautioned to verify by the use of reference materials, if available, that the precision and bias of this test method is adequate for the contemplated use.

³ American Leather Chemists Association, Office of Secretary-Treasurer, Campus Station, Cincinnati, OH 45221.

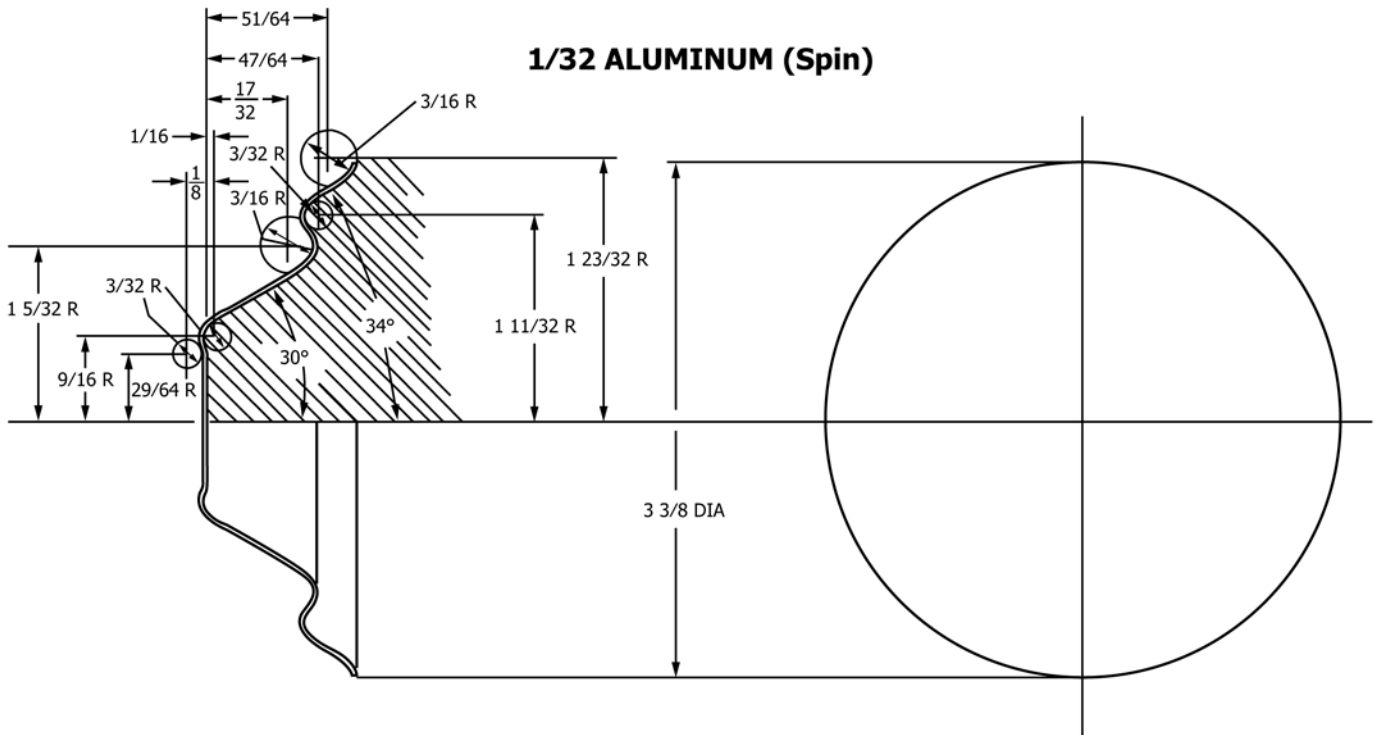


FIG. 2 Spining Stud for Water Vapor Permeability Dish

ASTM International takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.

This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.

This standard is copyrighted by ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (www.astm.org). Permission rights to photocopy the standard may also be secured from the Copyright Clearance Center, 222 Rosewood Drive, Danvers, MA 01923, Tel: (978) 646-2600; http://www.copyright.com/