



# Standard Test Method for Measurement of Barnacle Adhesion Strength in Shear<sup>1</sup>

This standard is issued under the fixed designation D5618; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon ( $\epsilon$ ) indicates an editorial change since the last revision or reapproval.

## 1. Scope

1.1 This test method covers the measurement of barnacle adhesion in shear to surfaces exposed in the marine environment. It is used to establish the ability of a surface to reduce biofouling adhesion. Surfaces with known barnacle adhesion strengths are included to serve as controls.

1.2 The values stated in SI units are to be regarded as the standard. The values given in parentheses are for information only.

1.3 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

## 2. Referenced Documents

2.1 *ASTM Standards:*<sup>2</sup>

**D3623 Test Method for Testing Antifouling Panels in Shallow Submergence**

2.2 *U.S. Military Specifications:*

**MIL-P-24441/1 Primer, Epoxy (Formula 150, Formula Sheet 24441/1)**<sup>3</sup>

## 3. Summary of Test Method

3.1 Test surfaces and coatings are immersed in the marine environment according to Test Method **D3623**. When barnacles are observed to have settled on the surface, the strength of adhesion of individuals is measured. Barnacle adhesive shear strength is calculated by dividing the shear force required to remove the barnacle by the surface area of the barnacle base

plate. This test method is most suited to small barnacles (generally with base diameters between 5 to 20 mm).

3.2 The diameter of the barnacle base is measured and an increasing shear force is applied to the base of the barnacle until it is removed from the surface.

## 4. Significance and Use

4.1 This test method is designed as a screening test in the evaluation of coating systems and other materials designed to resist biofouling attachment.

4.2 The degree and type of barnacle fouling will vary according to the geographic location of test sites and the time of year when tests are implemented. Surfaces with known barnacle adhesive shear strength should be exposed to provide comparative data.

## 5. Interferences<sup>4</sup>

5.1 Variations in barnacle adhesion strength may occur due to differences in species, age, and physical condition.

5.2 Incomplete removal of the barnacle base plate from the surface during testing may lead to erroneous adhesion values.

5.3 Care must be taken not to dislodge the barnacle during base diameter measurements.

## 6. Apparatus

6.1 *Hand-Held Probe*, used to apply force to the barnacle base. It is recommended that a 14- by 14-mm stainless steel plate be attached to the end of a 8-mm diameter stainless steel rod that is attached to a force measuring device (see **Fig. 1**).

6.2 *Force Measuring Device*, maybe a spring scale or force transducer.

6.2.1 The force measuring device should be capable of recording values between 0 to 150 N (0 to 34 lb) to an accuracy of  $\pm 0.5$  N ( $\pm 0.1125$  lb).

## 7. Procedure

7.1 Test and control surfaces are immersed in the marine environment according to Test Method **D3623**. Control surfaces should include polytetrafluoroethylene and MIL-P-24441 primer epoxy.

<sup>4</sup> Swain, G. W. J., Griffith, J., Bultman, D., and Vincent, H., "Barnacle Adhesion Measurements for the Field Evaluation of Candidate Antifouling Surfaces, *Biofouling*," Vol 6, 1992, pp. 105–114.

<sup>1</sup> This test method is under the jurisdiction of ASTM Committee **D01** on Paint and Related Coatings, Materials, and Applications and is the direct responsibility of Subcommittee **D01.45** on Marine Coatings.

Current edition approved June 1, 2011. Published June 2011. Originally approved in 1994. Last previous edition approved in 2005 as D5618 – 94 (2005). DOI: 10.1520/D5618-94R11.

<sup>2</sup> For referenced ASTM standards, visit the ASTM website, [www.astm.org](http://www.astm.org), or contact ASTM Customer Service at [service@astm.org](mailto:service@astm.org). For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

<sup>3</sup> Available from Standardization Documents Order Desk, DODSSP, Bldg. 4, Section D, 700 Robbins Ave., Philadelphia, PA 19111-5098, <http://dodssp.daps.dla.mil>.

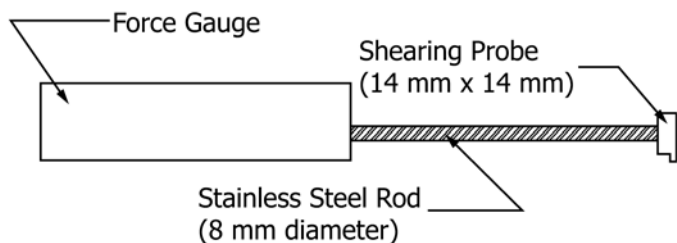


FIG. 1 Probe Design for the Detachment of Barnacles

7.2 Barnacles between 5 to 20 mm in diameter are selected for testing and identified with regard to species and condition. Test only barnacles that are at least 20 mm from the edges of the test panel and not in direct contact with other barnacles.

7.3 The barnacle base area is estimated from an average base diameter,  $d_a$ . This is obtained by measuring the barnacle base with calipers in four directions (0, 45, 90, 135°). The barnacle base area,  $A$ , is then calculated as follows:

$$A = \frac{1}{4} \pi d_a^2 \quad (1)$$

7.4 The probe is placed at the base of the barnacle.

7.5 A shear force is applied with a hand-held probe to the barnacle base at a rate of approximately 4.5 N/s (1 lb/s) until the barnacle becomes detached. Take care to apply the force parallel to the surface.

7.6 The force required for detachment is noted, and observations are made as to the mode of failure. If more than 10 % of the barnacle base plate is left attached to the substrate, the test is deemed void.

## 8. Calculations and Interpretation of Results

8.1 The strength of adhesion,  $\tau$ , (Pascals) is calculated by dividing the force required to remove the barnacle,  $F$ , (Newtons) by the area of the barnacle base plate,  $A$ , (square metres) as follows:

$$\tau = F/A \quad (2)$$

8.2 For each test surface the mean and standard deviation of the strength of adhesion,  $\tau$ , is calculated.

8.3 The strength of adhesion values for test surfaces are compared to the control surfaces of known adhesion.

## 9. Report

9.1 Report the following information:

9.1.1 For test panels report the substrate employed, the type of coating, and the days exposed,

9.1.2 Report the number of tests, their mean and range, and the species of barnacle,

9.1.3 Report the overall fouling and condition of the surface according to Method D3623, and

9.1.4 Provide similar data for the exposed control surfaces so that comparative conclusions with regard to adhesion strength can be drawn.

## 10. Precision and Bias

10.1 *Precision*—On the basis of static immersion of control surfaces at Florida Institute of Technology<sup>5</sup> (polytetrafluoroethylene and MIL-P-24441 primer epoxy) the following results were obtained:

Test Surface	MIL-P-24441 primer epoxy	Polytetrafluoroethylene
Barnacle species	<i>Balanus eburneus</i>	<i>Balanus eburneus</i>
Date	September 2, 1992	September 2, 1992
Days exposure	20	57
Number of readings	14	10
Mean, MPa	2.060	0.896
Standard deviation MPa	0.527	0.165
95 % Confidence interval	0.304	0.118
99 % Confidence interval	0.424	0.169

10.2 *Bias*—Bias is being determined.

## 11. Keywords

11.1 antifouling; barnacle adhesion; shear strength

<sup>5</sup> The tests were run at the Florida Institute of Technology Static Immersion Site, Indian River Lagoon, Grant, Florida.

ASTM International takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.

This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.

This standard is copyrighted by ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (www.astm.org). Permission rights to photocopy the standard may also be secured from the Copyright Clearance Center, 222 Rosewood Drive, Danvers, MA 01923, Tel: (978) 646-2600; http://www.copyright.com/