



# Standard Test Methods for Rubber—Determination of Carbon Black in Masterbatches<sup>1</sup>

This standard is issued under the fixed designation D5805; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon ( $\epsilon$ ) indicates an editorial change since the last revision or reapproval.

## 1. Scope

1.1 These test methods cover the determination of the amount of carbon black in a masterbatch and cover emulsion SBR-carbon black mixtures, but may be applicable to other polymers. Three test methods are included:

	Sections
Inert Atmosphere Pyrolysis	3 – 10
Vacuum Pyrolysis	11 – 17
Thermogravimetric Analyzer	18 – 24

NOTE 1—The nomenclature used in these test methods is in accordance with Practice D1418.

1.2 The values stated in SI units are to be regarded as the standard. The values given in parentheses are for information only.

1.3 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

## 2. Referenced Documents

2.1 *ASTM Standards:*<sup>2</sup>

D1418 Practice for Rubber and Rubber Latices—Nomenclature

D6370 Test Method for Rubber—Compositional Analysis by Thermogravimetry (TGA)

### TEST METHOD A—CARBON BLACK

*Inert Atmosphere Pyrolysis Test Method*

## 3. Summary of Test Method

3.1 The prepared dried sample and a sample of standard SBR black determinate are tested in triplicate. The samples are weighed accurately into tared crucibles and then placed in a

combustion tube at 550°C, which is continuously flushed with CO<sub>2</sub> until the rubber hydrocarbon is distilled. The crucibles and contents are cooled in a desiccator, weighed, then inserted into a muffle furnace at 550°C until all carbonaceous material is burned. The crucible and contents are again cooled in a desiccator and weighed. The percentage of carbon black is calculated from the weights.

## 4. Significance and Use

4.1 The carbon black content of an unvulcanized black or oil-black SBR masterbatch may be determined by this test method if an inert (CO<sub>2</sub>) atmosphere and a determinate (see Note 2) of known carbon black content are available.

NOTE 2—Determinate black masterbatch may be prepared by careful addition of exact amounts of rubber and carbon black on a mill. An alternative would be a thorough blending of a quantity of black masterbatch and determination of the carbon black by use of a previously established determinate.

## 5. Apparatus

5.1 *Drying Oven.*

5.2 *Porcelain Crucibles*, No. 00000, tared.

5.3 *Weighing Bottles*, tared.

5.4 *Fused Alumina Combustion Boats.*<sup>3</sup>

5.5 *Combustion Tubes.*<sup>4</sup>

5.6 *Combustion Furnace.*

## 6. Reagents

6.1 *Purity of Reagents*—Reagent grade chemicals shall be used in all tests. Unless otherwise indicated, it is intended that all reagents conform to the specifications of the Committee on Analytical Reagents of the American Chemical Society, where

<sup>1</sup> These test methods are under the jurisdiction of ASTM Committee D11 on Rubber and are the direct responsibility of Subcommittee D11.11 on Chemical Analysis.

Current edition approved Aug. 1, 2014. Published November 2014. Originally approved in 1995. Last previous edition approved in 2009 as D5805 – 00 (2009). DOI: 10.1520/D5805-00R14.

<sup>2</sup> For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

<sup>3</sup> Alundum No. 3 combustion boats have been found satisfactory for this purpose.

<sup>4</sup> The sole source of supply of the combustion tube known to the committee at this time is the McDaniel high-temperature combustion tube, 30 in. (762 mm) long by 1 in. (25.4 mm) in diameter available from Dunlap and Co., 623 Staring Lane, Baton Rouge, LA 70810. This tube will accommodate a maximum of two combustion boats containing six samples each within the heated area of the furnace. If you are aware of alternative suppliers, please provide this information to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee,<sup>1</sup> which you may attend.

such specifications are available.<sup>5</sup> Other grades may be used, provided it is first ascertained that the reagent is of sufficiently high purity to permit its use without lessening the accuracy of the determination.

## 7. Preparation of Sample

7.1 Blend 200 g of dried sample obtained in accordance with 4.1 or 9.1 by passing it five times between the rolls of a laboratory mill. Maintain the roll temperature at  $50 \pm 5^\circ\text{C}$  ( $122 \pm 9^\circ\text{F}$ ) and a distance between the rolls of  $0.5 \pm 0.13$  mm ( $0.020 \pm 0.005$  in.). After blending, sheet the sample from the mill with the distance between the rolls set at  $0.25 \pm 0.05$  mm ( $0.010 \pm 0.002$  in.). Dry approximately 2 g of the blended, thinly sheeted material for 1 h in the oven at  $100 \pm 5^\circ\text{C}$  ( $212 \pm 9^\circ\text{F}$ ). Keep the dried sheet in a desiccator until ready to weigh the samples.

## 8. Procedure

8.1 Into the tared porcelain crucibles accurately weigh three 0.3 to 0.5-g samples from the sheet of material being tested and three 0.3 to 0.5-g samples from a similarly prepared sheet of standard SBR black determinate (see Note 2). Due to the hygroscopic nature of the samples and the carbon black, weigh the crucibles and contents in the tared weighing bottles.

8.2 Place the six crucibles in a fused alumina combustion boat, or boats, alternating the samples of determinate and the test samples. Insert the combustion boat, or boats, into the combustion tube. Pass a stream of oxygen-free  $\text{CO}_2$  through the tube at a flow rate of 150 to 240  $\text{cm}^3$  (atmospheric pressure)/min. After the tube has been swept free of oxygen (approximately 5 min is sufficient time), place it in the combustion furnace maintained at a temperature of  $550 \pm 25^\circ\text{C}$ , and distill off the rubber hydrocarbon. Continue to pass  $\text{CO}_2$  through the tube, while allowing the tube to remain in the furnace for 30 min. At the end of this period, remove the combustion tube from the furnace and allow it to cool, meanwhile continuing the flow of  $\text{CO}_2$  through it. When it is cool, remove the boat, or boats, and place the crucibles in a desiccator until they cool to room temperature and are ready to be weighed. Accurately weigh the crucibles and contents.

8.3 After weighing the crucibles containing the carbon black residues, ignite the samples by either of the following methods:

8.3.1 Place the crucibles and contents in a combustion boat, or boats, and insert them into a second combustion tube. Place the tube in a combustion furnace maintained at  $550 \pm 25^\circ\text{C}$  and pass a stream of oxygen or air through the tube.

8.3.2 Alternately, place the crucibles and contents in a muffle furnace maintained at  $550 \pm 25^\circ\text{C}$ . After the carbon has been completely burned, remove the boat, or boats, from the muffle furnace and place the crucibles in a desiccator. When the crucibles have cooled to room temperature, weigh them.

<sup>5</sup> Reagent Chemicals, American Chemical Society Specifications, American Chemical Society, Washington, DC. For Suggestions on the testing of reagents not listed by the American Chemical Society, see *Annual Standards for Laboratory Chemicals*, BDH Ltd., Poole, Dorset, U.K., and the *United States Pharmacopeia and National Formulary*, U.S. Pharmacopeial Convention, Inc. (USPC), Rockville, MD.

## 9. Calculation

9.1 Calculate the percentage of ash,  $R$ , in the dry sample as follows:

$$R = [(F - E)/(D - E)] \times 100 \quad (1)$$

where:

$F$  = mass of crucible plus ash after ignition of the carbon black, g,  
 $E$  = mass of crucible, g, and  
 $D$  = mass of original dry sample plus crucible, g.

9.2 Calculate the individual values,  $c_1$ ,  $c_2$ , and  $c_3$ , for carbon black content of the material being tested on the dry, ash-free basis as follows:

$$c = 100(Q - F)/(D - E)(1 - 0.01R) \quad (2)$$

where:

$Q$  = mass of crucible and residue after distillation of hydrocarbon, g, and  $F$ ,  $D$ ,  $E$ , and  $R$  are defined in 9.1.

9.3 Calculate the individual values,  $c_1'$ ,  $c_2'$ , and  $c_3'$ , for carbon black content of the standard SBR carbon black determinate (see Note 2) on the dry, ash-free basis in accordance with 3.1.2, using the appropriate values obtained on the samples of the determinate.

9.4 Calculate the corrected percentage of carbon black in the material being tested as follows:

$$\text{Carbon black, \%} = C + A - C' \quad (3)$$

where:

$C$  = average of the three values of percentage carbon black ( $c_1$ ,  $c_2$ , and  $c_3$ ) on the dry, ash-free basis, obtained on the material being tested,  
 $A$  = percentage of carbon black assigned as the standard value for the standard SBR carbon black determinate (see Note 2), and  
 $C'$  = average of the three values of percentage carbon black,  $c_1'$ ,  $c_2'$ , and  $c_3'$ , on the dry, ash-free basis, obtained on the standard carbon black determinate.

## 10. Precision and Bias

10.1 Precision and bias have not been determined.

### TEST METHOD B

#### *Vacuum Pyrolysis Test Method*

## 11. Summary of Test Method

11.1 The prepared dried sample is tested in triplicate. The samples accurately are weighed into tared crucibles and placed in a combustion tube and maintained under very low pressure at  $600^\circ\text{C}$  until the rubber is distilled. The samples are cooled and returned to atmospheric pressure. The crucibles and contents are then further cooled in a desiccator and weighed. The percentage of carbon black is calculated on an ash-free basis.

## 12. Significance and Use

12.1 Carbon black in unvulcanized carbon black or oil-carbon black SBR masterbatch may be determined by this test method without the use of a determinate sample.

### 13. Apparatus

- 13.1 *Porcelain Crucible*, No. 00000.
- 13.2 *Combustion Boats*, sized to accommodate crucibles.
- 13.3 *Combustion Tube*, high-silica (see Fig. 1).<sup>4</sup>
- 13.4 *Combustion Furnace*, capable of controlling temperature at  $600 \pm 25^\circ\text{C}$ .
- 13.5 *Vacuum Pump*.
- 13.6 *Vacuum Seal Lubricant* for ground-glass joint.
- 13.7 *Muffle Furnace*, capable of controlling at  $550 \pm 25^\circ\text{C}$ .
- 13.8 *Drying Oven*, capable of controlling at  $105 \pm 5^\circ\text{C}$ .
- 13.9 *Insertion Rod*.
- 13.10 *Trap*, to condense vapors coming from combustion tube (see Fig. 1).

### 14. Preparation of Sample

14.1 Blend 200 g of the dried sample obtained in accordance with 4.1 or 9.1 by passing it five times between the rolls of a laboratory mill. Maintain the roll temperature at  $50 \pm 5^\circ\text{C}$  ( $122 \pm 9^\circ\text{F}$ ) and a distance between the rolls of  $0.5 \pm 0.13$  mm ( $0.20 \pm 0.005$  in.). After blending, sheet the sample from the mill with the distance between the rolls set at  $0.25 \pm 0.05$  mm ( $0.010 \pm 0.002$  in.). Dry approximately 2 g of the blended, thinly sheeted material for 1 h in the oven at  $105 \pm 5^\circ\text{C}$ . Keep the dried sheet in a desiccator until ready to weigh the samples.

### 15. Procedure

15.1 Place into a tared crucible 0.3 to 0.5 g (to the nearest 0.1 mg) from the sheet of material being tested. Using the insertion rod, insert the boat containing the crucibles into the tube to maximum depth. Insert the ground-glass stopper coated properly with vacuum seal lubricant, turn on the vacuum pump, and evacuate the tube to less than 1.3 kPa.

15.2 Introduce the combustion tube into the combustion furnace maintained at  $600 \pm 25^\circ\text{C}$ , using care not to rotate the tube or otherwise cause sample disturbance. Allow the tube to remain in the furnace for 10 min, maintaining maximum pressure of 1.3 kPa (10 mm Hg) during combustion. Remove the tube from the furnace, allow the tube and contents to cool for 7 min, and slowly allow pressure to increase to prevent blowing residue out of crucible.

15.3 Remove the boat and place it in a desiccator to cool to room temperature. Weigh each crucible and residue to the nearest 0.1 mg. Determine the ash content on a portion of sample.

### 16. Calculation

16.1 Calculate the percentage of carbon black as follows:

$$\text{Carbon black, \%} = [(A - B) - 0.01 CD] / (C - 0.01 CD) \times 100 \quad (4)$$

where:

- A* = mass of crucible and residue after distilling, g,
- B* = mass of crucible, g,
- C* = mass of original sample, g, and
- D* = percentage of ash.

### 17. Precision and Bias

17.1 Precision and bias have not been determined.

### TEST METHOD C

*Thermogravimetric Analyzer*

### 18. Summary of Test Method

18.1 The prepared, dried sample is placed in a calibrated thermogravimetric analyzer (TGA) where it is weighed using the integral balance (See Test Method D6370). The sample is heated to  $575^\circ\text{C}$  in an inert atmosphere to pyrolyze the rubber and other softeners. The atmosphere is then switched to air,

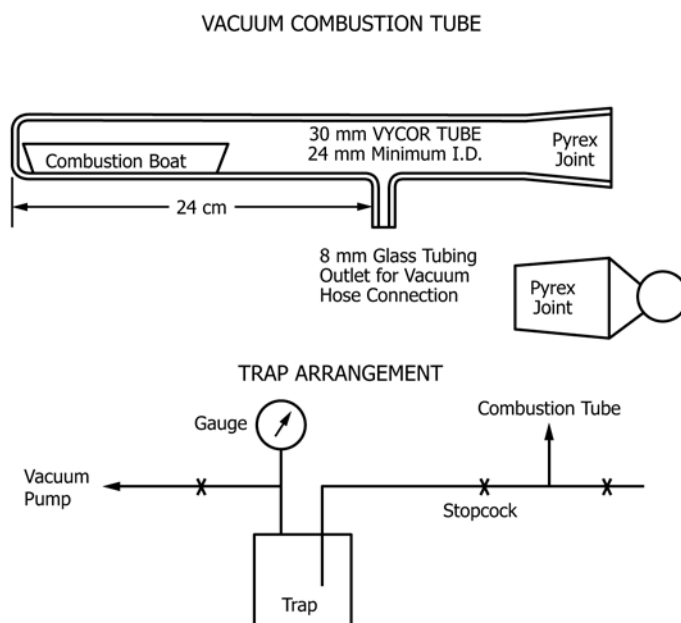


FIG. 1 Vacuum Combustion Tube and Trap Arrangement

combusting the carbon black. The difference in mass before and after the switch of gases is the mass of the carbon black contained in the sample.

## 19. Significance and Use

19.1 The carbon black content of any vulcanized or unvulcanized compound may be determined by this method without use of a determinate sample.

19.2 Expertise in thermogravimetric analysis (TGA) is necessary to the successful application of this test method.

## 20. Apparatus

20.1 *Thermogravimetric Analyzer*, maintained and operated in accordance with manufacturer's instructions.

## 21. Preparation of Sample

21.1 Blend 200 g of dried sample obtained in accordance with 4.1 or 9.1 by passing it five times between the rolls of a laboratory mill. Maintain the roll temperature at  $50 \pm 5^\circ\text{C}$  ( $122 \pm 9^\circ\text{F}$ ) and a distance between the rolls of  $0.5 \pm 0.13$  mm ( $0.020 \pm 0.005$  in.). After blending, sheet the sample from the mill with the distance between the rolls set at  $0.25 \pm 0.05$  mm ( $0.010 \pm 0.002$  in.). Dry approximately 2 g of the blended, thinly sheeted material for 1 h in the oven at  $100 \pm 5^\circ\text{C}$  ( $212 \pm 9^\circ\text{F}$ ). Keep the dried sheet in a desiccator until ready to weigh the samples.

## 22. Procedure

22.1 Set zero on the analyzer following manufacturer's instructions.

22.2 Place in the instrument pan  $10 \pm 3$  mg of the prepared sample. Weigh accurately using integral instrument balance.

22.3 Under inert atmosphere heat the sample to  $575 \pm 50^\circ\text{C}$  and hold until constant mass.

22.4 Switch atmosphere to air and hold until constant mass.

## 23. Calculation

23.1 Calculate the percentage of carbon black in the samples as follows:

$$C = (A - B)(100)/I \quad (5)$$

where:

$C$  = % carbon black in the sample,  
 $A$  = constant mass of sample at  $575^\circ\text{C}$  under inert gas,  
 $B$  = constant mass of sample at  $575^\circ\text{C}$  under air, and  
 $I$  = initial mass of sample.

23.2 Alternatively, the instrument may perform this calculation automatically.

## 24. Precision and Bias

24.1 Precision and bias have not been determined.

## 25. Keywords

25.1 carbon black; masterbatch; thermogravimetric analysis (TGA)

*ASTM International takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.*

*This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.*

*This standard is copyrighted by ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (www.astm.org). Permission rights to photocopy the standard may also be secured from the Copyright Clearance Center, 222 Rosewood Drive, Danvers, MA 01923, Tel: (978) 646-2600; http://www.copyright.com/*