



Standard Specification for Extruded, Compression Molded and Injection Molded Polyoxymethylene Shapes (POM)¹

This standard is issued under the fixed designation D6100; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

INTRODUCTION

This specification is intended to be a means of calling out plastic product used in the fabrication of end items or parts.

1. Scope*

1.1 This specification covers requirements and test methods for the material, dimensions, and workmanship, and the properties of extruded, compression molded and injection molded polyoxymethylene (POM) sheet, plate, rod, and tubular bar shapes, excluding pipe and fittings.

1.2 The properties included in this specification are those required for the compositions covered. Section 4 presents a classification system for defining requirements for particular characteristics important to specialized applications.

1.3 This specification allows for the use of recycled plastics.

1.4 The values stated in inch-pound units are to be regarded as the standard in all property and dimensional tables. For reference purposes, SI units are included in Table S-POM and Table 1 only.

1.5 The following precautionary caveat pertains only to the test method portions, Section 11, of this specification: *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

NOTE 1—There is no known ISO equivalent to this standard.

2. Referenced Documents

2.1 ASTM Standards:²

¹ This specification is under the jurisdiction of ASTM Committee D20 on Plastics and is the direct responsibility of Subcommittee D20.15 on Thermoplastic Materials.

Current edition approved May 1, 2014. Published May 2014. Originally approved in 1997. Last previous edition approved in 2011 as D6100 - 11. DOI: 10.1520/D6100-14.

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

[D256 Test Methods for Determining the Izod Pendulum Impact Resistance of Plastics](#)

[D618 Practice for Conditioning Plastics for Testing](#)

[D638 Test Method for Tensile Properties of Plastics](#)

[D790 Test Methods for Flexural Properties of Unreinforced and Reinforced Plastics and Electrical Insulating Materials](#)

[D883 Terminology Relating to Plastics](#)

[D3892 Practice for Packaging/Packing of Plastics](#)

[D6778 Classification System and Basis for Specification for Polyoxymethylene Molding and Extrusion Materials \(POM\)](#)

[D7209 Guide for Waste Reduction, Resource Recovery, and Use of Recycled Polymeric Materials and Products \(Withdrawn 2015\)³](#)

3. Terminology

3.1 Definitions:

3.1.1 *regrind (plastic), n*—a product or scrap such as sprues, runners and edge trim that have been reclaimed by shredding and granulating for use in-house.

3.1.2 For definitions of other technical terms pertaining to plastics used in this specification, see Terminology [D883](#) or Guide [D7209](#).

³ The last approved version of this historical standard is referenced on www.astm.org.

*A Summary of Changes section appears at the end of this standard

TABLE S-POM Requirements for Polyoxymethylene (POM) Shapes

Type	Description	Class	Description	Grade	Classification System D6778 Resin Callout ^A	Description	Ultimate Tensile Strength min, psi (MPa)	Tensile Elongation % at break, mm	Tensile Modulus min, psi	Dimensional Stability %, max
01	Homopolymer	1	Unfilled	1	POM0111 ^B	General Purpose	9000 (62)	25	350 000	0.4
				2	POM0110B56540 ^B	General Purpose	9000 (62)	15	350 000	0.4
				0	As Specified	Recycle Grade	8000 (55)	25	275 000	0.4
		2	Lubricated	1	POM0110L20A21730 ^B	General purpose	6100 (42)	10	345 000	0.4
				3	POM0110L13 ^B	General Purpose	6800 (47)	10	340 000	0.4
				4	POM0110L20A992 30(46)(2400) ^B	General Purpose	5500 (38)	10	325 000	0.4
5	Lubricated	4	POM0110L12 ^B	General Purpose	5800 (40)	5	375 000	0.4		
		6	POM0131 ^B	General Purpose	9000 (62)	25	350 000	0.4		
		2	POM0132 ^B	General Purpose	9000 (62)	25	350 000	0.4		
02	Copolymer	1	Unfilled	1	POM0211 ^B	General Purpose	8000 (55)	25	350 000	0.4
				2		Recycle Grade	7000 (48)	25	275 000	0.4
				0	As Specified	
00	Other PolyAc- etals	0	As Specified	1	As Specified	General Purpose
				2		Recycle Grade

^A Applicable Classification System D6778 resin type to be specified on purchase order.

^B In accordance with Classification System D6778.

3.2 Definitions of Terms Specific to This Standard:

3.2.1 *centerline porosity, n*—microvoids which are visibly detectable with the unaided eye using the dye penetration procedure detailed in 7.4.1.

3.2.2 *low porosity, n*—product which either exhibits no white centerline or a white centerline but no dye remains when tested in accordance with section 7.4.1.

3.2.3 *plate, n*—flat stock greater than ¼ in.

3.2.4 *Porosity Level 1, n*—products containing microvoids with a pore size greater than 50 µm (0.002 in.) in which dye remains either in a broken or continuous line which does not exceed 4 % centerline porosity when tested in accordance with 7.4.1.

3.2.5 *recycled plastic shape, n*—a product made from up to 100 % recycled plastic.

3.2.6 *rod, n*—solid cylindrical shape with a minimum diameter of ⅛ in.

3.2.7 *sheet, n*—flat stock less than and including ¼ in. (mm) thickness.

3.2.8 *tubular bar, n*—annular shapes with minimum inside diameter of ⅜ in. and minimum wall thickness of ⅛ in.

3.2.9 *virgin plastic shape, n*—product that is produced from 100 % plastic resin that has not been subjected to subsequent melt processing.

4. Classification and Material

4.1 Product shape and size as defined in the applicable purchase order.

4.2 This specification covers product as listed in Table S-POM. Products included in the designations reference Classification System D6778 callouts where applicable.

4.2.1 The type of POM extruded, compression molded or injection molded product is categorized by type, grade and class depending on resin and filler compositions as defined in Table S-POM.

4.3 POM shape products are categorized as General Purpose or Recycle Grade in accordance with the following criteria:

4.3.1 Grade 1—General Purpose:

4.3.1.1 Extruded, compression molded and injection molded product made using only 100 % POM resin. This specification allows for the use of polyoxymethylene plastic materials that are reconstituted, recovered, or reprocessed, or combination thereof, provided that the requirements as stated in this specification are met. It is the responsibility of the supplier and the buyer of reconstituted, recovered, or reprocessed polyoxymethylene plastic materials, or combination thereof, to ensure compliance. (See Guide D7209.)

TABLE A-1 Dimensional Requirements for POM Rod (Grade 1)

Size, in.	Tolerance, in.	Roundness TIR, in.	Camber
⅛ to <1 diameter	+0.003/−0 dia.	0.002	2½ in./8 ft
1 to <2½ diameter	+0.005/−0 dia.	0.005	1¼ in./8ft
2½ to 8 diameter	+0.250/−0 dia.	0.050	1 in./8ft
96 length	+1/−0		

4.3.2 Grade 2—Recycle Grade:

4.3.2.1 Extruded, compression molded or injection molded product made using any amount up to 100 % of recycled POM plastic.

4.4 The type class and grade is further differentiated based on dimensional stability (elevated temperature excursion test), Table S-POM and dimensional requirements, Tables A and B.

4.4.1 When the level of centerline porosity needs to be documented it will be designated as either low porosity (LP) or P1 (Porosity Level 1) that is determined using the procedure detailed in 7.4 and will be added to the callout as a suffix (see Example 2 in 4.6.1.2).

4.5 Property Tables:

4.5.1 Table S-POM is used to describe extruded, compression molded and injection molded products, except where it does not cover the product type being considered.

4.5.2 Table 1 is used to describe extruded, compression molded and injection molded products not included in Table S-POM via a cell callout which includes the applicable Table S-POM type and specific properties (Designations 1 through 7).

4.5.3 To facilitate the incorporation of future or special materials not covered by Table S-POM, the “as specified” category (OO) for type, class and grade is shown on the table with the basic properties to be obtained from Table 1, as they apply.

4.5.4 *Reinforcements and Additive Materials*—A symbol (single-letter) will be used for the major reinforcement or combination, or both, along with two numbers that indicate the percentage of addition by mass with the tolerances as tabulated below. This must be included in all Table 1 callouts (see Example 3 in 4.6.1.3).

Symbol	Material	Tolerance (Based on the Total Mass)
C	Carbon and graphite fiber	±2 %
G	Glass	±2 %
L	Lubricants (for example, PTFE, graphite, silicone and molybdenum disulfide)	by agreement between the supplier and the user
M	Mineral	±2 %
R	Combinations of reinforcements or fillers, or both	±3 % for the total reinforcement

4.6 *Callout Designation*—A one-line system shall be used to specify materials covered by this specification. The system uses pre-defined cells to refer to specific aspects of this specification as illustrated below:

4.6.1 *Description:*

4.6.1.1 *Example 1*—Product made from general purpose POM homopolymer:

CELL CALLOUT: S-POM0111

- S-POM01 = Product made from POM homopolymer in accordance with Table S-POM
- 1 = Unfilled class
- 1 = General purpose grade product

4.6.1.2 *Example 2*—Product made from general purpose POM copolymer, low porosity:

CELL CALLOUT: S-POM0211,LP

- S-POM02 = Product made from POM copolymer in accordance with Table S-POM
- 1 = Unfilled class
- 1 = General purpose grade product
- LP = Low porosity material

4.6.1.3 *Example 3*—Product made from 20 % PTFE reinforced general purpose POM homopolymer resin:

CELL CALLOUT: S-POM0143

- S-POM01 = Product made from POM homopolymer in accordance with Table S-POM
- 4 = Lubricated
- 3 = PTFE filled

4.6.2 The three examples illustrate how a one-line, alpha-numeric sequence can identify the product composition, commercial parameters and physical characteristics of extruded,

compression molded and injection molded product. A space must be used as a separator between the specification number and the type designation. No separators are needed between type, class and grade. When special notes are to be included, such information should be preceded by a comma. Special tolerances must be noted at time of order and are inserted after the grade in parenthesis and preceded by a comma.

TABLE B-1 Dimensional Requirements for POM Sheets and Plates (Grades 1 and 2)^A

NOTE 1—*Squareness*—All sizes 1/8 in. max. gap when measured in accordance with 11.4.

Size, in.	Thickness Tolerances	Length Camber, in./ft	Width Bow, in./ft
1/16 to 3/16	±10 %	3/4 /4	3/16 /2
1/4 to 1	+0.025/−0	3/4 /4	3/16 /2
1 1/8 to 3	+0.050/−0	1/4 /4	1/16 /2
3 1/8 and over	+0.125/−0	1/4 /4	1/8 /2

^ACompression molded plate is supplied sufficiently oversize to finish to nominal dimension listed.

TABLE B-2 Dimensional Requirements for POM Compression Molded Plates (Grade 1)

Size in.	Thickness Tolerances	Length Camber, in./ft	Width Bow, in./ft
1/4	+0.090/−0	3/8 /4	0.090/2
5/16	+0.090/−0	3/8 /4	0.090/2
3/8	+0.090/−0	3/8 /4	0.090/2
7/16	+0.090/−0	3/8 /4	0.090/2
1/2	+0.090/−0	3/8 /4	0.090/2
5/8	+0.090/−0	3/8 /4	0.090/2
3/4	+0.090/−0	3/8 /4	0.090/2
7/8	+0.090/−0	3/8 /4	0.090/2
1	+0.090/−0	1/8 /4	0.050/2
1 1/8	+0.090/−0	1/8 /4	0.050/2
1 1/4	+0.090/−0	1/8 /4	0.050/2
1 3/8	+0.090/−0	1/8 /4	0.050/2
1 1/2	+0.090/−0	1/8 /4	0.050/2
1 5/8	+0.090/−0	1/8 /4	0.050/2
1 3/4	+0.090/−0	1/8 /4	0.050/2
1 7/8	+0.090/−0	1/8 /4	0.050/2
2	+0.090/−0	1/8 /4	0.050/2

5. Physical Property Requirements

5.1 The physical property values listed within this specification’s tables are to be considered minimum specification values. Any requirement for specific test data for a given production lot should be specified at the time of order. If physical properties for products not yet included in Table S-POM are required, specify using Table 1 for extruded, compression molded and injection molded products.

6. Dimensional Requirements

6.1 The type, class and grade is further differentiated based on dimensional stability (elevated temperature excursion test), Table S-POM, and dimensional requirements, Tables A and B. Products shall be produced within commercial tolerances and with the lowest stress levels for machined parts as delineated in Tables A and B for extruded, compression molded or injection molded products.

6.2 Tubular bar dimensions shall be supplied in the unfinished condition, unless otherwise specified at time of order, sufficient to finish to the nominal dimension ordered.

6.3 The maximum allowable camber or bow, or both, shall be within the limits referenced in Tables A-1 and B-1.

TABLE 1 Additional Detail Requirements—Reinforced/Unreinforced POM Shapes

NOTE 1—The applicable Table S-POM callout (including resin type, fillers) must precede this table designation.

Designation Order Number	Property	0	1	2	3	4	5	6	7	8	9
1	Tensile strength, Test Method D638, min, psi (MPa)	Unspecified	6000 (41)	8000 (55)	10 000 (69)	12 000 (83)	14 000 (97)	16 000 (110)	20 000 (138)	25 000 (172)	Specify Value
2	Elongation at break, Test Method D638, %, min	Unspecified	1	3	5	10	20	50	100	200	Specify Value
3	Tensile modulus, Test Method D638, min, psi (MPa)	Unspecified	100 000 (690)	200 000 (1379)	300 000 (2073)	400 000 (2760)	500 000 (3448)	600 000 (4137)	800 000 (5516)	1 000 000 (6895)	Specify Value
4	Dimensional stability, max, %, in accordance with 11.2	Unspecified	0.1	0.2	0.3	0.4	0.6	0.8	1.0	1.5	Specify Value
5	Flexural modulus, Test Method D790, min, psi (MPa)	Unspecified	250 000 (1649)	350 000 (2400)	450 000 (3100)	550 000 (3792)	650 000 (4482)	750 000 (5171)	1 000 000 (6895)	1 500 000 (10 343)	Specify Value
6	Izod impact, Test Method D256, ft-lb/in. (J/m) of notch, min	Unspecified	0.4 (21)	0.6 (32)	0.8 (43)	1.0 (53)	2.0 (107)	3.0 (160)	4.5 (240)	6.0 (320)	Specify Value

7. Workmanship, Finish, and Appearance

7.1 Appearance—The color of products shall be as published by the shapes manufacturer. They shall be uniform in color throughout the thickness. Specific colors and color matching only as agreed to by order. Physical properties are sometimes affected by colors.

7.2 Finish—All products shall be free of blisters, wrinkles, cracks, gouges and defects that restrict commercial use of the product. Special surface finish shall be supplied only when specified in the purchase order or contract.

7.3 Defects—All products shall be free of dirt, foreign material and embedded particles exceeding 1/32 in. maximum diameter as defined in 7.3.1.


7.3.1 The criteria for determining the internal cleanliness shall be external visual inspection. A maximum number of two internal defects per square foot of plate/sheet and one foot length of rod and tubular bar. Clusters of defects less than 1/32 in. diameter are to be counted as a single defect.

7.4 Centerline Porosity—Maximum allowable porosity level for products designated as porosity Level 1 shall not exceed 4% as described in 7.4.1. Products identified low porosity (LP) shall not have any centerline porosity.

7.4.1 A rod (see Fig. 1) or plate (see Fig. 2) or tubular bar wall, full cross-section sample shall have a milled surface of approximately 72 RMS prior to testing. Color over this centerline or dot with red permanent magic marker and allow one minute for the markings to dry. For colored product a more sensitive ultraviolet fluorescent yellow permanent magic marker is required. Clean off the colored area with acetone. The ink or dye will not be washed from inside the porosity and will show up as colored particles. Measure the widest part or largest diameter of the porosity line. Colored product must be examined using a UV light sensor (long wavelength). This value is then divided by the diameter of the rod, thickness of the plate, or tubular bar wall thickness, and multiplied by 100 to obtain the percent centerline porosity value.



8. Sampling

8.1 The materials shall be sampled in accordance with a sampling procedure statistically adequate to satisfy the requirements of 12.1. A lot shall be considered as a unit of manufacture defined as a production run.

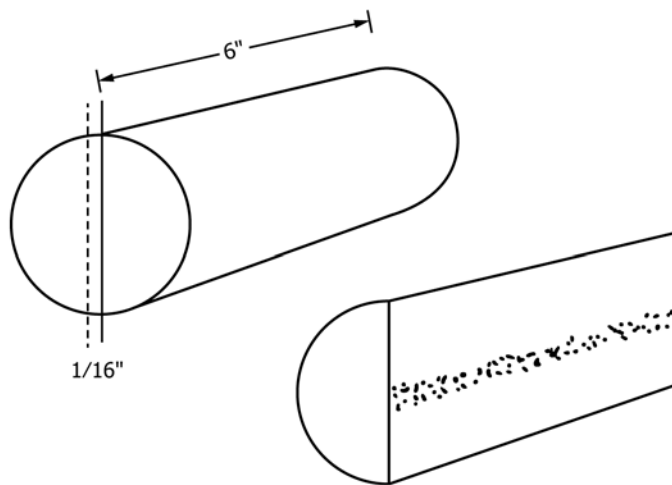

NOTE 1—A 6 in. length of POM rod is cut in half, approximately 1/16 in. off center to reveal center core of rod sample.

FIG. 1 POM Rod

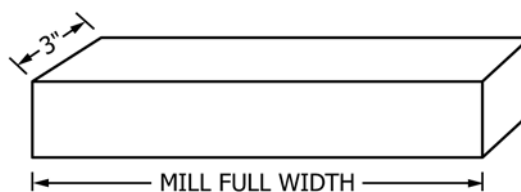

NOTE 1—A full-width sample of plate is cut to approximately a 3 in. length then face-milled 1/16 in. to properly display centerline of plate.

FIG. 2 Plate

9. Number of Tests

9.1 Routine lot inspection shall consist of all the criteria specified in the applicable product tables.

9.2 The criteria listed in these product tables and definitions are sufficient to establish conformity of the sheet, plate, rod or tubular bars to this specification. When the number of test

specimens is not stated in the test method, a single determination is sufficient. If more than single determinations and separate portions of the same sample are made, the results shall be averaged. The final result shall conform to the requirements prescribed in this specification.

10. Test Conditions

10.1 *Conditioning of Specimens*—The specification values and dimensions are based on conditioning techniques outlined in Procedure A of Practice **D618**.

10.2 *Standard Temperature*—Conduct the tests at the standard laboratory temperature of $73.4 \pm 3.6^\circ\text{F}$ ($23 \pm 2^\circ\text{C}$) and $50 \pm 10\%$ relative humidity (RH).

11. Test Methods

11.1 Test tensile strength at break, elongation at break, and tensile modulus (tangent) in accordance with Test Method **D638**, at the rate of 0.2 in./min.

11.1.1 Test all plate and sheet specimens in accordance with Test Method **D638**, Type 1. Whenever possible areas of acceptable porosity should be avoided.

11.1.2 Test all rod specimens in accordance with Test Method **D638**. Whenever possible, areas of acceptable porosity should be avoided.

11.1.3 Test all tubular bar specimens in accordance with Test Method **D638**. Whenever possible, areas of acceptable porosity should be avoided.

11.2 Dimensional Stability:

11.2.1 *Specimen Preparation (a Minimum of Three Test Samples Required):*

11.2.1.1 *Rods and Tubular Bar*—Prepare each specimen by cutting a 1.5 in. long slice from the shape to be tested. Then machine the slice using a coolant and good machining practices to a length of 1.000 ± 0.005 in. Each end of the specimen shall have a machined surface.

11.2.1.2 *Plate and Sheet*—The test is not applicable to sheet under $\frac{3}{16}$ in. thick. Each specimen shall consist of a 2 in. diameter disc machined from the flat (diameter shall equal test specimen thickness with a minimum of 2.0 in.). Use the same care in the machining as described above. The thickness of the specimen shall be that of the original flat from which it was cut, no machining being done on the top or bottom faces.

11.2.2 *Testing Procedure*—Measure the outside diameter and thickness or length of the specimen as applicable at $73.4 \pm 1.8^\circ\text{F}$ ($23 \pm 1^\circ\text{C}$) to the nearest 0.0001 in. Do all measurements on the center line and 90° from the center of the plate. Also take measurements for thickness halfway to center and for diameter at mid-point. Place the specimen in an oil bath consisting of polyalkylene glycol or an air circulating oven and heat to the applicable temperature for POM type as noted below. See **11.2.3**. After 6 h, allow the specimen to slowly cool to room temperature at a rate not to exceed 40°F (22°C) per hour. Then measure the specimen at $73.4 \pm 1.8^\circ\text{F}$ ($23 \pm 1^\circ\text{C}$) and calculate the percent change in each dimension.

11.2.3 Test Temperatures:

11.2.3.1 *POM* = $300 \pm 5.4^\circ\text{F}$ ($149 \pm 3^\circ\text{C}$).

11.3 *Lengthwise Camber and Widthwise Bow:*

11.3.1 Make all measurements for camber and bow using the maximum distance rod, sheet, or plate deviates from the straight line extended from edge to edge when measured in accordance with **11.3.2**. The shape shall be oriented such that the weight of the product doesn't influence the results.

11.3.2 Rod, Sheet and Plate:

11.3.2.1 *Rod*—Rod will be laid on side and measured with concave side facing the straight edge. Measure camber from the straight edge to the maximum concave point on rod. Camber is not to exceed the values of Table A-1 for the specified lengths of extruded, compression molded, or injection molded product.

11.3.2.2 *Sheet and Plate up to and Including $\frac{5}{8}$ in. Thick*—Plate up to and including $\frac{5}{8}$ in. in thickness shall meet the requirements of Tables B-1 or B-2 for extruded, compression molded or injection molded products with a straight edge, positioned in a lengthwise and widthwise direction, with the plate standing on its edge.

11.3.2.3 *Sheet and Plate Greater than $\frac{5}{8}$ in. Thick*—Plate above $\frac{5}{8}$ in. thick shall not exceed the requirements of Table B-1 for extruded, compression or injection molded product on the lengthwise ends and widthwise edges when laid on a flat surface (crown side up).

11.4 Squareness (Based on a 4 ft Nominal Length):

11.4.1 Measure and compare diagonal lengths (corner to corner). Accept the product if the difference is $\frac{1}{16}$ in. or less and the measured minimums diagonal meets the following requirements:

11.4.1.1 One foot wide is 49 $\frac{1}{2}$ in. minimum, 2 ft wide is 53 $\frac{3}{4}$ in. minimum, and 4 ft wide is 68 in. minimum.

11.4.2 If the diagonal difference exceeds $\frac{1}{16}$ in., proceed to measure the gap (that is the deviation from a 2 ft framing square). The maximum allowable gap shall not exceed $\frac{1}{8}$ in. except for the 1 ft wide sizes of sheet and plate that should not exceed $\frac{1}{16}$ in.

11.5 Test flexural modulus in accordance with Test Method **D790**, specimen $\frac{1}{4}$ in. thick maximum, testing speed 0.11 in./min. Whenever possible areas of acceptable porosity should be avoided.

11.6 Test Izod impact, in accordance with Method A of Test Method **D256** Fig. 4, notched, $\frac{1}{4}$ in. thick maximum specimen. Whenever possible areas of acceptable porosity should be avoided.

12. Certification

12.1 When requested at the time of order, the purchaser shall be furnished a certification that the lot is made from the required POM plastic (percent recycle, if applicable) and meets the requirements of this standard.

13. Packing, Packaging and Package Marking

13.1 All packing, packaging, and marking provisions of Practice **D3892** shall apply to this specification.

14. Ordering Information

14.1 All shapes covered by this specification shall be ordered using the proper callout designation (see **4.6**).

15. Keywords

15.1 POM; centerline porosity—POM; copolymer—POM; homopolymer—POM; low porosity—POM; plates—POM; porosity level 1—POM; recycled—POM; rod—POM; shapes—POM; sheet—POM; tubular bar—POM

SUMMARY OF CHANGES

Committee D20 has identified the location of selected changes to this standard since the last issue (D6100 - 11) that may impact the use of this standard. (May 1, 2014)

(1) Removed old subsection 2.2 and reference to ANSI Z1.9-2008. (2) Revised wording in 8.1.

ASTM International takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.

This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.

This standard is copyrighted by ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (www.astm.org). Permission rights to photocopy the standard may also be secured from the Copyright Clearance Center, 222 Rosewood Drive, Danvers, MA 01923, Tel: (978) 646-2600; <http://www.copyright.com/>