



# Standard Test Method for Accelerated Compressive Creep of Geosynthetic Materials Based on Time-Temperature Superposition Using the Stepped Isothermal Method<sup>1</sup>

This standard is issued under the fixed designation D7361; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon ( $\epsilon$ ) indicates an editorial change since the last revision or reapproval.

## 1. Scope

1.1 This test method covers accelerated testing for compressive creep properties using the Stepped Isothermal Method (SIM).

1.2 The test method is focused on geosynthetic drainage materials such as HDPE geonet specimens.

1.3 The SIM tests are laterally unconfined tests based on time-temperature superposition procedures.

1.4 Ramp and Hold (R+H) tests may be completed in conjunction with SIM tests. They are designed to provide additional estimates of the initial rapid compressive creep strain levels appropriate for the SIM results.

1.5 This method can be used to establish the sustained load compressive creep characteristics of a geosynthetic that demonstrates a relationship between time-dependent behavior and temperature. Results of this method are to be used to augment results of compressive creep tests performed at  $20 \pm 1^\circ\text{C}$  and may not be used as the sole basis for determination of long term compressive creep behavior of geosynthetic material.

1.6 The values stated in SI units are to be regarded as the standard. The values given in parentheses are for information only.

1.7 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

## 2. Referenced Documents

### 2.1 ASTM Standards:<sup>2</sup>

<sup>1</sup> This test method is under the jurisdiction of ASTM Committee D35 on Geosynthetics and is the direct responsibility of Subcommittee D35.02 on Endurance Properties.

Current edition approved July 1, 2012. Published July 2012. DOI: 10.1520/D7361-07R12.

<sup>2</sup> For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

D1621 Test Method for Compressive Properties of Rigid Cellular Plastics

D2990 Test Methods for Tensile, Compressive, and Flexural Creep and Creep-Rupture of Plastics

D4439 Terminology for Geosynthetics

D5262 Test Method for Evaluating the Unconfined Tension Creep and Creep Rupture Behavior of Geosynthetics

D6364 Test Method for Determining Short-Term Compression Behavior of Geosynthetics

## 3. Terminology

3.1 *Definitions:* For definitions related to geosynthetics see Terminology D4439.

3.2 *Definitions:* For definitions related to creep see Test Methods D2990, D5262 and D4439.

3.3 *Definitions of Terms Specific to This Standard:*

3.3.1 *viscoelastic response*—refers to polymeric creep, strain, stress relaxation or a combination thereof.

3.3.2 *compressive creep*—time-dependent deformation that occurs when a specimen is subjected to a constant compressive load.

3.3.3 *time-temperature superposition*—the practice of shifting viscoelastic response curves obtained at different temperatures along a horizontal log time axis so as to achieve a master curve covering an extended range of time.

3.3.4 *shift factor*—the displacement along the log time axis by which a section of the creep or creep modulus curve is moved to create the master curve at the reference temperature. Shift factors are denoted by the symbol  $\sim$  when the displacements are generally to shorter times (attenuation) or the symbol  $a_T$  when the displacements are generally to longer times (acceleration).

3.3.5 *stepped isothermal method (SIM)*—a method of exposure that uses temperature steps and dwell times to accelerate creep response of a material being tested under load.

3.3.6 *mean test temperature*—the arithmetic average of all temperature readings of the atmosphere surrounding the test specimen for a particular temperature step, starting at a time not later than established temperature ramp time, and finishing at a time just prior to the subsequent temperature reset.

3.3.7 *offset modulus method or pointing*—data analysis method used to normalize any prestrain in the samples by shifting the origin of a stress vs. strain curve to an axis origin of coordinates, that is, to coordinates (0,0).

3.3.8 *ramp and hold (R+H) test*—a creep test of very short duration, for example, 100–1000 seconds.

3.3.9 *dwell time*—time during which conditions (particular load) are held constant between temperature steps.

3.3.10 *compressive creep modulus*—in SIM analysis, the load divided by the percent compressive strain at any given point in time.

#### 4. Summary of Test Method

4.1 *SIM*—A procedure whereby specified temperature steps and dwell times are used to accelerate viscoelastic creep characteristics during which strain and load are monitored as a function of time.

4.1.1 *compressive creep*—Constant compressive load in conjunction with specified temperature steps and dwell times are used to accelerate compressive creep strain response.

4.2 *R+H*—Test specimens are ramp loaded at a predetermined loading rate to a predetermined load and held under constant load (short term creep test).

#### 5. Significance and Use

5.1 Use of the SIM decreases the time required for creep to occur and the obtaining of the associated data.

5.2 The statements set forth in Section 1.5 are very important in the context of significance and use, as well as scope of the standard.

5.3 Creep test data are used to calculate the creep modulus of materials as a function of time. These data are then used to predict the long-term creep deformation expected of geosynthetics used in drainage applications.

NOTE 1—Currently, SIM testing has focused mainly geonets made from high density polyethylene. Additional testing on other materials is ongoing.

5.4 R+H testing is done to establish the range of creep strains experienced in the brief period of very rapid response following the peak of the load ramp.

#### 6. Apparatus

6.1 *Loading Platens*—Loading platens for SIM and R+H tests should conform to Test Method D6364, Standard Test Method for Determining the Short-Term Compression Behavior of Geosynthetics.

6.2 *Testing Machine*—A universal testing machine or a dead-weight loading system with the following capabilities and accessories shall be used for testing:

6.2.1 load measurement and control,

6.2.2 strain measurement,

6.2.3 time measurement,

6.2.4 environmental temperature chamber to facilitate control of test conditions,

6.2.4.1 temperature measurement and control facilities,

6.2.5 other environmental measurement and control, and

6.2.6 computer data acquisition and control.

#### 7. Sampling

7.1 The specimens used for R+H and SIM tests should all be taken from the same sample.

7.2 Remove one (1) test specimen from the sample for each SIM test.

7.3 Remove one (1) test specimen from the sample for each R+H test.

#### 8. Test Specimens

8.1 Specimens should be at least 120 mm × 120 mm (4.7 in. × 4.7 in.).

8.2 *Number of tests*—

8.2.1 A single specimen is usually sufficient to define a master creep or relaxation curve using the SIM. However, if only a single SIM test is to be performed, the location of the onset of creep strain or modulus curve should be confirmed using at least two R+H tests.

#### 9. Conditioning

9.1 Compression testing via Test Method D6364 and SIM testing shall be conducted using  $20 \pm 1^\circ\text{C}$  as the reference or temperature standard. If the laboratory is not within this range, perform tests in a suitable environmental chamber capable of controlled cooling and heating. The environmental chamber should have a programmable- or set-point controller so as to maintain temperature to  $20 \pm 1^\circ\text{C}$ . When agreed to, a reference temperature other than  $20^\circ\text{C}$  can be utilized. Also, when agreed to, the results of testing under this standard can be shifted from one reference temperature to another.

9.2 Allow the specimen adequate time to come to temperature equilibrium in the laboratory or environmental chamber. Generally, this can be accomplished within a few hours (see Note 2).

9.3 Record the relative humidity in the laboratory or environmental chamber for all tests.

#### 10. Selection of Test Conditions

10.1 The standard environment for testing is dry, since the effect of elevated temperature is to reduce the humidity of ambient air without special controls.

10.2 The standard reference temperature is  $20^\circ\text{C}$  unless otherwise agreed to. The individual reference temperature for each SIM test is the average achieved temperature of the first dwell time.

10.3 Testing temperatures are to be within  $\pm 2^\circ\text{C}$  of the target test temperatures. It is critically important that the test specimen has equilibrated throughout its thickness so as to avoid nonisothermal conditions. Initial trials are necessary to establish this minimum equilibrium time.

NOTE 2—Laboratory experience has suggested that the use of calibrated thermocouples located near, affixed to or embedded within the test specimen may facilitate a successful temperature compliance test for the specimen material. It is suggested that the laboratory perform the planned SIM temperature steps using an unloaded sacrificial test specimen and,

with the use of these thermocouples, measure the temperature change of the specimen at its thickest or most mass-dense region. The time required for the specimen to reach the target temperature is recorded and used as the minimum dwell time. The upper limit of the temperature ramp time is not known. Successful tests with some materials have been run with temperature ramp times of up to four minutes.

10.4 Testing temperatures are to be maintained within  $\pm 1.0^\circ\text{C}$  of the mean achieved temperature.

10.4.1 Temperature steps and dwell times must be such that the steady state creep rate at the beginning of a new step is not so different from that of the previous that it cannot be established within the identified ramp time.

## 11. Procedure

11.1 The same or similar load or strain control shall be applied to the load ramp portion of R+H and SIM tests. The load rate control (in units of kN per min.) that is applied shall achieve a narrow range of strain rates expressed in percent per minute, as agreed upon. Generally 10 % of the nominal thickness of the test specimen per minute or  $1.0 \pm 0.1$  mm per minute ( $0.04 \pm 0.004$  inches per minute), whichever is greater will be satisfactory.

NOTE 3—A linear ramp of load vs. time will not generally result in a linear strain vs. time relationship because stress vs. strain curves are not linear for most geosynthetic materials.

11.2 Achieve the test loads for R+H and SIM tests within  $\pm 2$  % of the target loads, and maintain any achieved load within  $\pm 0.5$  % of its values for the duration of the test. A brief overshoot of the target load that is within  $\pm 2$  % of the target load and limited to a 1 to 2 second time duration is acceptable for load control systems.

11.3 Replicate test loads for R+H and SIM tests should be within  $\pm 0.5$  % of the average of the achieved loads for a test set.

11.4 Inspect the specimen installation to be sure the material is properly aligned with the platens and with the loading axis.

11.5 Ensure that the load cell used is calibrated properly such that it will accurately measure the range of compressive loads anticipated.

11.6 Ensure that the extensometer used (if any) is calibrated properly such that it will accurately measure the range of compressive strains anticipated.

11.7 Time, load and deformation data shall be collected at a minimum rate of two readings per second during the initial loading ramp portions of tests and a minimum rate of two readings per minute during constant load portions of tests. If load is applied by means of dead weights, with or without a lever, regular measurement of load after the ramp is not necessary.

11.8 The environmental chamber and temperature cooler shall be capable of maintaining the specimen temperature within  $\pm 1^\circ\text{C}$  in range of 0 to  $100^\circ\text{C}$ , and of changing the specimen temperature by up to  $15^\circ\text{C}$ , within the identified ramp time (see [Note 2](#)).

11.9 Unless otherwise agreed upon, the temperature steps for polyolefin geosynthetics shall not exceed  $7^\circ\text{C}$ .

NOTE 4—Examples that have been successful are a  $7^\circ\text{C}$  step with a 10 000 second dwell time for HDPE.

11.10 Unless otherwise agreed upon, the dwell time for all SIM tests shall not be less than 10 000 seconds. Unless otherwise agreed upon, the total time for SIM tests not terminated in rupture shall not be less than 60 000 sec.

11.11 The temperature data acquisition rate during SIM shall be a minimum of once per minute.

11.12 If desired, accelerated compressive property tests can be conducted in liquid, vapor, or gaseous mixtures to simulate unique environmental exposures.

## 12. Calculation

### 12.1 Ramp and Hold (R+H) Results:

12.1.1 Plot stress and secant (creep) modulus vs. strain, and strain and secant (creep) modulus vs. linear and log time. Use the offset modulus method to point the curves as described in [Section 12.1.2](#).

12.1.2 Identify the elastic strains at the ramp peaks and the initial rapid creep strain levels for comparison to the ramp and initial creep portions of the SIM results.

### 12.2 SIM Test Results (See [Appendix X1](#) for Examples):

12.2.1 Compute and plot stress and secant (compressive creep) modulus vs. strain for each specimen, using the offset modulus method to point the curve. Then plot compressive creep strain, compressive creep modulus, stress and temperature as a function of linear time. Inspect these plots to identify that the test objectives were achieved.

12.2.2 Plot compressive creep modulus (or compressive strain) vs. log time after rescaling the elevated temperature segments to achieve slope matching as follows: The semi-logarithmic slopes of a modulus (or compressive strain) curve at the beginning of a higher temperature step should be adjusted to match the slope of the end of the preceding lower temperature by subtracting a time "t" from each of the dwell times of higher temperature steps.

12.2.3 Re-plot the compressive creep modulus (or strain) vs. log time after rescaling as above and after employing vertical shifts of the modulus (or compressive strain) data for each elevated temperature to account for system thermal expansion.

12.2.4 Report the compressive creep modulus and compressive strain vs. log time curves as rescaled and vertically shifted above and after employing horizontal shifts of the elevated temperature segments to the right of the initial reference temperature dwell segment. The result of this final manipulation should be a smooth master curve for each specimen subjected to SIM.

12.2.5 The rescaling, vertical shifting and horizontal shifting steps generally require some iteration to achieve smooth master curves.

12.2.6 Prepare a plot of the logarithm of the cumulative shift factor vs. temperature.

12.2.7 Compute the mean temperature and a measure of temperature variation such as standard deviation or extreme values for each temperature step.

**13. Report (See Appendix X1 for Examples)**

13.1 Report the material type and structure along with the brand name and style nomenclature and the structure (geonet, etc.) of the geosynthetic product.

13.2 Document the tests performed and the electronic data files wherein original data is stored.

13.3 Complete and provide the graphs specified in Section 12.

13.4 Results generated under this standard shall be stated as having been measured by SIM testing protocol per this test method.

**14. Keywords**

14.1 creep; geosynthetics; hold test; ramp; stepped isothermal method; time-temperature superposition

**APPENDIX**

(Nonmandatory Information)

**X1. APPENDIX**

Introduction

the results for a polyethylene geonet before and after scaling and shifting.

X1.1 The following graphs are typical of those used in the report section of the SIM test procedure. Figs. X1.1-X1.8 show

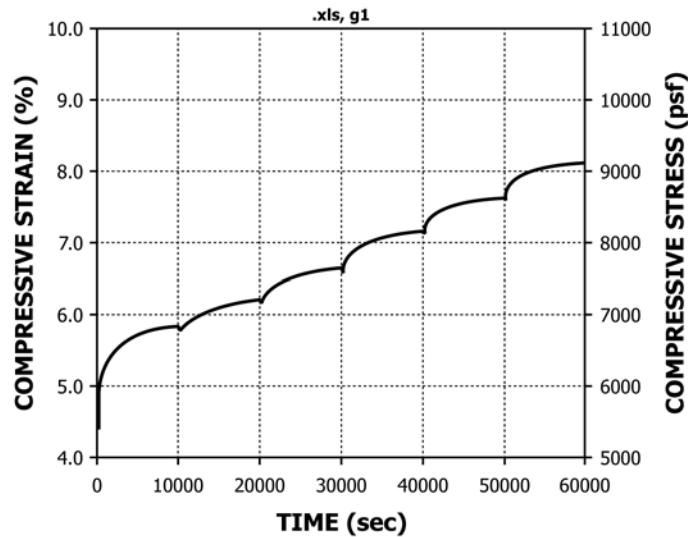


FIG. X1.1 Stress and Compressive Creep Strain vs. Linear Time

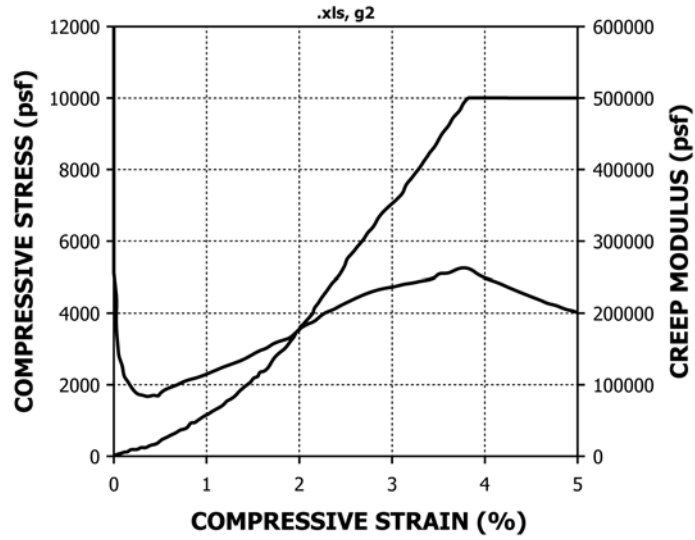


FIG. X1.2 Stress and Secant Modulus vs. Compressive Strain

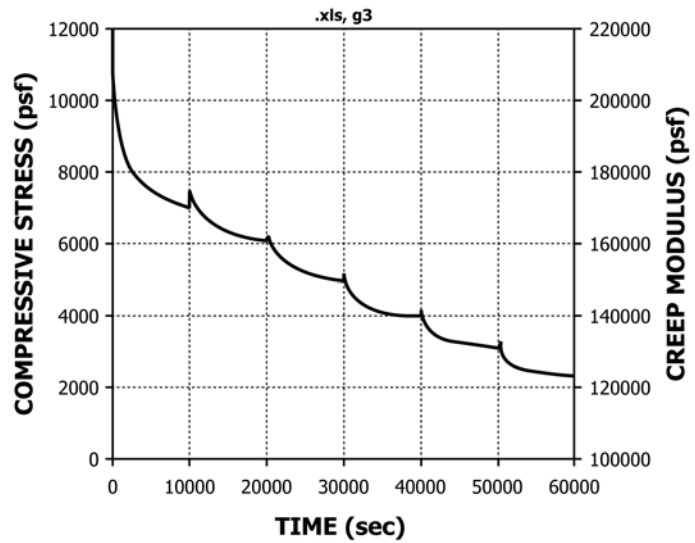


FIG. X1.3 Stress and Compressive Creep Modulus vs. Linear Time

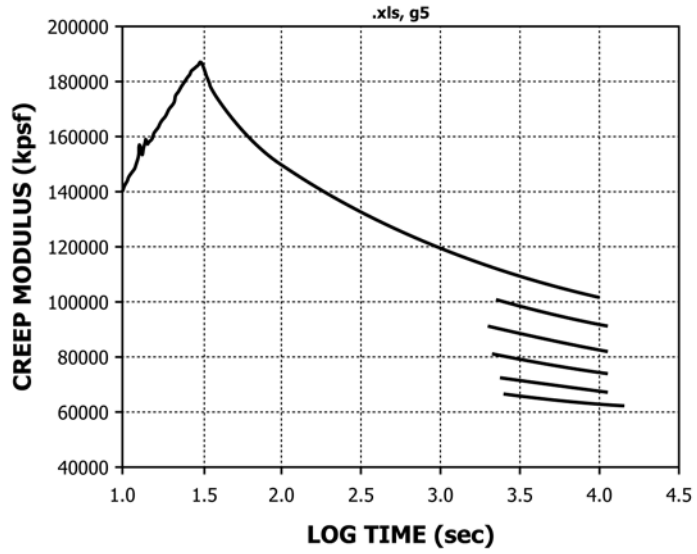


FIG. X1.4 Compressive Creep Modulus vs. Log Time After Rescaling

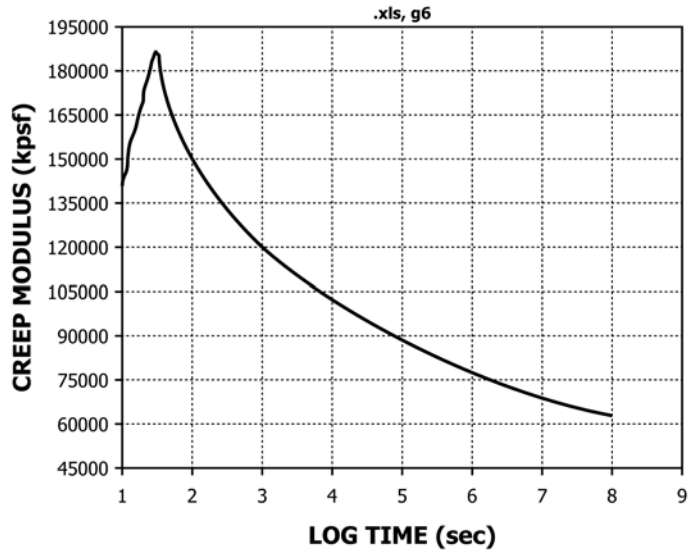


FIG. X1.5 Master Compressive Creep Modulus vs. Log Time Curve at the Step One Reference Temperature



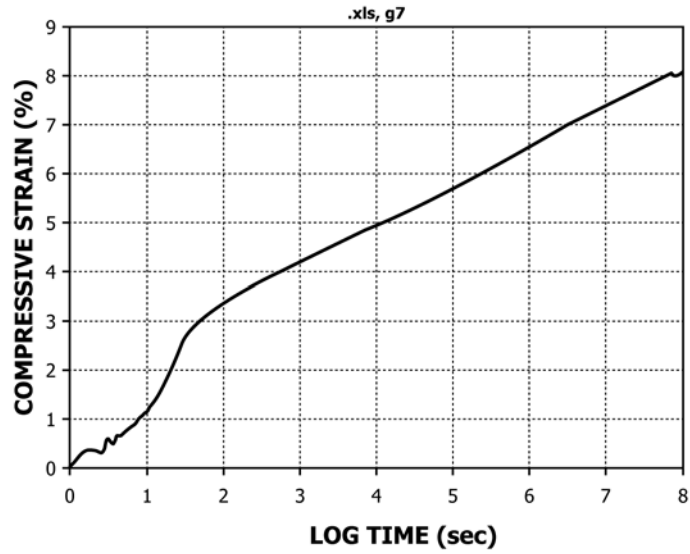


FIG. X1.6 Master Compressive Creep Strain vs. Log Time at the Step One Reference Temperature

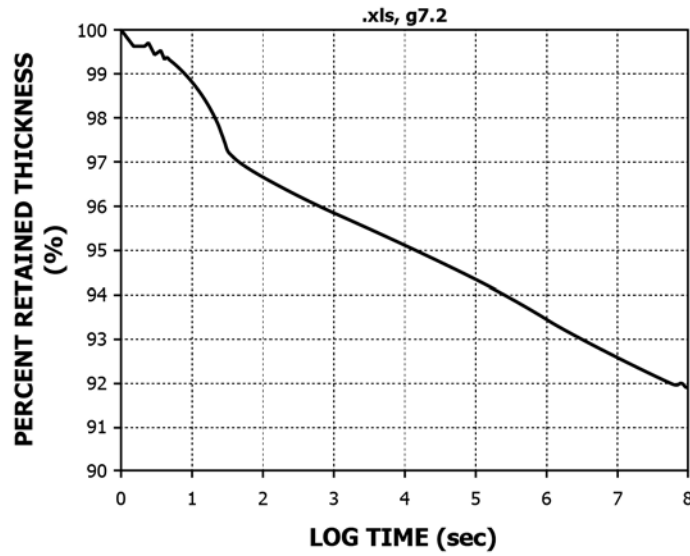


FIG. X1.7 Master Compressive Creep Strain (Plotted as Percent Retained of Original Thickness) vs. Log Time at the Step One Reference Temperature

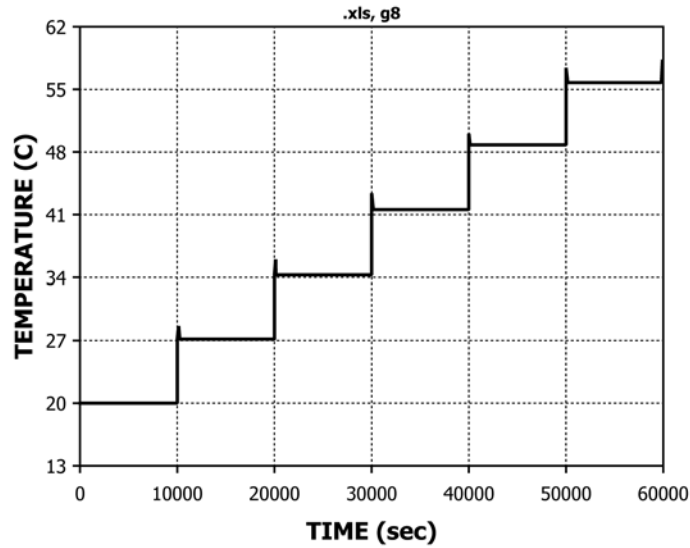


FIG. X1.8 SIM Temperature Steps vs. Time Steps

ASTM International takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.

This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.

This standard is copyrighted by ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (www.astm.org). Permission rights to photocopy the standard may also be secured from the Copyright Clearance Center, 222 Rosewood Drive, Danvers, MA 01923, Tel: (978) 646-2600; http://www.copyright.com/