



Designation: D7755 – 11 (Reapproved 2017)

# Standard Practice for Determining the Wear Volume on Standard Test Pieces Used by High-Frequency, Linear-Oscillation (SRV) Test Machine<sup>1</sup>

This standard is issued under the fixed designation D7755; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon ( $\epsilon$ ) indicates an editorial change since the last revision or reapproval.

## 1. Scope

1.1 This practice covers a procedure for determining the wear volume  $W_V$  of wear scars and tracks on test pieces tribologically stressed under high-frequency, linear-oscillation motion using a SRV test machine by means of stylus tip profilometry.

1.2 The values stated in SI units are to be regarded as standard. No other units of measurement are included in this standard.

1.3 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

1.4 *This international standard was developed in accordance with internationally recognized principles on standardization established in the Decision on Principles for the Development of International Standards, Guides and Recommendations issued by the World Trade Organization Technical Barriers to Trade (TBT) Committee.*

## 2. Referenced Documents

### 2.1 ASTM Standards:<sup>2</sup>

**D2714** Test Method for Calibration and Operation of the Falex Block-on-Ring Friction and Wear Testing Machine

**D2782** Test Method for Measurement of Extreme-Pressure Properties of Lubricating Fluids (Timken Method)

**D3702** Test Method for Wear Rate and Coefficient of Friction of Materials in Self-Lubricated Rubbing Contact Using a Thrust Washer Testing Machine

**D4175** Terminology Relating to Petroleum Products, Liquid

### Fuels, and Lubricants

**D5620** Test Method for Evaluating Thin Film Fluid Lubricants in a Drain and Dry Mode Using a Pin and Vee Block Test Machine (Withdrawn 2010)<sup>3</sup>

**D5706** Test Method for Determining Extreme Pressure Properties of Lubricating Greases Using a High-Frequency, Linear-Oscillation (SRV) Test Machine

**D5707** Test Method for Measuring Friction and Wear Properties of Lubricating Grease Using a High-Frequency, Linear-Oscillation (SRV) Test Machine

**D6425** Test Method for Measuring Friction and Wear Properties of Extreme Pressure (EP) Lubricating Oils Using SRV Test Machine

### 2.2 DIN Standards:<sup>4</sup>

**DIN 51631:1999-04** Special-boiling-point spirit – Requirements and testing

**DIN 51834-3:2008-12** Testing of lubricants – Tribological test in translatory oscillation apparatus – Part 3: Determination of tribological behaviour of materials in cooperation with lubricants

**DIN EN ISO 13565-2:1998** Geometrical Product Specifications (GPS) – Surface texture: Profile method; Surfaces having stratified functional properties – Part 2: Height characterization using linear material ratio curve (replaces of DIN 4776:1990: Measurement of surface roughness; parameters  $R_K$ ,  $R_{PK}$ ,  $R_{VK}$ ,  $M_{r1}$ ,  $M_{r2}$  for the description of the material portion)

## 3. Terminology

### 3.1 Definitions:

3.1.1 *Hertzian contact area,  $n$* —the apparent area of contact between two non-conforming solid bodies pressed against each other.

3.1.2 *Hertzian contact pressure,  $n$* —magnitude of the pressure at any specified location in a Hertzian contact area, as calculated from Hertz's equations of elastic deformation. The Hertzian contact pressure can also be calculated and reported


<sup>1</sup> This practice is under the jurisdiction of ASTM Committee D02 on Petroleum Products, Liquid Fuels, and Lubricants and is the direct responsibility of Subcommittee D02.L0 on Industrial Lubricants and Engineering Sciences of High Performance Fluids and Solids.

Current edition approved June 1, 2017. Published July 2017. Originally approved in 2011. Last previous edition approved in 2011 as D7755 – 11. DOI: 10.1520/D7755-11R17.


<sup>2</sup> For referenced ASTM standards, visit the ASTM website, [www.astm.org](http://www.astm.org), or contact ASTM Customer Service at [service@astm.org](mailto:service@astm.org). For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

<sup>3</sup> The last approved version of this historical standard is referenced on [www.astm.org](http://www.astm.org).

<sup>4</sup> Available from Deutsches Institut für Normung e.V.(DIN), Beuth Verlag GmbH, Burggrafenstraße 6, D-10787 Berlin 30, Germany, <http://www.din.de>.

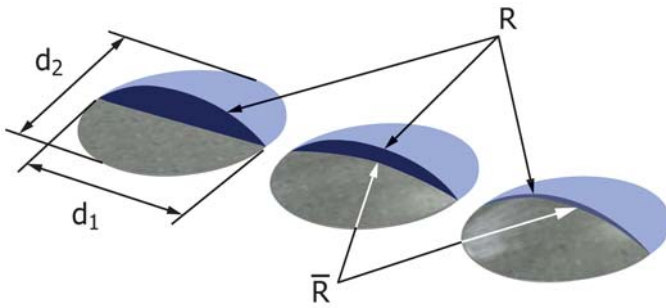

NOTE 1— $R$  is smaller than  $\bar{R}$ . The wear volumes are marked in blue.  
**FIG. 1 Ball—Comparison of Iso-wear Scar Diameters with Wear Volume in Relation to the Initial Radius  $R$  and the Radius in the Scar  $\bar{R}$  at Test End**

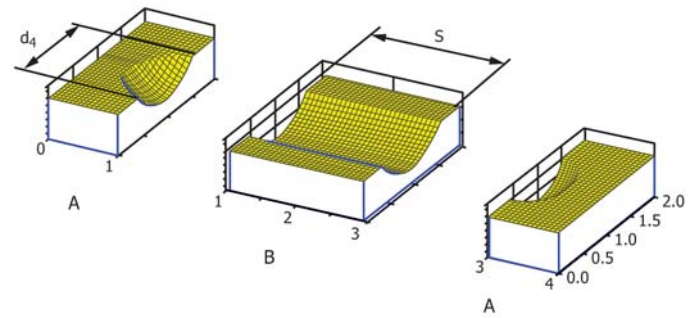

**FIG. 2 Schematic Illustration of the Segmentation of the Wear Track**

as maximum value  $P_{\max}$  in the centre of the contact or as  $P_{\text{average}}$  as average over the total contact area. **D4175**

3.1.3 *seizure, n*—localized fusion of metal between the rubbing surfaces of the test pieces. **D5706**

3.1.3.1 *Discussion*—Seizure is usually indicated by a sharp increase in coefficient of friction, wear, or unusual noise and vibration. In this test method, increase in coefficient of friction is displayed on the chart recorder as permanent rise in the coefficient of friction from a steady value.

3.1.4 *wear, n*—damage to a solid surface, generally involving progressive loss of material, due to the relative motion between that surface and a contacting substance or substances. **D2714, D2782, D5620**

3.1.5 *wear rate, n*—the rate of material removal or dimensional change due to wear per unit of exposure parameter; for example, quantity of material removed (mass, volume, thickness) in unit distance of sliding or unit time.

3.1.5.1 *Discussion*—Another term sometimes used synonymously is wear factor. **D3702**

### 3.2 Definitions of Terms Specific to This Standard:

3.2.1 *planimetric wear,  $W_q$ , n*—seen in the center of the wear track of the disk perpendicular to the sliding direction at test end and can be understood as cross section area of wear.

3.2.2 *wear volume,  $W_v$ , n*—the irreversible loss of volume to the ball or the disk (flat) at end of test. **D5707, D6425**

### 3.3 Abbreviations:

3.3.1 *SRV, n*—Schwingung, Reibung, Verschleiß, (German); oscillating, friction, wear (English translation).

## 4. Summary of Practice

4.1 This practice applies to test pieces tribologically stressed on a SRV test machine typically used in different ASTM (and DIN) test methods and are a test ball oscillating against a flat test disk.

4.2 As illustrated in Fig. 1, the same wear scar diameter on the ball not consequently indicates materials loss, the amount of material loss and different volumetric material losses can be related to exact one wear scar diameter.

NOTE 1—An extreme and ideal, but frequent case, is the case of a lubricant, which fully protects against wear, but a wear scar diameter is marked only visibly by tribo-chemistry and the wear scar diameter

corresponds to the initial Hertzian contact diameter describing the elastic deformation. By using the ball diameter of diameter  $\varnothing = 10$  mm, the elastic constants for AISI 52100 (100Cr6H) and  $F_N = 200$  N, the initial Hertzian contact diameter calculates to 0.374 mm and for  $F_N = 300$  N is 0.428 mm. When now unloading the ball after test, the elastic deformation is released and the initial shape recovers, showing, for example, no wear, but a marked wear scar, which is reported as wear scar diameter, even no, less or minor wear can be detected by means of stylus tip profilometry.

4.3 The wear scar diameter on the test ball is measured and the shape of the wear track on the disk is determined by means of a stylus tip profilometer in the centre of the track length (see Fig. 2) and this perpendicular to the sliding direction.

4.3.1 The worn or displaced volume ( $W_{v,\text{ball}}$ ;  $W_{v,\text{flat}}$ ) can be calculated by numerical methods<sup>5-7</sup> from the stylus tip profile data and assuming an ideal shape of the test specimen.

NOTE 2—In general, the wear volume is calculated by integrating a multitude of cross section area taken at different lengths of the wear track. The wear volume in this practice is based only on one cross section area (planimetric wear) in the centre of the wear track.

4.4 The planimetric wear  $W_{q,\text{flat}}$  of the disk is derived from a 2D-profilogram by using a stylus tip profilometer.

## 5. Significance and Use

5.1 The determination of the wear volume becomes in tribological testing a key element, as it is more discriminative than the wear scar diameter, because an optically visible wear scar diameter may or may not indicate wear on the surface of the ball and the wear track as an irreversible loss of material. Users of this test method should determine whether results correlate with field performance or other applications.

NOTE 3—It is believed, that tactile stylus tip profilometer determines the most realistic figure and are more frequent in use, than it can be achieved by optical profilometers operating in a non-contacting mode.

## 6. Apparatus

6.1 *Microscope*, equipped with a filar eyepiece graduated in 0.005 mm division or equipped with a micrometer stage readable to 0.005 mm. Magnification should be sufficient to

<sup>5</sup> Ruff, A. W., "Wear Measurement," *ASM Handbook*, Vol 18, 1992, pp. 362–369.

<sup>6</sup> Klaffke, D., "Fretting Wear of Ceramics," *Tribology International*, Vol 22, No. 2, 1989, pp. 89–101.

<sup>7</sup> Kalin, M., and Vižintin, J., "Use of Equations for Wear Volume Determination in Fretting Experiments," *WEAR*, 237, 2000, pp. 39–48.

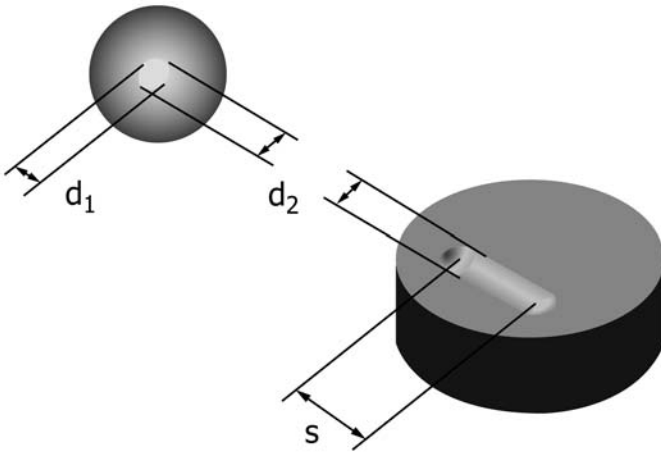


FIG. 3 Scheme of Wear Scar (Ball) and Track (Disk, Flat) on the Test Specimen

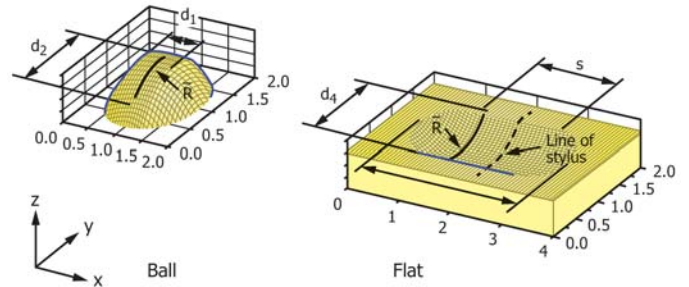


FIG. 4 Scheme of Variables Used to Calculate the Wear Volume of Ball and Disk

allow for ease of measurement. One to 10 times magnification has been found acceptable.

### 6.2 Stylus Tip Profilometer:

6.2.1 The stationary working place of the stylus tip profilometer should be composed of a stone (granite) base plate, the column, a transverse unit, a skidless tracing arm (skidless pick-up) and have the necessary software.

6.2.2 The stylus tip has a tip radius of 2 μm and a tip angle of 60° with a tip orientation (stylus position) of 90°. The resolution of the transverse unit is 0.1 μm or better.

## 7. Reagents and Materials

7.1 *Cleaning Solvent*, the test balls and disks have to be cleaned by a liquid solvent (non-chlorinated, non-film forming). (**Warning**—Flammable. Health Hazard.)

NOTE 4—It is recommended to use special boiling point spirit type 2 according to DIN 51631:1999.

## 8. Preparation of Apparatus

8.1 Most ASTM test methods related to SRV run with a ball sliding on a flat. In consequence and after the test, a wear scar marks the ball and a wear track the flat (see Fig. 3).

## 9. Procedure

9.1 *Cleaning of the Specimen*—Clean the test ball and disk by wiping the surfaces with laboratory tissue soaked with the cleaning solvent. Repeat wiping until no dark residue appears on the tissue. Immerse the specimen ball and disk in a beaker of the cleaning solvent under ultrasonic vibration for 10 min. Dry the test ball and disk with a clean tissue ensuring no streaking occurs on the surface.

### 9.2 Stylus Tip Profilometry:

9.2.1 The wear scar and track should be free of seizure marks.

9.2.2 The measuring length should have on each side of the track at least 0.500 mm in order to define the base line of the surface topography. A tracing speed of 0.15 mm/s has been found acceptable.

9.2.3 Set manually the bars on the left side and right side of the track shown in the profilogram displayed on the screen in order to define the borders. Set manually the horizontal bar for the base of the surface topography (see Fig. X1.1). The software iterates (calculates) the planimetric wear area.

9.3 *Calculation of the Wear Volume*—The variables used in Eq 1-4 are illustrated in Figs. 2 and 4.

9.3.1 The wear volume of the ball  $W_{v,ball}$  in mm<sup>3</sup> is calculated by using Eq 1.

$$W_{v,ball} = \frac{\pi \cdot d_1^2 \cdot d_2^2}{64} \left( \frac{1}{\bar{R}} - \frac{1}{R} \right) \quad (1)$$

and by using:

$$\bar{R} = \frac{d_4^3}{12 \cdot W_{q,flat}} \quad (2)$$

where:

- $\bar{R}$  = resulting radius of the shape of the wear scar after the test in mm;
- $R$  = initial radius of the ball in mm;
- $d_1$  = the wear scar diameter on the ball parallel to the sliding direction in mm;
- $d_2$  = wear scar diameter on the ball perpendicular to the sliding direction in mm and
- $W_{q,flat}$  = planimetric wear of the wear track in the middle of the wear track length and seen perpendicular to the sliding direction in mm<sup>2</sup>.

9.3.2 The shape of the wear track on the disk (flat) can be composed from three sections in Fig. 2 and represent the basis for Eq 3. Thus Eq 3 contains the element, B, plus the two elements, A, describing the ball scar.

9.3.2.1 The wear volume of the wear track on the flat disk  $W_{v,flat}$  in mm<sup>3</sup> is calculated by using Eq 3.

$$W_{v,flat} = \frac{\pi \cdot d_4^2 (d_3 - s)^2}{64} \cdot \frac{1}{\bar{R}} + s \cdot W_{q,flat} \quad (3)$$

where:

- $d_3$  = the total length of wear track in sliding direction in mm,
- $d_4$  = the width of the wear track in mm, and
- $s$  = stroke in mm.

and

$$\bar{R} = \frac{d_4^3}{12 \cdot W_{q,flat}} \quad (4)$$

where:

measured diameter  $d_4 = d_2$  in mm.

NOTE 5—The equations represent an approximation for strokes smaller than 2 mm to 2.5 mm and assume that  $R < R'$  and the wear height of the scar is  $\ll R$ .

NOTE 6—The wear tracks produced by other oscillating test methods with strokes of smaller than 2 mm may be also evaluated according to this practice. The mathematical approach of this practice does not properly reflect the aspects and shapes of longer wear tracks.

**10. Report**

10.1 Report the following information:

10.1.1 All parameters used to evaluate the lubricant as stated in the test method.

10.2 Report both wear scar diameter measurements ( $d_1$  and  $d_2$ ) taken on the ball.

10.3 Report the planimetric wear area  $W_{q,flat}$  determined in the wear track of the disk.

10.4 Report the calculated wear volumes of ball  $W_{v,ball}$  and disk  $W_{v,flat}$ .

**11. Precision and Bias**

11.1 The calculation of the wear volumes is exact and no precision limits can be assigned to this calculation.

11.2 The accuracy of calculated wear volume will depend on the precision of the optical wear diameter measurement and of the planimetric surface area from the stylus tip profilometry.

11.3 *Bias*—The calculation of the wear volume is exact and no bias can be assigned to this calculation.

**12. Keywords**

12.1 lubricating grease and oil; oscillation; SRV; wear; wear volume

**APPENDIX**

(Nonmandatory Information)

**X1. MEASUREMENTS OF WEAR VOLUME**

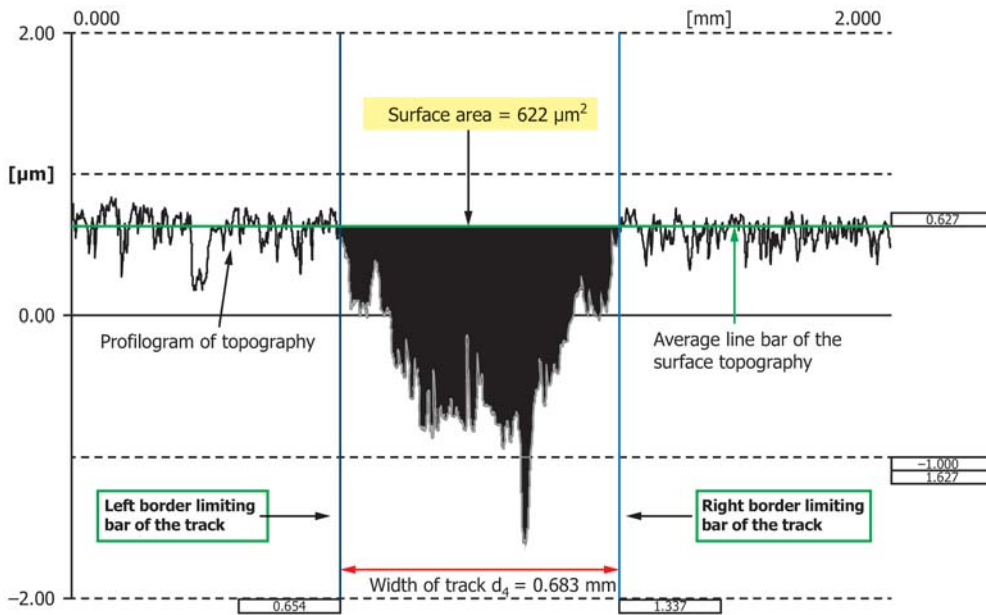


FIG. X1.1 Profilogram Displayed On a Screen and Taken Perpendicular in the Center of the Wear Track on a SRV Test Disk

X1.1 Fig. X1.1 illustrates the setting of the bar limits by cursor on the screen in order to enable the software to iterate the planimetric wear area. These vertical bars limits the left border and right border of the wear track width (see diameter

or width  $d_4$ ) and horizontal bar indicates the average line of the surface topography. The iterated surface area is marked in black and the iteration result stated.

*ASTM International takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.*

*This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.*

*This standard is copyrighted by ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or [service@astm.org](mailto:service@astm.org) (e-mail); or through the ASTM website ([www.astm.org](http://www.astm.org)). Permission rights to photocopy the standard may also be secured from the Copyright Clearance Center, 222 Rosewood Drive, Danvers, MA 01923, Tel: (978) 646-2600; <http://www.copyright.com/>*