



Standard Test Method for Evaluation of Asphalt Mixture Cracking Resistance using the Semi-Circular Bend Test (SCB) at Intermediate Temperatures¹

This standard is issued under the fixed designation D8044; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

1. Scope

1.1 This test method covers the procedures for preparation, testing, and measurement of asphalt mixture cracking resistance at Long Term Pavement Performance (LTPP) database intermediate temperatures using semi-circular bend (SCB) geometry laboratory prepared or pavement core asphalt mix samples tested monotonically. The SCB sample is a half-disk with a notch cut parallel to the loading and vertical axis. The test method describes the determination of the critical strain energy release rate, J_c , and other parameters determined from the load-displacement curve. These parameters can be used to rank the resistance of asphalt mixtures to cracking.

1.2 The text of this standard references notes and footnotes which provide explanatory material. These notes and footnotes (excluding those in tables and figures) shall not be considered as requirements of the standard.

1.3 The values stated in SI units are to be regarded as standard. No other units of measurement are included in this standard.

1.4 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

2. Referenced Documents

2.1 ASTM Standards:²

[D979/D979M Practice for Sampling Bituminous Paving Mixtures](#)

[D2041/D2041M Test Method for Theoretical Maximum Specific Gravity and Density of Bituminous Paving Mixtures](#)

[D2726/D2726M Test Method for Bulk Specific Gravity and Density of Non-Absorptive Compacted Bituminous Mixtures](#)

[D3203/D3203M Test Method for Percent Air Voids in Compacted Dense and Open Bituminous Paving Mixtures](#)

[D3666 Specification for Minimum Requirements for Agencies Testing and Inspecting Road and Paving Materials](#)

[D5361/D5361M Practice for Sampling Compacted Asphalt Mixtures for Laboratory Testing](#)

[D6373 Specification for Performance Graded Asphalt Binder](#)

[D6857/D6857M Test Method for Maximum Specific Gravity and Density of Bituminous Paving Mixtures Using Automatic Vacuum Sealing Method](#)

[D6925 Test Method for Preparation and Determination of the Relative Density of Asphalt Mix Specimens by Means of the Superpave Gyrotory Compactor](#)

[E4 Practices for Force Verification of Testing Machines](#)

[E29 Practice for Using Significant Digits in Test Data to Determine Conformance with Specifications](#)

[E178 Practice for Dealing With Outlying Observations](#)

[E399 Test Method for Linear-Elastic Plane-Strain Fracture Toughness \$K_{Ic}\$ of Metallic Materials](#)

[E2309/E2309M Practices for Verification of Displacement Measuring Systems and Devices Used in Material Testing Machines](#)

[E3029 Practice for Determining Relative Spectral Correction Factors for Emission Signal of Fluorescence Spectrometers](#)

2.2 AASHTO Standards:³

[R30 Practice for Mixture Conditioning of Hot Mix Asphalt \(HMA\)](#)

[M320 Standard Specification for Performance-Graded Asphalt Binder](#)

[M332 Standard Specification for Performance-Graded Using Multiple Stress Creep Recovery \(MSCR\) Test](#)

¹ This test method is under the jurisdiction of ASTM Committee D04 on Road and Paving Materials and is the direct responsibility of Subcommittee D04.20 on Mechanical Tests of Asphalt Mixtures.

Current edition approved July 1, 2016. Published August 2016. DOI: 10.1520/D8044-16.

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

³ Available from American Association of State Highway and Transportation Officials (AASHTO), 444 N. Capitol St., NW, Suite 249, Washington, DC 20001, <http://www.transportation.org>.

3. Terminology

3.1 Definitions:

3.1.1 J_c —critical strain energy release rate (kJ/m^2), value used to evaluate mixture resistance to cracking.

3.1.2 U —strain energy to failure (kJ) is the area under the loading portion of the load versus deflection curves, up to the maximum load measured for each notch depth.

4. Summary of Test Method

4.1 A semi-circular specimen is loaded monotonically until fracture failure occurs under a constant rate of deformation in a three-point bending load configuration. The load and deformation are continuously recorded and are used to compute the strain energy for a given notch depth. The test is repeated at multiple notch depths to compute the critical strain energy release rate, J_c . High J_c values are desirable for fracture-resistant mixtures. A J_c value ranging from 0.5 to 0.60 kJ/m^2 is typically recommended to ensure adequate fracture resistance of the mixture.

4.2 This test procedure considers the elasto-plastic/visco-elastic relationship of asphalt mixtures and fracture mechanics (Mull, et al., 2006, Anderson 2005 and suggested by Wu et al., 2005).

5. Significance and Use

5.1 The critical strain energy release rate, J_c , is used to compare the cracking resistance of asphalt mixtures prepared with different binder and aggregate types prepared to meet the volumetric requirements of differing traffic levels tested at intermediate temperatures.

5.2 This engineering property is a performance indicator of intermediate temperature cracking.

NOTE 1—The quality of the results produced by this standard are dependent on the competence of the personnel performing the procedure and the capability, calibration, and maintenance of the equipment used. Agencies that meet the criteria of Specification D3666 are generally considered capable of competent and objective testing/sampling/inspection/etc. Users of this standard are cautioned that compliance with Specification D3666 alone does not completely assure reliable results. Reliable results depend on many factors; following the suggestions of Specification D3666 or some similar acceptable guideline provides a means of evaluating and controlling some of those factors.

6. Apparatus

6.1 *Load Test System*—A load test system consisting of an axial loading device, environmental chamber, and control and data acquisition system. The test system shall meet the minimum requirements specified in Table 1. (See Practices E2309/E2309M.)

TABLE 1 Test System Minimum Requirements

Measurement	Range	Accuracy
Load Measurement and Control	0 to 10 kN	$\pm 1\%$
Displacement Measurement and Control	0 to 30 mm	$\pm 0.5\%$
Temperature Measurement and Control Range	5 to 35 °C	$\pm 0.3\text{ °C}$

6.1.1 *Axial Loading Device*—The load apparatus shall be capable of maintaining a constant deformation rate of 0.5 mm/min.

6.1.2 *Environmental Chamber*—A chamber capable of maintaining $\pm 0.3\text{ °C}$ of the climatic intermediate temperature calculated in 8.4.

6.1.3 *Control and Data Acquisition System*—The system shall include a data acquisition system comprising analog to digital conversion or digital input, or both, for storage and analysis on a computer. The system shall be capable of measuring and recording three signals during the test including load, displacement, and chamber temperature at a sampling rate of 10 Hz. The minimum resolution of the measurements is provided in Table 1.

6.2 Measurement Devices:

6.2.1 *Load Measuring Device*—The load measuring device shall consist of an electronic load cell, designed for placement between the load platen and piston, with the minimum capacity and sensitivity stated in Table 1. The load cell shall be calibrated in accordance with Practices E4.

6.2.2 *Axial Deformations*—Axial deformations shall be measured with linear variable differential transformers (LVDT) or other devices capable of measuring displacement within the range and tolerance provided in Table 1. The LVDT shall be calibrated in accordance with Practice E3029, Class B.

6.2.3 *Temperature*—Chamber temperature shall be measured with Resistance Temperature Detectors (RTD) or other suitable devices accurate to within $\pm 0.3\text{ °C}$.

6.3 *Gyratory Compactor*—A gyratory compactor and associated equipment for preparing laboratory specimens in accordance with Test Method D6925 shall be used.

6.4 *Saw*—The saw shall be capable of producing three different notch sizes ranging from 0 to 50 mm. The width of the saw blade shall be $<3.5\text{ mm}$.

6.5 *Test Fixture*—The loading frame shall consist of a loading rod and two sample support rods. The schematic of the test apparatus is shown in Fig. 1. The diameters of the loading and supports rods shall be 25 mm and the anvil span shall be 127 mm.

6.6 *Reaction Surface Treatment*—Polytetrafluoroethylene (PTFE) strips are used to reduce friction between the specimen and the lower two support rollers.

7. Sampling, Test Specimens, and Test Units

7.1 Semi-circular bend testing may be performed on field cores or laboratory prepared test specimens. (See Practices D5361/D5361M and D979/D979M.)

7.2 Laboratory-compacted asphalt mixture samples:

7.2.1 *Specimen Size*—The specimens shall be 150 mm in diameter by 120 mm thick.

7.2.2 *Air Void Content*—Prepare a minimum of three gyratory specimens at the target air void content using the Superpave Gyratory Compactor (SGC) according to Test Method D6925 at the target air void content $\pm 0.5\%$. The typical air void target for the test specimens is 7.0 %.

NOTE 2—The specimen air voids are calculated using Test Methods

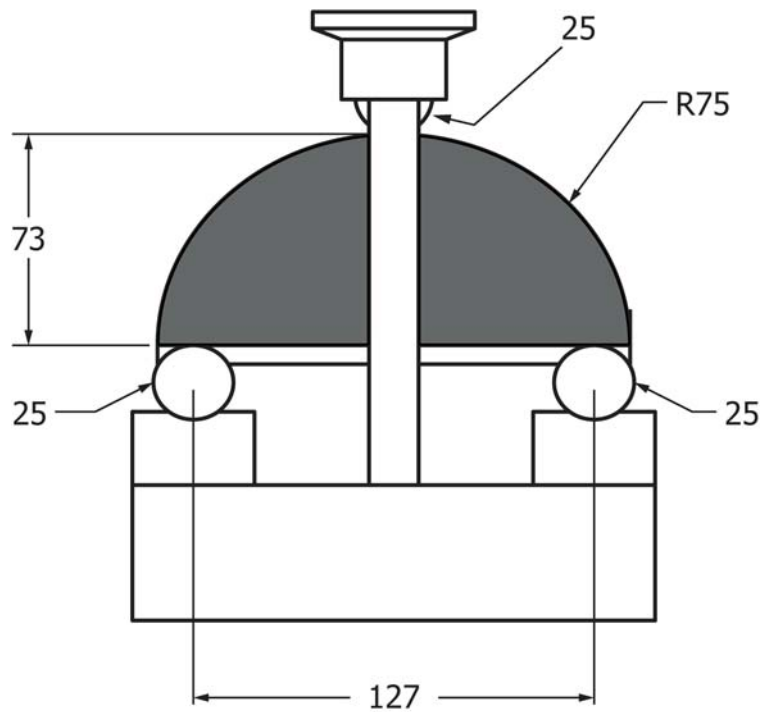
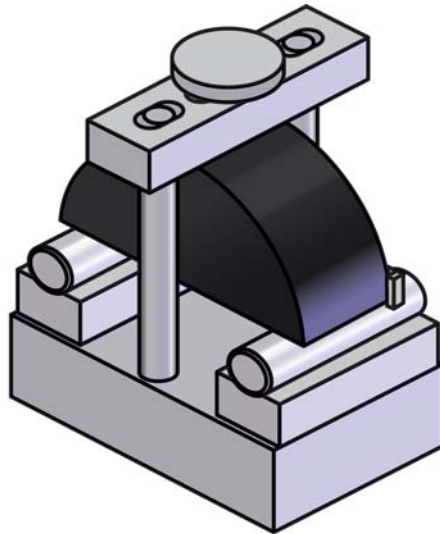


FIG. 1 Shop Drawing of SCB Test Fixture

D2041/D2041M, D2726/D2726M, D3203/D3203M, and D6857/D6857M.

7.2.3 The semi-circular shaped specimens are prepared by first cutting a 150 mm diameter by 120 mm thick specimen into two equal circular test samples 57 mm thick. These samples are cut along its central axis into two equal semi-circular samples. The height (radius) of the two samples shall be within 1 mm of each other.

NOTE 3—Some practitioners believe that the test should be conducted on specimens with two cut faces. If this approach is used, increase the

compacted sample height by approximately 15 ± 5 mm such that the semi-circular shaped specimens with two cut faces have a final thickness of 57 ± 1 mm.

7.3 Samples Cored from Asphalt Pavement:

7.3.1 Roadway cores can be used if pavement layer thickness is between 38 and 60 mm. Cores shall be taken full depth so that no prying action is needed to extract the cores from the pavement. Care shall be taken to avoid stress or damage to the interface during coring, handling, and transportation. The cores shall be trimmed such that only a single layer is tested.

7.3.2 Roadway core specimens shall be approximately 150 mm diameter with all surface of the perimeter perpendicular to the surface of the core within 6 mm. If the thickness of the core being tested is greater than 57 mm, it shall be trimmed with a wet masonry saw to a height of 57 mm.

7.3.3 The semi-circular shaped specimens are prepared by slicing the 150 mm diameter specimen prepared in 7.2.3 along its central axis into two equal semi-circular samples. The height (radius) of the two halves shall be within 1 mm of each other.

7.4 *Notching*—A straight vertical notch is cut along the symmetrical axis of each semi-circular specimen. The location of the notch shall be in the center of the specimen within 0.3 mm. The three nominal notch depths are 25 mm, 32 mm, and 38 mm. The notch depth tolerance is ± 1.0 mm. The width of the notch shall be <3.5 mm.

NOTE 4—Ruggedness testing between four laboratories has shown the J_c for split samples to have a within laboratory COV of 9.9 % for specimens with notch widths between 1.3 mm and 3.4 mm. The specimens should be symmetrical about the cut notch.

7.5 *Aging*—Laboratory-prepared test specimens shall be long term temperature-conditioned in according to AASHTO R30. Roadway cores need not be aged prior to testing.

7.6 A minimum of four semi-circular specimens shall be tested at each of the following notch depths: 25 mm, 32 mm, and 38 mm.

NOTE 5—A loose mix aging method is under development that may be able to achieve the AASHTO R30 level of aging in 12 to 24 h, NCHRP 9-54 Long Term Aging of Asphalt Mixtures for Performance Testing and Prediction. The long term temperature aging is needed to account for binder source, RAP, RAS and rejuvenators on mix performance (Reinke, et al., 2009, 2015, Cooper, et al. 2014, 2015).

8. Procedure

8.1 Inspect the fixture to ensure all contact surfaces are clean and free of debris. Place the PTFE tape or pads to reduce friction caused by interactions between the specimen and testing fixture during loading. The PTFE pads can be placed between the specimen and the bottom support rollers.

8.2 Load the specimen in the fixture, ensuring the specimen is centered and making uniform contact (level) on the support rollers (as shown in Fig. 2).

8.3 Set the environmental chamber temperature and allow it to stabilize to the test temperature $\pm 0.3^\circ\text{C}$. A dummy specimen with a temperature sensor mounted to its center can be monitored to determine when the specimen reaches the test temperature $\pm 0.3^\circ\text{C}$. In the absence of a dummy specimen, the specimens should be placed in the environmental chamber set at the test temperature for a minimum of 2 ± 0.5 h to reach the required temperature equilibrium.

NOTE 6—Dummy specimens are typically the same material as the test specimens.

8.4 Select test temperature based on the climatic intermediate temperature performance grade temperature as defined in Specification D6373, AASHTO M320, or M332 and provided below in Eq 1:

$$PG\ IT = \frac{PG\ HT + PG\ LT}{2} + 4 \quad (1)$$

where:

$PG\ IT$ = Intermediate performance grade temperature ($^\circ\text{C}$),
 $PG\ HT$ = Climatic high performance grade temperature, and
 $PG\ LT$ = Climatic low performance grade temperature.

8.5 After temperature equilibrium is reached, apply a pre-load of 45 ± 10 N for a maximum duration of 30 s to specimen to ensure the sample is seated properly. After ensuring the sample is level, release the load.

8.6 Begin to apply load to specimen in displacement control at a rate of 0.5 mm/min ensuring that time, force, and displacement are measured and recorded at a sampling rate of 10 Hz. Test may be terminated when the applied load decreases to 25 % of the peak load.

9. Calculation or Interpretation of Results

9.1 The critical value of J-integral (J_c) is determined using Eq 2:

$$J_c = \frac{-1}{b} \left(\frac{dU}{da} \right) \quad (2)$$

where:

J_c = critical strain energy release rate (kJ/m^2),
 b = sample thickness (m),
 a = notch depth (m),
 U = strain energy to failure (kJ), and
 dU/da = change of strain energy with notch depth (kJ/m).




(a)



(b)



(c) Sample Placed in Marshall Fixture

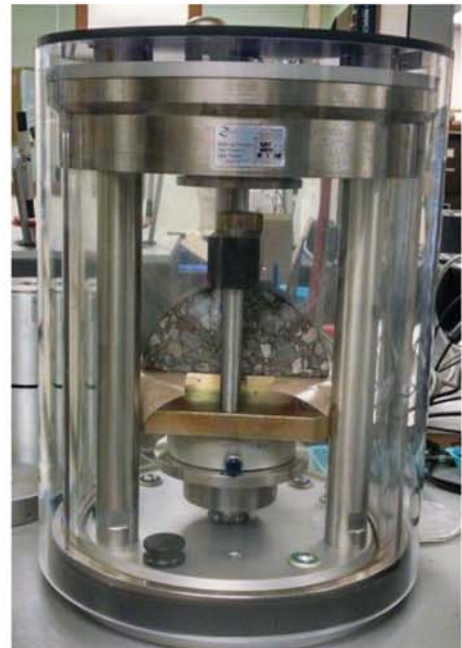

(d) Fixture in AMPT

FIG. 2 Examples of SCB Test Fixtures for a Universal Testing Machine (a and b) and a Marshall Press (c) or AMPT (d)

9.1.1 Strain energy to failure, U , is the area under the loading portion of the load versus deflection curves, up to the maximum load measured for each notch depth (shown in Fig. 3). Calculate the strain energy using the quadrangle rule provided in Eq 3:

$$U = \sum_{i=1}^n (u_{i+1} - u_i) \times P_i + \frac{1}{2} \times (u_{i+1} - u_i) \times (P_{i+1} - P_i) \quad (3)$$

where:

- P_i = applied load (kN) at the i load step application,
- P_{i+1} = applied load (kN) at the $i+1$ load step application,
- u_i = crosshead displacement (m) at the i step, and
- u_{i+1} = crosshead displacement (m) at the $i+1$ step.

NOTE 7—An alternative analysis method is to fit the load versus displacement curve for each notch depth with a sixth order polynomial and integrate from the origin to the displacement that corresponds to the maximum load. Report the test results according to Practice E29.

9.2 Examine the load versus displacement curves for each specimen to verify that the linear region of the data trace is consistent. Inconsistencies can be caused by machine compliance, sample seating, sample preparation, or other factors.

9.3 Calculate the strain energy, U (kJ) for each sample using Eq 3 or instructions in Note 7.

9.4 Apply Practice E178 to test replicates at each notch depth to identify the presence of outliers in the data set at a confidence level of 90 %. Remove any outliers from the data set.

9.5 For all observations plot U versus notch depth and model the data with a linear regression line, an example is

shown in Fig. 4. The slope of the linear regression line represents the change of strain energy with notch depth (dU/da). Determine the coefficient of determination (R^2) for the regression line. The coefficient of determination (R^2) is expected to be equal or greater than 90 % for asphalt mixture tested.

9.6 Divide the slope of the linear regression line by the average sample thickness to calculate the critical strain energy release rate, J_c .

NOTE 8—A reference for the test procedure and analysis is Test Method E399.

10. Report

10.1 The report shall include the following parameters:

- 10.1.1 Asphalt mixture type,
- 10.1.2 Test temperature, °C,
- 10.1.3 Specimen air voids, %,
- 10.1.4 Specimen thickness, mm,
- 10.1.5 Notch depth per sample, mm,
- 10.1.6 Strain energy (U) to failure per notch depth, kJ.
- 10.1.7 Average strain energy (U) per notch depth, kJ,
- 10.1.8 Standard deviation of strain energy (U) per notch depth, kJ,
- 10.1.9 Coefficient of variation of strain energy (U) per notch depth, %,
- 10.1.10 Coefficient of determination of standard deviation of U versus notch depth, %, and
- 10.1.11 J_c , value, kJ/m^2 .

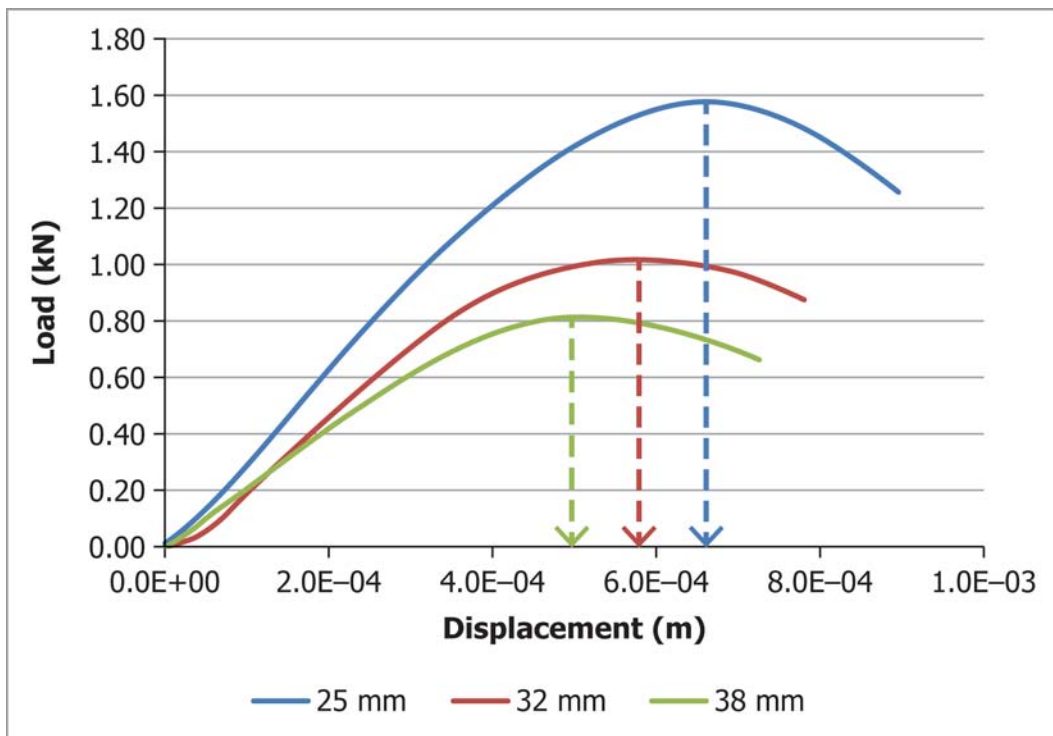


FIG. 3 Load Versus Displacement Plots for Each Notch Depth

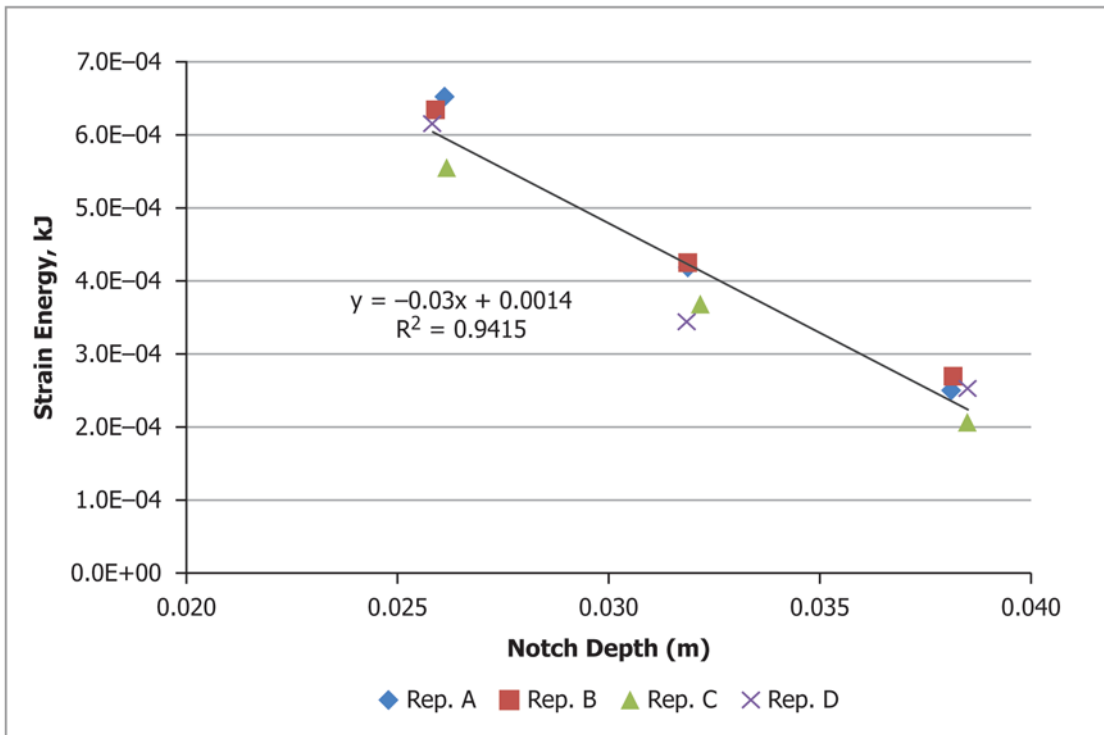


FIG. 4 Example of Notch Depth Versus Strain Energy Plot Used to Determine (dU/da)

11. Precision and Bias

11.1 The within-laboratory COV repeatability has been estimated to be 9.9 %, based on 2 labs, 27 test replicates, and 2 different samples. The between-laboratory COV reproducibility of this test method is being determined and will be available on or before June 2020. Therefore, this Test Method should not be used for acceptance or rejection of a material for purchasing purposes.

12. Keywords

12.1 asphalt intermediate temperature performance grade; asphalt mixture cracking resistance; semi-circular bend test

ASTM International takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.

This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.

This standard is copyrighted by ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (www.astm.org). Permission rights to photocopy the standard may also be secured from the Copyright Clearance Center, 222 Rosewood Drive, Danvers, MA 01923, Tel: (978) 646-2600; http://www.copyright.com/