



# Standard Guide for Material Selection and Fabrication of Reference Blocks for the Pulsed Longitudinal Wave Ultrasonic Testing of Metal and Metal Alloy Production Material<sup>1</sup>

This standard is issued under the fixed designation E1158; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon ( $\epsilon$ ) indicates an editorial change since the last revision or reapproval.

## 1. Scope\*

1.1 This guide covers general procedures for the material selection and fabrication of reference blocks made of metal or metal alloys and intended to be used for the examination of the same or similar production materials by pulsed longitudinal ultrasonic waves applied perpendicular to the beam entry surface. Primary emphasis is on solid materials but some of the techniques described may be used for midwall examination of pipes and tubes of heavy wall thickness. Near-surface resolution in any material depends upon the characteristics of the instrument and search unit employed.

1.2 This guide covers the fabrication of reference blocks for use with either the immersion or the contact method of ultrasonic examination.

1.3 Reference blocks fabricated in accordance with this guide can be used to determine proper ultrasonic system operation. Area-amplitude and distance-amplitude curves can also be determined with these reference blocks.

1.4 This guide does not specify reference reflector sizes or product rejection limits. It does describe typical industry fabrication practices and commonly applied tolerances where they lend clarity to the guide. In all cases of conflict between this guide and customer specifications, the customer specification shall prevail.

1.5 The values stated in inch-pound units are to be regarded as standard. The values given in parentheses are mathematical conversions to SI units that are provided for information only and are not considered standard.

1.6 *This standard does not purport to address the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and to determine the applicability of regulatory limitations prior to use.*

<sup>1</sup> This guide is under the jurisdiction of ASTM Committee E07 on Nondestructive Testing and is the direct responsibility of Subcommittee E07.06 on Ultrasonic Method.

Current edition approved June 1, 2014. Published July 2014. Originally approved in 1990. Last previous edition approved in 2009 as E1158 - 09. DOI: 10.1520/E1158-14.

## 2. Referenced Documents

### 2.1 ASTM Standards:<sup>2</sup>

E127 Practice for Fabricating and Checking Aluminum Alloy Ultrasonic Standard Reference Blocks<sup>3</sup>

E428 Practice for Fabrication and Control of Metal, Other than Aluminum, Reference Blocks Used in Ultrasonic Testing

E1316 Terminology for Nondestructive Examinations

## 3. Terminology

3.1 *Definitions*—For definitions of terms used in this guide, see Terminology E1316.

## 4. Summary of Guide

4.1 This guide describes a method of selecting suitable reference block material from current or previous production and the subsequent fabrication and checking of the resulting ultrasonic reference blocks.

## 5. Significance and Use

5.1 This guide is intended to illustrate the fabrication of ultrasonic reference blocks that are representative of the production material to be examined. Care in material selection and fabrication can result in the manufacture of reference blocks that are ultrasonically similar to the production material thus eliminating the reference block as an examination variable.

## 6. Material Selection

6.1 It is good practice to use a sample removed from the production lot of material as the reference block material. When this is not possible the following guidelines should be followed.

<sup>2</sup> For referenced ASTM standards, visit the ASTM website, [www.astm.org](http://www.astm.org), or contact ASTM Customer Service at [service@astm.org](mailto:service@astm.org). For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

<sup>3</sup> The reference blocks in Practice E127 are used to check the performance of ultrasonic examination equipment and for standardization and control of ultrasonic examinations of aluminum alloy products. The ultrasonic response of the blocks in Practice E127 is evaluated against a standard target. The blocks described in this standard are used for the examination of production material and may be used to establish accept-reject criteria.

\*A Summary of Changes section appears at the end of this standard

6.2 The reference block material should be of the same general shape and dimensions, surface finish, chemical composition, and microstructure as the production material to be examined.

6.3 To ensure that the material chosen is suitable for use as reference block material and is free of potentially interfering reflectors, ultrasonically examine the reference block material at the anticipated frequency and at a sensitivity that produces an acoustic noise level of 20 % screen height. The entire block should be scanned from the surface which will be used for standardization. Any discrete indication that exceeds 40 % screen height should be cause to remove the material from consideration as an ultrasonic reference block.


6.4 Reference block material that meets the guidelines of 6.3 should then be examined at a sensitivity that produces multiple reflections from the back surface (between 3 and 5 reflections in most metals and metal alloys). The production material should be examined at the same sensitivity level to determine that the same number of back reflections are obtained. This procedure may have to be repeated several times and an average number of back reflections determined in the case of some materials (see Note 1).

NOTE 1—In some highly attenuative materials more than one or two back reflections may not be attainable. In these cases, selection of the reference block material may be based on similar acoustic noise levels from both the production material and that chosen for a reference block.

7. Reference Block Configuration


7.1 There are many different types of reference blocks used in industry depending upon the size and shape of the material to be examined. Some of the more common flat bottom hole (FBH) types are described in 7.2 through 7.7, and shown in Figs. 1-7. An alternate method for fabricating FBH's is described in the annex.

7.2 Fig. 1 shows the typical reference standards used for ultrasonic examination when the product to be examined consists of large round bar stock, between 1 to 10 in. (25.4 to 245.0 mm) in diameter. With such products it is often necessary to correct for the loss of signal with increasing examination distance (distance-amplitude-correction, or DAC). Therefore, a stepped block, as shown in Fig. 1 is commonly used. This type of block is typically referred to as a distance-amplitude-block. It contains a number of holes of the same size at various distances from the scan surface. A typical FBH size found in many such blocks is 5/64 in. (1.98 mm) or larger depending

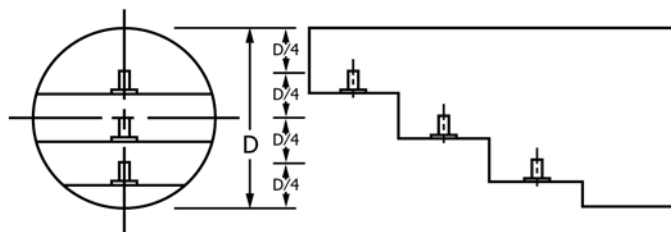


NOTE 1—All holes are the same diameter.

FIG. 1 Typical Distance-Amplitude Reference Block Configuration for the Ultrasonic Testing of Large Metal and Metal Alloy Bars from 1 to 10 in. (25.4 to 254.0 mm) Diameter and Larger

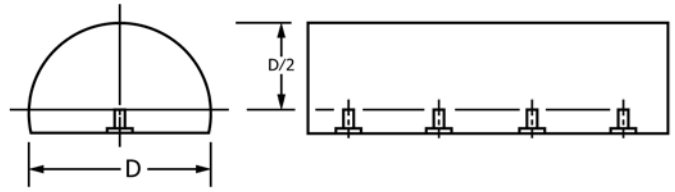


NOTE 1—Holes are of different diameters.

FIG. 2 Typical Area-Amplitude Reference Block for use in Ultrasonic Testing of Round Bars as in Fig. 1

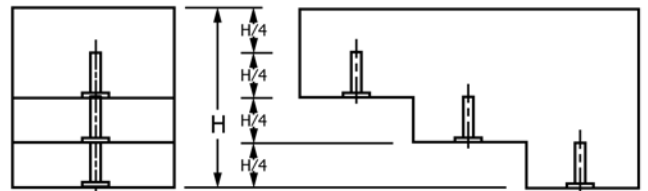

NOTE 1—All holes are the same diameter.

FIG. 3 Typical Distance-Amplitude Reference Block for the Ultrasonic Testing of Large Square or Rectangular Bars Greater than 1 in. (25.4 mm)



NOTE 1—Holes are of different diameters.

FIG. 4 Typical Area-Amplitude Reference Block for the Ultrasonic Testing of Square or Rectangular Bars


upon the ultrasonic attenuation, or the internal structure of the product, or both. For even larger diameter bars the distance amplitude correction reference standard may contain even larger FBH's, possibly 1/4 in. (6.35 mm) or greater.

7.3 To determine the linearity of the examination and to establish the quality level of the large-diameter product, (7.2), an area-amplitude reference block as shown in Fig. 2 is common. An area-amplitude-block contains holes of different cross-sectional areas placed at the same distance from the scan surface. Typical hole sizes range from between 3/64 and 5/64 in. (0.79 and 3.18 mm) with even larger flat-bottom holes used in reference blocks intended for use for the largest bars.

7.4 For small round bar stock, typically 1 in. (25.4 mm) and under, a distance-amplitude block is normally not required. The typical area-amplitude block for this product is the same as for the larger diameter material as shown in Fig. 2, but on a smaller scale. The hole sizes typically range from between 3/64 and 5/64 in. (0.79 and 1.98 mm) for many metal and metal alloy products.


7.5 When the product to be examined consists of large square or rectangular bar stock, the distance-amplitude reference block is often of the type shown in Fig. 3. The typical area-amplitude reference block is shown in Fig. 4. The reference block hole sizes are typically the same as those used for similar thickness round bars.

7.6 The smaller sizes of square or rectangular bar stock, 1 in. (25.4 mm) and under in the direction of examination, often

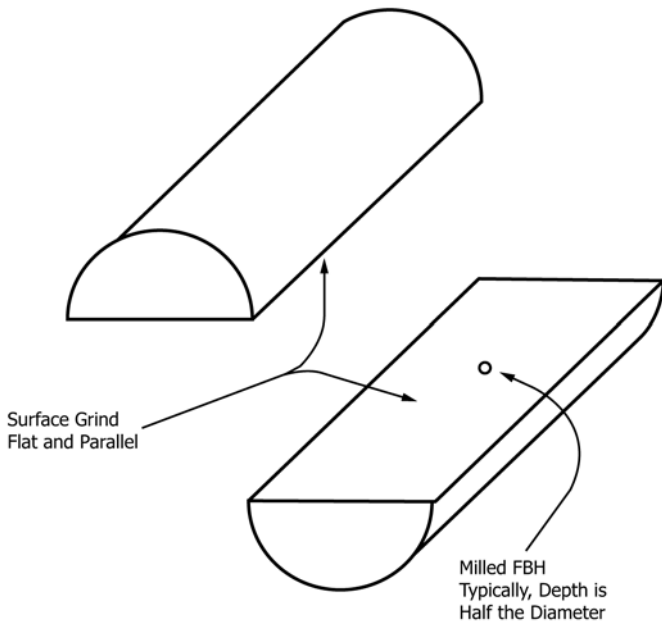

NOTE 1—The finish and fitup of the mating surfaces strongly influence the success of the bond.

FIG. 5 Typical Example of a Diffusion Bonded Reference Block for Small Diameter Round Bars

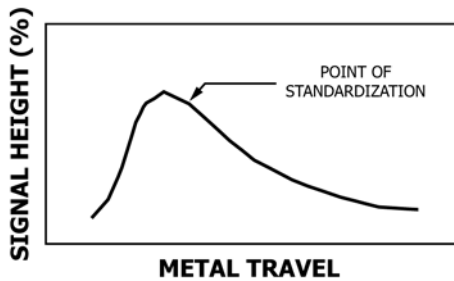

NOTE 1—The shape of the curve may differ as discussed in 10.1.  
FIG. 6 Typical Distance-Amplitude Ultrasonic Response Curve

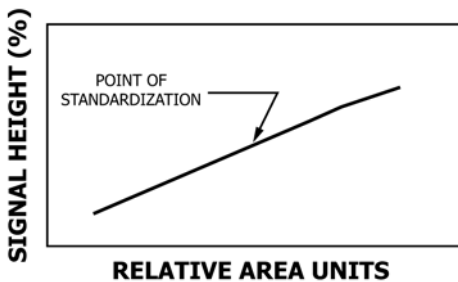


FIG. 7 Typical Area-Amplitude Ultrasonic Response Curve

## 8. Fabrication Procedure

8.1 Specific fabricating procedures are dependent upon the configuration of the reference block, the block composition, the examination criticality, and even the skill of the machinists. Some general guidelines are given in 8.2 through 8.3.2.

8.2 *Flat-Bottom Holes*—FBH's should be drilled such that the hole bottom is perpendicular to the examining sound beam. For the fabrication of reference standards of the types shown in Figs. 1-4, a common procedure involves the drilling of the chosen hole diameters to a desired depth using a conventional fluted drill bit. In Fig. 1 this depth would be  $\frac{3}{4}$  in. (19.05 mm). The fluted drill bit, or another of the same size, is carefully ground to remove the point and square the tip. An optical comparator or tool maker's microscope is useful to determine when the point has been completely removed and the drill bit end is flat and square.

8.2.1 The flattened drill bit is then used to carefully flatten the bottom of the drilled hole. This operation normally requires great care to avoid drill breakage while still ensuring that the hole bottom is flat. A physician's ear examination microscope with a tip of the proper diameter is helpful in determining when the hole bottom is truly flat.

8.2.2 If the ultrasonic examination is to be conducted with the product (and therefore the reference block) immersed in a liquid, it is considered good practice to plug the holes in the reference block. Before plugging the holes it is important that the holes be free of debris and totally dry. Moisture, metal shavings, or both, can influence the ultrasonic response from the hole bottom.

8.2.3 When using metal plugs, counter bores are machined in the block to seat the plugs. An alternative method is to use plastic or rubber type sealant forced a short distance into the holes and allowed to harden.

8.3 *Diffusion Bonding Method*—The diffusion bonding technique offers an alternative method of reference block manufacture. With this method it is possible to fabricate reference blocks containing flat disc-shaped ultrasonic reflectors instead of FBH's. In many cases this permits the examination of the reference block from more than one direction thus enhancing the utility of the block.

8.3.1 A typical example is shown in Fig. 5. A diffusion-bonded reference block for small diameter rounds could be fabricated as shown. A section is removed from one of the round bars to be examined. The bar section is split lengthwise and both split surfaces are carefully ground. An end mill of the desired diameter is used to mill a shallow (typically  $\frac{1}{2}$  the hole diameter in depth) FBH in one of the split sections. The sections are then bonded back together using the diffusion bonding process. (The application of heat and pressure on the two sections for a period of time results in a sound diffusion bond which is indistinguishable ultrasonically from the normal structure.) (See Note 2.) The result is a reference standard that can be examined from either of 2 sides.

NOTE 2—The time, temperature, and pressure requirements for a

do not require the use of a distance-amplitude reference block. The area-amplitude block may be similar to that shown in Fig. 4. The reference block hole sizes are usually similar to those used for round bars of the same thickness.

7.7 The reference blocks used for the ultrasonic examination of products with more complex geometries are normally fabricated from production samples so that the effects of geometry variations are minimized.

diffusion bond are both material and configuration dependent and therefore are beyond the scope of this guide. The American Welding Society<sup>4</sup> can furnish information on the subject.

8.3.2 With developed skills, all of the reference blocks shown in Figs. 1-4 along with many more types can be successfully fabricated using the diffusion bonding technique.

## 9. Verification of Reflector Acceptability

9.1 It is often desirable or required by specification, or both, that the FBH's be proven to be of the proper size and flatness. A hole replication method is often used to measure these hole characteristics. This method, more often used for holes of  $\frac{3}{64}$  in. (1.19 mm) or greater diameter, involves forcing a liquid rubber or plastic compound into the clean, dry FBH hole, removing all entrapped air. When the material hardens it can be removed in the form of a plug or replica. This plug or hole replica can then be examined for the proper size and flatness. The removal of the hardened plug is facilitated if a small wire or other object is inserted into the hole while the replicating material is still liquid. When the replicating material solidifies the wire serves as a handle permitting easy removal of the plug.

9.2 Replication of the disc-shaped reflector in diffusion bonded reference blocks is not possible. An alternative method

<sup>4</sup> Available from American Welding Society (AWS), 550 NW LeJeune Rd., Miami, FL 33126, <http://www.aws.org>.

of determining whether the reflector has been distorted by the bonding process is to fabricate a second block under identical conditions for destructive examination at the conclusion of the process.

## 10. Ultrasonic Response Characteristics

10.1 If the fabrication procedure, either drilling or diffusion bonding, was sufficiently accurate, then the distance amplitude reference block set may yield an ultrasonic response curve similar to that shown in Fig. 6. The shape of the curve may differ significantly with any change of test frequency, search unit diameter, couplant method or water path length. The procedure used to obtain distance-amplitude curves for flat-entry-surface cylindrical FBH reference blocks is described in Practice E428.

10.2 An area-amplitude block set should yield a plot similar to that shown in Fig. 7. The shape of the curve may differ significantly and depends on examination frequency, search unit diameter, couplant method, and water path length. The procedure for obtaining this curve for flat-entry-surface cylindrical FBH reference blocks is also presented in Practice E428.

## 11. Keywords

11.1 area-amplitude; diffusion bonding; distance-amplitude; flat-bottom hole; material selection; nondestructive testing; reference block; response curve; ultrasonic examination

## APPENDIX

### (Nonmandatory Information)

#### X1. ALTERNATE METHOD FOR FABRICATION OF DEEP FLAT- BOTTOM HOLES

##### X1.1 Introduction

X1.1.1 This annex describes a method for fabricating deep FBH's that can be simpler, faster and less expensive than those used to fabricate the blocks shown in Figs. 1-5. A pilot hole is used to locate and position the FBH thus eliminating the milling of the steps show in Figs. 1-5. This allows the bar circumference to remain for support during standardization which is much more representative to production material. This alternate method also results in an added advantage for mechanical examination of moving material by allowing signals from the reference block to be more easily evaluated dynamically as the block is moved at the maximum scanning rate.

##### X1.2 Description of Method

X1.2.1 The alternate method is simply to use a larger pilot drill to produce a hole to within a short distance of the depth of the FBH. The body and bottoming drills for the FBH are then successively mounted in a holder of the same diameter as the pilot drill for the final drilling and flattening operations. This helps to insure that the flat bottom of the final hole will be parallel to a tangent of the top surface at a point immediately above the hole. This is due to the increased stiffness of the pilot

drill and the holder being much greater than that of the smaller final drills. That prevents skewing of the final holes that could result from deep drilling of a small hole due to excess drilling speed or pressure or to grain anomalies or small hardness variations in the material that might deflect smaller drills if used for the total distance.

X1.2.2 The size of a typical pilot hole used for this purpose is 0.375 in. (9.53 mm). The pilot hole is typically drilled to within approximately 0.50 in. (12.7 mm) of the final desired FBH depth. After the FBH is drilled, cleaned and verified the entrance to the pilot hole must be sealed to prevent the entry of couplant or other foreign material.

##### X1.3 Use on Cylindrical Material

X1.3.1 Fig. X1.1 shows cross sectional views of a FBH placed in the center of a round bar by this method.

X1.3.2 For standardization of a system for examination of cylindrical material the bottom of the FBH fabricated in accordance with this procedure at any depth in the material may be used for "static" standardization (that is, with no relative motion between standard and search unit). "Dynamic" standardization is performed with rotary and translational motion between standard and search unit at the maximum

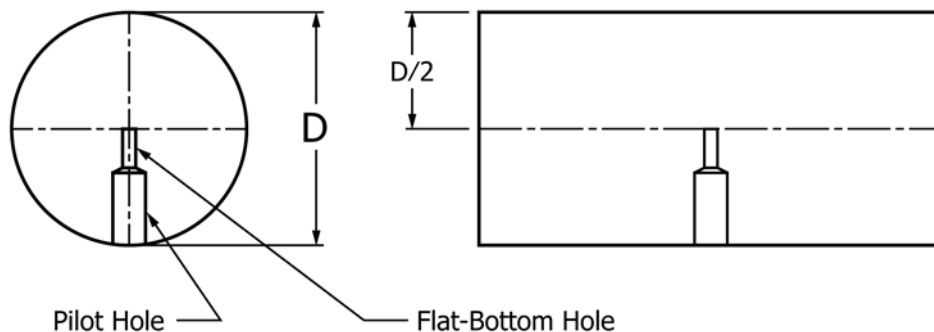


FIG. X1.1 Flat-Bottom Hole Placed at the Center of a Round Bar by This Method

speeds to be used for the final examination. In this case the instrument alarm gate may be set to be activated by the signal from any FBH drilled to a depth of less than a radius of the

material while not responding to signals from the sides of the pilot or FBH drills as they enter the beam from the search unit.

### SUMMARY OF CHANGES

Committee E07 has identified the location of selected changes to this standard since the last issue (E1158-09) that may impact the use of this standard.

(1) Annex was changed to an Appendix to reflect non-mandatory nature of the information.

*ASTM International takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.*

*This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.*

*This standard is copyrighted by ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (www.astm.org). Permission rights to photocopy the standard may also be secured from the Copyright Clearance Center, 222 Rosewood Drive, Danvers, MA 01923, Tel: (978) 646-2600; http://www.copyright.com/*