



Standard Test Method for Determining the Shear Strength of the Bond between a Surface Mount Device (SMD) and Substrate in a Membrane Switch¹

This standard is issued under the fixed designation F1995; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

1. Scope

1.1 This test method covers the determination of the shear integrity of materials and procedures used to attach surface mount devices (SMD) to a membrane switch circuit.

1.2 This test method is typically used to indicate the sufficient cure of conductive adhesive or underfill, or both. In general, this test method should be used prior to encapsulation. This test may also be used to demonstrate the Shear Force with encapsulation.

1.3 The values stated in SI units are to be regarded as standard. No other units of measurement are included in this standard.

1.4 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

2. Terminology

2.1 Definitions:

2.1.1 *membrane switch*—A momentary switching device in which at least one contact is on (or made of) a flexible substrate.

2.1.2 *shear load*—A force applied parallel to the mounting surface sufficient to shear the SMD from its mounting.

2.1.3 *SMD*—Abbreviation for surface mount device (for example, light emitting diode (LED), resistor)

2.1.4 *attachment media*—A mounting adhesive used for electrical or mechanical bonding, or both, of the SMD to the substrate.

2.1.5 *plating*—A thin metallic coating (that is, gold, nickel) covering the leads of the SMD or circuit, or both, in the electrical interface area.

¹ This test method is under the jurisdiction of ASTM Committee F01 on Electronics and is the direct responsibility of Subcommittee F01.18 on Membrane Switches.

Current edition approved May 1, 2013. Published June 2013. Originally approved in 1999. Last previous edition approved in 2012 as F1995–12. DOI: 10.1520/F1995-13.

3. Significance and Use

3.1 The different combinations of SMD types, attachment medias, circuit substrates, plating options, and process variation can account for significant variation in test outcome.

3.2 The SMD shear strength test is useful to manufacturers and users for determining the bond strength of the component to the membrane switch circuit.

4. Interferences

4.1 The following parameters may affect the results of this test:

- 4.1.1 Temperature and humidity, and
- 4.1.2 Substrate movement during test.

5. Apparatus

5.1 *Device*, shall consist of a load-applying instrument with an accuracy of $\pm 5\%$ of full scale capable of indicating peak hold.

5.2 *Mounting Fixture*, method to secure specimen to insure stability during test.

5.3 *SMD Contact Tool*, suitable to apply a uniform distribution of force to an edge of the SMD.

5.4 *Magnification Device*, suitable to facilitate visual observation of the SMD and contact tool interface during testing (optional).

6. Procedure

6.1 Pretest Setup:

6.1.1 Attach specimen to the test base to minimize movement of the substrate during test. Ensure that no damage occurs during attachment to the test base that could affect bond performance.

6.1.2 The direction of applied force shall be parallel with the plane of the circuit substrate.

6.1.3 The SMD contact tool shall load against an edge of the component, which most closely approximates a 90° angle with the base of the circuit substrate. Contact tool should make contact to SMD at a point equal to or less than $\frac{1}{2}$ the total SMD height, (see Fig. 1).

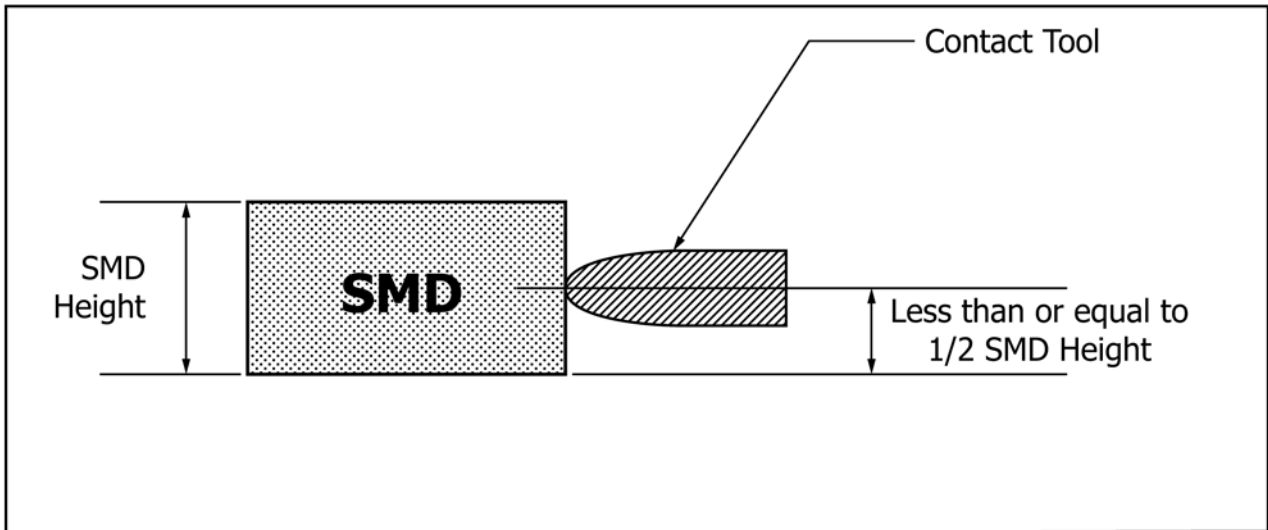


FIG. 1 SMD Contact

6.2 *In-Process Test:*

- 6.2.1 Bring contact tool into contact with SMD specimen.
- 6.2.2 Gradually increase force, not to exceed 225 g/s, until bond failure.
- 6.2.3 After initial contact with the SMD edge and during the application of force, the relative position of the contact tool shall not move such that contact is made with the circuit plane or SMD attachment media. If the tool rides over the SMD, a new specimen shall be substituted.
- 6.2.4 Record force measured to shear SMD.

7. Report

- 7.1 Report the following information:
 - 7.1.1 Temperature.
 - 7.1.2 Humidity.
 - 7.1.3 Shape and size of contact tool.
 - 7.1.4 Orientation of SMD to contact tool.
 - 7.1.5 SMD information: SMD part number, plating type, etc.

- 7.1.6 Circuit or substrate type.
- 7.1.7 Attachment media type.
- 7.1.8 Force applied by contact tool when bond failure occurred.
- 7.1.9 SMD size.
- 7.1.10 Type of encapsulant used.

8. Precision and Bias

- 8.1 *Precision*—It is not possible to specify the precision of the procedure in Test Method F1995 for measuring Shear Force because the test is destructive allowing only limited repeatability in comparison testing.
- 8.2 *Bias*—No information can be presented on the bias of the procedure in F1995 for measuring Shear Force because no standard sample is available for this industry.

9. Keywords

- 9.1 adhesion; bond strength; LED; membrane switch; shear force; SMD; surface mount

ASTM International takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.

This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.

This standard is copyrighted by ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (www.astm.org). Permission rights to photocopy the standard may also be secured from the Copyright Clearance Center, 222 Rosewood Drive, Danvers, MA 01923, Tel: (978) 646-2600; http://www.copyright.com/