

BS EN ISO 527-1:2012



BSI Standards Publication

Plastics — Determination of tensile properties

Part 1: General principles

NO COPYING WITHOUT BSI PERMISSION EXCEPT AS PERMITTED BY COPYRIGHT LAW

raising standards worldwide™



National foreword

This British Standard is the UK implementation of . It supersedes BS EN ISO 527-1:1996 which is withdrawn.

The UK participation in its preparation was entrusted to Technical Committee PRI/21, Testing of plastics.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© The British Standards Institution 2012. Published by BSI Standards Limited 2012

ISBN 978 0 580 70622 6

ICS 83.080.01

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 31 March 2012.

Amendments issued since publication

| Date | Text affected |
|------|---------------|
|------|---------------|

EUROPEAN STANDARD

EN ISO 527-1

NORME EUROPÉENNE

EUROPÄISCHE NORM

February 2012

ICS 83.080.01

Supersedes EN ISO 527-1:1996

English Version

Plastics - Determination of tensile properties - Part 1: General principles (ISO 527-1:2012)

Plastiques - Détermination des propriétés en traction -
Partie 1: Principes généraux (ISO 527-1:2012)

Kunststoffe - Bestimmung der Zugeigenschaften - Teil 1:
Allgemeine Grundsätze (ISO 527-1:2012)

This European Standard was approved by CEN on 14 February 2012.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN-CENELEC Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

Management Centre: Avenue Marnix 17, B-1000 Brussels

Foreword

This document (EN ISO 527-1:2012) has been prepared by Technical Committee ISO/TC 61 "Plastics" in collaboration with Technical Committee CEN/TC 249 "Plastics" the secretariat of which is held by NBN.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by August 2012, and conflicting national standards shall be withdrawn at the latest by August 2012.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN [and/or CENELEC] shall not be held responsible for identifying any or all such patent rights.

This document supersedes EN ISO 527-1:1996.

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and the United Kingdom.

Endorsement notice

The text of ISO 527-1:2012 has been approved by CEN as a EN ISO 527-1:2012 without any modification.

Contents

Page

| | |
|--|-----------|
| Foreword | iv |
| 1 Scope | 1 |
| 2 Normative references | 1 |
| 3 Terms and definitions | 2 |
| 4 Principle and methods | 5 |
| 4.1 Principle | 5 |
| 4.2 Method | 6 |
| 5 Apparatus | 6 |
| 5.1 Testing machine | 6 |
| 5.2 Devices for measuring width and thickness of the test specimens | 9 |
| 6 Test specimens | 9 |
| 6.1 Shape and dimensions | 9 |
| 6.2 Preparation of specimens | 9 |
| 6.3 Gauge marks | 10 |
| 6.4 Checking the test specimens | 10 |
| 6.5 Anisotropy | 10 |
| 7 Number of test specimens | 10 |
| 8 Conditioning | 11 |
| 9 Procedure | 11 |
| 9.1 Test atmosphere | 11 |
| 9.2 Dimensions of test specimen | 11 |
| 9.3 Gripping | 11 |
| 9.4 Prestresses | 12 |
| 9.5 Setting of extensometers | 12 |
| 9.6 Test speed | 12 |
| 9.7 Recording of data | 13 |
| 10 Calculation and expression of results | 13 |
| 10.1 Stress | 13 |
| 10.2 Strain | 13 |
| 10.3 Tensile modulus | 14 |
| 10.4 Poisson's ratio | 15 |
| 10.5 Statistical parameters | 16 |
| 10.6 Significant figures | 16 |
| 11 Precision | 16 |
| 12 Test report | 16 |
| Annex A (informative) Determination of strain at yield | 18 |
| Annex B (informative) Extensometer accuracy for the determination of Poisson's ratio | 20 |
| Annex C (normative) Calibration requirements for the determination of the tensile modulus | 21 |
| Bibliography | 23 |

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 527-1 was prepared by Technical Committee ISO/TC 61, *Plastics*, Subcommittee SC 2, *Mechanical properties*.

This second edition cancels and replaces the first edition (ISO 527-1:1993), which has been technically revised. It incorporates ISO 527-1:1993/Cor 1:1994 and ISO 527-1:1993/Amd 1:2005. The main changes are as follows.

- A method for the determination of Poisson's ratio has been introduced. It is similar to the one used in ASTM D638, but in order to overcome difficulties with precision of the determination of the lateral contraction at small values of the longitudinal strain, the strain interval is extended far beyond the strain region for the modulus determination.
- Definitions and methods have been optimized for computer controlled tensile test machines.
- The preferred gauge length for use on the multipurpose test specimen has been increased from 50 mm to 75 mm. This is used especially in ISO 527-2.
- Nominal strain and especially nominal strain at break will be determined relative to the gripping distance. Nominal strain in general will be calculated as crosshead displacement from the beginning of the test, relative to the gripping distance, or as the preferred method if multipurpose test specimens are used, where strains up to the yield point are determined using an extensometer, as the sum of yield strain and nominal strain increment after the yield point, the latter also relative to the gripping distance.

ISO 527 consists of the following parts, under the general title *Plastics — Determination of tensile properties*:

- *Part 1: General principles*
- *Part 2: Test conditions for moulding and extrusion plastics*
- *Part 3: Test conditions for films and sheets*
- *Part 4: Test conditions for isotropic and orthotropic fibre-reinforced plastic composites*
- *Part 5: Test conditions for unidirectional fibre-reinforced plastic composites*

Plastics — Determination of tensile properties —

Part 1: General principles

1 Scope

1.1 This part of ISO 527 specifies the general principles for determining the tensile properties of plastics and plastic composites under defined conditions. Several different types of test specimen are defined to suit different types of material which are detailed in subsequent parts of ISO 527.

1.2 The methods are used to investigate the tensile behaviour of the test specimens and for determining the tensile strength, tensile modulus and other aspects of the tensile stress/strain relationship under the conditions defined.

1.3 The methods are selectively suitable for use with the following materials:

- rigid and semi-rigid (see 3.12 and 3.13, respectively) moulding, extrusion and cast thermoplastic materials, including filled and reinforced compounds in addition to unfilled types; rigid and semi-rigid thermoplastics sheets and films;
- rigid and semi-rigid thermosetting moulding materials, including filled and reinforced compounds; rigid and semi-rigid thermosetting sheets, including laminates;
- fibre-reinforced thermosets and thermoplastic composites incorporating unidirectional or non-unidirectional reinforcements, such as mat, woven fabrics, woven rovings, chopped strands, combination and hybrid reinforcement, rovings and milled fibres; sheet made from pre-impregnated materials (prepregs),
- thermotropic liquid crystal polymers.

The methods are not normally suitable for use with rigid cellular materials, for which ISO 1926 is used, or for sandwich structures containing cellular materials.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 291, *Plastics — Standard atmospheres for conditioning and testing*

ISO 2602, *Statistical interpretation of test results — Estimation of the mean — Confidence interval*

ISO 7500-1:2004, *Metallic materials — Verification of static uniaxial testing machines — Part 1: Tension/compression testing machines — Verification and calibration of the force-measuring system*

ISO 9513:1999, *Metallic materials — Calibration of extensometers used in uniaxial testing*

ISO 16012, *Plastics — Determination of linear dimensions of test specimens*

ISO 20753, *Plastics — Test specimens*

ISO 23529, *Rubber — General procedures for preparing and conditioning test pieces for physical test methods*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

3.1 gauge length

L_0
initial distance between the gauge marks on the central part of the test specimen

NOTE 1 It is expressed in millimetres (mm).

NOTE 2 The values of the gauge length that are indicated for the specimen types in the different parts of ISO 527 represent the relevant maximum gauge length.

3.2 thickness

h
smaller initial dimension of the rectangular cross-section in the central part of a test specimen

NOTE It is expressed in millimetres (mm).

3.3 width

b
larger initial dimension of the rectangular cross-section in the central part of a test specimen

NOTE It is expressed in millimetres (mm).

3.4 cross-section

A
product of initial width and thickness, $A = bh$, of a test specimen.

NOTE It is expressed in square millimetres, (mm²)

3.5 test speed

v
rate of separation of the gripping jaws

NOTE It is expressed in millimetres per minute (mm/min).

3.6 stress

σ
normal force per unit area of the original cross-section within the gauge length

NOTE 1 It is expressed in megapascals (MPa)

NOTE 2 In order to differentiate from the true stress related to the actual cross-section of the specimen, this stress is frequently called "engineering stress"

3.6.1 stress at yield

σ_y
stress at the yield strain

NOTE 1 It is expressed in megapascals (MPa).

NOTE 2 It may be less than the maximum attainable stress (see Figure 1, curves b and c)

3.6.2 strength

σ_m
stress at the first local maximum observed during a tensile test

NOTE 1 It is expressed in megapascals (MPa).

NOTE 2 This may also be the stress at which the specimen yields or breaks (see Figure 1).

3.6.3 stress at x % strain

σ_x
stress at which the strain reaches the specified value x expressed as a percentage

NOTE 1 It is expressed in megapascals (MPa).

NOTE 2 Stress at x % strain may, for example, be useful if the stress/strain curve does not exhibit a yield point (see Figure 1, curve d).

3.6.4 stress at break

σ_b
stress at which the specimen breaks

NOTE 1 It is expressed in megapascals (MPa).

NOTE 2 It is the highest value of stress on the stress-strain curve directly prior to the separation of the specimen, i.e. directly prior to the load drop caused by crack initiation.

3.7 strain

ε
increase in length per unit original length of the gauge.

NOTE It is expressed as a dimensionless ratio, or as a percentage (%).

3.7.1 strain at yield yield strain

ε_y
the first occurrence in a tensile test of strain increase without a stress increase

NOTE 1 It is expressed as a dimensionless ratio, or as a percentage (%).

NOTE 2 See Figure 1, curves b and c.

NOTE 3 See Annex A (informative) for computer-controlled determination of the yield strain.

3.7.2 strain at break

ε_b
strain at the last recorded data point before the stress is reduced to less than or equal to 10 % of the strength if the break occurs prior to yielding

NOTE 1 It is expressed as a dimensionless ratio, or as a percentage (%).

NOTE 2 See Figure 1, curves a and d.

3.7.3 strain at strength

ε_m
strain at which the strength is reached

NOTE It is expressed as a dimensionless ratio, or as a percentage (%).

3.8 nominal strain

ε_t
crosshead displacement divided by the gripping distance

NOTE 1 It is expressed as a dimensionless ratio, or as a percentage (%).

NOTE 2 It is used for strains beyond the yield strain (see 3.7.1) or where no extensometers are used.

NOTE 3 It may be calculated based on the crosshead displacement from the beginning of the test, or based on the increment of crosshead displacement beyond the strain at yield, if the latter is determined with an extensometer (preferred for multipurpose test specimens).

3.8.1 nominal strain at break

ε_{tb}
nominal strain at the last recorded data point before the stress is reduced to less than or equal to 10 % of the strength if the break occurs after yielding

NOTE 1 It is expressed as a dimensionless ratio, or as a percentage (%).

NOTE 2 See Figure 1, curves b and c.

3.9 modulus

E_t
slope of the stress/strain curve $\sigma(\varepsilon)$ in the strain interval between $\varepsilon_1 = 0,05$ % and $\varepsilon_2 = 0,25$ %

NOTE 1 It is expressed in megapascals (MPa).

NOTE 2 It may be calculated either as the chord modulus or as the slope of a linear least-squares regression line in this interval (see Figure 1, curve d).

NOTE 3 This definition does not apply to films.

3.10 Poisson's ratio

μ
negative ratio of the strain increment $\Delta\varepsilon_n$, in one of the two axes normal to the direction of extension, to the corresponding strain increment $\Delta\varepsilon_l$ in the direction of extension, within the linear portion of the longitudinal versus normal strain curve

NOTE It is expressed as a dimensionless ratio.

3.11 gripping distance

L
initial length of the part of the specimen between the grips

NOTE It is expressed in millimetres (mm).

3.12 rigid plastic

plastic that has a modulus of elasticity in flexure (or, if that is not applicable, in tension) greater than 700 MPa under a given set of conditions

3.13 semi-rigid plastic

plastic that has a modulus of elasticity in flexure (or, if that is not applicable, in tension) between 70 MPa and 700 MPa under a given set of conditions

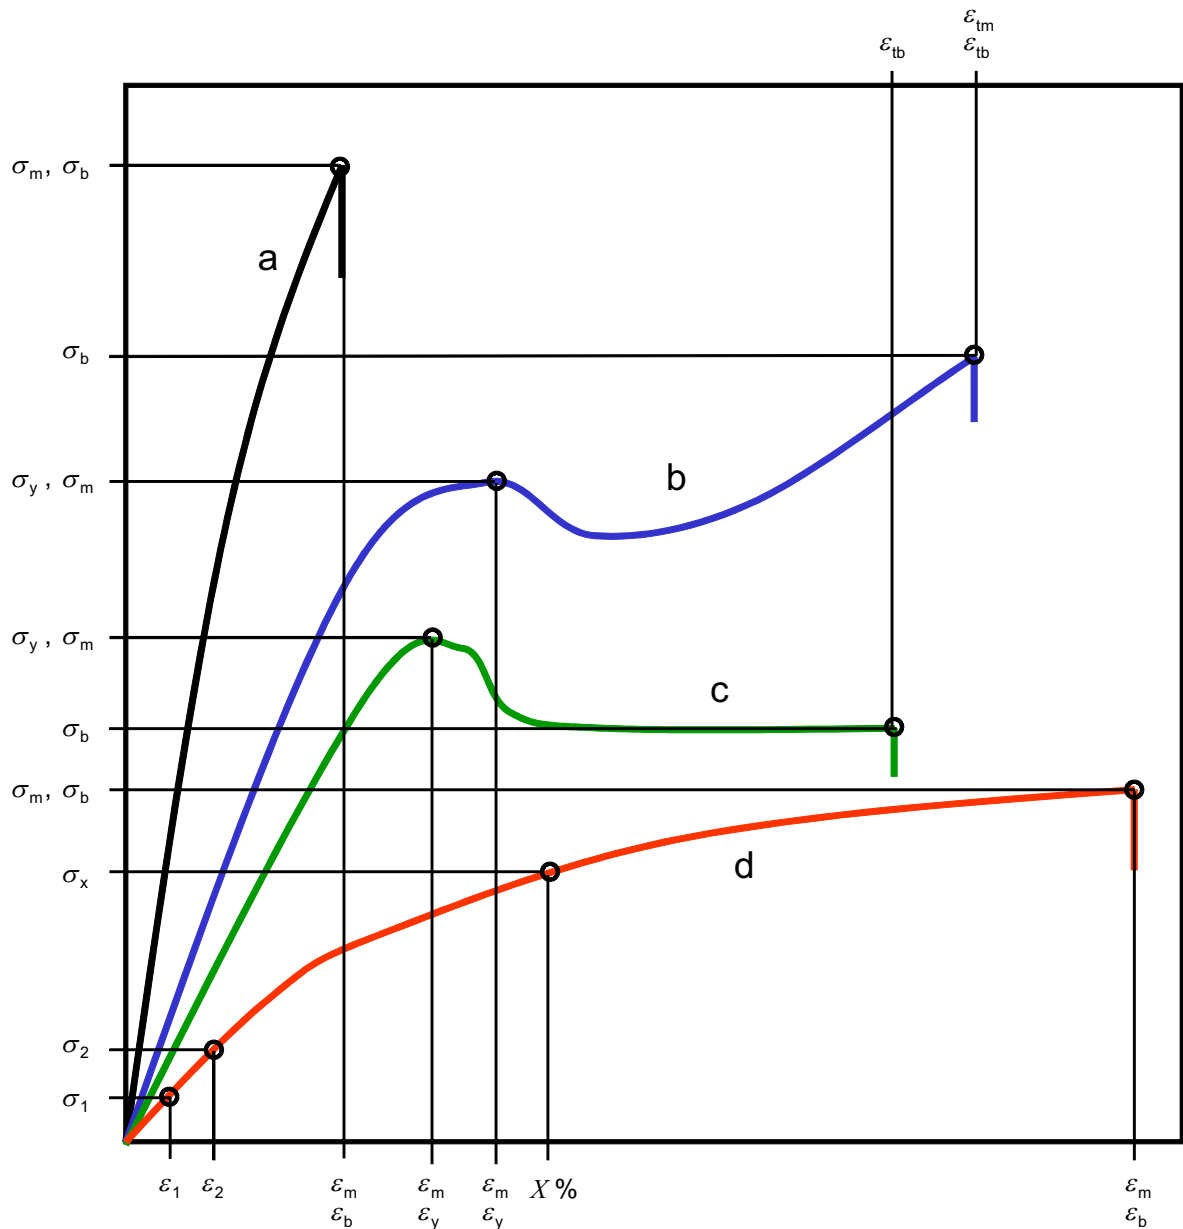


Figure 1 — Typical stress/strain curves

NOTE Curve (a) represents a brittle material, breaking without yielding at low strains. Curve (d) represents a soft rubberlike material breaking at larger strains (>50 %).

4 Principle and methods

4.1 Principle

The test specimen is extended along its major longitudinal axis at a constant speed until the specimen fractures or until the stress (load) or the strain (elongation) reaches some predetermined value. During this procedure, the load sustained by the specimen and the elongation are measured.

4.2 Method

4.2.1 The methods are applied using specimens which may be either moulded to the chosen dimensions or machined, cut or punched from finished and semi-finished products, such as mouldings, laminates, films and extruded or cast sheet. The types of test specimen and their preparation are described in the relevant part of ISO 527 typical for the material. In some cases, a multipurpose test specimen may be used. Multipurpose and miniaturized test specimens are described in ISO 20753.

4.2.2 The methods specify preferred dimensions for the test specimens. Tests which are carried out on specimens of different dimensions, or on specimens which are prepared under different conditions, may produce results which are not comparable. Other factors, such as the speed of testing and the conditioning of the specimens, can also influence the results. Consequently, when comparative data are required, these factors shall be carefully controlled and recorded.

5 Apparatus

5.1 Testing machine

5.1.1 General

The machine shall comply with ISO 7500-1 and ISO 9513, and meet the specifications given in 5.1.2 to 5.1.6, as follows.

5.1.2 Test speeds

The tensile-testing machine shall be capable of maintaining the test speeds as specified in Table 1.

Table 1 — Recommended test speeds

| Test speed v mm/min | Tolerance % |
|-----------------------------|----------------|
| 0,125 | ±20 |
| 0,25 | |
| 0,5 | |
| 1 | |
| 2 | |
| 5 | |
| 10 | ±10 |
| 20 | |
| 50 | |
| 100 | |
| 200 | |
| 300 | |
| 500 | |

5.1.3 Grips

Grips for holding the test specimen shall be attached to the machine so that the major axis of the test specimen coincides with the direction of extension through the centre line of the grip assembly. The test specimen shall be held such that slip relative to the gripping jaws is prevented. The gripping system shall not cause premature fracture at the jaws or squashing of the specimen in the grips.

For the determination of the tensile modulus, it is essential that the strain rate is constant and does not change, for example, due to motion in the grips. This is important especially if wedge action grips are used.

NOTE For the prestress, which might be necessary to obtain correct alignment (see 9.3) and specimen seating and to avoid a toe region at the start of the stress/strain diagram, see 9.4.

5.1.4 Force indicator

The force measurement system shall comply with class 1 as defined in ISO 7500-1:2004.

5.1.5 Strain indicator

5.1.5.1 Extensometers

Contact extensometers shall comply with ISO 9513:1999, class 1. The accuracy of this class shall be attained in the strain range over which measurements are being made. Non-contact extensometers may also be used, provided they meet the same accuracy requirements.

The extensometer shall be capable of determining the change in the gauge length of the test specimen at any time during the test. It is desirable, but not essential, that the instrument should record this change automatically. The instrument shall be essentially free of inertia lag at the specified speed of testing.

For accurate determination of the tensile modulus E_t , an instrument capable of measuring the change of the gauge length with an accuracy of 1 % of the relevant value or better shall be used. When using test specimens of type 1A, this corresponds to a requirement of absolute accuracy of $\pm 1,5 \mu\text{m}$, for a gauge length of 75 mm. Smaller gauge lengths lead to different accuracy requirements, see Figure 2.

NOTE Depending on the gauge length used, the accuracy requirement of 1 % translates to different absolute accuracies for the determination of the elongation within the gauge length. For miniaturized specimens, these higher accuracies might not be attainable, due to lack of appropriate extensometers (see Figure 2)

Commonly used optical extensometers record the deformation taken at one broad test-specimen surface: In the case of such a single-sided strain-testing method, ensure that low strains are not falsified by bending, which may result from even faint misalignment and initial warpage of the test specimen, and which generates strain differences between opposite surfaces of the test specimen. It is recommended to use strain-measurement methods that average the strains of opposite sides of the test specimen. This is relevant for modulus determination, but less so for measurement of larger strains.

5.1.5.2 Strain gauges

Specimens may also be instrumented with longitudinal strain gauges; the accuracy of which shall be 1 % of the relevant value or better. This corresponds to a strain accuracy of 20×10^{-6} (20 microstrains) for the measurement of the modulus. The gauges, surface preparation and bonding agents should be chosen to exhibit adequate performance on the subject material

5.1.6 Recording of data

5.1.6.1 General

The data acquisition frequency needed for the recording of data (force, strain, elongation) must be sufficiently high in order to meet accuracy requirements.

5.1.6.2 Recording of strain data

The data acquisition frequency for recording of strain data depends on

- v the test speed, in mm/min;
- L_0/L the ratio between the gauge length and initial grip-to-grip separation;

- r the minimum resolution, in mm, of the strain signal required to obtain accurate data. Typically, it is half the accuracy value or better.

The minimum data acquisition frequency f_{\min} , in Hz, needed for integral transmission from the sensor to the indicator can then be calculated as:

$$f_{\min} = \frac{v}{60} \times \frac{L_0}{L \cdot r} \quad (1)$$

The recording frequency of the test machine shall be at least equal to this data rate f_{\min} .

5.1.6.3 Recording of force data

The required recording rate depends on the test speed, the strain range, the accuracy and the gripping distance. The modulus, the test speed and the gripping distance determine the rise rate of force. The ratio of rise rate of force to the accuracy needed determines the recording frequency. See below for examples.

Rise rate of force is given by:

$$\dot{F} = \frac{E \cdot A \cdot v}{60L} \quad (2)$$

where

- E is the Elastic Modulus, expressed in megapascals (MPa);
- A is the cross-sectional area of the test specimen, expressed in square millimetres (mm²);
- v is the test speed, expressed in millimetres per minute (mm/min);
- L is the gripping distance, expressed in millimetres (mm).

Using the force difference in the modulus range to define accuracy requirement in the same way as for the extensometer, the following equations apply, assuming that the relevant force is to be determined to within 1 %:

Force difference in modulus range:

$$\Delta F = E \cdot A \cdot (\varepsilon_2 - \varepsilon_1) = E \cdot A \cdot \Delta\varepsilon \quad (3)$$

Accuracy (half of 1 %):

$$r = 5 \times 10^{-3} \times \Delta F = 5 \times 10^{-3} \times E \cdot A \cdot \Delta\varepsilon \quad (4)$$

Recording frequency:

$$f_{\text{force}} = \frac{\dot{F}}{r} = \frac{E \cdot A \cdot v}{E \cdot A \cdot \Delta\varepsilon \times 60 \times L \times 5 \times 10^{-3}} \quad (5)$$

EXAMPLE:

With $v = 1$ mm/min, $\Delta\varepsilon = 2 \times 10^{-3}$ and $L = 115$ mm, a recording frequency of $f_{\text{force}} = 14,5$ Hz is found.

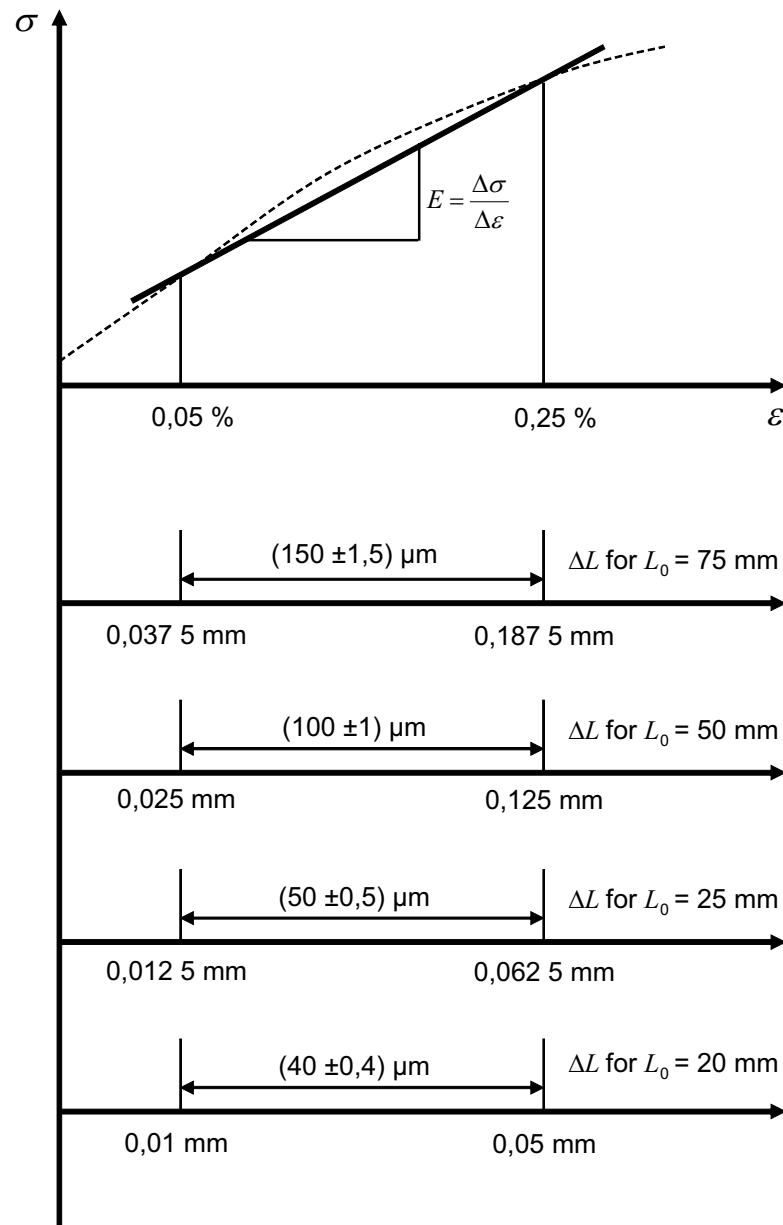


Figure 2 — Accuracy requirements for extensometers for modulus determination at different gauge lengths, assuming an accuracy of 1 %

5.2 Devices for measuring width and thickness of the test specimens

See ISO 16012 and ISO 23529, where applicable.

6 Test specimens

6.1 Shape and dimensions

See the part of ISO 527 relevant to the material being tested.

6.2 Preparation of specimens

See the part of ISO 527 relevant to the material being tested.

6.3 Gauge marks

See the appropriate part of ISO 527 for the relevant conditions of the gauge length.

If optical extensometers are used, especially for thin sheet and film, gauge marks on the specimen may be necessary to define the gauge length. These shall be equidistant from the midpoint (± 1 mm), and the gauge length shall be measured to an accuracy of 1 % or better.

Gauge marks shall not be scratched, punched or impressed upon the test specimen in any way that may damage the material being tested. It must be ensured that the marking medium has no detrimental effect on the material being tested and that, in the case of parallel lines, they are as narrow as possible.

6.4 Checking the test specimens


Ideally the specimens shall be free of twist and shall have mutually perpendicular pairs of parallel surfaces (see Note below). The surfaces and edges must be free from scratches, pits, sink marks and flash.

The specimens shall be checked for conformity with these requirements by visual observation against straight-edges, squares and flat plates, and with micrometer callipers.

Use measurement tips/knife edges of such size and orientation as to allow the precise determination of the dimension in the desired location.

Specimens showing observed or measured departure from one or more of these requirements shall be rejected. If non-conforming specimens have to be tested, report the reasons.

Injection-moulded specimens need draft angles of 1° to 2° to facilitate demoulding. Also, injection-moulded test specimens are never absolutely free of sink marks. Due to differences in the cooling history, generally the thickness in the centre of the specimen is smaller than at the edge. A thickness difference of $\Delta h \leq 0,1$ mm is considered to be acceptable (see Figure 3).

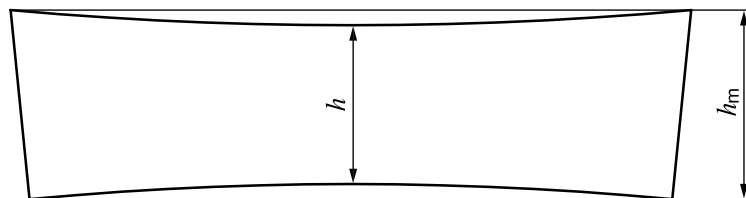

Key

h_m largest thickness of test specimen in this cross-section

h smallest thickness of test specimen in this cross-section

$\Delta h = h_m - h \leq 0,1$ mm

Figure 3 — Cross-section of injection-moulded test specimen with sink marks and draft angle (exaggerated)

NOTE ISO 294-1:1996, Annex D, gives guidance on how to reduce sink marks in injection-moulded test specimens.

6.5 Anisotropy

See the part of ISO 527 relevant to the material being tested.

7 Number of test specimens

7.1 A minimum of five test specimens shall be tested for each of the required directions of testing. The number of measurements may be more than five if greater precision of the mean value is required. It is possible to evaluate this by means of the confidence interval (95 % probability, see ISO 2602).

7.2 Dumb-bell specimens that break or slip inside the grips shall be discarded and further specimens shall be tested.

Data, however variable, shall not be excluded from the analysis for any other reason, as the variability in such data is a function of the variable nature of the material being tested.

8 Conditioning

The test specimen shall be conditioned as specified in the appropriate standard for the material concerned. In the absence of this information, the most appropriate set of conditions from ISO 291 shall be selected and the conditioning time is at least 16 h, unless otherwise agreed upon by the interested parties, for example, for testing at elevated or low temperatures.

The preferred atmosphere is $(23 \pm 2) ^\circ\text{C}$ and $(50 \pm 10) \% \text{ R.H.}$, except when the properties of the material are known to be insensitive to moisture, in which case humidity control is unnecessary.

9 Procedure

9.1 Test atmosphere

Conduct the test in the same atmosphere used for conditioning the test specimen, unless otherwise agreed upon by the interested parties, for example, for testing at elevated or low temperatures.

9.2 Dimensions of test specimen

Determine the dimensions of the test specimens in accordance with ISO 16012 or ISO 23529, as applicable.

Record the minimum and maximum values for width and thickness of each specimen at the centre of the specimen and within 5 mm of each end of the gauge length, and make sure that they are within the tolerances indicated in the standard applicable for the given material. Use the means of the measured widths and thicknesses to calculate the cross-section of the test specimen.

For injection-moulded test specimens, it is sufficient to determine the width and thickness within 5 mm of the centre of the specimen.

In the case of injection-moulded specimens, it is not necessary to measure the dimensions of each specimen. It is sufficient to measure one specimen from each lot to make sure that the dimensions correspond to the specimen type selected (see the relevant part of ISO 527). With multiple-cavity moulds, ensure that the dimensions of the specimens do not differ by more than $\pm 0,25 \%$ between cavities.

For test specimens cut from sheet or film material, it is permissible to assume that the mean width of the central parallel portion of the die is equivalent to the corresponding width of the specimen. The adoption of such a procedure should be based on comparative measurements taken at periodic intervals.

For the purposes of this part of ISO 527, the test specimen dimensions used for calculating tensile properties are measured at ambient temperature only. For the measurement of properties at other temperatures, therefore, the effects of thermal expansion are not taken into account.

9.3 Gripping

Place the test specimen in the grips, taking care to align the longitudinal axis of the test specimen with the axis of the testing machine. Tighten the grips evenly and firmly to avoid slippage of the test specimen and movement of the grips during the test. Gripping pressure shall not cause fracture or squashing of the test specimen (see Note 2).

NOTE 1 Stops can be used to facilitate alignment of the test specimen, especially in manual operation.

For gripping test specimens within a temperature chamber, it is recommended to close initially only one grip and to tighten the second one only after the temperature of the test specimen is equilibrated, unless the machine is capable of continuously reducing thermal stress if it arises.

NOTE 2 Fracture in the grips can happen, for example, when testing of specimens after heat aging. Squashing can occur in tests at elevated temperatures.

9.4 Prestresses

The specimen shall not be stressed substantially prior to testing. Such stresses can be generated during centring of a film specimen, or can be caused by the gripping pressure, especially with less rigid materials. They are, however necessary to avoid a toe region at the start of the stress/strain diagram (see 5.1.3). The prestress σ_0 at the start of a test shall be positive but shall not exceed the following value,

for modulus measurement:

$$0 < \sigma_0 \leq E_t/2000 \quad (6)$$

which corresponds to a prestrain of $\varepsilon_0 \leq 0,05$ %, and

for measuring relevant stresses σ^* , e.g. $\sigma^* = \sigma_y$ or σ_m :

$$0 < \sigma_0 \leq \sigma^*/100 \quad (7)$$

If, after gripping, stresses outside the intervals given by Equations (6) and (7) are present in the specimen, remove these by slow movement of the crosshead, e.g. with 1 mm/min, until the prestress is within the allowed range.

If the modulus or the stress value needed to adjust the prestress is not known, perform a preliminary test to obtain an estimate of these values.

9.5 Setting of extensometers

After setting the prestress, set and adjust a calibrated extensometer to the gauge length of the test specimen, or provide longitudinal strain gauges, in accordance with 5.1.5. Measure the initial distance (gauge length) if necessary. For the measurement of Poisson's ratio, two elongation- or strain-measuring devices shall be provided to act in the longitudinal and transverse axes simultaneously.

For optical measurements of elongation, place gauge marks on the specimen in accordance with 6.3, if required by the system used.

Extensometers shall be positioned symmetrically about the middle of the parallel portion and on the centre line of the test specimen. Strain gauges shall be placed in the middle of the parallel portion and on the centre line of the test specimen.

9.6 Test speed

Set the test speed in accordance with the appropriate standard for the material concerned. In the absence of this information, the test speed shall be selected from Table 1 or agreed upon between the interested parties.

For the measurement of the tensile modulus, the selected test speed shall provide a strain rate as near as possible to 1% of the gauge length per minute. The resulting testing speed for different types of specimens is given in the part of ISO 527 that is relevant to the material being tested.

It may be necessary or desirable to adopt different speeds for the determination of the tensile modulus, of the stress/strain diagram up to the yield point, and of properties beyond the yield point. After determining stresses for the tensile modulus determination (up to the strain of $\varepsilon_2 = 0,25$ %), the same test specimen can be used to continue the test.

It is preferable to unload the test specimen before testing at a different speed, but it is also acceptable to change the speed without unloading after the tensile modulus has been determined. When changing the speed during the test, make sure that the change in speed occurs at strains $\varepsilon \leq 0,3 \%$.

For any other testing purposes, separate specimens shall be used for different test speeds.

9.7 Recording of data

Preferably record the force and the corresponding values of the increase of the gauge length and of the distance between the grips during the test. This requires three data channels for data acquisition. If only two channels are available, record the force signal and the extensometer signal. It is preferable to use an automatic recording system.

10 Calculation and expression of results

10.1 Stress

Calculate all stress values, defined in 3.6, using the following equation:

$$\sigma = \frac{F}{A} \quad (8)$$

where

σ is the stress value in question, expressed in megapascals (MPa);

F is the measured force concerned, expressed in newtons (N);

A is the initial cross-sectional area of the specimen, expressed in square millimetres (mm²).

When determining stress at $x \%$ strain, x shall be taken from the relevant product standard or agreed upon by the interested parties.

10.2 Strain

10.2.1 Strains determined with an extensometer

For materials and/or test conditions for which a homogeneous strain distribution is prevalent in the parallel section of the test specimen, i.e. for strains prior and up to a yield point, calculate all strain values, defined in 3.7, using the following equation:

$$\varepsilon = \frac{\Delta L_0}{L_0} \quad (9)$$

where

ε is the strain value in question, expressed as a dimensionless ratio, or as a percentage;

L_0 is the gauge length of the test specimen, expressed in millimetres (mm);

ΔL_0 is the increase of the specimen length between the gauge marks, expressed in millimetres (mm).

The determination of strain values using an extensometer averages strains over the gauge length. This is correct and useful, as long as the deformation of the test specimen within the gauge length is homogeneous. If the material starts necking, the strain distribution becomes inhomogeneous and strains determined with an extensometer are strongly influenced by the position and size of the neck zone. In such cases, use nominal strain to describe the strain evolution after a yield point.

10.2.2 Nominal strain

10.2.2.1 General

Nominal strain is used when no extensometer is used, for example, on miniaturized test specimens or when strain determination with extensometers becomes meaningless due to strain localisation (necking) after a yield point. Nominal strain is based on the increase of distance between the grips relative to the initial gripping distance. Instead of measuring the displacement between the grips, it is acceptable to record crosshead displacement. Crosshead displacement shall be corrected for effects of machine compliance.

Nominal strain may be determined using the following two methods.

10.2.2.2 Method A

Record the displacement between the grips of the machine from the beginning of the test. Calculate nominal strain by:

$$\varepsilon_t = \frac{L_t}{L} \quad (10)$$

where

- ε_t is the nominal strain, expressed as a dimensionless ratio or percentage;
- L is the gripping distance, expressed in millimetres (mm); the gripping distance is defined in the relevant parts of ISO 527;
- L_t is the increase of the gripping distance occurring from the beginning of the test, expressed in millimetres (mm).

10.2.2.3 Method B

Method B is preferred for use with multipurpose test specimens that show yielding and necking, but where the strain at yield has been precisely determined with an extensometer. Record the displacement between the grips of the machine from the beginning of the test. Calculate nominal strain by:

$$\varepsilon_t = \varepsilon_y + \frac{\Delta L_t}{L} \quad (11)$$

where

- ε_t is the nominal strain, expressed as a dimensionless ratio or percentage;
- ε_y is the yield strain, expressed as a dimensionless ratio or percentage;
- L is the gripping distance, expressed in millimetres (mm); the gripping distance is defined in the relevant parts of ISO 527;
- ΔL_t is the increase of the gripping distance from the yield point onwards, expressed in millimetres (mm).

10.3 Tensile modulus

10.3.1 General

Calculate the tensile modulus, defined in 3.9, using one of the following alternatives.

10.3.2 Chord slope

$$E_t = \frac{\sigma_2 - \sigma_1}{\varepsilon_2 - \varepsilon_1} \quad (12)$$

where

E_t is the tensile modulus, expressed in megapascals (MPa);

σ_1 is the stress, expressed in megapascals (MPa), measured at the strain value $\varepsilon_1 = 0,000\ 5$ (0,05 %);

σ_2 is the stress, expressed in megapascals (MPa), measured at the strain value $\varepsilon_2 = 0,002\ 5$ (0,25 %).

10.3.3 Regression slope

With computer-aided equipment, the determination of the tensile modulus E_t using two distinct stress/strain points can be replaced by a linear regression procedure applied on the part of the curve between these mentioned points.

$$E = \frac{d\sigma}{d\varepsilon} \quad (13)$$

where $\frac{d\sigma}{d\varepsilon}$ is the slope of a least-squares regression line fit to the part of the stress/strain curve in the strain interval $0,000\ 5 \leq \varepsilon \leq 0,002\ 5$, expressed in megapascals (MPa).

10.4 Poisson's ratio

Plot the width or thickness of the specimen as a function of the length of the gauge section for the part of the stress/strain curve before a yield point, if present, and excluding those sections that may be influenced by changes in test speed.

Determine the slope $\Delta n/\Delta L_0$ of the change-in-width (thickness) versus the change-in-gauge-length curve. This slope shall be calculated by using a linear least-squares regression analysis between two limits, preferably after the modulus region and an ensuing speed change, if applicable, that are in a linear portion of this curve. Poisson's ratio is determined from the following equation:

$$\mu = -\frac{\Delta\varepsilon_n}{\Delta\varepsilon_l} = -\frac{L_0}{n_0} \frac{\Delta n}{\Delta L_0} \quad (14)$$

where

μ is Poisson's ratio; it is dimensionless;

$\Delta\varepsilon_n$ is the strain decrease in the selected transverse direction, while the longitudinal strain increases by $\Delta\varepsilon_l$, expressed as a dimensionless ratio or percentage;

$\Delta\varepsilon_l$ is the strain increase in the longitudinal direction, a dimensionless ratio or percentage;

L_0, n_0 are the initial gauge lengths in the longitudinal and transverse directions, respectively, expressed in millimetres (mm);

Δn is the decrease of the specimen gauge length in the transverse direction: $n = b$ (width) or $n = h$ (thickness), expressed in millimetres (mm);

ΔL_0 is the corresponding increase of the gauge length in the longitudinal direction, expressed in millimetres (mm).

Poisson's ratio is indicated as μ_b (width direction) or μ_h (thickness direction) according to the relevant axis.

It is recommended to determine Poisson's ratio at higher strains, in a strain range $0,3\ \% \leq \varepsilon < \varepsilon_y$ (See Annex B). The validity of the evaluation region can be determined from a plot of Δn vs. ΔL_0 , (dimension change in

transverse direction vs. dimension change in longitudinal direction). Poisson's ratio is determined from the slope of the linear part of this plot.

NOTE Plastics are viscoelastic materials. As such, Poisson's ratio is dependent on the stress range where it is determined. Therefore, the width (thickness) as a function of length might not be a straight line.

10.5 Statistical parameters

Calculate the arithmetic means of the test results and, if required, the standard deviations and the 95 % confidence intervals of the mean values in accordance with the procedure given in ISO 2602.

10.6 Significant figures

Calculate the stresses and the tensile modulus to three significant figures. Calculate the strains and Poisson's ratio to two significant figures.

11 Precision

See the part of ISO 527 relevant to the material being tested.

12 Test report

The test report shall include the information specified in Items a) to q). Add the word "tensile" to individual and average properties, see Items m), n) and o):

- a) a reference to the relevant part of ISO 527;
- b) all the data necessary for identification of the material tested, including type, source, manufacturer's code number and history, where these are known;
- c) description of the nature and form of the material in terms of whether it is a product, semi-finished product, test panel or specimen; it should include the principal dimensions, shape, method of manufacture, succession of layers and any pretreatment;
- d) type of test specimen; the width and thickness of the parallel section, including mean, minimum and maximum values;
- e) method of preparing the test specimens, and any details of the manufacturing method used;
- f) if the material is in product form or semi-finished product form, the orientation of the specimen in relation to the product or semi-finished product from which it is cut;
- g) number of the test specimen tested;
- h) standard atmosphere for conditioning and testing, plus any special conditioning treatment, if required by the relevant standard for the material or product concerned;
- i) accuracy grading of the test machine and extensometer (see ISO 7500-1, ISO 9513 and 5.1.5);
- j) type of elongation or strain indicator, and the gauge length L_0 ;
- k) type of gripping device, the gripping distance L ;
- l) testing speeds;
- m) individual test results of the properties defined in Clause 3;
- n) mean value(s) of the measured property(ies), quoted as the indicative value(s) for the material tested;
- o) standard deviation, and/or coefficient of variation, and/or confidence limits of the mean, if required;

- p) statement as to whether any test specimens have been rejected and replaced, and, if so, the reasons, and reasons for testing non-conforming specimens.;
- q) date of measurement.

Annex A (informative)

Determination of strain at yield

Historically, strain at yield was determined by drawing a horizontal tangent to a continuously recorded stress-strain curve. With the advent of computer-controlled machines, the evaluation of stress/strain curves had to use a set of discrete data points sampled according to the properties of the recording electronics. Due to signal noise (electronic as well as mechanical), there is always some scatter in the data set available and this has to be taken into account when deriving properties.

For the determination of the yield point, the following items are important.

- Plastic materials show a wide range of different stress/strain behaviours. The yielding region may be a narrow peak (e.g. for ASA) or a wide plateau (e.g. POM, moist PA6).
- Determination of the strain at yield involves identifying the highest data point within the yielding region (necessary condition).
- However, the point selected must be physically meaningful: Signal noise may cause selection of unsuitable points.
- The point must allow meaningful design decisions. For example, for a material showing a yielding plateau, a useful design limit would be close to its beginning rather than in the centre.

Determining such points from digital data can be done by different methods.

- Point-to-point comparison for a maximum value. This is a simple procedure, but it needs additional checks to prevent selecting noise-related maximum values erroneously. This may, for example, involve employing a moving evaluation interval, the width of which will be system dependent. System in this sense means the combined effects of material behaviour and experimental set-up.
- Slope method: This would be a method involving a higher amount of calculation, but feasible within the computing power provided by current PCs. A slope criterion would also involve a moving evaluation interval within which the regression slope of the stress/strain curve is calculated. This method has a smoothing / filtering effect and reduces noise influence. Additionally, a criterion must be defined for which slope would be indicative of having found a yield point, for example:
 - Centre-point of the evaluation interval for which the slope becomes negative for the first time.
 - Centre-point of the evaluation interval for which the slope attains some limiting positive value for the first time. The working draft for the previous revision of this part of ISO 527 proposed the following criterion, applied to the centre-point of a moving interval, for which the slope becomes equal to or smaller than the stress value at this point:

$$\varepsilon_y = \varepsilon \left[\frac{d\sigma}{d\varepsilon} \leq \sigma \right] \quad (\text{A.1})$$

- The advantage of such a criterion would be to identify only such yield strains that are close to the first major slope change of the stress/strain curve. Yield strain values, however, would be smaller than with the current methods. This method is less useful for broad yielding peaks.
- Also, for a slope method, the correct width of the evaluation interval is again system dependent and identifying it requires the user to have a thorough understanding of the test method and the material.

These examples show that there are multiple ways to determine strain at yield. Selecting and imposing one of them for the sake of comparability of test results would, in principle, be possible but, considering existing machines and the different software packages, this would be a futile attempt.

One solution could be a verification system. This verification system would involve reference data sets (stress/strain curves) for which the relevant properties are agreed on by experts. These data sets can be fed to any evaluation software and used to check whether, or under which parameters, the software returns the “correct values”. This system would ensure comparability of test results while allowing different evaluation procedures.

A similar system for tensile testing of metals was worked out. More information on this may be found under:

<http://www.npl.co.uk/server.php?show=ConWebDoc.2886>.

For the estimation of the width of strain intervals, the following equations can be used.


$$n = f \Delta t = f \frac{\Delta \varepsilon}{\dot{\varepsilon}}$$

$$\Delta \varepsilon = \dot{\varepsilon} \frac{n}{f} = \frac{v}{60L} \frac{n60L}{vL_0} \frac{r}{L_0} = \frac{nr}{L_0}$$
(A.2)

where

- n is the number of data points;
- f is the data rate of the machine, see Equation (1), in s^{-1} ;
- $\Delta \varepsilon$ is the strain interval;
- $\dot{\varepsilon}$ is the strain rate, in s^{-1} ;
- v is the crosshead rate, in mm/min;
- L is the gripping distance, in mm;
- L_0 is the gauge length, in mm;
- r is the resolution, in mm.

The strain interval according to Equation (A.2) is shown in Figure A.1 as a function of the number of data points with the resolution r as parameter.

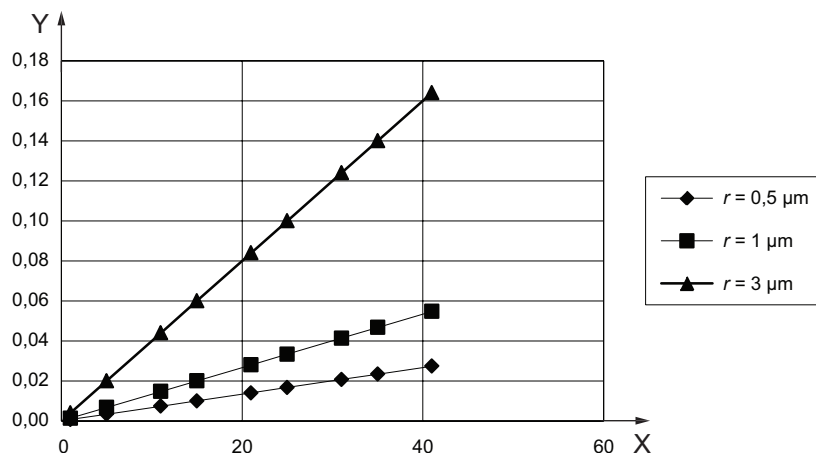

Key

- X number of data points
- Y strain interval, %

Figure A.1 — Strain interval according to Equation (A.2)

Annex B (informative)

Extensometer accuracy for the determination of Poisson's ratio

It is not recommended to determine Poisson's ratio in the strain region used for the modulus determination.

In the modulus region, the elongation of the gauge length is determined with an accuracy of 1 %, i.e. using a multipurpose test specimen, the extensometer must be capable of measuring the elongation to within 1,5 µm (see 5.1.5 and Figure 2) when a gauge length of 75 mm is used. Assuming a Poisson's ratio of 0,4, which is typical for most thermoplastics, and a gauge length of 75 mm, the length of the gauge section increases by 150 µm while the width decreases by 8 µm. In order to have the same relative accuracy of 1% as for the longitudinal direction, the measurement system for determining the transverse deformation should be capable of measuring within 0,1 µm, which is a severe condition.

Assuming that Poisson's ratio is determined in a range of $0,3 \% < \varepsilon < 1,5 \%$, the decrease in width will be 50 µm, requiring a resolution of 0,5 µm for a 1 % accuracy in lateral contraction.

Annex C (normative)

Calibration requirements for the determination of the tensile modulus

C.1 General

The general requirements for extensometer verification are described in 5.1.5. If the equipment is intended to perform measurements of tensile modulus E_t , the extensometer must satisfy an additional, more stringent, accuracy requirement. This annex specifies the procedures used and the performance of the calibration equipment required to verify that the extensometer meets this additional accuracy requirement.

NOTE All references to specific paragraphs refer to ISO 9513: 1999. The structure of later versions will be subject to alterations.

C.2 Calibration procedure

C.2.1 General

It is expected that the additional verification will take place at the same time as the verification to ISO 9513; however, the verification can be carried out independently. Unless otherwise stated, the conditions of calibration shall be the same as described in ISO 9513.

Perform the procedure described in 5.5.1 of ISO 9513:1999 to prepare the system for the verification.

Follow the procedure described in 5.5.2 of ISO 9513:1999, using two, additional, measurements, in the increasing travel direction corresponding to 0,05 % and 0,25 % of the required gauge length (see Table B.1 of ISO 9513:1999). The average value of the difference between the two readings from two runs shall then be compared to the difference in the applied displacements. In order to comply with the requirements of this part of ISO 527, the relative error between the applied displacement and the indicated displacement shall be less than or equal to ± 1 % of the displacement for gauge lengths of 50 mm or above or less than or equal to ± 1 μm for gauge lengths less than 50 mm.

Table C.1 — Extensometer accuracy requirements

| Gauge length mm | First displacement μm | Second displacement μm | Change in displacement μm | Accuracy requirement (see 5.1.5) $\pm\mu\text{m}$ |
|--------------------|-------------------------------------|--------------------------------------|--|--|
| 75 | 37,5 | 187,5 | 150 | 1,5 |
| 50 | 25 | 125 | 100 | 1 |
| 25 | 12,5 | 62,5 | 50 | 1 |
| 20 | 10 | 50 | 40 | 1 |

NOTE The extensometer error limits apply to the change in reading between the first and second displacement.

Because of the difficulty in achieving the extensometer performance required at gauge lengths below 50 mm, it is recommended that modulus measurements are made on specimens with gauge lengths of 50 mm and greater.

C.2.2 Calibration-apparatus accuracy requirements

The calibration apparatus shall conform to the requirements given in ISO 9513:1999, Table 2, for class 0,2.

C.2.3 Calibration report

The calibration report shall contain the following information:

- a) a reference to this annex of this part of ISO 527 (i.e. ISO 527-1:2012, Annex C);
- b) the name and address of the owner of the extensometer system;
- c) all other information required to be reported in ISO 9513;
- d) the result of the calibration.

Bibliography

- [1] ISO 294-1:1996, *Plastics — Injection moulding of test specimens of thermoplastic materials — Part 1: General principles, and moulding of multipurpose and bar test specimens*
- [2] ISO 1926, *Rigid cellular plastics — Determination of tensile properties*
- [3] ASTM D638, *Standard Test Method for Tensile Properties of Plastics*

British Standards Institution (BSI)

BSI is the independent national body responsible for preparing British Standards and other standards-related publications, information and services. It presents the UK view on standards in Europe and at the international level.

BSI is incorporated by Royal Charter. British Standards and other standardisation products are published by BSI Standards Limited.

Revisions

British Standards and PASs are periodically updated by amendment or revision. Users of British Standards and PASs should make sure that they possess the latest amendments or editions.

It is the constant aim of BSI to improve the quality of our products and services. We would be grateful if anyone finding an inaccuracy or ambiguity while using British Standards would inform the Secretary of the technical committee responsible, the identity of which can be found on the inside front cover. Similar for PASs, please notify BSI Customer Services.

Tel: +44 (0)20 8996 9001 Fax: +44 (0)20 8996 7001

BSI offers BSI Subscribing Members an individual updating service called PLUS which ensures that subscribers automatically receive the latest editions of British Standards and PASs.

Tel: +44 (0)20 8996 7669 Fax: +44 (0)20 8996 7001

Email: plus@bsigroup.com

Buying standards

You may buy PDF and hard copy versions of standards directly using a credit card from the BSI Shop on the website www.bsigroup.com/shop. In addition all orders for BSI, international and foreign standards publications can be addressed to BSI Customer Services.

Tel: +44 (0)20 8996 9001 Fax: +44 (0)20 8996 7001

Email: orders@bsigroup.com

In response to orders for international standards, BSI will supply the British Standard implementation of the relevant international standard, unless otherwise requested.

Information on standards

BSI provides a wide range of information on national, European and international standards through its Knowledge Centre.

Tel: +44 (0)20 8996 7004 Fax: +44 (0)20 8996 7005

Email: knowledgecentre@bsigroup.com

BSI Subscribing Members are kept up to date with standards developments and receive substantial discounts on the purchase price of standards. For details of these and other benefits contact Membership Administration.

Tel: +44 (0)20 8996 7002 Fax: +44 (0)20 8996 7001

Email: membership@bsigroup.com

Information regarding online access to British Standards and PASs via British Standards Online can be found at www.bsigroup.com/BSOL

Further information about British Standards is available on the BSI website at www.bsi-group.com/standards

Copyright

All the data, software and documentation set out in all British Standards and other BSI publications are the property of and copyrighted by BSI, or some person or entity that own copyright in the information used (such as the international standardisation bodies) has formally licensed such information to BSI for commercial publication and use. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI. This does not preclude the free use, in the course of implementing the standard, of necessary details such as symbols, and size, type or grade designations. If these details are to be used for any other purpose than implementation then the prior written permission of BSI must be obtained. Details and advice can be obtained from the Copyright & Licensing Department.

Tel: +44 (0)20 8996 7070

Email: copyright@bsigroup.com

BSI

389 Chiswick High Road London W4 4AL UK

Tel +44 (0)20 8996 9001

Fax +44 (0)20 8996 7001

www.bsigroup.com/standards