

# Microstructure of cast irons

## Part 1: Graphite classification by visual analysis (ISO 945-1:2008)

ICS 77.080.10; 77.140.80

## National foreword

This British Standard is the UK implementation of EN ISO 945-1:2008. It supersedes BS EN ISO 945:1994 which is withdrawn.

The UK participation in its preparation was entrusted to Technical Committee ISE/35, Cast iron.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

**Compliance with a British Standard cannot confer immunity from legal obligations.**

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 31 December 2008

© BSI 2008

ISBN 978 0 580 55522 0

### Amendments/corrigenda issued since publication

Date	Comments

English Version

**Microstructure of cast irons - Part 1: Graphite classification by  
visual analysis (ISO 945-1:2008)**

Microstructure des fontes - Partie 1: Classification du  
graphite par analyse visuelle (ISO 945-1:2008)

Mikrostruktur von Gusseisen - Teil 1: Graphitklassifizierung  
durch visuelle Auswertung (ISO 945-1:2008)

This European Standard was approved by CEN on 1 November 2008.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION  
COMITÉ EUROPÉEN DE NORMALISATION  
EUROPÄISCHES KOMITEE FÜR NORMUNG

**Management Centre: rue de Stassart, 36 B-1050 Brussels**

## Foreword

This document (EN ISO 945-1:2008) has been prepared by Technical Committee ISO/TC 25 "Cast iron and pig iron" in collaboration with Technical Committee CEN/TC 190 "Foundry technology", the secretariat of which is held by DIN.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by May 2009, and conflicting national standards shall be withdrawn at the latest by May 2009.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN [and/or CENELEC] shall not be held responsible for identifying any or all such patent rights.

This document supersedes EN ISO 945:1994.

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland and the United Kingdom.

### Endorsement notice

The text of ISO 945-1:2008 has been approved by CEN as EN ISO 945-1:2008 without any modification.

## Contents

Page

Foreword.....	iv
Introduction .....	v
<b>1 Scope .....</b>	<b>1</b>
<b>2 General.....</b>	<b>1</b>
2.1 Designation system for classifying graphite in cast irons.....	1
2.2 Visual classification of graphite.....	9
<b>3 Sampling and preparation of samples.....</b>	<b>10</b>
3.1 Samples taken from a casting .....	10
3.2 Sample preparation .....	10
<b>4 Procedure for graphite classification .....</b>	<b>10</b>
4.1 Procedure for visual classification of graphite .....	10
4.2 Evaluation of the analysis results.....	10
<b>5 Reference images .....</b>	<b>11</b>
5.1 General.....	11
5.2 Reference images for graphite form .....	11
5.3 Reference images for the distribution of graphite (form I).....	11
5.4 Reference images for graphite size .....	11
<b>6 Designation of graphite by form, distribution and size .....</b>	<b>11</b>
6.1 Designation system .....	11
6.2 Designation of intermediate graphite sizes .....	12
6.3 Designation of mixed graphite forms, distributions and sizes.....	12
6.4 Nodule count .....	13
<b>7 Report .....</b>	<b>13</b>
<b>Annex A (informative) Typical graphite forms in cast-iron materials (Examples of photomicrographs)....</b>	<b>15</b>
<b>Annex B (informative) Distribution of flake (lamellar) graphite (form I) (Examples of photomicrographs).....</b>	<b>16</b>
<b>Annex C (informative) Common terminology and main occurrences concerning graphite in cast irons .....</b>	<b>17</b>
<b>Bibliography .....</b>	<b>19</b>

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 945-1 was prepared by Technical Committee ISO/TC 25, *Cast irons and pig irons*.

Together with ISO 945-2, this first edition of ISO 945-1 cancels and replaces ISO 945:1975, which has been technically revised to take into account the expanding range of cast-iron alloys available. In addition, photomicrographs have been included together with schematic images to aid classification.

ISO 945 consists of the following parts, under the general title *Microstructure of cast irons*:

— *Part 1: Graphite classification by visual analysis*

Graphite classification by image analysis will be the subject of a future Part 2.

## **Introduction**

Microstructure designation is a useful feature that provides a means of classifying the graphite form, distribution and size in cast irons.

Graphite classification by visual analysis is a well-established method which is well recognized within the foundry industry as a means of quickly determining the overall graphite microstructure of a cast-iron casting.





# Microstructure of cast irons —

## Part 1: Graphite classification by visual analysis

### 1 Scope

This part of ISO 945 specifies a method of classifying the microstructure of graphite in cast irons by comparative visual analysis.

The purpose of this part of ISO 945 is to provide information about the method of graphite classification. It is not intended to give information on the suitability of cast-iron types and grades for any particular application.

The particular material grade is specified by results from tensile tests or hardness testing and, in the case of austenitic cast irons, by their chemical composition. The interpretation of graphite form and size does not allow a statistically valid statement on the fulfilment of the requirements specified in the relevant material standard. The structure of the metallic matrix (e.g. ferrite, pearlite) has a significant effect on the material properties. Such an interpretation is not the purpose of this part of ISO 945.

### 2 General

#### 2.1 Designation system for classifying graphite in cast irons

When cast-iron materials are examined under a microscope in accordance with this part of ISO 945, the graphite shall be classified by

- a) its form, designated by Roman numerals I to VI (see Figure 1 and Annex A);
- b) its distribution, designated by capital letters A to E (see Figure 2 and Annex B); the graphite distribution designation is only specified for grey cast iron (form I);
- c) its size, designated by Arabic numerals 1 to 8 (see Figures 3, 4 and 5 and Table 1).

NOTE Figures 1 to 5 show only the outlines and not the structure of the graphite.

FORM

Magnification  $\times 100$

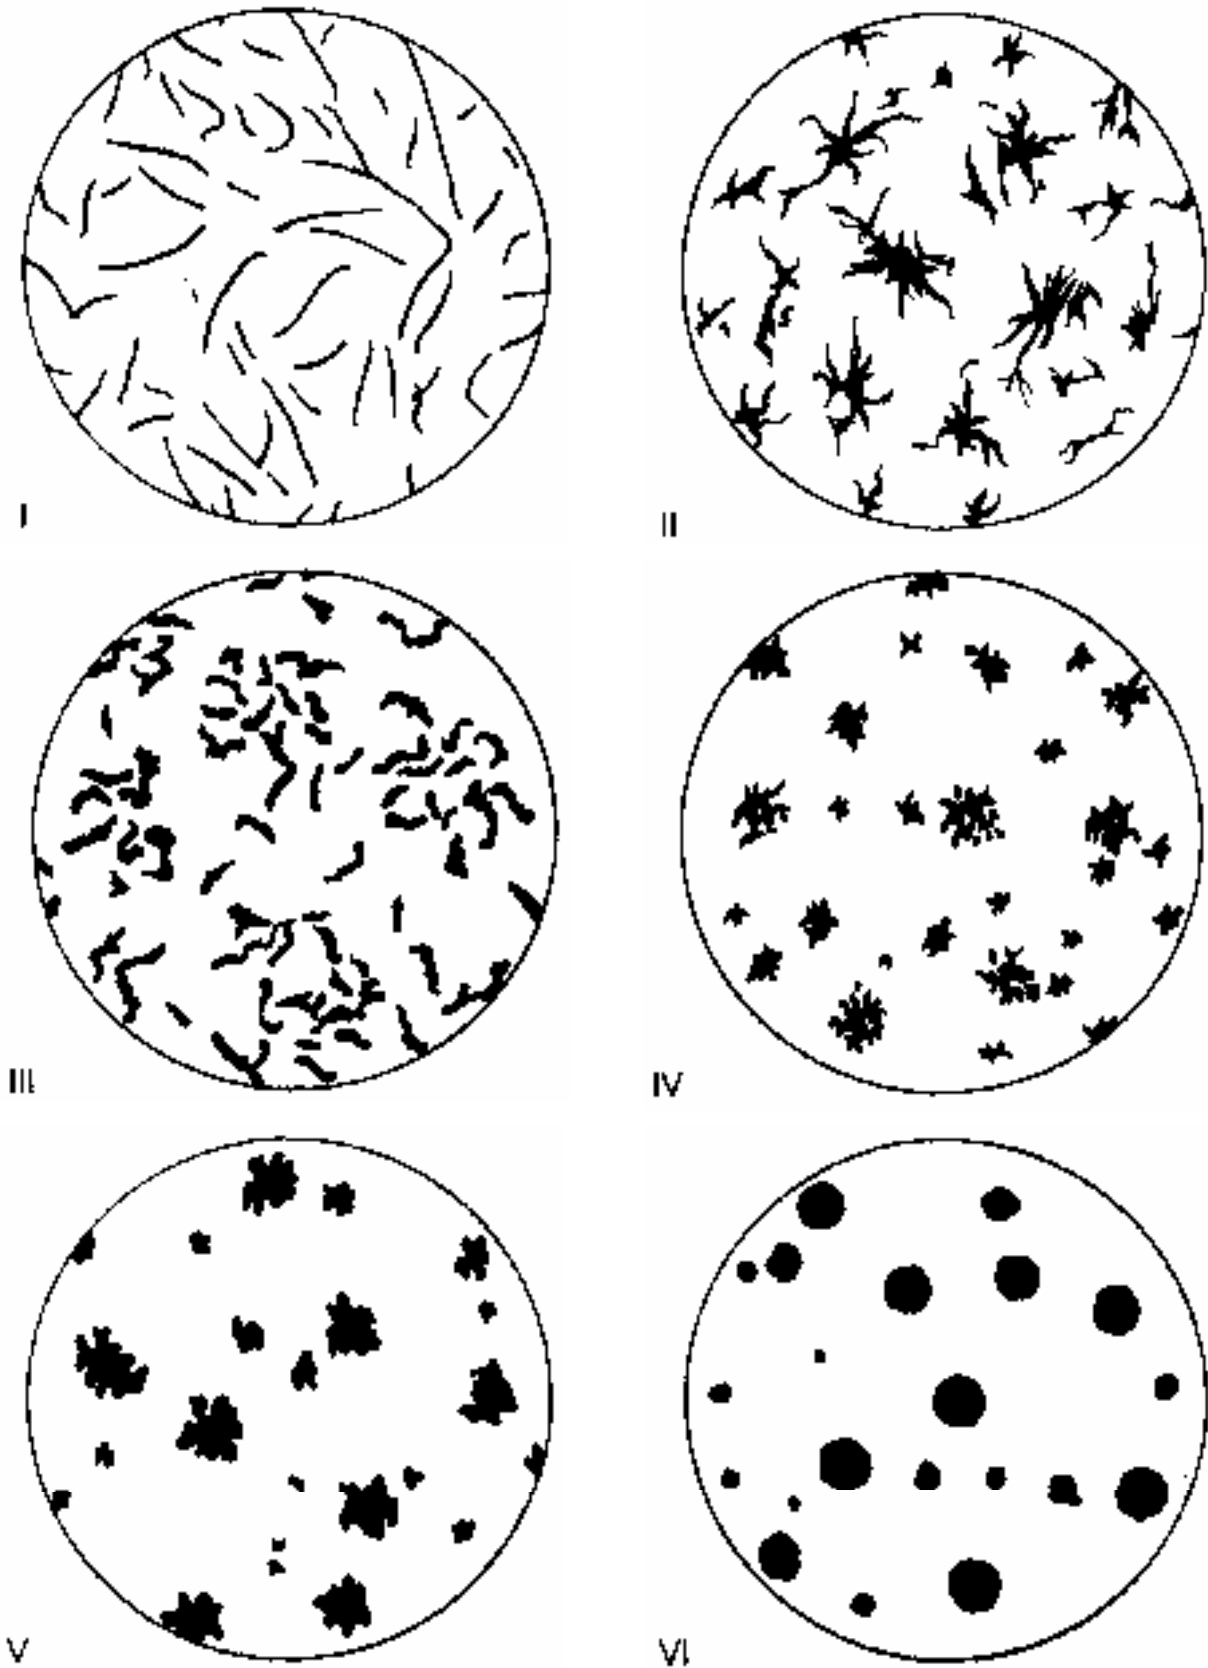


Figure 1 — Principal graphite forms in cast-iron materials — Reference images

DISTRIBUTION

Magnification  $\times 100$


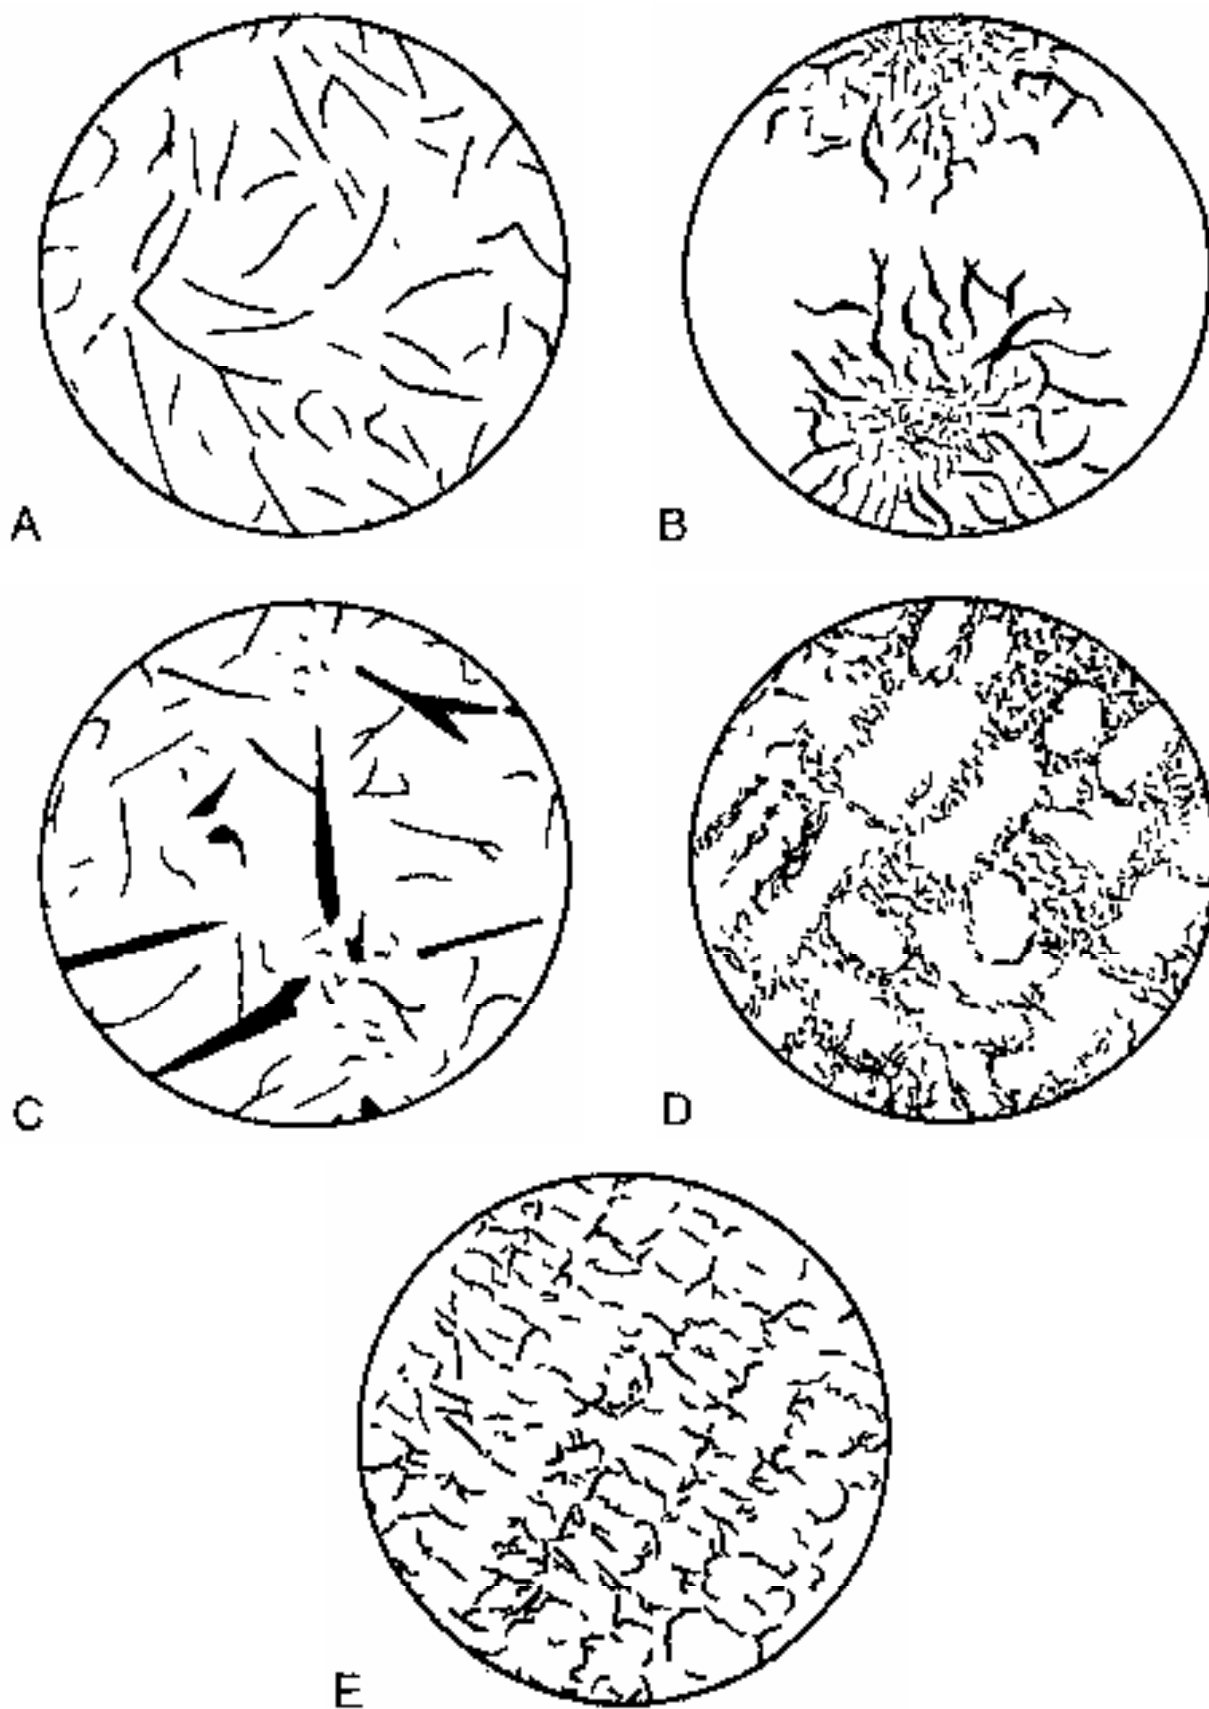


Figure 2 — Reference images for graphite distribution (form I)

SIZE

Magnification  $\times 100$

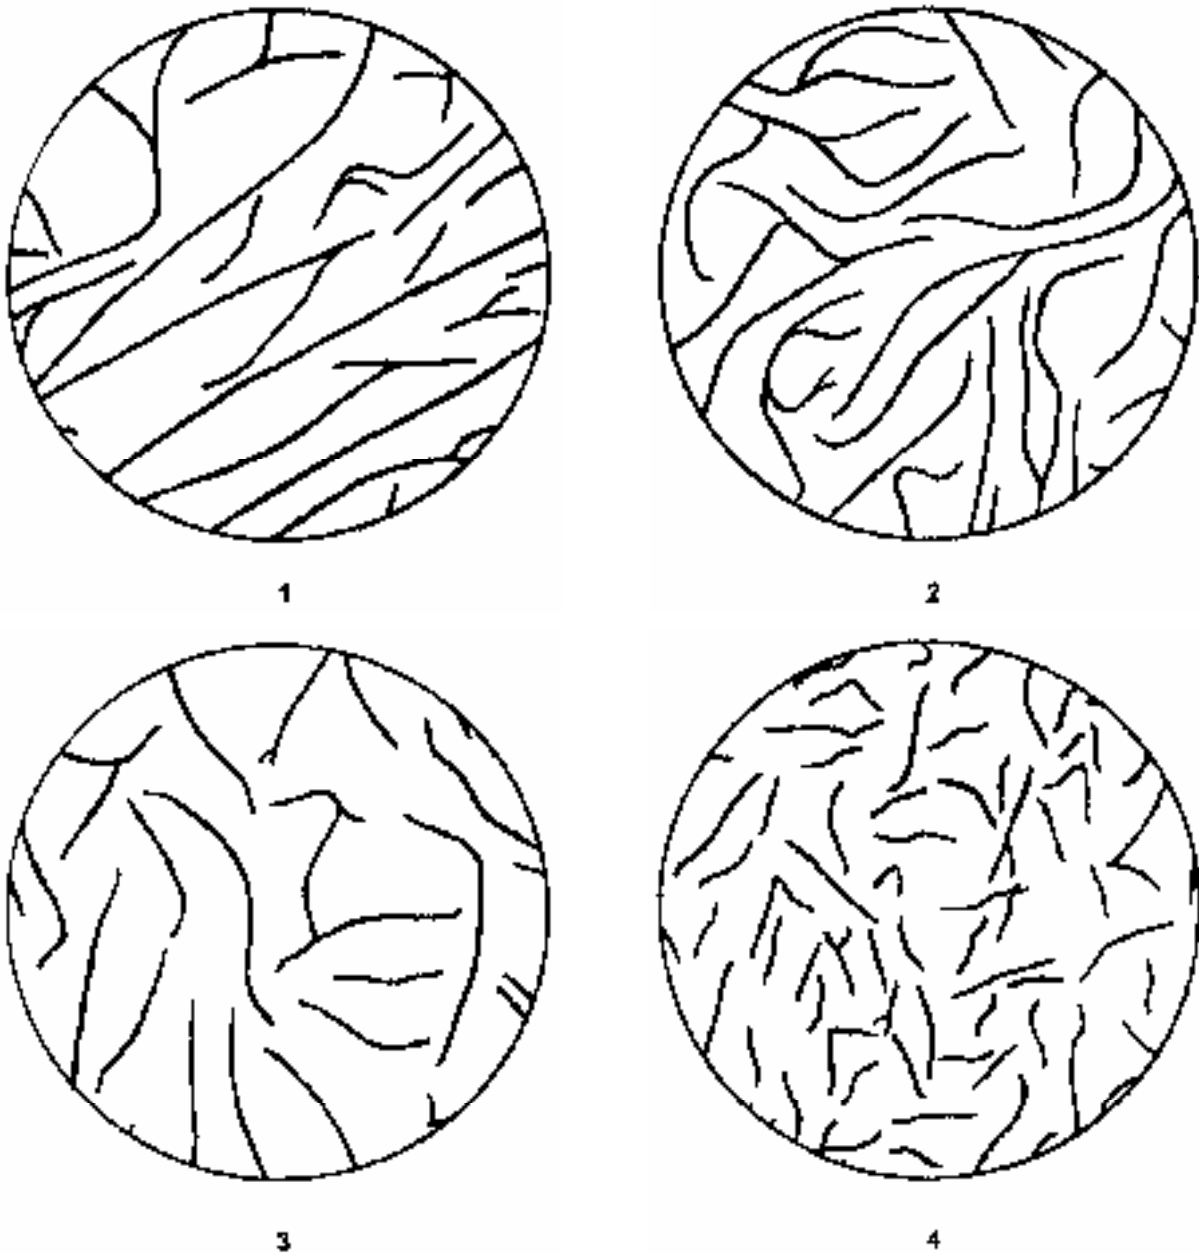


a) Sizes 1 to 4


Figure 3 — Reference images for graphite size (form I)

SIZE


Magnification  $\times 100$

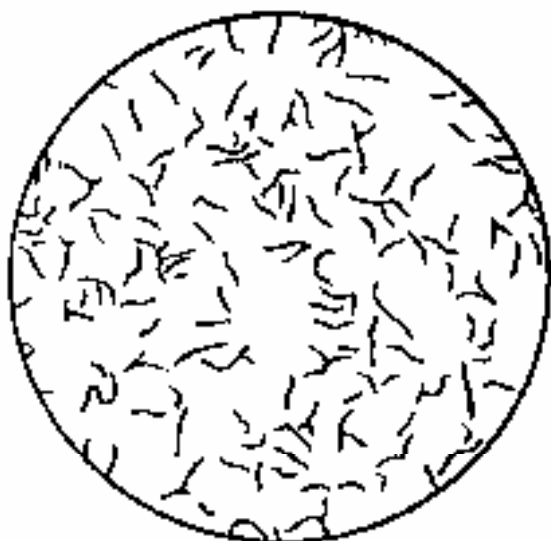


5

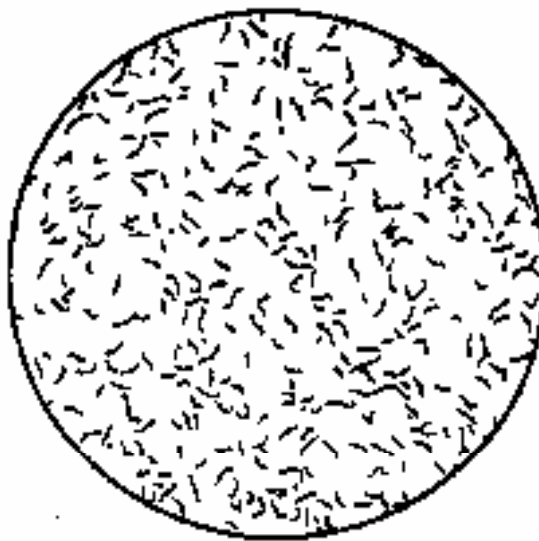

6

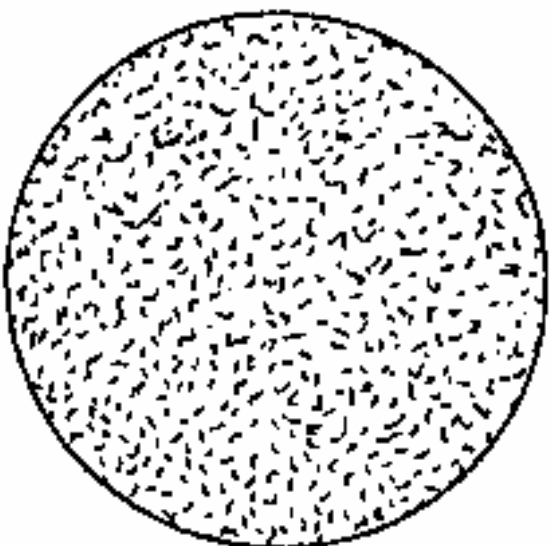

7

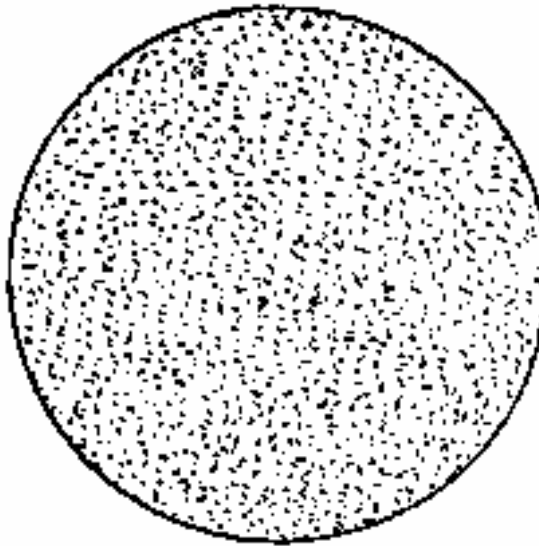


8

b) Sizes 5 to 8

Figure 3 — Reference images for graphite size (form I)

SIZE

Magnification  $\times 100$

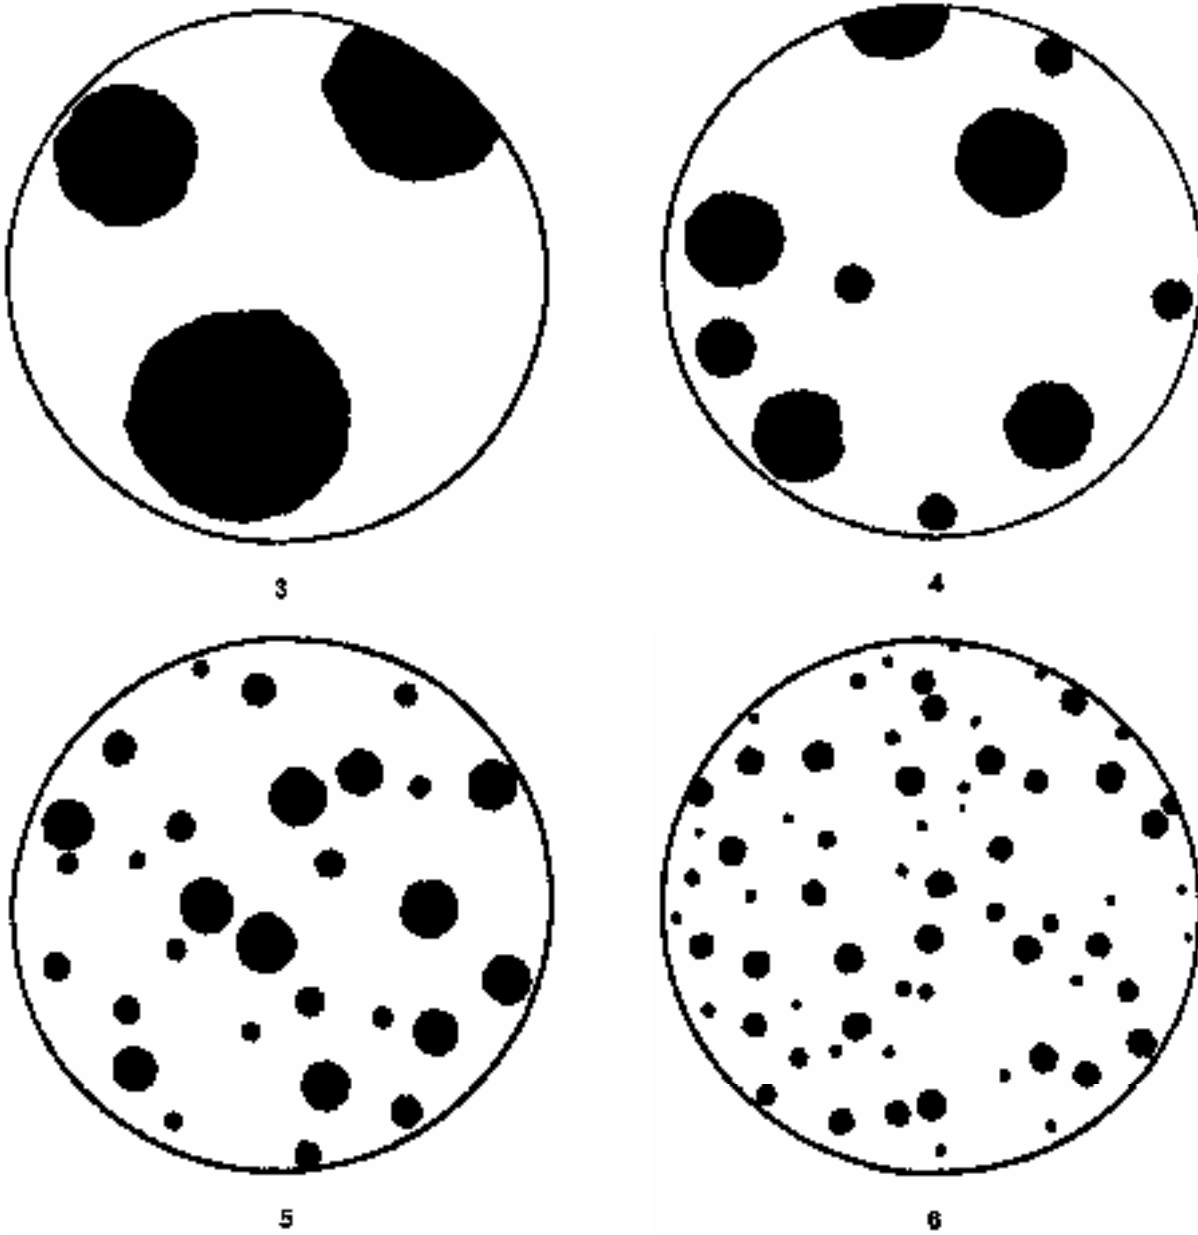


a) Sizes 3 to 6

Figure 4 — Reference images for graphite size (forms IV to VI)

SIZE

Magnification  $\times 100$

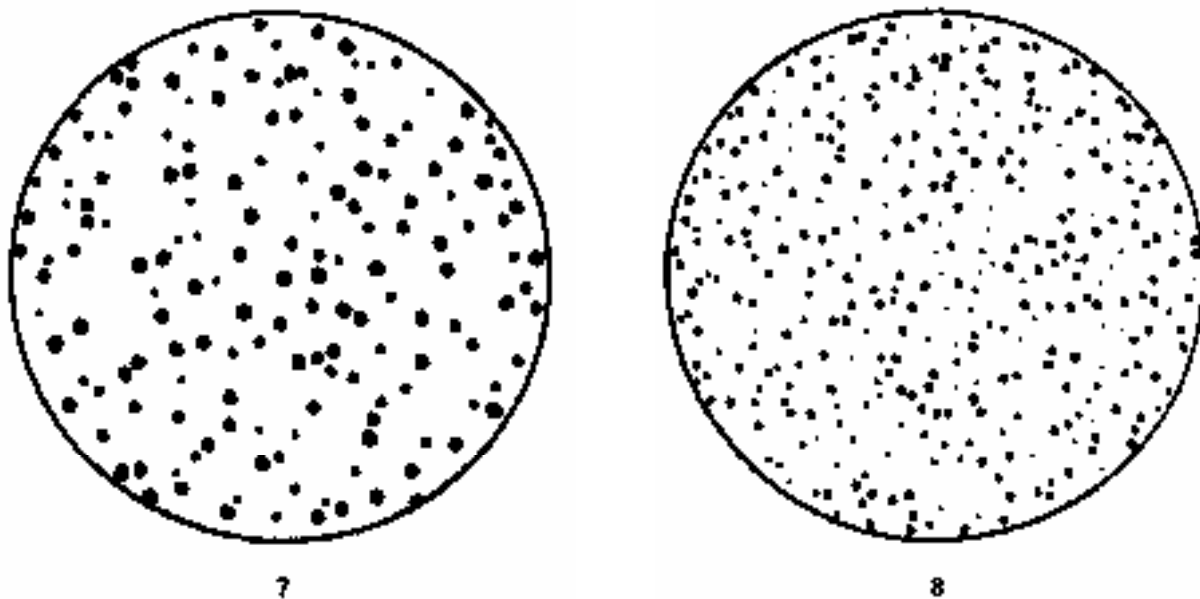


b) Sizes 7 and 8

Figure 4 — Reference images for graphite size (forms IV to VI)

SIZE

Magnification  $\times 100$

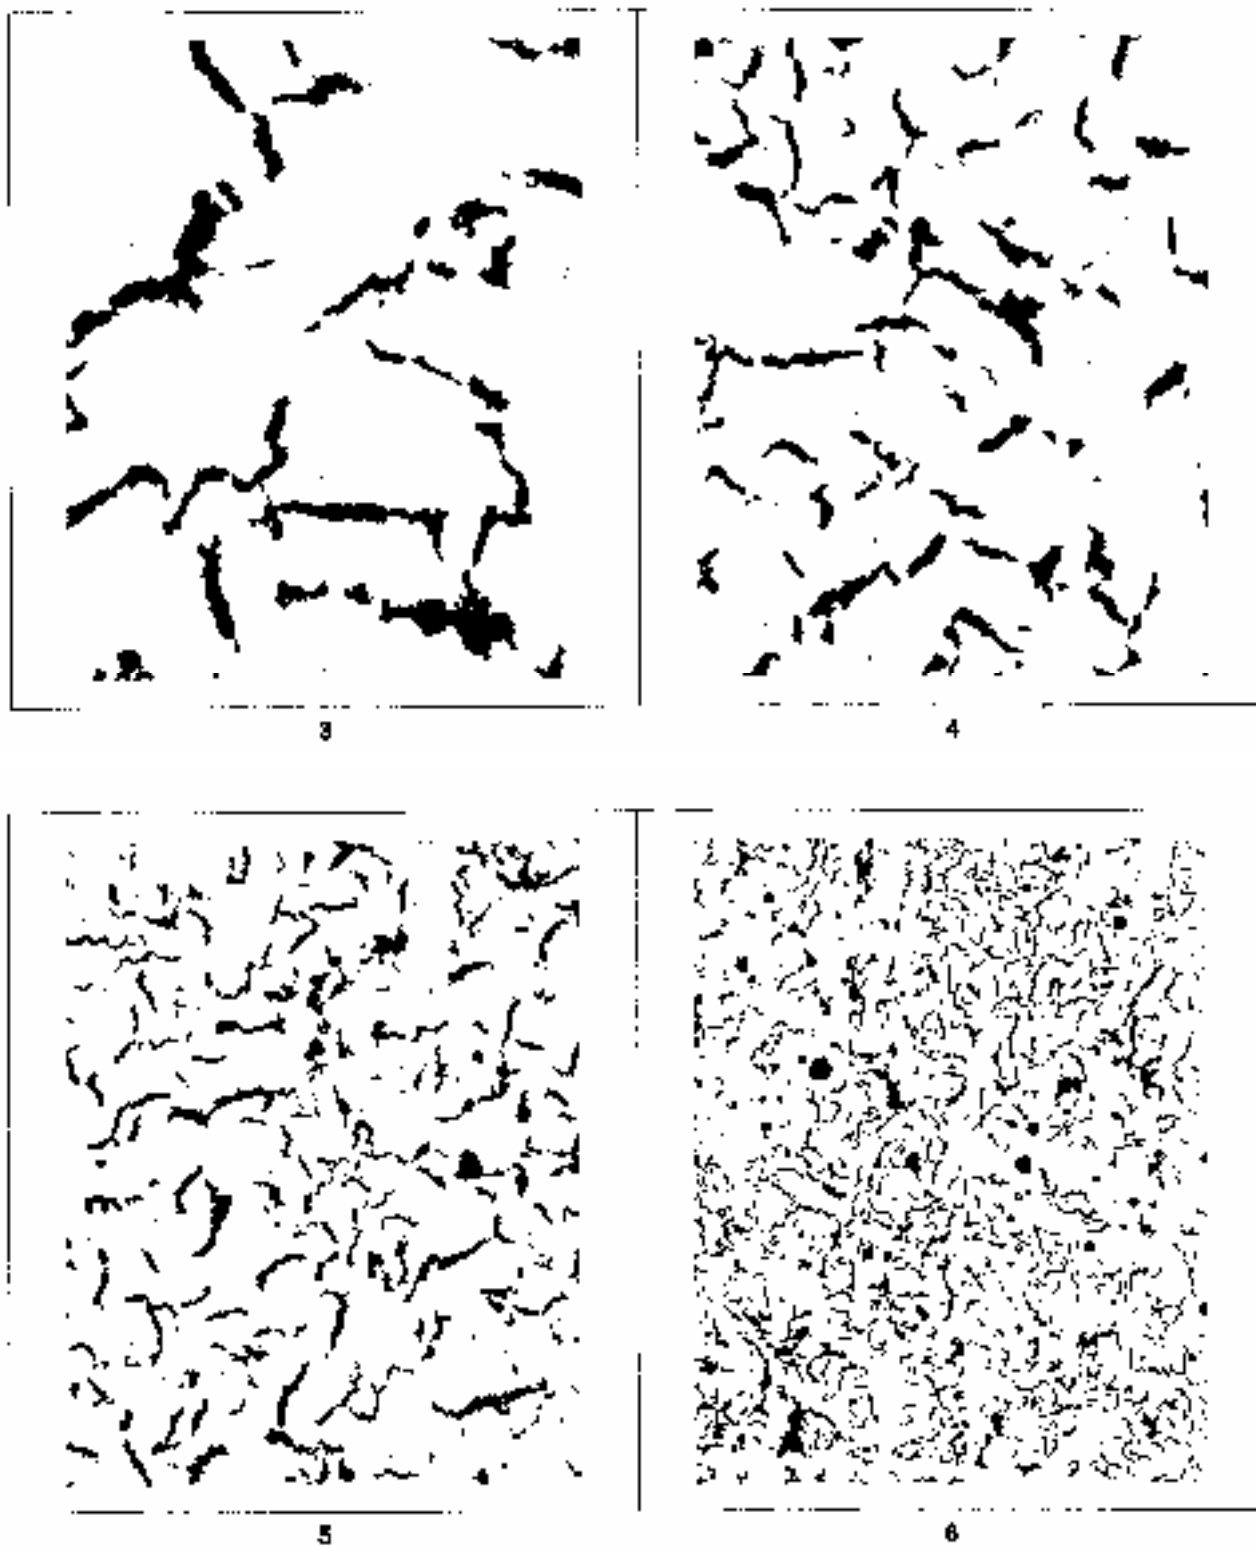


a) Sizes 3 to 6

Figure 5 — Reference images for graphite size (form III)



SIZE

Magnification  $\times 100$

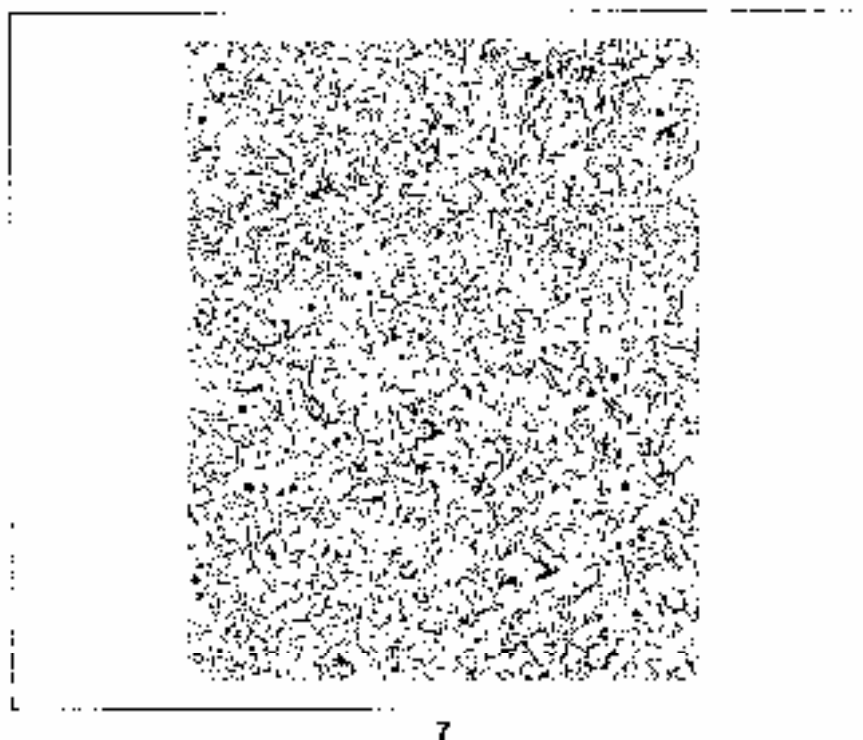

b) Size 7

Figure 5 — Reference image for graphite size (form III)

## 2.2 Visual classification of graphite

The reference images given in Figures 1, 2, 3, 4 and 5 provide a basis for classifying graphite forms, distribution and size. The characteristic features of the graphite which occur are designated by letters and numerals. For this purpose, microstructures of graphite are arranged in a series of reference images consisting of schematic microstructures and photomicrographs of cast-iron microstructures. Therefore, among the images representing the size of the graphite, those for graphite form III (vermicular) in Figure 5 correspond to actual structures with the matrix removed. Those for graphite form I in Figure 3 and for graphite forms IV to VI in Figure 4 are fully schematic.

The form, distribution and size of the graphite observed are determined by comparison with the reference images and the allocation of the same classification as that of the images that resemble them most closely. This method permits quick identification of the graphite form.

NOTE The comparison of actual microstructures with schematic images or photomicrographs depends on the subjective impression of the metallographer.

### **3 Sampling and preparation of samples**

#### **3.1 Samples taken from a casting**

When taking samples from a casting, it is essential that attention be paid to the location, to the wall thickness, to the distance from the surface and to the presence of chills. The location of the sample in the casting shall be recorded in a report.

If more than one casting is examined, the samples shall be taken from the same location in each casting for the purpose of comparability.

The location of the metallographic specimen shall be agreed between the manufacturer and the purchaser, as stated in the relevant material standard.

#### **3.2 Sample preparation**

The area of the polished surface shall be sufficient to give a true representation of the graphite structure. Attention shall be paid to the careful grinding and polishing of the samples, so that the graphite particles appear in their original form, size and distribution. Inappropriate grinding and polishing can cause an unacceptable alteration of the microstructure. If necessary, the method of polishing may be agreed between the manufacturer and the purchaser.

The examination of the graphite under the microscope is usually carried out on the unetched polished section.

### **4 Procedure for graphite classification**

#### **4.1 Procedure for visual classification of graphite**

The polished samples shall be scanned under a microscope in such a manner that a representative area is examined. To examine the graphite form and distribution, a  $\times 100$  magnification should preferably be chosen. If necessary, the magnification may be adapted in relation with the wall thickness so that the form and distribution of graphite can be determined by using the reference images given in Figures 1 and 2 (see also Annexes A, B and C). Adjust the microscope magnification to match as closely as possible the corresponding images in Figures 1 and 2 before classifying the graphite form and its distribution, if appropriate. The graphite size shall only be determined by reference to Figures 3, 4 and 5 and Table 1, preferably at  $\times 100$  magnification. Other magnifications are permitted (see Table 1, Notes 1 and 2, as well as 5.4).

Examination under the microscope shall be carried out by direct observation in the microscope or by projection on the ground glass of the microscope or on a visual display screen. The field of view should preferably have approximately the same size as the reference images. The measurement of the graphite particles can be facilitated by the use of suitably calibrated eye-pieces.

Form and distribution of graphite shall be determined by using the reference images, given in Figures 1 and 2 (see also Annexes A, B and C). Adjust the microscope magnification to match as closely as possible the corresponding images in Figures 1 and 2 before classifying the graphite form and its distribution, if appropriate.

If the microstructure is visualized on a visual display screen, the combined magnification of both microscope and screen (depending on its size) shall be taken into account.

#### **4.2 Evaluation of the analysis results**

The evaluation of the analysis results shall be carried out by an operator trained in this metallographic technique.

## 5 Reference images

### 5.1 General

A series of reference images (see Figures 1 to 5) showing schematic microstructures and photomicrographs is provided for the classification of the form, distribution and size of the graphite in cast iron.

In addition to reference images, the photomicrographs show actual graphite microstructures (see Annexes A and B).

### 5.2 Reference images for graphite form

The reference images for the graphite form (see Figure 1) show six characteristic forms which are designated by the Roman numerals I to VI (see also Annex A). These represent the principal types of graphite observed in cast-iron materials. Annex C gives the common terminology and the occurrence of these types of graphite.

The graphite forms are specified in the relevant material standards. Percentages of these graphite forms may also be specified by these standards, e.g. in the case of compacted (vermicular) graphite cast irons.

**NOTE** ASTM A 247 designates graphite forms in the reverse order compared to this part of ISO 945. It is therefore necessary to specify the test method used to classify the graphite form.

### 5.3 Reference images for the distribution of graphite (form I)

The reference images for the graphite distribution (see Figure 2) show characteristic graphite distributions designated by the letters A to E.

In addition to reference images, the photomicrographs show actual graphite microstructures (see Annex B).

A variant of distribution C, designated C', has been included in Annex B. This distribution corresponds to thin-walled castings.

### 5.4 Reference images for graphite size

Figures 3, 4 and 5 shall be used to determine the graphite size. By agreement between the manufacturer and the purchaser, Table 1 may be used in addition. For  $\times 100$  magnification, sizes are indicated ranging from a maximum size of the particle of  $> 100 \mu\text{m}$  (size 1) down to  $< 1,5 \mu\text{m}$  (size 8). The size ranges covered by the size reference numbers 3 to 7 inclusive are based on an average particle size which is half that in the larger size range. When using Table 1, alternative magnifications may be used (see Table 1, Notes 1 and 2).

If necessary, different size ranges may be agreed upon.

**NOTE** Sizes 1 and 2 have no practical application for graphite forms III to VI. Therefore, they have not been included in Figures 4 and 5.

## 6 Designation of graphite by form, distribution and size

### 6.1 Designation system

To characterize the graphite observed, indications are generally necessary on the form, distribution and size of the graphite particles. For this purpose, the following symbols shall be used at different positions of the designation:

- the Roman numerals given in Figure 1 are used for the graphite form at position 1;
- for form I, the capital letters given in Figure 2 are used for the distribution at position 2;
- the Arabic numerals given in Figures 3, 4, and 5 and Table 1 are used for the graphite size at position 3.

EXAMPLE 1 For a grey cast iron with flake (lamellar) shaped graphite particles of form I, distribution A, and size 4, the following designation is used to describe that structure:

I A 4

EXAMPLE 2 For a cast iron with spheroidal graphite particles of form VI and size 4, the following designation is used to describe that structure:

VI 4

**Table 1 — Dimensions of graphite particle forms I to VI**

Dimensions in millimetres

Size range reference number	Indication of the particle size observed at $\times 100$ magnification	Actual dimension
1	$\geq 100$	$\geq 1$
2	50 to $< 100$	0,5 to $< 1$
3	25 to $< 50$	0,25 to $< 0,5$
4	12 to $< 25$	0,12 to $< 0,25$
5	6 to $< 12$	0,06 to $< 0,12$
6	3 to $< 6$	0,03 to $< 0,06$
7	1,5 to $< 3$	0,015 to $< 0,03$
8	$< 1,5$	$< 0,015$

NOTE 1 When determining size ranges 1 and 2, a lower magnification ( $\times 25$  or  $\times 50$ ) may be used.  
 NOTE 2 When determining size ranges 6 to 8, a higher magnification ( $\times 200$  or  $\times 500$ ) may be used.  
 NOTE 3 For determining size ranges, the largest visible graphite particle size is used.

## 6.2 Designation of intermediate graphite sizes

If the graphite observed covers two sizes, reference to both is possible:

EXAMPLE 1 3/4

In addition, the predominant size may be emphasized by underlining:

EXAMPLE 2 3/4

This method can be extended to cover microstructures where more than two sizes are present.

## 6.3 Designation of mixed graphite forms, distributions and sizes

More complex microstructures containing different types of graphite can be defined by estimating the percentage proportions of the different types of graphite.

EXAMPLE 1 For a cast iron with a graphite area comprising 60 % flake (lamellar) shaped graphite particles of form I, distribution A and size 4 and 40 % flake (lamellar) shaped graphite particles of form I, distribution D and size 7, the following designation is used to describe the structure:

60 % I A 4 + 40 % I D 7

EXAMPLE 2 For a cast iron with a graphite area comprising 85 % spheroidal graphite particles of form VI and size 4 and 15 % vermicular graphite particles of form III and covering sizes 3 and 4, the following designation is used to describe the structure:

85 % VI 4 + 15 % III 3/4

## 6.4 Nodule count

The graphite nodule count  $n_F$  is determined by using the planimetric method (see Reference [2]). Nodules are particles normally classified as form VI or V (or even form IV).

$$n_F = \frac{N}{A} \times F^2 \quad (1)$$

where

$n_F$  is the number of particles per unit surface area of the sample;

$N$  is the number of nodules counted;

$A$  is the magnified area;

$F$  is the linear magnification factor.

**EXAMPLE** At a magnification of  $\times 100$ , a circle measuring 79,8 mm in diameter ( $= 5\,000\text{ mm}^2$ ) is superimposed over a micrograph. At the preferred magnification of  $\times 100$ , the circular area should preferably contain at least 50 graphite particles in order to minimize the counting error associated with a circular test pattern. Two counts are made:

$n_1$  is the number of graphite particles completely within the test circle;

$n_2$  is the number of graphite particles intersected by the test circle.

The total number of graphite particles in this circle of  $5\,000\text{ mm}^2$  is

$$n_{100} = n_1 + \frac{n_2}{2} \quad (2)$$

In this case, to express the nodule count as nodules/mm<sup>2</sup>, the result given by Equation (2) has to be multiplied by 2, since

$$\frac{F^2}{A} = \frac{100^2}{5\,000} \quad (3)$$

This operation is repeated on other fields.

The larger the number of fields measured, the more representative is the result.

## 7 Report

If a report is required, it shall contain the following information:

- identification of the sample or casting;
- the sampling location(s);
- the number of samples taken and the number of areas evaluated;
- the form, distribution and size of the graphite;
- the magnification used;
- a reference to this part of ISO 945;
- the date of the report;

- the name of the organization;
- the name of the person authorized to sign the report.

If required, the report shall also contain the following information:

- the nodule count;
- the designation of the material;
- the metallographic preparation procedure used;
- the size of the cast-on sample or separately cast sample and/or the wall thickness of the respective sample;
- the size of the graphite;
- details of the presence of any other graphite form not covered by this part of ISO 945.

One or more photomicrographs may also be included in the report.

**Annex A**  
(informative)

**Typical graphite forms in cast-iron materials**  
(Examples of photomicrographs)

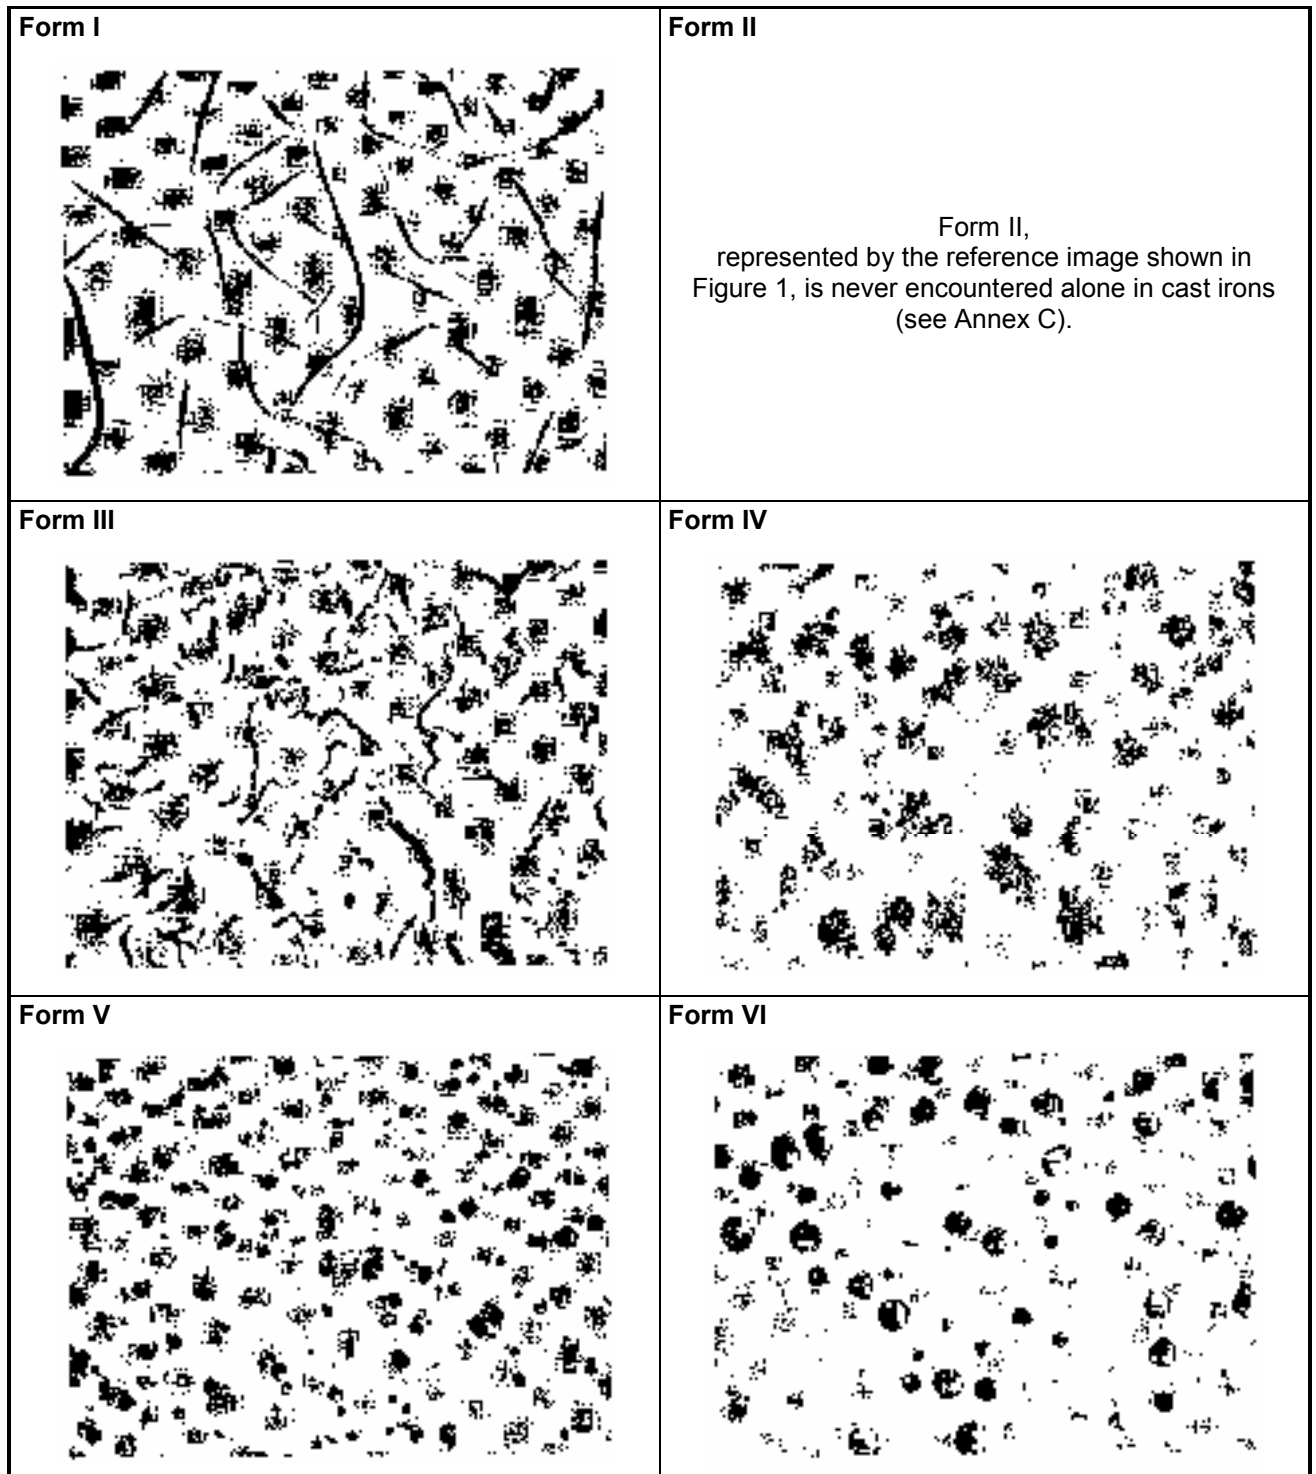


Figure A.1 — Examples of photomicrographs

**Annex B**  
(informative)

**Distribution of flake (lamellar) graphite (form I)**  
(Examples of photomicrographs)

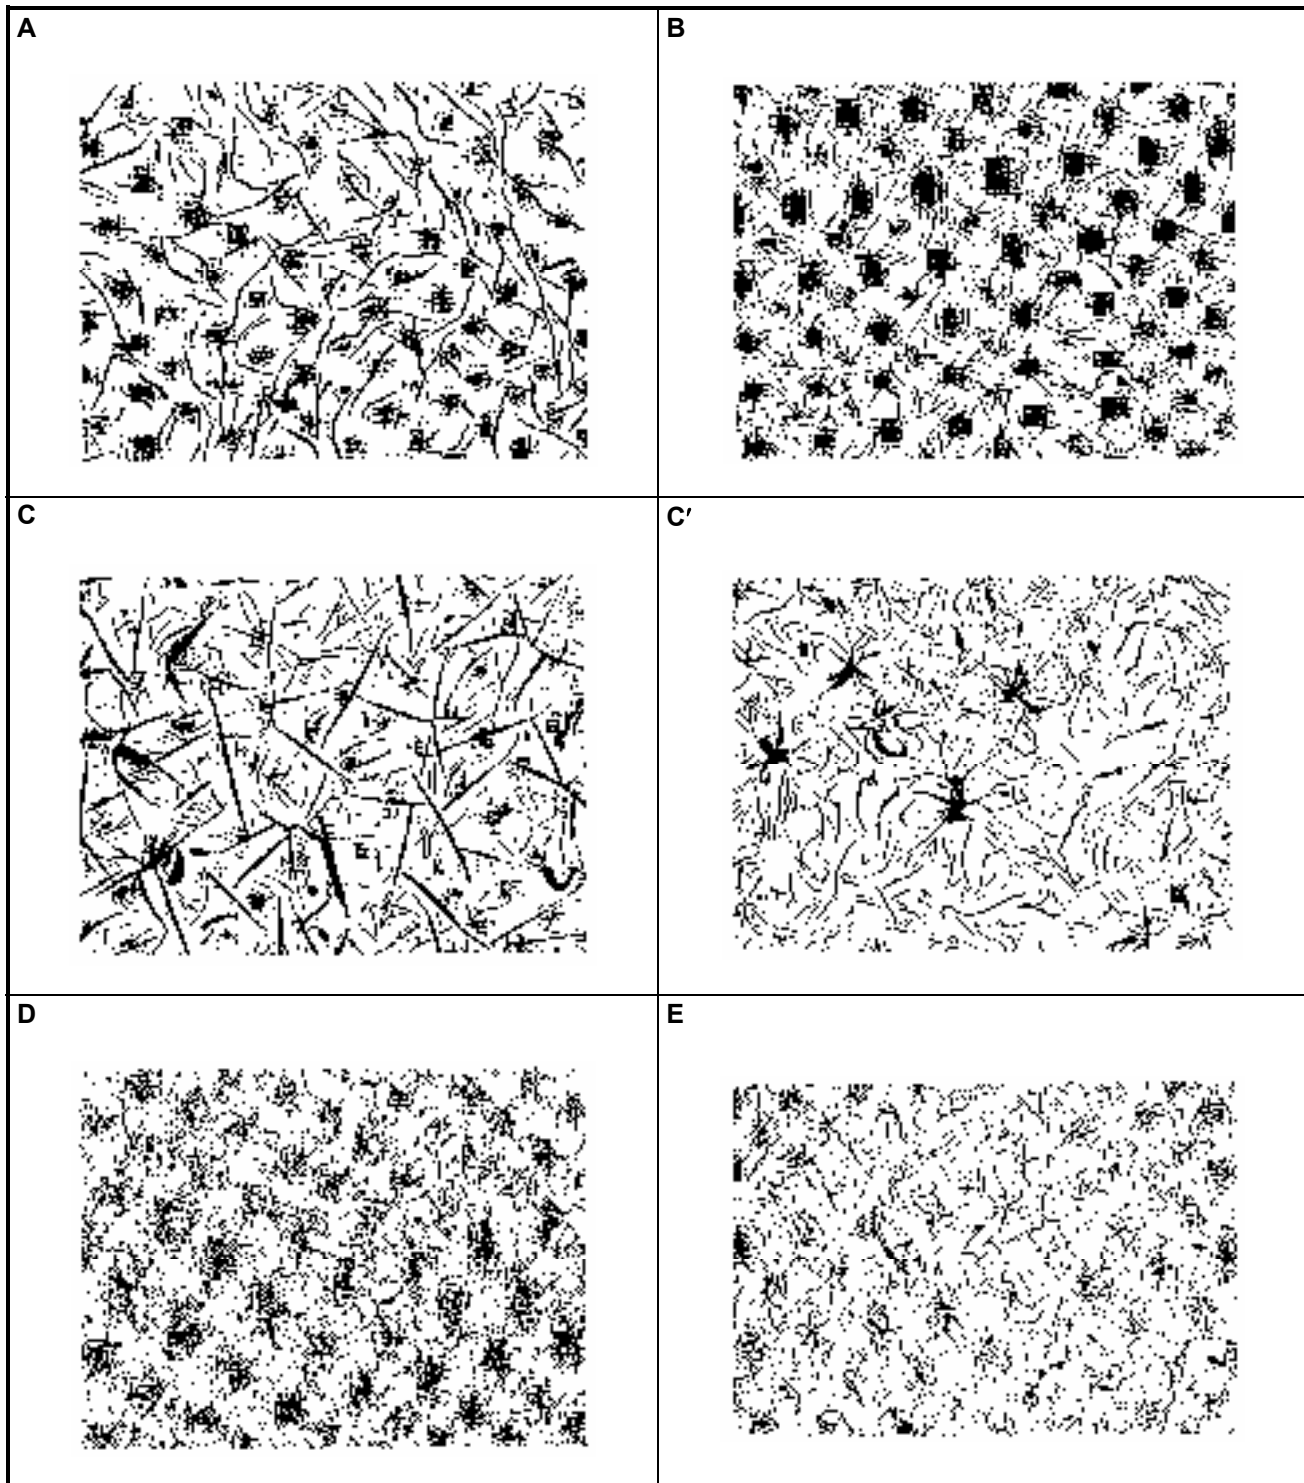


Figure B.1 — Examples of photomicrographs



## Annex C (informative)

### Common terminology and main occurrences concerning graphite in cast irons

**Table C.1 — Graphite forms** (see Figure 1 and Annex A)

<b>Form</b>	<b>Usual terminology</b>	<b>Main spatial characteristics</b>	<b>Occurrence</b>	<b>Relevant material standard</b>
I	Lamellar graphite Flake graphite	Interconnected particles within eutectic cells; lamellar graphite with sharp ends	Principal form in grey cast iron  Austenitic cast iron with lamellar/flake graphite  Can occur in the rim zone of other cast-iron materials	ISO 185  ISO 2892
II	Crab graphite	Aggregate of graphite flakes	Can occur in rapidly cooled hypereutectic grey cast irons (see Annex B and Table C.2)  Can also occur in segregation areas of thick-walled spheroidal-graphite iron castings	ISO 185
III	Vermicular graphite Compacted graphite	Usually interconnected particles within eutectic cells; worm-like appearance with rounded ends	Principal form in compacted-graphite cast iron  Can occur in spheroidal-graphite cast iron	ISO 16112
IV	Temper carbon	Isolated particles	Principal form in malleable cast iron	ISO 5922
V	Slightly irregular spheroidal or nodular graphite particles	Isolated particles	Principal form in thick-walled castings made of spheroidal-graphite cast iron, ausferritic spheroidal-graphite cast iron and austenitic cast iron with spheroidal graphite  Occurs to a specified extent in compacted-graphite cast iron	ISO 1083 ISO 17804 ISO 2892
VI	Spheroidal or nodular graphite particles	Isolated particles	Principal form in spheroidal-graphite cast iron, ausferritic spheroidal-graphite cast iron and austenitic cast iron with spheroidal graphite  Occurs to a specified extent in compacted-graphite cast iron	ISO 1083 ISO 17804 ISO 2892

**Table C.2 — Graphite distributions in grey cast iron**  
 (see Figure 2 and Annex B)

Distribution	Alternative terminology	Main 2D appearance	Occurrences
A	—	Apparently uniform distribution	Cast iron solidified with a low to intermediate degree of undercooling.
B	Rosette graphite Rosette graphite with undercooling graphite	—	Cast iron solidified with an intermediate degree of undercooling, particularly thin-walled castings.
C	Primary graphite	Aggregate of larger graphite flakes surrounded by smaller, randomly oriented graphite flakes (eutectic graphite)	Hypereutectic cast iron. In thin-walled castings, the larger particles can adopt form II (see Annex B, distribution C').
D	Fine (interdendritic) graphite Undercooling graphite	Finely branched graphite Fine, randomly oriented graphite flakes in the interdendritic position	Cast iron solidified with a high degree of undercooling. The distribution can be associated with other distributions (for example A and/or B and/or E). Distribution D can appear in the centre of rosette groupings in the case of a relatively high degree of undercooling.
E	Interdendritic graphite	Preferentially orientated graphite flakes in the interdendritic position	Cast iron with low carbon equivalent, solidified with low or moderate undercooling. Local area corresponding to a plane of polish cutting through the main axis of some highly oriented dendrites.

## Bibliography

- [1] ISO 185, *Grey cast irons — Classification*
- [2] ISO 643, *Steels — Micrographic determination of the apparent grain size*
- [3] ISO 1083, *Spheroidal graphite cast irons — Classification*
- [4] ISO 2892, *Austenitic cast irons — Classification*
- [5] ISO 5922, *Malleable cast iron*
- [6] ISO 16112, *Compacted (vermicular) graphite cast irons — Classification*
- [7] ISO 17804, *Founding — Ausferritic spheroidal graphite cast irons — Classification*
- [8] ASTM A 247, *Standard Test Method for Evaluating the Microstructure of Graphite in Iron Castings*
- [9] *Foundrymen's Guide to Ductile Iron Microstructures*, 2nd edition, 1987

---

## BSI - British Standards Institution

BSI is the independent national body responsible for preparing British Standards. It presents the UK view on standards in Europe and at the international level. It is incorporated by Royal Charter.

### Revisions

British Standards are updated by amendment or revision. Users of British Standards should make sure that they possess the latest amendments or editions.

It is the constant aim of BSI to improve the quality of our products and services. We would be grateful if anyone finding an inaccuracy or ambiguity while using this British Standard would inform the Secretary of the technical committee responsible, the identity of which can be found on the inside front cover. Tel: +44 (0)20 8996 9000. Fax: +44 (0)20 8996 7400.

BSI offers members an individual updating service called PLUS which ensures that subscribers automatically receive the latest editions of standards.

### Buying standards

Orders for all BSI, international and foreign standards publications should be addressed to Customer Services. Tel: +44 (0)20 8996 9001. Fax: +44 (0)20 8996 7001 Email: [orders@bsigroup.com](mailto:orders@bsigroup.com) You may also buy directly using a debit/credit card from the BSI Shop on the Website <http://www.bsigroup.com/shop>

In response to orders for international standards, it is BSI policy to supply the BSI implementation of those that have been published as British Standards, unless otherwise requested.

### Information on standards

BSI provides a wide range of information on national, European and international standards through its Library and its Technical Help to Exporters Service. Various BSI electronic information services are also available which give details on all its products and services. Contact Information Centre. Tel: +44 (0)20 8996 7111 Fax: +44 (0)20 8996 7048 Email: [info@bsigroup.com](mailto:info@bsigroup.com)

Subscribing members of BSI are kept up to date with standards developments and receive substantial discounts on the purchase price of standards. For details of these and other benefits contact Membership Administration. Tel: +44 (0)20 8996 7002 Fax: +44 (0)20 8996 7001 Email: [membership@bsigroup.com](mailto:membership@bsigroup.com)

Information regarding online access to British Standards via British Standards Online can be found at <http://www.bsigroup.com/BSOL>

Further information about BSI is available on the BSI website at <http://www.bsigroup.com>.

### Copyright

Copyright subsists in all BSI publications. BSI also holds the copyright, in the UK, of the publications of the international standardization bodies. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI.

This does not preclude the free use, in the course of implementing the standard, of necessary details such as symbols, and size, type or grade designations. If these details are to be used for any other purpose than implementation then the prior written permission of BSI must be obtained.

Details and advice can be obtained from the Copyright and Licensing Manager. Tel: +44 (0)20 8996 7070 Email: [copyright@bsigroup.com](mailto:copyright@bsigroup.com)