

BS EN ISO 1927-7:2012



BSI Standards Publication

Monolithic (unshaped) refractory products

Part 7: Tests on pre-formed shapes

bsi.

...making excellence a habit.™

National foreword

This British Standard is the UK implementation of EN ISO 1927-7:2012. It supersedes BS EN 1402-7:2003, which is withdrawn.

The UK participation in its preparation was entrusted to Technical Committee RPI/1, Refractory products and materials.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© The British Standards Institution 2013.

Published by BSI Standards Limited 2013.

ISBN 978 0 580 65762 7

ICS 81.080

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 31 January 2013.

Amendments issued since publication

Amd. No.	Date	Text affected
----------	------	---------------

English Version

Monolithic (unshaped) refractory products - Part 7: Tests on pre-formed shapes (ISO 1927-7:2012)Produits réfractaires monolithiques (non façonnés) - Partie
7: Essais sur pièces pré-formées (ISO 1927-7:2012)Ungeformte (monolithische) feuerfeste Erzeugnisse - Teil 7:
Prüfungen an Fertigteilen (ISO 1927-7:2012)

This European Standard was approved by CEN on 30 November 2012.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN-CENELEC Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and United Kingdom.

EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG**Management Centre: Avenue Marnix 17, B-1000 Brussels**

Contents

Page

Foreword.....	3
---------------	---

Foreword

This document (EN ISO 1927-7:2012) has been prepared by Technical Committee ISO/TC 33 "Refractories" in collaboration with Technical Committee CEN/TC 187 "Refractory products and materials" the secretariat of which is held by BSI.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by June 2013, and conflicting national standards shall be withdrawn at the latest by June 2013.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN [and/or CENELEC] shall not be held responsible for identifying any or all such patent rights.

This document supersedes EN 1402-7:2003.

According to the CEN/CENELEC Internal Regulations, the national standards organisations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and the United Kingdom.

Endorsement notice

The text of ISO 1927-7:2012 has been approved by CEN as a EN ISO 1927-7:2012 without any modification.

Contents		Page
1	Scope	1
2	Normative references	1
3	Terms and definitions	1
4	Principle	4
5	Apparatus	4
6	Inspection by attributes	6
	6.1 Preparation of the test piece.....	6
	6.2 Measurement of dimensions.....	6
	6.3 Measurement of angles.....	6
	6.4 Measurement of warpage.....	7
	6.5 Measurement of corner defects.....	8
	6.6 Measurement of edge defects.....	9
	6.7 Measurement of craters and bubbles.....	10
	6.8 Measurement of cracks.....	11
	6.9 Measurement of protrusions and indentations.....	11
	6.10 Measurement of fins.....	12
	6.11 Segregations.....	12
	6.12 Friability.....	12
7	Inspection by variables	12
	7.1 Destructive test methods.....	12
	7.2 Non-destructive test methods.....	14
8	Test report	19
	Bibliography	21

Monolithic (unshaped) refractory products —

Part 7: Tests on pre-formed shapes

1 Scope

This part of ISO 1927 specifies methods for the testing of as-delivered pre-formed shapes. It applies to shapes fabricated from dense and insulating castables and ramming materials as defined in ISO 1927-1.

NOTE Acceptance values for the individual test methods described should be agreed between the parties involved.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 1927-1, *Monolithic (unshaped) refractory products – Part 1 Introduction and classification*

ISO 1927-6, *Monolithic (unshaped) refractory products — Part 6: Measurement of physical properties*


3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

3.1

corner defect

missing corner, defined by the three dimensions a , b and c as indicated in Figure 1

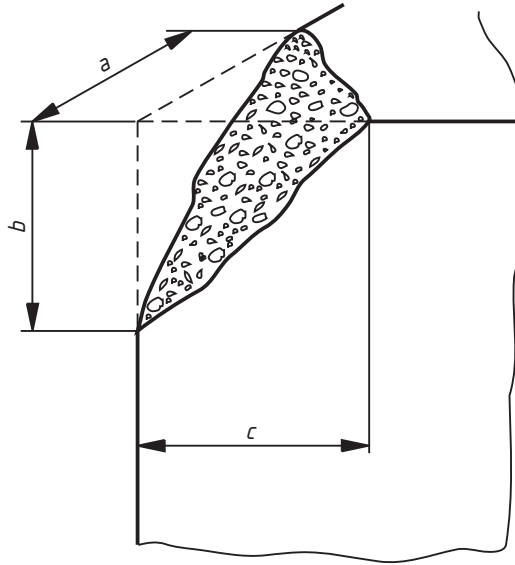


Key
a, b and c Three dimensions defining the missing corner

Figure 1 — Typical corner defect

3.2
edge defect

missing edge, defined by the three dimensions, *e, f, and g* as indicated in Figure 2

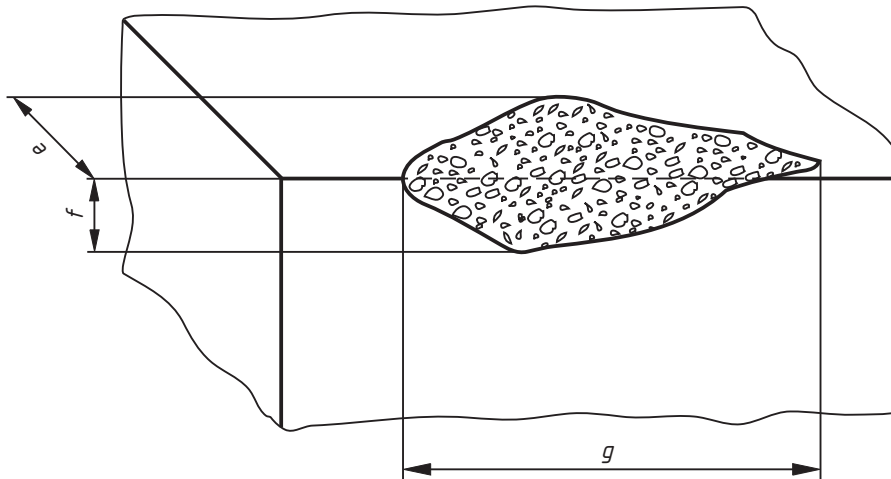

Key
e, f, and g Three dimensions defining the missing edge

Figure 2 — Typical edge defect


3.3
crater

clearly defined hole in the surface of a shape whose parameters, i.e. maximum diameter, minimum diameter and depth, can be measured

NOTE Its origin can be a bubble produced during manufacture.

**3.4
hairline cracks**

fine cracks visible on the surface of a shape whose length can be measured and whose width is less than or equal to 0,2 mm, see Figure 3

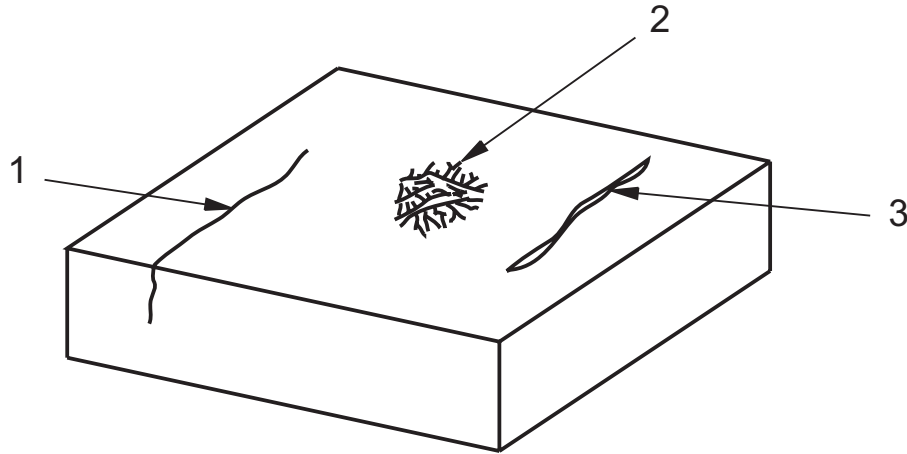

Key

- | | |
|---|-----------------|
| 1 | Hairline crack |
| 2 | Surface crazing |
| 3 | Open cracks |

Figure 3 — Typical cracks

**3.5
surface crazing**

network of hairline cracks confined to the surface of the shape, see Figure 3

**3.6
open cracks**

cracks or tears on the surface whose length is more than 10 mm and whose width is more than 0,2 mm
See Figure 3.

**3.7
protrusions and indentations**

imperfections that can occur during fabrication or firing, if applicable

**3.8
fins**

thin layer of material on the face of a shape that projects beyond the edge

**3.9
segregation**

separation of aggregate and fines during fabrication to leave a honeycomb appearance and/or a layer of excess fines

**3.10
friability**

crumbly texture due to poor consolidation and/or mould leakage

**3.11
warp**

deviation of a plane surface from being flat

4 Principle

Testing of pre-formed shapes by qualitative and/or quantitative methods. These methods are of two types:

- a) **Inspection by attributes** by evaluating the integrity of a refractory shape by visual inspection of cracks or other surface defects and by conformance to dimensional tolerances;
- b) **Inspection by variables** by evaluating the quality of a refractory shape by determining physical properties using appropriate destructive or non-destructive test methods.

NOTE It is not obligatory to use all the test methods described in this part of ISO 1927 when determining the quality of a pre-formed shape.

5 Apparatus

5.1 Linear measuring devices, steel tape and/or callipers in accordance with the tolerance required and conforming to an accuracy that is twice the intended accuracy of the measurement.


NOTE Where possible, linear tolerances less than 1 mm should be measured with callipers. Steel tape measurements are accurate to the millimetre (0,5 mm can be estimated) whereas callipers are accurate to 0,1 mm.

5.2 Steel straightedge, at least 5 mm thick and of sufficient length to span the diagonal of the largest shape to be measured.


5.3 Two steel measuring wedges, which shall be either:

- a) type 1, at least 50 mm in length and 10 mm in thickness at one end, of uniform cross-section for a length of at least 10 mm from that end and then tapering to zero thickness at the other end (see for example Figure 4a), or
- b) type 2, up to 160 mm in length with an even taper from 4 mm to zero (see for example Figure 4b).

Each wedge shall be graduated and numbered along the slope to show the thickness of the wedge between the base and the slope in increments of either 0,5 mm (type 1) or 0,1 mm (type 2).

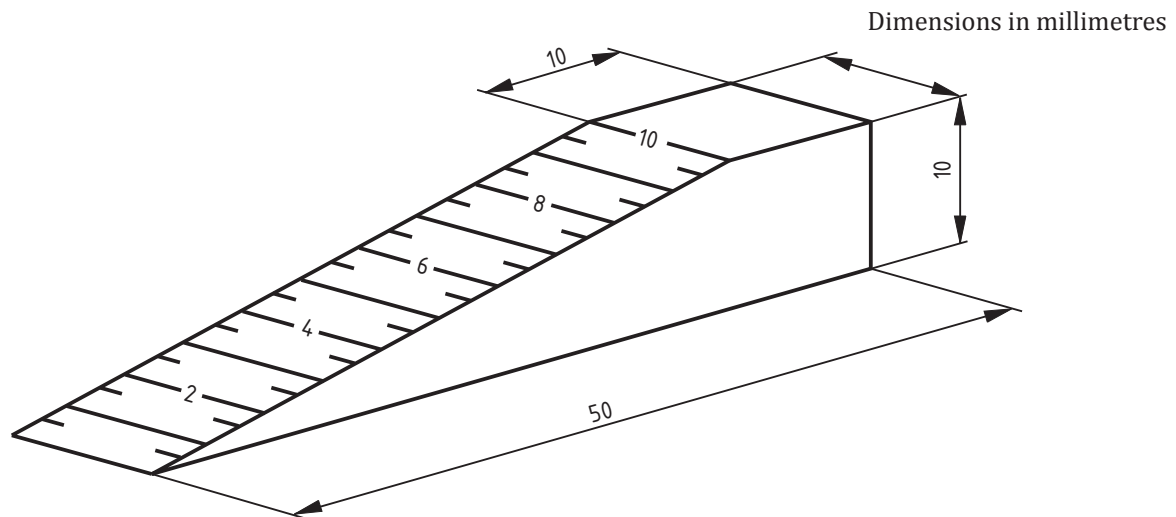

a) Type 1

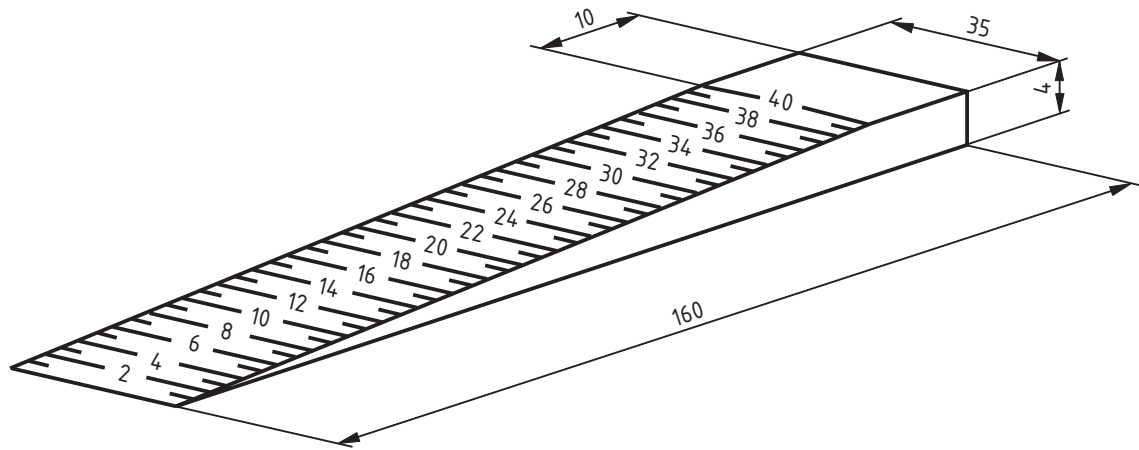

b) Type 2

Figure 4 — Two types of measuring wedge

5.4 **Graticule**, with 0,1 mm graduations and/or **feeler gauges** of an appropriate size and accuracy to be used for the measurement of crack width. If necessary, the gauges can be replaced by measuring wedges of appropriate accuracy.

5.5 **Sliding bevel**, for the measurement of angles.

5.6 **Depth gauge** calibrated in millimetres of depth, having a probe of 3 mm diameter.

5.7 **Breakage defect sizer**, with a slot uncovering 2 mm on both surfaces, for determination of minimum defect sizes for corner and edge defects, according to Figure 5.

NOTE 1 One breakage defect sizer can be used together with a steel straightedge for the measurement of corner defects (see 6.5). Two breakage defect sizers can be used together with a linear measuring device for the measurement of edge defects (see 6.6).

NOTE 2 A breakage defect sizer permits an objective definition of the point of departure for the measurement of the size of a broken edge.

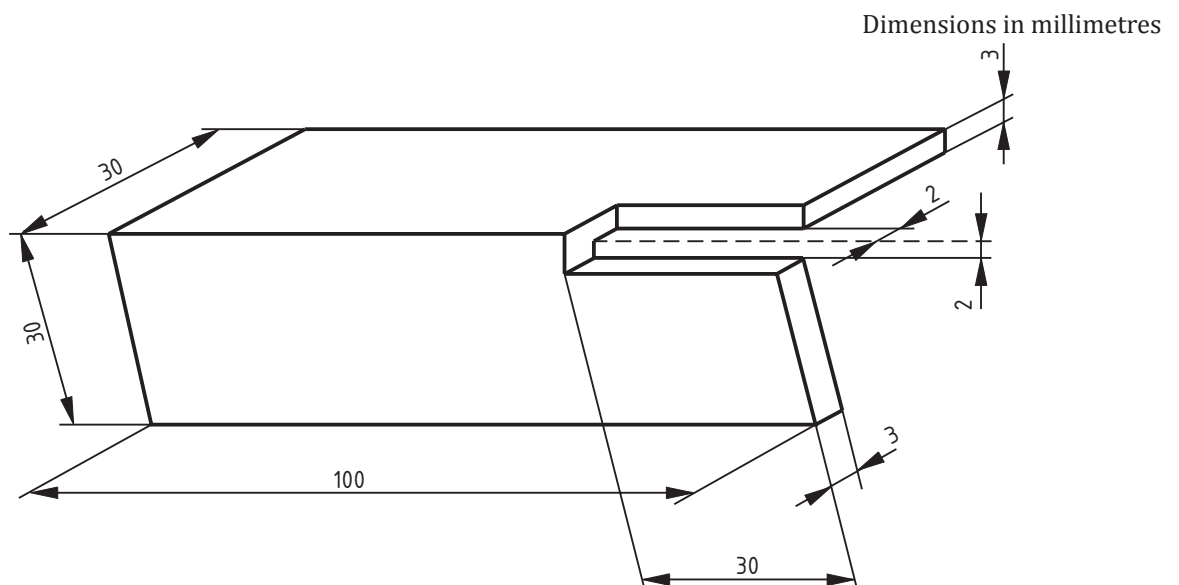


Figure 5 — Breakage defect sizer

5.8 **Balance**, capable of measuring to an accuracy of 1 %.

5.9 **Ultrasonic pulse velocity measuring equipment.**

5.10 **Equipment for determining the resonant frequency by mechanical shock.**

5.11 **Rebound hammer.**

5.12 **Drying oven**, capable of being controlled at $110\text{ °C} \pm 5\text{ °C}$.

5.13 **Furnace**, capable of operating at $1\ 050\text{ °C} \pm 25\text{ °C}$.

6 Inspection by attributes

6.1 Preparation of the test piece

The definition of edges may be improved, after any protrusions or indentations have been measured, by removing any projections such as fins or protrusions. This can normally be achieved by light abrasion.

6.2 Measurement of dimensions

Linear dimensions shall be measured by means of a linear measuring device (see 5.1), and unless otherwise agreed, shall be measured to the nearest 0,5 mm.

6.3 Measurement of angles

Angles shall be measured by adjusting the sliding bevel to fit the shape (see Figure 6) and the angle determined by the use of a protractor (see Figure 7).

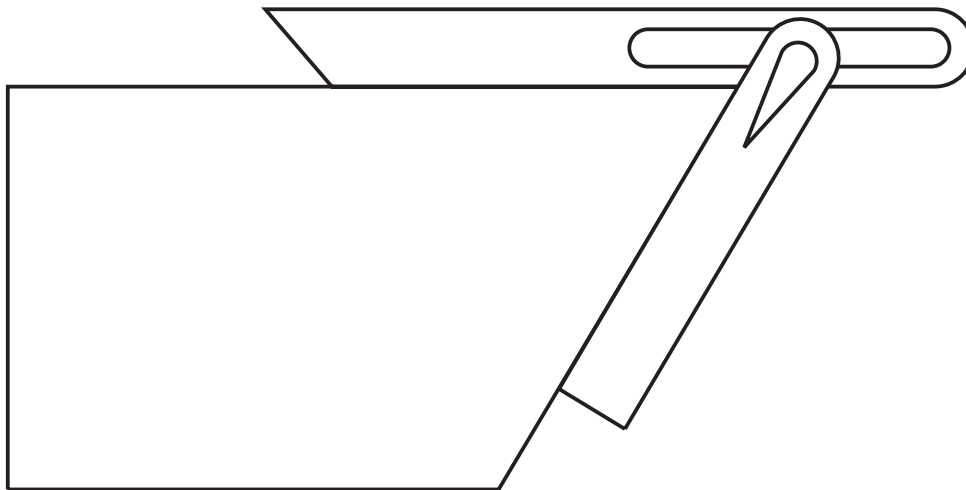


Figure 6 — Positioning the sliding bevel


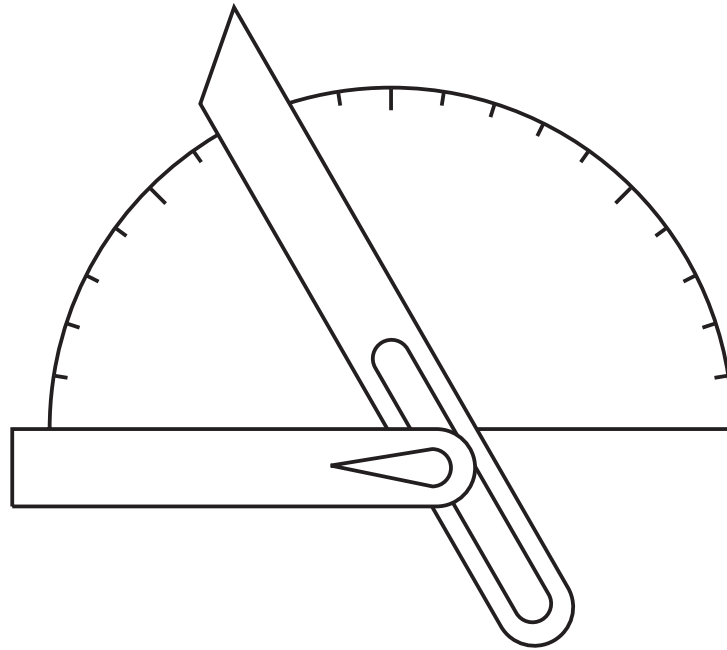


Figure 7 — Measurement of the angle

6.4 Measurement of warpage

For a concave surface, place the straightedge on edge across a diagonal of the surface being tested, insert a wedge at the point of maximum warpage (ensuring that the reading is not affected by raised imperfections on the castable surface) and record the maximum obtainable reading to the nearest 0,5 mm at the point of contact between the wedge and the straightedge.

For a convex surface, insert a wedge at each end of the straightedge and perpendicular to it as shown in Figure 8. Adjust the wedges, to a position not more than 15 mm from the corner of the shape, so that equal readings are obtained from each of them, making certain that contact is maintained by the straightedge at the point of maximum convexity. Record the readings to the nearest 0,5 mm.

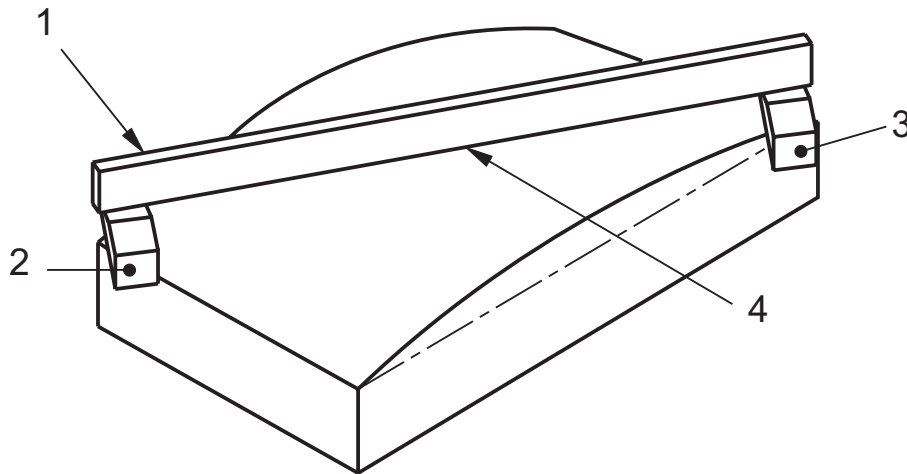

Key

- 1 Straight edge
- 2 Wedge
- 3 Wedge
- 4 Contact maintained at highest point of profile

Figure 8 — Measurement of convex warpage

Calculate the warpage ratio, W in percent, using the equation:

$$W = \frac{h}{l} \times 100$$


where

l is the length of the diagonal of the surface being tested, in millimetres;

h is the reading of the amount of warpage, in millimetres.

6.5 Measurement of corner defects

Measure the dimensions a , b and c of a corner defect using a steel straightedge, a breakage defect sizer and a steel tape, as indicated in Figure 9. The breakage defect sizer shall be positioned along the edge to be measured in such a way that the leading edge of the slot coincides with the broken corner on at least one surface of the shape, as shown in Figure 10. The dimensions a , b , and c are measured between the steel straightedge and the leading edge of the breakage defect sizer, to the nearest millimetre.

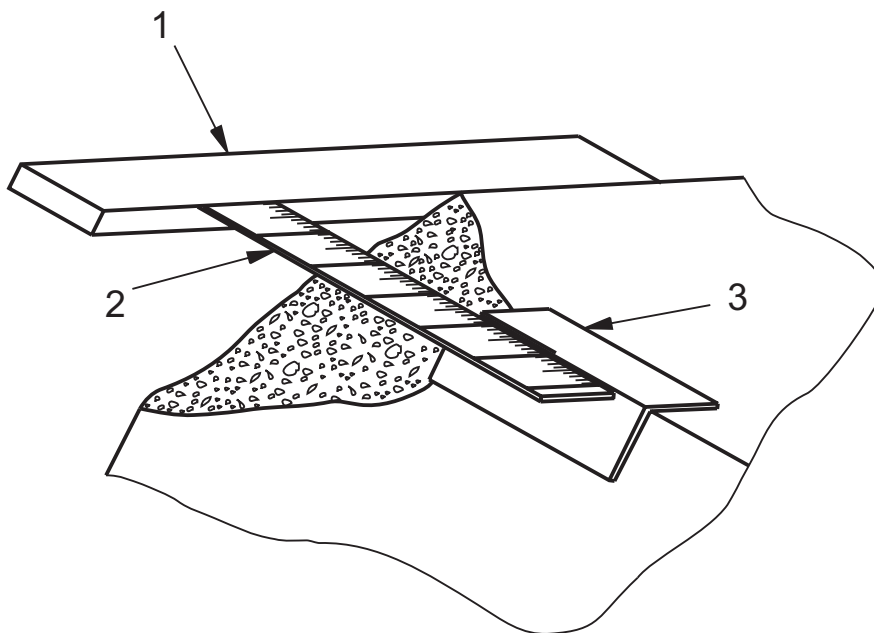

Key

- 1 Steel straightedge
- 2 Steel tape
- 3 Breakage defect sizer

Figure 9 — Measurement of a corner defect


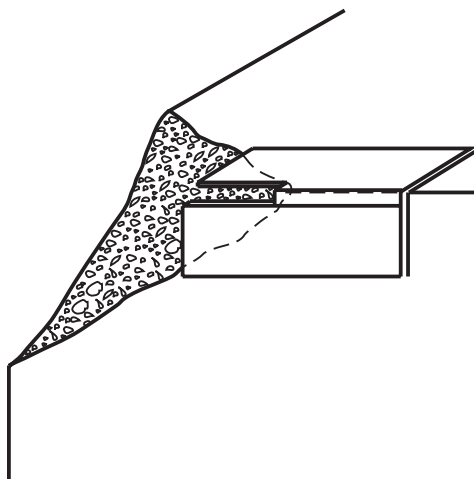


Figure 10 — Positioning the breakage defect sizer

6.6 Measurement of edge defects

Measure the length, g , of an edge defect using two breakage defect sizers and a steel tape, as indicated in Figure 11. Measure the depth of the edge defect as defined by e and f using a steel straightedge and a steel tape. Measure all dimensions to the nearest millimetre.

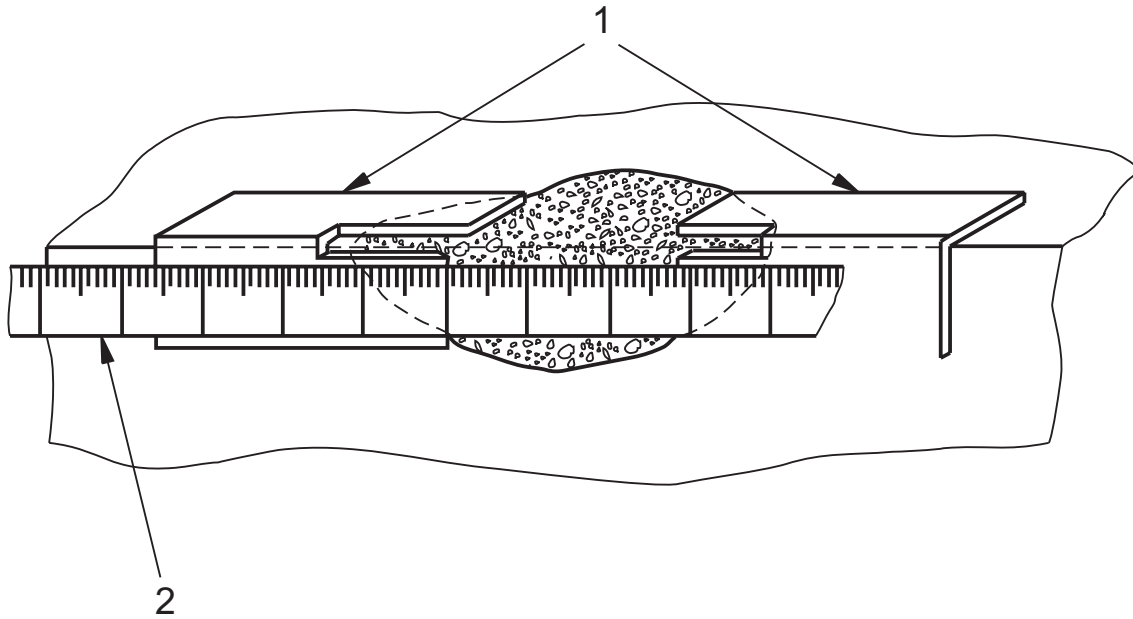

- Key**
- 1 Breakage defect sizers
 - 2 Steel tape

Figure 11 — Measurement of the length of an edge defect

6.7 Measurement of craters and bubbles


Measure the maximum and minimum diameter of a crater using a steel tape as indicated in Figure 12. The apparent crater diameter, d_a , is given by the equation:

$$d_a = \frac{D+d}{2}$$

where

- D is the maximum diameter of the crater, in mm;
- d is the minimum diameter of the crater, in mm.

Measure the depth, h in mm, of a crater using a depth gauge as indicated in Figure 12.

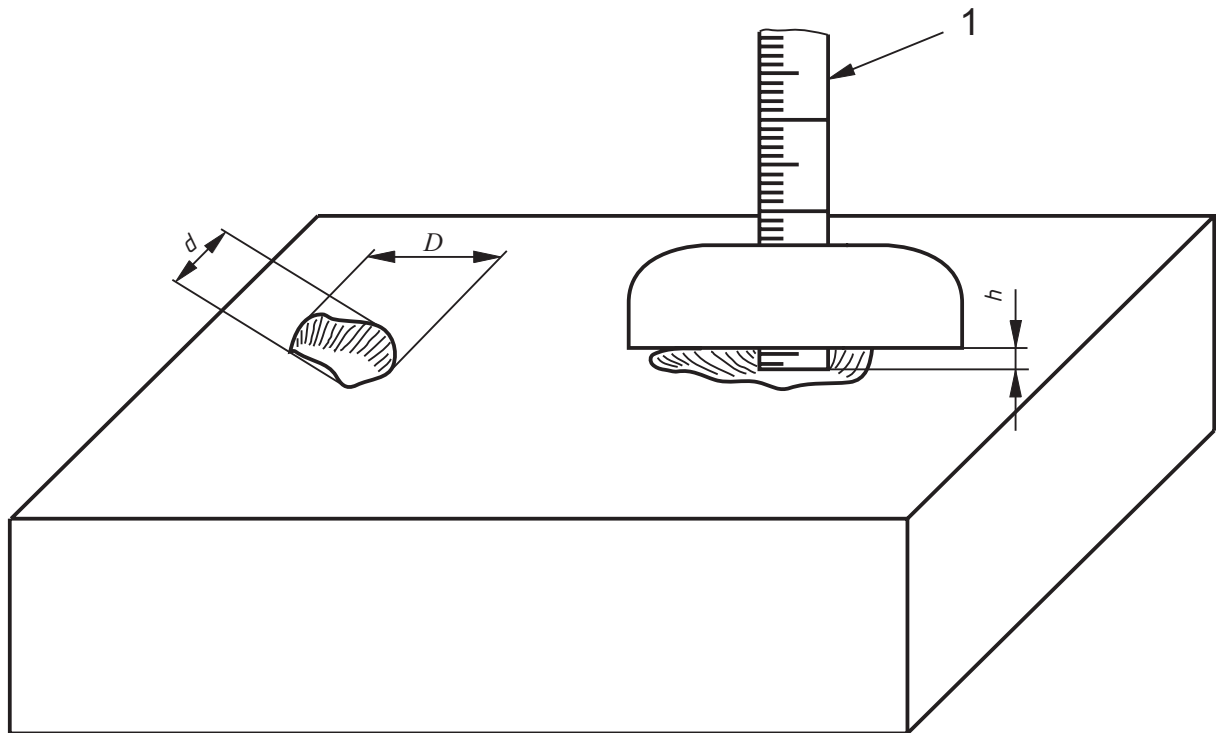

Key

- 1 depth gauge \varnothing 3 mm
- D maximum diameter of a crater
- d minimum diameter of a crater
- h depth of a crater

Figure 12 — Measurement of craters and bubbles

6.8 Measurement of cracks

Measure the maximum visible width of a crack with a steel tape in one or more straight lines. If the crack continues on more than one surface, then the crack length is equal to the sum of the crack lengths on each surface.

Measure the width of a crack either with a graticule or with feeler gauges (see 5.4).

Table 1 — Accuracy of measurement


Measurement	Accuracy of measurement
Length of crack	1 mm
Width of open crack: between 0,2 mm and 1 mm	0,2 mm
Width of open crack: greater than 1 mm	0,5 mm

Measure the dimensions of cracks to the accuracy given in Table 1. Surface crazing (see 3.5) shall be measured using a steel tape and reported in cm^2 .

6.9 Measurement of protrusions and indentations

Measure the height of a protrusion from the surface of the shape by means of a straightedge (see 5.2) and measuring wedges (see 5.3), to the nearest 0,5 mm. Place the straightedge parallel to the surface and in contact with the protrusion and adjust the measuring wedges so that equal readings are obtained

on each of them, as indicated in Figure 13. Measure indentations using the same method as used for craters (see 6.7).

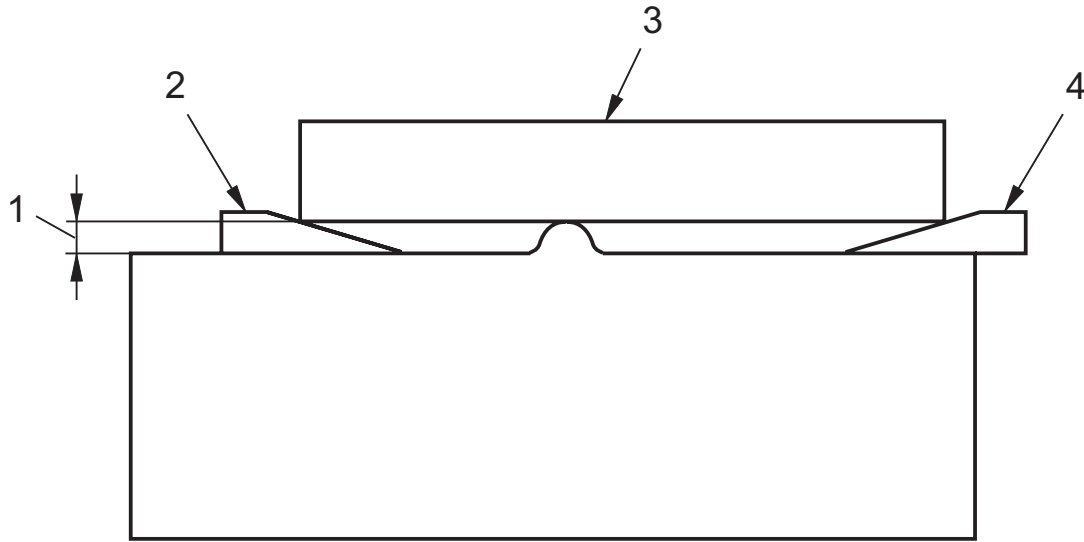

Key

1	Height
2	Measuring wedge
3	Straightedge
4	Measuring wedge

Figure 13 — Measurement of the height of a protrusion

6.10 Measurement of fins

Measure the height of fins to the nearest millimetre by the depth gauge or steel tape.

6.11 Segregations

Measure the extent of the honeycombed structure using a linear measuring device. Measure dimensions to the nearest millimetre.

NOTE If possible, the extent of fines segregation should be measured using a linear measuring device.

6.12 Friability

For dense castables, measure the extent to which areas of a block can be rubbed away using hand pressure.

7 Inspection by variables

7.1 Destructive test methods

7.1.1 General

The position in the shape from where test pieces will be taken shall be agreed between the parties involved and noted in the final report. If agreement cannot be reached, the reference for the location of the sample will be the centre of the shape. If a wet cutting method has been used to obtain a test piece from a pre-formed shape, it shall be dried immediately following preparation.

7.1.2 Physical properties

Wherever possible, the dimensions and testing of test pieces cut from pre-formed shapes shall be in accordance with ISO 1927-6. If this is not feasible, for example, if test pieces have to be cored or are of non standard dimensions, the test data will vary due to different test piece geometry.

NOTE The results obtained on testing a pre-formed shape will not equate to those obtained from a laboratory prepared test piece prepared according to ISO 1927-5..

7.1.3 Moisture content (see NOTE 2 of 7.1.4)

Weigh the shape or test piece on an appropriate sized balance to the nearest 1 %, and dry it in a drying oven at $110\text{ °C} \pm 5\text{ °C}$ to constant mass.

Calculate the loss in mass, M , as a percentage of the original mass using the equation:

$$M = \frac{m_1 - m_2}{m_1} \cdot 100$$

where

M is the moisture content, as a percentage;

m_1 is the original mass in kilograms;

m_2 is the dried mass in kilograms.

7.1.4 Loss on ignition

Dry the shape or test piece at $110\text{ °C} \pm 5\text{ °C}$ until constant mass. Allow to cool to ambient temperature and weigh to the nearest 1 %, recording the mass as m_3 . Fire at $1\ 050\text{ °C} \pm 25\text{ °C}$ until constant mass. Allow to cool and weigh to the nearest 1 %, recording the mass as m_4 .

Calculate the loss on ignition, L_1 , as a percentage of the final mass using the following equation:

$$L_1 = \frac{m_3 - m_4}{m_3} \cdot 100$$

where

L_1 is the loss on ignition, as a percentage;

m_3 is the mass after drying in kilograms;

m_4 is the final mass in kilograms.

NOTE 1 An intermediate temperature can be assigned for determining the loss on ignition. This temperature should be agreed between the parties involved prior to testing and noted in the final report.

NOTE 2 If it is not possible to determine the moisture content or the loss on ignition on a full shape then a test piece should be obtained without using wet cutting methods, for example by breaking the shape to obtain a representative test piece.

7.2 Non-destructive test methods

7.2.1 Ultrasonic testing

7.2.1.1 General

Ultrasonic testing techniques do not give commonly accepted physical properties, but are used to determine an overall quality level. The methods employed are applied to pre-dried and cooled shapes at ambient temperature.

7.2.1.2 Principle

Propagation of ultrasonic waves through a test piece and determining their velocity.


NOTE Shapes with special geometry (e.g. tubes, plates) or with irregular geometry can give spurious results. In such cases the reliability of the measurement should be checked by preliminary testing. Wherever possible, the contact surface should be greater than the area of the sensor.

7.2.1.3 Testing equipment (see Figure 14)

7.2.1.3.1 Two identical low frequency sensors, (between 40 kHz and 100 kHz) with low damping rate. One sensor shall be the emitter and the other sensor shall be the receiver.

7.2.1.3.2 A suitable contact system as a couplant between the sensors and the test pieces, e.g. silicone grease and/or rubber disks.

If possible, use a clamping device to maintain the sensors in contact with the test piece.

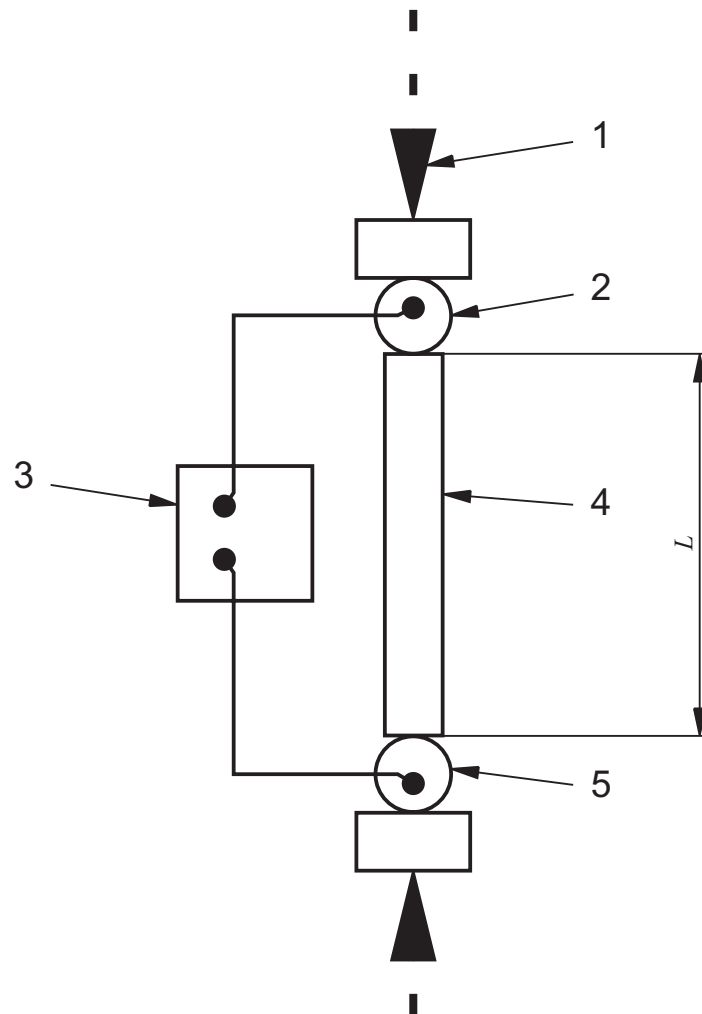

Key

- 1 System for moderate contact force
- 2 Transmitting transducer
- 3 Pulse transit timer
- 4 Test piece
- 5 Receiving transducer
- L Dimension along which the ultrasonic waves will be transmitted

Figure 14 — Block diagram of a suitable ultrasonic pulse velocity apparatus

7.2.1.4 Procedure

Measure, to within 0,5 mm, the dimension (L) along which the ultrasonic waves will be transmitted.

Calibrate the measuring apparatus with the calibration bar supplied by the manufacturer, or with an appropriate reference material, using the sensor couplant which will be used for the test.

Set the test piece between the sensors with the appropriate couplant in place.

Maintain the sensors in contact with the test piece at the points of measurement by hand pressure or using an appropriate device. Note the displayed propagation time. Repeat the test to check reproducibility. Recalibrate the apparatus when starting, every 50 measurements or when changing operators.

NOTE The number and direction of individual measurements on the test piece will depend on the test piece geometry.

7.2.1.5 Calculation

Calculate the ultrasonic propagation velocity, V in m/s, using the equation:

$$V = \frac{L}{t}$$

where

L is the dimension along the line of propagation in metres;

t is the propagation time in seconds.

7.2.1.6 Test report

The test report shall include the following information:

- a) the reference of the ultrasonic measurement apparatus and its characteristics;
- b) the reference and characteristics of the sensors;
- c) the type of contact system;
- d) individual and mean values of propagation velocity for each measurement direction.

7.2.2 Determination of the resonant frequency by mechanical shock

7.2.2.1 Principle

Excitation of a prismatic shape with an aspect ratio greater than 3 by mechanical shock and determination of its bending fundamental resonant frequency.

7.2.2.2 Testing equipment (see Figure 15)


7.2.2.2.1 Sensor, for the detection of the resonant frequency by contact (piezo electric pen) or without contact (microphone).

7.2.2.2.2 Impact hammer, (for example, a light hammer or screwdriver which has to be appropriate for the size and the hardness of the test piece).

7.2.2.2.3 Test piece support made from acoustically insulating material (for example, a layer of polyurethane foam, rubber prisms, or cylinders).

7.2.2.2.4 Acoustic insulating support, either a blanket of polyurethane foam, or two rubber bars with triangular or circular cross-section set at a distance from the shape extremities equal to 0,224 multiplied by the length of the test piece.

To obtain reproducible results, the impact and signal receiving points shall be accurately determined.

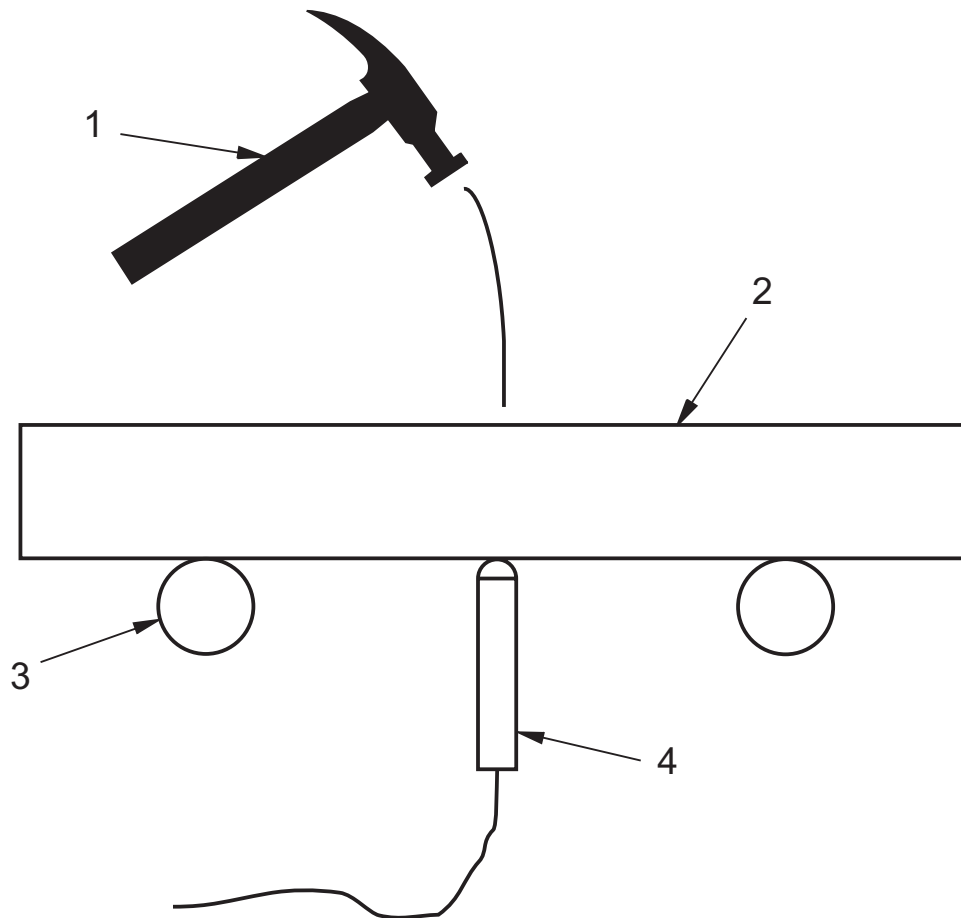

Key

- | | |
|---|---------------------|
| 1 | hammer |
| 2 | shape or test piece |
| 3 | rubber support |
| 4 | microphone |

Figure 15 — Block diagram of a suitable resonance frequency by mechanical shock apparatus

7.2.2.3 Procedure

Set the test piece on the acoustical insulating support.

Set the receiving sensor at the mid-length of the shape, taking into account the following considerations:

- if a piezoelectric pen is used, it shall be kept in contact with the centre of one of the largest sized faces;
- if a microphone is used, it shall be kept in contact with the centre of the lower face of the shape. In such a case the test piece shall be set on rubber prisms or cylinders.

Strike the centre of the upper face of the shape with a hammer and let it bounce freely. Note the reading displayed on the measuring apparatus. Repeat the measurement so as to obtain five corresponding values (the tolerance shall be defined with respect to the type of material and the size of the shape).

Report the mean of these five values, *S*.

7.2.2.4 Calculation

Calculate the resonant frequency, F in Hertz, using the equation:

$$F = \frac{2 \cdot 10^6}{t}$$

where t is the mean of the five values read on the apparatus, in microseconds.

7.2.2.5 Test report

The test report shall include the following information:

- a) the geometry of the shapes tested;
- b) the reference of the measuring apparatus for resonant frequency and its characteristics;
- c) the nature and the characteristics of the receiving sensor;
- d) the nature of the supports;
- e) the nature of the striking hammer;
- f) impact and receiving points of the measurement;
- g) individual and mean values of the resonant frequency.

7.2.3 Rebound hammer

7.2.3.1 Principle

A steel hammer impinges with a predetermined amount of energy a steel plunger in contact with a surface of the shape and the distance that the hammer rebounds is measured.

7.2.3.2 Testing equipment

7.2.3.2.1 Rebound hammer, consisting of a spring-loaded steel hammer which when released strikes a steel plunger in contact with the surface of the shape. The spring-loaded hammer shall travel with a consistent and reproducible velocity. The rebound distance of the steel hammer from the steel plunger is measured on a linear scale attached to the frame of the instrument.

7.2.3.2.2 Abrasive stone, consisting of a medium grain textured silicon carbide or equivalent material.

7.2.3.2.3 Test anvil, approximately 150 mm diameter by 150 mm high cylinder of high carbon tool steel with an impact area hardened to Rockwell 65 C to 67 C. An instrument guide is required to centre the rebound hammer over the impact area and keep the instrument perpendicular to the surface.

7.2.3.3 Test shapes

Shapes to be tested shall be at least 100 mm thick. Areas exhibiting honeycombing, scaling or high porosity shall be avoided.

A test area shall be at least 150 mm in diameter. Heavily textured, soft or loose surfaces shall be ground smooth with the abrasive stone.

7.2.3.4 Procedure

Hold the instrument firmly so that the plunger is perpendicular to the test surface. Gradually push the instrument towards the test surface until the hammer strikes. After impact, maintain pressure on the instrument and, if necessary, depress the button on the side of the instrument to lock the plunger in its retracted position. Estimate the rebound number on the scale to the nearest whole number. Take 10 readings from each test area. No two impact tests shall be closer than 25 mm. Examine the impression made on the surface of the shape after impact, and if the impact crushes or breaks through a surface void disregard the reading and take another.

7.2.3.5 Test report

The test report shall contain the following information:

- a) location of the area tested on the shape;
- b) description of test area including surface characteristics;
- c) if surface was ground and depth of grinding;
- d) hammer identification and serial number;
- e) orientation of hammer during test;
- f) average rebound number for test area.

7.2.4 Mass

Weigh the shape to the nearest 1 % on an appropriate sized balance.

7.2.5 Bulk density

Calculate the geometric bulk density, ρ_g , in kilograms per cubic metre, using the equation:

$$\rho_g = \frac{m}{V}$$

where

m is the mass of the shape as determined in 7.2.4, in kilograms;

V is the volume of the shape obtained by calculation using the mean dimensions as determined in 6.2, in cubic metres.

Express the result to the nearest 1 %.

8 Test report

The test report shall contain the following information:

- a) all information necessary for identification of the sample tested, including the designation of the pre-formed shapes tested (manufacturer, type, shape, date of forming, batch number and, if applicable, any thermal pre-treatment);
- b) a reference to this International Standard, i.e. ISO 1927-7:2012;
- c) the methods used and the properties inspected;
- d) the number of items tested;

- e) if test pieces have been taken, the number and location in the pre-formed shape;
- f) the results of the tests, including the results of the individual determinations and their means, calculated as specified in Clauses 6 and 7, and including extra information specified in those clauses;
- g) any deviations from the procedure specified;
- h) any unusual features (anomalies) observed during the test;
- i) the name of the testing establishment;
- j) date of the test.

Bibliography

- [1] ISO 1927-3, *Unshaped refractory products - Part 3: Characterization as received*
- [2] ISO 1927-5, *Unshaped refractory products - Part 5: Preparation and treatment of test pieces*
- [3] ISO 12678-1, *Refractory products — Measurement of dimensions and external defects of refractory bricks — Part 1: Dimensions and conformity to drawings*
- [4] ISO 12678-2, *Refractory products — Measurement of dimensions and external defects of refractory bricks — Part 2: Corner and edge defects and other surface imperfections*

British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at bsigroup.com/standards or contacting our Customer Services team or Knowledge Centre.

Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at bsigroup.com/shop, where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to bsigroup.com/subscriptions.

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

PLUS is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit bsigroup.com/shop.

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email bsmusales@bsigroup.com.

BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK

Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

Copyright

All the data, software and documentation set out in all British Standards and other BSI publications are the property of and copyrighted by BSI, or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI. Details and advice can be obtained from the Copyright & Licensing Department.

Useful Contacts:

Customer Services

Tel: +44 845 086 9001

Email (orders): orders@bsigroup.com

Email (enquiries): cservices@bsigroup.com

Subscriptions

Tel: +44 845 086 9001

Email: subscriptions@bsigroup.com

Knowledge Centre

Tel: +44 20 8996 7004

Email: knowledgecentre@bsigroup.com

Copyright & Licensing

Tel: +44 20 8996 7070

Email: copyright@bsigroup.com



...making excellence a habit.™