

CONTROLLED

ORIGINAL

**Textiles —**

**Yarns from packages —**

**Determination of single-end  
breaking force and elongation  
at break**

The European Standard EN ISO 2062 : 1995 has the status of a British Standard



THE LONDON POLYTECHNIC  
UNIVERSITY LIBRARY  
SPECIAL COLLECTIONS

NO COPYING OR DISTRIBUTION WITHOUT PERMISSION FROM BSI

BSI

8 SEP 1995

# Committees responsible for this British Standard

CONTROLLED

ORIGINAL

The preparation of this British Standard was entrusted to Technical Committee TCI/24, Physical testing of textiles, upon which the following bodies were represented:

Association of Consulting Scientists  
 Association of Suppliers to the British Clothing Industry  
 British Nonwovens Manufacturers' Association  
 British Polyolefin Textiles Association  
 British Textile Confederation  
 British Textile Machinery Association  
 British Textile Technology Group  
 British Throwsters Association  
 Furniture Industry Research Association  
 International Wool Secretariat  
 Ministry of Defence  
 National Wool Textile Export Corporation  
 SATRA Footwear Technology Centre  
 Society of Dyers and Colourists  
 Textile Finishers' Association  
 Textile Institute

This British Standard, having been prepared under the direction of the Materials and Chemicals Sector Board, was published under the authority of the Standards Board and comes into effect on 15 June 1995

© BSI 1995

The following BSI references relate to the work on this standard:

Committee reference TCI/24  
 Draft for comment 91.417147 DC

## Amendments issued since publication

Amd. No.	Date	Text affected

CONTROLLED

# Contents

ORIGINAL

	Page
Committees responsible	Inside front cover
National foreword	ii
Foreword	2
<b>Method</b>	
Introduction	3
1 Scope	4
2 Normative references	4
3 Definitions	4
4 Principle	5
5 Apparatus and materials	5
6 Sampling	5
7 Preconditioning and conditioning	6
8 Procedure	6
9 Test report	7
<b>Annexes</b>	
<b>A</b> (informative) Alternative methods using constant rate of travel (CRT) and constant rate of loading (CRL) testers	8
<b>NA</b> (normative) Normative references to international publications with their relevant European publications	10

CONTROLLED



## National foreword

ORIGINAL

This British Standard has been prepared by Technical Committee TCI/24 and is the English language version of EN ISO 2062 : 1995 *Textiles — Yarns from packages — Determination of single-end breaking force and elongation at break*, published by the European Committee for Standardization (CEN). It is identical with ISO 2062 : 1993 published by the International Organization for Standardization (ISO).

This British Standard supersedes BS 1932 : Part 1 : 1989, which is withdrawn.

**Compliance with a British Standard does not of itself confer immunity from legal obligations.**



ICS 59.080.20

Descriptors: Breaking load, definitions, elongation at fracture, sampling methods, testing, textile testing, textiles, twine, yarn, elongation at break, sampling, textile industry, tests

English version

## Textiles — Yarns from packages — Determination of single-end breaking force and elongation at break

(ISO 2062 : 1993)

Textiles — Fils sur enroulements — Détermination de la force de rupture et l'allongement à la rupture du fil individuel  
(ISO 2062 : 1993)

Textilien — Garne von Aufmachungseinheiten — Bestimmung der Höchstzugkraft und Höchstzugkraftdehnung von Garnabschnitten  
(ISO 2062 : 1993)

This European Standard was approved by CEN on 1995-12-12. CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration.

Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Central Secretariat or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Central Secretariat has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and United Kingdom.

### CEN

European Committee for Standardization  
Comité Européen de Normalisation  
Europäisches Komitee für Normung

Central Secretariat: rue de Stassart 36, B-1050 Brussels

**CONTROLLED**


**ORIGINAL**

## **Foreword**

The text of the International Standard has been taken as a European Standard by the Technical Committee CEN/TC 248, Textiles and textile products, from ISO/TC 38, Textiles, of the International Organization for Standardization

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by October 1995, and conflicting national standards shall be withdrawn at the latest by October 1995.

According to the CEN/CENELEC Internal Regulations the following countries are bound to implement this European Standard: Austria, Belgium, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland, United Kingdom.

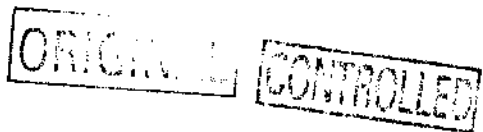

## Introduction

In the 1950s and 1960s when this International Standard was first prepared, three types of tensile tester were in wide use: constant rate of specimen extension (CRE), constant rate of travel (CRT), and constant rate of loading (CRL). It was therefore advisable to state the rate of operation in a way which would be common to all three types of tester. In addition, the best possible agreement was sought between test results of the three types of tester. Consequently, the principle of constant time to break was adopted and 20 s to break was chosen for this International Standard and also for a number of national standards.

In the early 1990s when the present revision was prepared, CRE testers were recognized as the best type, while CRT and CRL testers were quickly becoming obsolete. However, since CRT and CRL testers are still in use internationally, the procedure for using them is included in an informative annex. There is no assurance that the results from the three types of tester will agree.

This International Standard considers CRE testers only, so the time-to-break principle is no longer needed and a simpler statement of rate of displacement is used. The rate of extension of 100 % per minute is adopted as standard, but higher rates are permitted by agreement for automatic testers.

CONTROLLED

ORIGINAL

# Textiles — Yarns from packages — Determination of single-end breaking force and elongation at break

## 1 Scope

1.1 This International Standard specifies methods for the determination of the breaking force and elongation at break of textile yarns taken from packages.

Four methods are given:

- A: manual; specimens are taken directly from conditioned packages;
- B: automatic; specimens are taken directly from conditioned packages;
- C: manual; relaxed test skeins are used after conditioning;
- D: manual; specimens are used after wetting.

1.2 Method C should be used in cases of dispute regarding elongation at break of the yarn.

NOTE 1 Methods A, B and C are expected to give the same results for yarn strength but method C may give somewhat truer (and higher) values of elongation than A or B. Method D is likely to give results differing, for both breaking force and elongation at break, from those obtained method A, B or C.

1.3 This International Standard specifies methods using constant rate of specimen extension (CRE) tensile testers. Testing on the now obsolete constant rate of travel (CRT) and constant rate of loading (CRL) instruments is covered, for information, in annex A, in recognition of the fact that these instruments are still popular and may be used by agreement.

1.4 This International Standard applies to all types of yarn except glass yarns, elastomeric yarns, aramid yarns, ceramic yarns, carbon yarns and polyolefin tape yarns.

NOTE 2 A method for the testing of glass yarns is given in ISO 3341:1984, *Textile glass — Yarns — Determination of breaking force and breaking elongation*.

1.5 This International Standard is applicable to yarns from packages but can be applied to yarns extracted from fabrics, subject to agreement between the interested parties.

1.6 It is intended for the single-end (single-strand) testing of yarns.

NOTE 3 The skein method of testing is given in ISO 6939:1988, *Textiles — Yarns from packages — Method of test for breaking strength of yarn by the skein method*.

## 2 Normative references

The following standards contain provisions which, through reference in this text, constitute provisions of this International Standard. At the time of publication, the editions indicated were valid. All standards are subject to revision, and parties to agreements based on this International Standard are encouraged to investigate the possibility of applying the most recent editions of the standards indicated below. Members of IEC and ISO maintain registers of currently valid International Standards.

ISO 139:1973, *Textiles — Standard atmospheres for conditioning and testing*.

ISO 2060:—<sup>1)</sup>, *Textiles — Yarn from packages — Determination of linear density (mass per unit length) by the skein method*.

## 3 Definitions

For the purposes of this International Standard, the following definitions apply.

1) To be published. (Revision of ISO 2060:1972)



ORIGINAL

CONTROLLED

**3.1 breaking force (load):** Maximum force applied to a specimen in a tensile test carried to rupture. For yarns, it is preferably expressed in centinewtons.

**3.2 elongation at break:** Increase in length of a specimen produced by the breaking force. It is expressed as a percentage of the original nominal length.

**3.3 breaking tenacity:** Ratio of a yarn's breaking force to its linear density. It is usually expressed in centinewtons per tex.

**3.4 constant rate of specimen extension (CRE) tester:** Testing machine in which one end of the specimen is held in a virtually stationary clamp and the other end is gripped in a clamp that is driven at a constant speed. A suitable system is provided for detecting and recording the force applied and the elongation.

**3.5 clamp:** That part of a tensile testing machine used to grip the specimen by means of suitable jaws.

**3.6 jaws:** Those elements of a clamp which grip the specimen.

**3.7 gauge length:** Length of the specimen measured between the points of attachment to clamps while under tension. In bollard or capstan clamps, it is the distance between their gripping points, measured along the path of the yarn.

**3.8 package:** Length of yarn in a form suitable for use, handling, storing, etc. Packages can be supported (e.g. cones, bobbins) or unsupported (e.g. skeins, balls).

## 4 Principle

A specimen of yarn is extended until rupture by a suitable mechanical device, and the breaking force and elongation at break are recorded. A constant rate of specimen extension of 100 % per minute (based on the initial specimen length) is used, but higher rates are permitted for automatic testers on agreement. Two gauge lengths are permitted: usually 500 mm (with a rate of displacement of 500 mm/min), and exceptionally 250 mm (with a rate of displacement of 250 mm/min).

## 5 Apparatus and materials

**5.1 Constant rate of specimen extension (CRE) tester,** which complies with the following requirements.

- a) The tester shall be capable of being set at gauge lengths of  $500 \text{ mm} \pm 2 \text{ mm}$  or  $250 \text{ mm} \pm 1 \text{ mm}$ , or preferably both.

- b) The constant rate of displacement of the moving clamp shall be 500 mm/min or 250 mm/min, to an accuracy of  $\pm 2 \%$ , with higher rates being permitted for automatic testers on agreement.

- c) The maximum error of the indicated force shall not exceed 2 % of the true force.

- d) The tester may be of the manual or automatic type.

- e) The clamps for gripping the specimens shall prevent slipping or cutting of the specimens and breaks at the jaws. Flat-faced unlined jaws shall be the normal type but, if these cannot prevent slippage, then other types of clamp may be used on agreement, such as lined jaws, bollard clamps or other types of snubbing device. As the type of clamp may influence the reading of the elongation, all parties shall use the same type.

- f) The tester shall be equipped with an autographic force/elongation recording device of sufficiently fast response, or with a system directly recording the breaking force and elongation at break.

- g) The tester shall be capable of setting a pretension either by means of a set of pretensioning weights or by the use of the force-measuring device.

**5.2 Reel,** for preparing test skeins from the laboratory sample (for methods C and D).

**5.3 Swift,** or similar device, for holding the test skein under zero tension and permitting easy transfer of the yarn to the tensile tester (for method C).

**5.4 Receptacles,** for immersing the sample or the specimens in water (for method D).

**5.5 Tap water,** at room temperature (for method D).

**5.6 Nonionic surfactant,** 0,1 % aqueous solution (for method D).

## 6 Sampling

**6.1** Samples shall be taken in accordance with

- a) the directions given in the material specification when available, or  
b) the procedures described in 6.2 to 6.7.

**6.2** A bulk sample shall be taken of one or more cases, as representative of the lot to be tested as follows:

CONTROLLED

ORIGINAL

No. of cases	No. of cases selected at random
3 or less	1
4 to 10	2
11 to 30	3
31 to 75	4
76 or more	5

**6.3** If only mean values are required, then 10 packages shall be taken from the bulk sample, distributed as evenly as possible among the cases and among the levels in each case.

**6.4** Except for the provisions of 6.5, the minimum number of specimens to be tested shall be 50 for single spun yarns and 20 for other yarns. The specimens shall be distributed as evenly as possible among the 10 packages.

**6.5** If the variability of the tests is known and only mean values are required, then the number of specimens shall be calculated as  $0,17v^2$ , where  $v$  is the coefficient of variation of the individual breaks (expressed as a percentage) obtained from experience on similar material.

#### NOTES

4 This number of specimens will give a precision ( $1,96 \times$  the standard error of the mean) of  $\pm 4\%$  at a probability level of 90 %.

5 Strength testing is a "one-tail" test; that is, "yarn shall not be weaker than ..." but "may be stronger than ...". When specifying 90 % probability, one tail of the distribution is 5 %, or exactly the same as the two tails together of the more common 95 % probability appropriate for a "two-tail" test.

**6.6** If the coefficient of variation is to be determined in addition to the mean, then 20 packages shall be taken from the bulk sample and at least 200 specimens shall be tested for single spun yarns and at least 100 specimens for all other types of yarn.

**6.7** If specimens are to be extracted from fabrics [not suitable for automatic testers (method B)], then the fabric sample shall be large enough to furnish a sufficient number and length of specimens. The test specimens shall be taken so that the twist in the yarn is not changed during sampling. In woven fabrics, warp specimens shall be taken from different ends and weft specimens shall be taken at random from several sections of the sample to be as representative of the yarn as possible. In knitted fabrics, specimens shall represent as many different yarns as possible.

## 7 Preconditioning and conditioning

**7.1** The atmospheres for preconditioning, conditioning and testing shall be as specified in ISO 139.

**7.2** For methods A to C, the sample packages or test skeins shall be preconditioned for a minimum of 4 h.

NOTE 6 Preconditioning can often be dispensed with if the samples are conditioned directly "from the dry side".

**7.3** After preconditioning, the sample shall be brought to moisture equilibrium under the conditioning atmosphere. For skeins, overnight conditioning is usually sufficient, but for tightly wound packages a minimum of 48 h is necessary.

**7.4** Preconditioning and conditioning are not required for wet tests (method D).

## 8 Procedure

### 8.1 General

**8.1.1** If more than one condition of testing is permitted, usually by agreement, then all parties interested in the test results shall perform the test under the same conditions (i.e. gauge length, rate of displacement, type of clamp, temperature, pretension).

**8.1.2** Two gauge lengths are permitted: the usual length of 500 mm, and a length of 250 mm which can be used only if

- the extension of the instrument is insufficient to accommodate a 500 mm specimen, or
- by agreement between the parties.

**8.1.3** If calculation of the breaking tenacity is required, determine the linear density of the yarn in accordance with ISO 2060.

**8.1.4** Use a rate of displacement of 500 mm/min at the gauge length of 500 mm, and 250 mm/min at the gauge length of 250 mm. In addition, for automatic testers only (method B), higher rates are permitted by agreement; 400 %/min or 1 000 %/min are recommended.

**8.1.5** Unwind the yarn from the package as is done in normal use.

**8.1.6** Before clamping the specimen, check that the jaws are correctly aligned and parallel, so that the force applied produces no angular deviation.

**8.1.7** Insert the specimen in the clamps with a pretension of  $0,5 \text{ cN/tex} \pm 0,1 \text{ cN/tex}$  for conditioned specimens, or  $0,25 \text{ cN/tex} \pm 0,05 \text{ cN/tex}$  for wet specimens. For textured yarns, use a pretension which will remove the crimp but not stretch the yarn.

ORIGINAL

CONTROL

**NOTE 7** For textured yarns, the following pretensions are recommended (unless otherwise agreed), calculated on the nominal linear density of the yarn:

2,0 cN/tex  $\pm$  0,2 cN/tex, for polyester and polyamide yarns;

1,0 cN/tex  $\pm$  0,1 cN/tex, for acetate, triacetate and viscose yarns;

0,5 cN/tex  $\pm$  0,05 cN/tex, for bi-shrinkage and jet-bulked yarns, except for carpet yarns heavier than 50 tex.

**8.1.8** Finally, secure the specimen in the clamps.

**8.1.9** Perform the test under the standard atmosphere for testing, as specified in 7.1.

**8.1.10** During the test, check that the specimen does not slip between the jaws by more than 2 mm. If it does so repeatedly, change the clamps or jaw lining. Discard the results of the tests where slippage occurs. Also discard results of jaw breaks where breaks occur 5 mm to the jaws or closer.

**8.1.11** Record the breaking force and elongation at break (done automatically in method B). For fancy yarns, record values for the first component that breaks.

#### NOTES

8 The values recorded for fancy yarns may be lower than those defined in 3.1 and 3.2.

9 With bollard or capstan clamps, measurement of the elongation is not accurate and is discouraged.

### 8.2 Method A, manual

Take specimens directly from the conditioned packages.

Follow the procedures given in 8.1.1 to 8.1.11. Insert the test specimens manually into the clamps to perform the tensile test.

### 8.3 Method B, automatic

Take specimens directly from the conditioned packages.

Follow the procedures given in 8.1.1 to 8.1.6 and 8.1.9 to 8.1.11. Set the instrument to take specimens from the 10 or 20 packages of the sample (see 6.3 and 6.6). The test will be performed automatically.

### 8.4 Method C, manual, conditioned specimens

**8.4.1** Using the reel (5.2), take one test skein from each package of the sample. The test skeins shall be of sufficient length to give the required number and length of test specimens.

**8.4.2** Using the swift (5.3), allow the test skeins to relax under minimal tension in the preconditioning and conditioning atmospheres (see 7.1).

**8.4.3** Follow the procedures given in 8.1.1 to 8.1.11. When taking a specimen from the test skein for insertion between the clamps, make sure its length is at least 100 mm greater than the selected gauge length; an excess of 500 mm is recommended. Be careful not to change the twist.

**NOTE 10** With suitable modifications (see 6.7), this method may also be used for yarns from fabrics.

### 8.5 Method D, manual, wet specimens

**8.5.1** Take test skeins as described in 8.4.1.

**8.5.2** Before removing the test skein from the reel, wrap two or three turns of a strong thread (e.g. sewing thread) tightly around the skein at two places about 2 cm apart and securely tie the ends of the thread. Cut the skein midway between the two places. Fill a receptacle (5.4) with water (5.5). Lay the cut skein flat on the surface of the water and leave it until it sinks below the surface under its own weight.

**8.5.3** If the skein will not sink in the water, then hold the yarn under the surface, e.g. by means of weights attached to the ends, until the yarn is thoroughly saturated (e.g. for 30 min). When the yarns are normally resistant to wetting, use a nonionic wetting agent (5.6). Rinse out the wetting agent thoroughly with water before testing the yarn.

**8.5.4** Remove the specimens individually from the water and test them within 60 s thereafter, following the procedures given in 8.1.1 to 8.1.11.

## 9 Test report

### 9.1 General information

The test report shall include the following information:

- a) a reference to this International Standard (ISO 2062);
- b) lot number or other identification of the sample;
- c) type of package (cone, bobbin, etc.), its condition (dyed, bleached, etc.), and the manner in which

the yarn was withdrawn from the package (over-end or from the side);

- d) conditioning atmosphere and testing atmosphere used;
- e) sampling scheme used, the number of specimens tested, and number of specimens discarded;
- f) make of tester used;
- g) test method used (A to D);
- h) gauge length, rate of displacement and pretension used;
- i) type of clamp and jaws used;
- j) date of the test.

## **9.2 Test results**


The following test results shall be given:

- a) mean breaking force, in centinewtons (to three significant figures);
- b) mean elongation at break, as a percentage (to two significant figures);
- c) coefficient of variation of the breaking force, if required (to the nearest 0,1 %);
- d) coefficient of variation of percent elongation at break, if required (to the nearest 0,1 %);
- e) linear density of the yarn, if determined, in tex (to three significant figures);
- f) breaking tenacity, if required, in centinewtons per tex (to the nearest 0,1 cN/tex).

ORIGINAL

CONTROLLED

**Annex A**  
(informative)

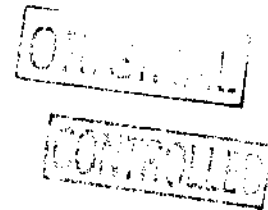

**Alternative methods using constant rate of travel (CRT) and constant rate of loading (CRL) testers**

**A.1 Scope**

This annex describes seven methods:

- E: CRT testers, manual; specimens are taken directly from conditioned packages;
- F: CRT testers, manual; relaxed test skins are used after conditioning;
- G: CRT testers, manual; relaxed test skins are used after wetting;
- H: CRL testers, manual; specimens are taken directly from conditioned packages;
- J: CRL testers, automatic, specimens are taken directly from conditioned packages;
- K: CRL testers, manual; relaxed test skins are used after conditioning;
- L: CRL testers, manual; relaxed test skins are used after wetting.

These methods are given for information only and can be used on agreement between the interested parties.

**A.2 Procedure**

**A.2.1 General**

Follow clauses 8.1 to 8.3, 8.5, 8.6, if possible 8.7, and also 8.8 to 8.11 and 9.

**A.2.2 Method E: CRT testers, manual**

**A.2.2.1** Use a pendulum tester which complies with the following requirement. After the first 2 s of the test, the average rate of travel for the pulling clamp in any 2-s interval shall not differ by more than 5 % from the average rate of travel over the whole period of the test.

Adjust the instrument so that the average time-to-break shall be  $20 \text{ s} \pm 3 \text{ s}$ . Also adjust the tester so

that the recorded breaking force lies between 15 % and 85 % of the instrument's scale.

**A.2.2.2** Follow the procedure given in method A (8.2), omitting 8.1.4.

**A.2.3 Method F: CRT testers, manual**

Follow the procedure given in A.2.2.1 and then follow method C (8.4), omitting 8.1.4.

**A.2.4 Method G: CRT testers, manual**

Follow the procedure given in A.2.2.1 and then follow method D (8.5), omitting 8.1.4.

**A.2.5 Method H: CRL testers, manual**

**A.2.5.1** Use an inclined-plane tester complying with the following requirement. After the first 4 s of the test, the average rate of increase of force in any 2-s interval shall not differ by more than 25 % from the average rate of increase of the force over the whole period of the test.

Adjust the instrument so that the average time-to-break shall be  $20 \text{ s} \pm 3 \text{ s}$ . Also adjust the tester so that the recorded breaking force lies between 15 % and 85 % of the instrument's scale.

**A.2.5.2** Follow the procedure given for method A (8.2), omitting 8.1.4.

**A.2.6 Method J: CRL testers, automatic**

Follow the procedure given in A.2.5.1 and then follow method B (8.3), omitting 8.1.4.

**A.2.7 Method K: CRL testers, manual**

Follow the procedure given in A.2.5.1 and then follow method C (8.4), omitting 8.1.4.

**A.2.8 Method L: CRL testers, manual**

Follow the procedure given in A.2.5.1 and then follow method D (8.5), omitting 8.1.4.

CONTROLLED

ORIGINAL

**Annex ZA (normative)****Normative references to international publications with their relevant European publications**

This European Standard incorporates by dated or undated reference, provisions from other publications. These normative references are cited at the appropriate places in the text and the publications are listed hereafter. For dated references, subsequent amendments to or revisions of any of these publications apply to this European Standard only when incorporated in it by amendment or revision. For undated references the latest edition of the publication referred to applies (including amendments).

Publication	Year	Title	EN	Year
ISO 139	1973	<i>Textiles — Standard atmospheres for conditioning and testing</i>	EN 20139	1992
ISO 2060	1994	<i>Textiles — Yarn from packages — Determination of linear density (mass per unit length) by the skein method</i>	EN ISO 2060	1995

## BSI — British Standards Institution

BSI is the independent national body responsible for preparing British Standards. It presents the UK view on standards in Europe and at the international level. It is incorporated by Royal Charter.

### Contract requirements

A British Standard does not purport to include all the necessary provisions of a contract. Users of British Standards are responsible for their correct application.

### Revisions

British Standards are updated by amendment or revision. Users of British Standards should make sure that they possess the latest amendments or editions.

Any person who finds an inaccuracy or ambiguity while using this British Standard should bring it to the attention of the Quality Manager, BSI without delay so that the matter may be investigated swiftly.

BSI offers members an individual updating service called PLUS which ensures that subscribers automatically receive the latest editions of standards.

### Buying standards

Orders for all BSI, international and foreign standards publications should be addressed to Customer Services, Sales Department at Chiswick:  
Tel: 0181 996 7000; Fax: 0181 996 7001.

In response to orders for international standards, it is BSI policy to supply the BSI implementation of those that have been published as British Standards, unless otherwise requested.

### Information on standards

BSI provides a wide range of information on national, European and international standards through its Library, the Standardline Database, the BSI Information Technology Service (BITS) and its Technical Help to Exporters Service. Contact the Information Department at Chiswick:  
Tel: 0181 996 7111; Fax: 0181 996 7048.

Subscribing members of BSI are kept up to date with standards developments and receive substantial discounts on the purchase price of standards. For details of these and other benefits contact Customer Services, Membership at Chiswick: Tel: 0181 996 7002; Fax: 0181 996 7001.

### Copyright

Copyright subsists in all BSI publications and no part may be reproduced in any form without the prior permission in writing of BSI. This does not preclude the free use, in the course of implementing the standard of necessary details such as symbols and size, type or grade designations including use by incorporation into computer programs, but where these details are reproduced including without limitation in printed form, in computer programs or in any other form whatsoever, the permission in writing of BSI must be obtained and if granted will be on terms including royalty, before the product is sold, licensed or otherwise exploited for commercial gain. Enquiries about copyright should be made to the Copyright Manager at Chiswick.

