

BS EN ISO 2417:2016



BSI Standards Publication

# Leather — Physical and mechanical tests — Determination of the static absorption of water

**bsi.**

...making excellence a habit.™

**National foreword**

This British Standard is the UK implementation of EN ISO 2417:2016. It supersedes BS EN ISO 2417:2002 which is withdrawn.

The UK participation in its preparation was entrusted to Technical Committee TCI/69, Footwear, leather and coated fabrics.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© The British Standards Institution 2016.  
Published by BSI Standards Limited 2016

ISBN 978 0 580 89905 8

ICS 59.140.30

**Compliance with a British Standard cannot confer immunity from legal obligations.**

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 31 March 2016.

**Amendments issued since publication**

Date	Text affected
------	---------------

---

EUROPEAN STANDARD

**EN ISO 2417**

NORME EUROPÉENNE

EUROPÄISCHE NORM

March 2016

ICS 59.140.30

Supersedes EN ISO 2417:2002

English Version

## Leather - Physical and mechanical tests - Determination of the static absorption of water (ISO 2417:2016)

Cuir - Essais physiques et mécaniques - Détermination de l'absorption statique d'eau (ISO 2417:2016)

Leder - Physikalische und mechanische Prüfungen - Bestimmung der statischen Wasseraufnahme (ISO 2417:2016)

This European Standard was approved by CEN on 23 January 2016.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN-CENELEC Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION  
COMITÉ EUROPÉEN DE NORMALISATION  
EUROPÄISCHES KOMITEE FÜR NORMUNG

**CEN-CENELEC Management Centre: Avenue Marnix 17, B-1000 Brussels**

<b>Contents</b>	<b>Page</b>
<b>European foreword.....</b>	<b>3</b>

## **European Foreword**

This document (EN ISO 2417:2016) has been prepared by Technical Committee IULTCS "International Union of Leather Technologists and Chemists Societies" in collaboration with Technical Committee CEN/TC 289 "Leather" the secretariat of which is held by UNI.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by September 2016, and conflicting national standards shall be withdrawn at the latest by September 2016.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN [and/or CENELEC] shall not be held responsible for identifying any or all such patent rights.

This document supersedes EN ISO 2417:2002.

According to the CEN-CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and the United Kingdom.

### **Endorsement notice**

The text of ISO 2417:2016 has been approved by CEN as EN ISO 2417:2016 without any modification.

# Contents

Page

Foreword .....	iv
<b>1 Scope .....</b>	<b>1</b>
<b>2 Normative references .....</b>	<b>1</b>
<b>3 Principle .....</b>	<b>1</b>
<b>4 Apparatus .....</b>	<b>1</b>
<b>5 Sampling and sample preparation .....</b>	<b>2</b>
<b>6 Procedure .....</b>	<b>2</b>
<b>7 Expression of results .....</b>	<b>3</b>
<b>8 Test report .....</b>	<b>3</b>

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see [www.iso.org/directives](http://www.iso.org/directives)).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see [www.iso.org/patents](http://www.iso.org/patents)).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the WTO principles in the Technical Barriers to Trade (TBT) see the following URL: [Foreword - Supplementary information](#)

ISO 2417 was prepared by the Physical Test Commission of the International Union of Leather Technologists and Chemists Societies (IUP Commission, IULTCS) in collaboration with the European Committee for Standardization (CEN) Technical Committee CEN/TC 289, *Leather*, the secretariat of which is held by UNI, in accordance with the Agreement on technical cooperation between ISO and CEN (Vienna Agreement).

It is based on IUP 7 originally published in *J. Soc. Leather Trades Chemists* **44**, p. 367, (1960) and declared an official method of the IULTCS in 1961. This updated version was published in *J. Soc. Leather Tech. Chem.* **84**, p. 323, (2000) and reconfirmed as an official method in March 2001. The same principle is used but the text has been updated and includes the number of test pieces to be taken.

IULTCS, originally formed in 1897, is a world-wide organization of professional leather societies to further the advancement of leather science and technology. IULTCS has three Commissions, which are responsible for establishing international methods for the sampling and testing of leather. ISO recognizes IULTCS as an international standardizing body for the preparation of test methods for leather.

This third edition cancels and replaces the second edition (ISO 2417:2002), of which it constitutes a minor revision to align item c) of Clause 8 with ISO 2419:2012.

# Leather — Physical and mechanical tests — Determination of the static absorption of water

## 1 Scope

This International Standard specifies a method for determining the water absorption of leather under static conditions. The method is applicable to all leather, particularly heavy leather.

## 2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 2418, *Leather — Chemical, physical and mechanical and fastness tests — Sampling location*

ISO 2419, *Leather — Physical and mechanical tests — Sample preparation and conditioning*

ISO 2420, *Leather — Physical and mechanical tests — Determination of apparent density*

ISO 3696, *Water for analytical laboratory use — Specification and test methods*

## 3 Principle

A test piece of known mass or volume is immersed in water for a known period of time and the volume of water absorbed measured.

## 4 Apparatus

**4.1 Glass Kubelka apparatus**, as shown in [Figure 1](#). The graduated scale shall be readable to 0,1 ml with an accuracy of  $\pm 0,1$  ml. The total volume of the bulb (A) and the graduated tube shall be 75 ml  $\pm$  2 ml.

**4.2 Rubber stopper (C)**, fitted with a glass rod or a nickel or stainless steel wire of diameter about 1 mm and of sufficient length to keep the test piece at the end of the cylinder (B) distant from the stopper (C).

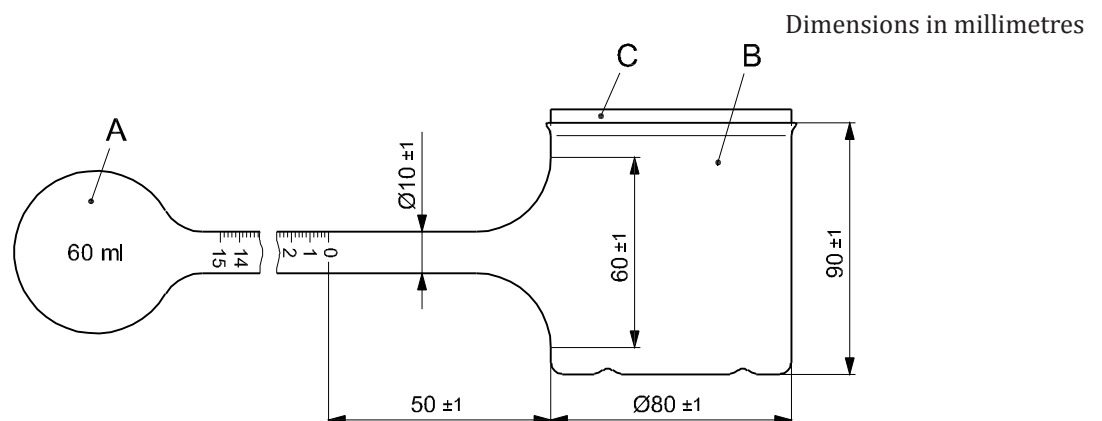


Figure 1 — Kubelka apparatus and stopper



**4.3 Press knife**, the inner wall of which is a right angled circular cylinder of diameter  $70 \text{ mm} \pm 1 \text{ mm}$  as specified in ISO 2419.

**4.4 Balance**, reading to 0,001 g.

**4.5 Distilled or de-ionised water**, conforming to the requirements of grade 3 of ISO 3696.

## 5 Sampling and sample preparation

**5.1** Sample in accordance with ISO 2418. From the sample, cut three test pieces by applying the press knife (4.3) to the grain surface. Condition the test pieces in accordance with ISO 2419.

If there is a requirement for more than two hides or skins to be tested in one batch, then only one sample need be taken from each hide or skin, provided that the overall total is not less than three test pieces.

**5.2** Weigh the test piece to the nearest 0,001 g or determine its volume in accordance with ISO 2420.

**5.3** Carry out all further operations at a temperature of  $20 \text{ }^\circ\text{C} \pm 2 \text{ }^\circ\text{C}$  or  $23 \text{ }^\circ\text{C} \pm 2 \text{ }^\circ\text{C}$ . There is no further need for humidity control.

## 6 Procedure

**6.1** Ensure that the Kubelka apparatus (4.1) is clean and free of grease. Wet the interior surfaces with distilled or de-ionized water (4.5) and pour out the excess.

**6.2** Place the apparatus with the bulb (A) directly below the cylinder (B) and fill with sufficient distilled or de-ionized water (4.5) at  $20 \text{ }^\circ\text{C} \pm 2 \text{ }^\circ\text{C}$  or  $23 \text{ }^\circ\text{C} \pm 2 \text{ }^\circ\text{C}$  to give a water level between 0 ml and 1 ml on the graduated scale. Record the scale reading.

**6.3** Place the test piece in the cylinder (B) and pour the water from the bulb (A) into the cylinder. Close the cylinder with the stopper (C) to prevent evaporation losses and place the apparatus on a level surface.

**6.4** After the test piece has been immersed for a specific time (see Note 1 to 6.5) turn the apparatus so that the water drains into the bulb. One min after drainage, note the scale reading at the water level and calculate the volume of water absorbed.

**6.5** If the water absorption is required at other time intervals, turn the apparatus immediately so that the water flows back into the cylinder (B) and again covers the test piece. Repeat the operation in 6.4.

**NOTE 1** For most purposes, measurements after two periods of immersion are sufficient. If possible, the periods are taken from the following,  $15 \text{ min} \pm 0,2 \text{ min}$ ;  $30 \text{ min} \pm 0,2 \text{ min}$ ;  $60 \text{ min} \pm 0,5 \text{ min}$ ;  $120 \text{ min} \pm 0,5 \text{ min}$ ;  $24 \text{ h} \pm 0,1 \text{ h}$ .

**NOTE 2** The periods of 1 min during which the water is being drained back are not to be considered as part of periods of immersion which precede them, but are considered as parts of subsequent periods of immersion. For example, if the water absorptions during periods of immersion of 15 min and 60 min are to be measured on the same test piece, and the instant of first immersion is at time zero, subsequent actions will be as follows:

- at 15 min, begin draining,
- at 16 min, read off the residual volume and immediately re-immersed the test piece,
- at 60 min, begin draining,
- at 61 min, read off the residual volume.

## 7 Expression of results

Calculate the water absorption,  $Q$ , (%V/m) in millilitres per 100 g, using Formula (1); or calculate the water absorption,  $P$ , (%V/V) in millilitres per 100 ml, using Formula (2).

$$Q = \frac{V_1}{m} \times 100 \quad (1)$$

$$P = \frac{V_1}{V_2} \times 100 \quad (2)$$

where

$V_1$  is the volume of water absorbed in millilitres as determined in [6.4](#);

$V_2$  is the volume of the test piece in millilitres as determined in [5.2](#) (see Note);

$m$  is the mass of the test piece in grams as determined in [5.2](#).

NOTE ISO 2420 determines the volume in cubic millimetres. Thus it is divided by 1 000 to give the correct value of  $V_2$  in millilitres.

## 8 Test report

The test report shall include the following:

- a) a reference to this International Standard, i.e. ISO 2417;
- b) the mean water absorption (in millilitres per 100 g,  $Q$ , or in millilitres per 100 ml,  $P$ ) for each period of immersion;
- c) the standard atmosphere used for conditioning and testing as given in ISO 2419;
- d) any deviations from the method specified in this International Standard;
- e) full details for identification of the sample and any deviation from ISO 2418 with respect to sampling.

BS EN ISO 2417:2016  
ISO 2417:2016(E)  
IULTCS/IUP 7:2016(E)

---

---

**ICS 59.140.30**

Price based on 3 pages

© ISO 2016 – All rights reserved





# British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

## About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

## Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at [bsigroup.com/standards](http://bsigroup.com/standards) or contacting our Customer Services team or Knowledge Centre.

## Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at [bsigroup.com/shop](http://bsigroup.com/shop), where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

## Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to [bsigroup.com/subscriptions](http://bsigroup.com/subscriptions).

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

**PLUS** is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit [bsigroup.com/shop](http://bsigroup.com/shop).

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email [bsmusales@bsigroup.com](mailto:bsmusales@bsigroup.com).

## Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

## Copyright

All the data, software and documentation set out in all British Standards and other BSI publications are the property of and copyrighted by BSI, or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI. Details and advice can be obtained from the Copyright & Licensing Department.

## Useful Contacts:

### Customer Services

**Tel:** +44 845 086 9001

**Email (orders):** [orders@bsigroup.com](mailto:orders@bsigroup.com)

**Email (enquiries):** [cservices@bsigroup.com](mailto:cservices@bsigroup.com)

### Subscriptions

**Tel:** +44 845 086 9001

**Email:** [subscriptions@bsigroup.com](mailto:subscriptions@bsigroup.com)

### Knowledge Centre

**Tel:** +44 20 8996 7004

**Email:** [knowledgecentre@bsigroup.com](mailto:knowledgecentre@bsigroup.com)

### Copyright & Licensing

**Tel:** +44 20 8996 7070

**Email:** [copyright@bsigroup.com](mailto:copyright@bsigroup.com)

## BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK

