

# Welding consumables — Covered electrodes for manual metal arc welding of non-alloy and fine grain steels — Classification

The European Standard EN ISO 2560:2005 has the status of a  
British Standard

ICS 25.160.20

## National foreword

This British Standard is the official English language version of EN ISO 2560:2005. It is identical with ISO 2560:2002. It supersedes BS EN 499:1995 which is withdrawn.

The UK participation in its preparation was entrusted to Technical Committee WEE/39, Welding consumables, which has the responsibility to:

- aid enquirers to understand the text;
- present to the responsible international/European committee any enquiries on the interpretation, or proposals for change, and keep UK interests informed;
- monitor related international and European developments and promulgate them in the UK.

A list of organizations represented on this committee can be obtained on request to its secretary.

### Cross-references

The British Standards which implement international or European publications referred to in this document may be found in the *BSI Catalogue* under the section entitled “International Standards Correspondence Index”, or by using the “Search” facility of the *BSI Electronic Catalogue* or of British Standards Online.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

**Compliance with a British Standard does not of itself confer immunity from legal obligations.**

### Summary of pages

This document comprises a front cover, an inside front cover, the EN ISO title page, the EN ISO foreword page, the ISO title page, pages ii to v, a blank page, pages 1 to 28, an inside back cover and a back cover.

The BSI copyright notice displayed in this document indicates when the document was last issued.

### Amendments issued since publication

Amd. No.	Date	Comments

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 6 January 2006

© BSI 6 January 2006

ISBN 0 580 47569 7

English Version

**Welding consumables - Covered electrodes for manual metal  
arc welding of non-alloy and fine grain steels - Classification  
(ISO 2560:2002)**

Produits consommables pour le soudage - Electrodes  
enrobées pour le soudage manuel à l'arc des aciers non  
alliés et des aciers à grains fins - Classification (ISO  
2560:2002)

Schweißzusätze - Umhüllte Stabelektroden zum  
Lichtbogenhandschweißen von unlegierten Stählen und  
Feinkornstählen - Einteilung (ISO 2560:2002)

This European Standard was approved by CEN on 24 November 2005.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Central Secretariat or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Central Secretariat has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Slovakia, Slovenia, Spain, Sweden, Switzerland and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION  
COMITÉ EUROPÉEN DE NORMALISATION  
EUROPÄISCHES KOMITEE FÜR NORMUNG

**Management Centre: rue de Stassart, 36 B-1050 Brussels**

## Foreword

The text of ISO 2560:2002 has been prepared by Technical Committee ISO/TC 44 "Welding and allied processes" of the International Organization for Standardization (ISO) and has been taken over as EN ISO 2560:2005 by Technical Committee CEN/TC 121 "Welding" the secretariat of which is held by DIN.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by June 2006, and conflicting national standards shall be withdrawn at the latest by June 2006.

This document supersedes EN 499:1994.

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Slovakia, Slovenia, Spain, Sweden, Switzerland and United Kingdom.

### Endorsement notice

The text of ISO 2560:2002 has been approved by CEN as EN ISO 2560:2005 without any modifications.

INTERNATIONAL  
STANDARD

**ISO**  
**2560**

Second edition  
2002-11-01

---

---

**Welding consumables — Covered  
electrodes for manual metal arc welding of  
non-alloy and fine grain steels —  
Classification**

*Produits consommables pour le soudage — Électrodes enrobées pour le  
soudage manuel à l'arc des aciers non alliés et des aciers à grains fins —  
Classification*



Reference number  
ISO 2560:2002(E)



## Contents

Page

Foreword .....	iv
Introduction.....	v
<b>1</b> <b>Scope</b> .....	<b>1</b>
<b>2</b> <b>Normative references</b> .....	<b>1</b>
<b>3</b> <b>Classification</b> .....	<b>2</b>
<b>4</b> <b>Symbols and requirements</b> .....	<b>3</b>
4.1 <b>Symbol for the product/process</b> .....	3
4.2 <b>Symbol for strength and elongation of all-weld metal</b> .....	3
4.3 <b>Symbol for impact properties of all-weld metal</b> .....	4
4.4 <b>Symbol for the chemical composition of all-weld metal</b> .....	4
4.5 <b>Symbol for type of electrode covering</b> .....	5
4.6 <b>Symbol for condition of post-weld heat-treatment of all-weld metal</b> .....	6
4.7 <b>Symbol for nominal electrode efficiency and type of current</b> .....	7
4.8 <b>Symbol for welding position</b> .....	7
4.9 <b>Symbol for hydrogen content of deposited metal</b> .....	8
<b>5</b> <b>Mechanical tests</b> .....	<b>8</b>
5.1 <b>Preheating and interpass temperatures</b> .....	8
5.2 <b>Pass sequence</b> .....	11
<b>6</b> <b>Chemical analysis</b> .....	<b>12</b>
<b>7</b> <b>Fillet weld test</b> .....	<b>14</b>
<b>8</b> <b>Retest</b> .....	<b>17</b>
<b>9</b> <b>Technical delivery conditions</b> .....	<b>17</b>
<b>10</b> <b>Examples of designation</b> .....	<b>18</b>
<b>Annex A</b> (informative) <b>Classification systems</b> .....	<b>19</b>
<b>Annex B</b> (informative) <b>Description of types of electrode covering — Classification by yield strength and 47 J impact energy</b> .....	<b>22</b>
<b>Annex C</b> (informative) <b>Description of types of electrode covering — Classification by tensile strength and 27 J impact energy</b> .....	<b>24</b>
<b>Annex D</b> (informative) <b>Notes on diffusible hydrogen</b> .....	<b>27</b>
<b>Bibliography</b> .....	<b>28</b>

## **Foreword**

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 3.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this International Standard may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 2560 was prepared in collaboration with the International Institute of Welding which has been approved by the ISO Council as an international standardizing body in the field of welding.

This second edition cancels and replaces the first edition (ISO 2560:1973), which has been technically revised.

Annexes A to D of this International Standard are for information only.



## Introduction

This International Standard recognizes that there are two somewhat different approaches in the global market to classifying a given electrode, and allows for either or both to be used, to suit a particular market need. Application of either type of classification designation (or of both where suitable) identifies a product as classified according to this International Standard. The classification according to system A is mainly based on EN 499. The classification according to system B is mainly based upon standards used around the Pacific Rim.

This International Standard provides a classification in order to designate covered electrodes in terms of the yield strength, tensile strength and elongation of the all-weld metal. The ratio of yield to tensile strength of weld metal is generally higher than that of parent metal. Users should note that matching weld metal yield strength to parent metal yield strength will not necessarily ensure that the weld metal tensile strength matches that of the parent metal. Therefore, where the application requires matching tensile strength, selection of the consumable should be made by reference to column 3 of Table 1A or to Table 1B and Table 8B.

It should be noted that the mechanical properties of all-weld metal test specimens used to classify the electrodes will vary from those obtained in production joints because of differences in welding procedure such as electrode size, width of weave, welding position and parent metal composition.

Requests for official interpretation of any aspect of this International Standard should be directed to the Secretariat of ISO/TC 44/SC 3 via the member body in the user's country, a complete listing of which can be found at [www.iso.org](http://www.iso.org).

*blank*

# Welding consumables — Covered electrodes for manual metal arc welding of non-alloy and fine grain steels — Classification

## 1 Scope

This International Standard specifies requirements for classification of covered electrodes and deposited metal in the as-welded condition and in the post-weld heat-treated condition for manual metal arc welding of non-alloy and fine grain steels with a minimum yield strength of up to 500 N/mm<sup>2</sup> or a minimum tensile strength of up to 570 N/mm<sup>2</sup>.

This International Standard is a combined specification providing for classification utilizing a system based upon the yield strength and the average impact energy of 47 J of all-weld metal, or utilizing a system based upon the tensile strength and the average impact energy of 27 J of all-weld metal.

- 1) Paragraphs and tables which carry the suffix letter "A" are applicable only to covered electrodes classified to the system based upon the yield strength and the average impact energy of 47 J of all-weld metal in this International Standard.
- 2) Paragraphs and tables which carry the suffix letter "B" are applicable only to covered electrodes classified to the system based upon the tensile strength and the average impact energy of 27 J of all-weld metal in this International Standard.
- 3) Paragraphs and tables which do not have either the suffix letter "A" or the suffix letter "B" are applicable to all covered electrodes classified in this International Standard.

## 2 Normative references

The following normative documents contain provisions which, through reference in this text, constitute provisions of this International Standard. For dated references, subsequent amendments to, or revisions of, any of these publications do not apply. However, parties to agreements based on this International Standard are encouraged to investigate the possibility of applying the most recent editions of the normative documents indicated below. For undated references, the latest edition of the normative document referred to applies. Members of ISO and IEC maintain registers of currently valid International Standards.

ISO 31-0:1992, *Quantities and units — Part 0: General principles*

ISO 544, *Welding consumables — Technical delivery conditions for welding filler metals — Type of product, dimensions, tolerances and marking*

ISO 2401, *Covered electrodes — Determination of the efficiency, metal recovery and deposition coefficient*

ISO 3690, *Welding and allied processes — Determination of hydrogen content in ferritic steel arc weld metal*

ISO 6847, *Welding consumables — Deposition of a weld metal pad for chemical analysis*

ISO 6947, *Welds — Working positions — Definitions of angles of slope and rotation*

ISO 13916, *Welding — Guidance on the measurement of preheating temperature, interpass temperature and preheat maintenance temperature*

ISO 14344, *Welding and allied processes — Flux and gas shielded electrical welding processes — Procurement guidelines for consumables*

ISO 15792-1:2000, *Welding consumables — Test methods — Part 1: Test methods for all-weld metal test specimens in steel, nickel and nickel alloys*

ISO 15792-3:2000, *Welding consumables — Test methods — Part 3: Classification testing of positional capacity and root penetration of welding consumables in a fillet weld*

### 3 Classification

Classification designations are based upon two approaches to indicate the tensile properties and the impact properties of the all-weld metal obtained with a given electrode. The two designation approaches include additional designators for some other classification requirements, but not all, as will be clear from the following sections. In most cases, a given commercial product can be classified in both systems. Then either or both classification designations can be used for the product.

The classification includes all-weld metal properties obtained with a covered electrode as given below. The classification is based on the electrode size 4 mm with the exception of the symbol for welding position which is based on ISO 15792-3.

#### 3A Classification by yield strength and 47 J impact energy

The classification is divided into eight parts:

- 1) the first part gives a symbol indicating the product/process to be identified;
- 2) the second part gives a symbol indicating the strength and elongation of all-weld metal (see Table 1A);
- 3) the third part gives a symbol indicating the impact properties of all-weld metal (see Table 2A);
- 4) the fourth part gives a symbol indicating the chemical composition of all-weld metal (see Table 3A);
- 5) the fifth part gives a symbol indicating the type of electrode covering (see 4.5A);
- 6) the sixth part gives a symbol indicating the nominal electrode efficiency and type of current (see Table 5A);
- 7) the seventh part gives a symbol indicating the welding position (see Table 6A);
- 8) the eighth part gives a symbol indicating the hydrogen content of deposited metal (see Table 7).

In order to promote the use of this International Standard, the classification is split into two sections:

##### a) Compulsory section

This section includes the symbols for the type of product, the strength and elongation, the impact properties, the chemical composition and the type of covering, i.e. the symbols defined in 4.1, 4.2A, 4.3A, 4.4A and 4.5A.

#### 3B Classification by tensile strength and 27 J impact energy

The classification is divided into seven parts:

- 1) the first part gives a symbol indicating the product/process to be identified;
- 2) the second part gives a symbol indicating the strength of all-weld metal (see Table 1B);
- 3) the third part gives a symbol indicating the type of electrode covering, the type of current, and the welding position (see Table 4B);
- 4) the fourth part gives a symbol indicating the chemical composition of all-weld metal (see Table 3B);
- 5) the fifth part gives a symbol indicating the condition of postweld heat treatment under which the all-weld metal test was conducted (see 4.6B);
- 6) the sixth part gives a symbol indicating that the electrode has satisfied a requirement for 47 J impact energy at the temperature normally used for the 27 J requirement;
- 7) the seventh part gives a symbol indicating the hydrogen content of deposited metal (see Table 7).

In order to promote the use of this International Standard, the classification is split into two sections:

##### a) Compulsory section

This section includes the symbols for the type of product, the strength, the type of covering, the type of current, the welding position, the chemical composition and the condition of heat treatment, i.e., the symbols defined in 4.1, 4.2B, 4.4B, 4.5B and 4.6B.

## b) Optional section

This section includes the symbols for the nominal electrode efficiency, the type of current, the welding positions for which the electrode is suitable, and the symbol for hydrogen content, i.e. the symbols defined in 4.7A, 4.8A and 4.9.

## b) Optional section

This section includes the symbol for the optional supplemental designator for 47 J impact energy, i.e., the symbol defined in 4.3B; and the symbol for the hydrogen content, i.e., the symbol defined in 4.9.

The full designation (see clause 10) shall be used on packages and in the manufacturer's literature and data sheets. See Figure A.1, for a schematic representation of the full designation of electrodes classified by yield strength and 47 J impact energy, system A. See Figure A.2, for a schematic representation of the full designation of electrodes classified by tensile strength and 27 J impact energy.

## 4 Symbols and requirements

### 4.1 Symbol for the product/process

The symbol for the covered electrode used in the manual metal arc welding process shall be the letter E placed at the beginning of the designation.

### 4.2 Symbol for strength and elongation of all-weld metal

#### 4.2A Classification by yield strength and 47 J impact energy

The symbols in Table 1A indicate yield strength, tensile strength and elongation of the all-weld metal in the as-welded condition determined in accordance with clause 5.

#### 4.2B Classification by tensile strength and 27 J impact energy

The symbols in Table 1B indicate tensile strength of the all-weld metal in the as-welded condition or in the post-weld heat-treated condition determined in accordance with clause 5. The yield strength and elongation requirements depend upon the specific chemical composition, heat treatment condition and coating type, as well as upon the tensile strength requirements, as given for the complete classification in Table 8B.

**Table 1A — Symbol for strength and elongation of all-weld metal** (Classification by yield strength and 47 J impact energy)

Symbol	Minimum yield strength <sup>a</sup> N/mm <sup>2</sup>	Tensile strength N/mm <sup>2</sup>	Minimum elongation <sup>b</sup> %
35	355	440 to 570	22
38	380	470 to 600	20
42	420	500 to 640	20
46	460	530 to 680	20
50	500	560 to 720	18

<sup>a</sup> For yield strength, the lower yield ( $R_{eL}$ ) shall be used when yielding occurs, otherwise the 0,2 % proof strength ( $R_{p0,2}$ ) shall be used.

<sup>b</sup> Gauge length is equal to five times the specimen diameter.

**Table 1B — Symbol for strength of all-weld metal** (Classification by tensile strength and 27 J impact energy)

Symbol	Minimum tensile strength N/mm <sup>2</sup>
43	430
49	490
55	550
57	570

**4.3 Symbol for impact properties of all-weld metal**

**4.3A Classification by yield strength and 47 J impact energy**

The symbols in Table 2A indicate the temperature at which an average impact energy of 47 J is achieved under the conditions given in clause 5. Three specimens shall be tested. Only one individual value may be lower than 47 J but not lower than 32 J. When an all-weld metal has been classified for a certain temperature, it automatically covers any higher temperature in Table 2A.

**Table 2A — Symbol for impact properties of all-weld metal** (Classification by yield strength and 47 J impact energy)

Symbol	Temperature for minimum average impact energy of 47 J °C
Z	No requirement
A	+ 20
0	0
2	- 20
3	- 30
4	- 40
5	- 50
6	- 60

**4.4 Symbol for the chemical composition of all-weld metal**

**4.4A Classification by yield strength and 47 J impact energy**

The symbols in Table 3A indicate the chemical composition of all-weld metal, determined in accordance with clause 6.

**4.3B Classification by tensile strength and 27 J impact energy**

There is no specific symbol for impact properties. The complete classification in Table 8B determines the temperature at which an impact energy of 27 J is achieved in the as-welded condition or in the post-weld heat-treated condition under the conditions given in clause 5. Five test specimens shall be tested. The lowest and highest values obtained shall be disregarded. Two of the three remaining values shall be greater than the specified 27 J level, one of the three may be lower but shall not be less than 20 J. The average of the three remaining values shall be at least 27 J.

The addition of the optional symbol U, immediately after the symbol for condition of heat treatment, indicates that the supplemental requirement of 47 J impact energy at the normal 27 J impact test temperature has also been satisfied. For the 47 J impact requirement, three specimens shall be tested. The impact value shall be determined by the average of the three test specimens. The average of the three values shall be 47 J or greater.

**4.4B Classification by tensile strength and 27 J impact energy**

The symbols in Table 3B indicate the principal alloying elements, and sometimes the nominal alloy level of the most significant alloy element, of all-weld metal, determined in accordance with clause 6. The symbol for chemical composition does not immediately follow the symbol for strength, but follows the symbol for coating type. The complete classification, given in Table 10B, determines the exact chemical composition requirements for a particular electrode classification.

**Table 3A — Symbol for chemical composition of all-weld metal** (Classification by yield strength and 47 J impact energy)

Alloy symbol	Chemical composition (mass %) <sup>a, b, c</sup>		
	Mn	Mo	Ni
No symbol	2,0	—	—
Mo	1,4	0,3 to 0,6	—
MnMo	1,4 to 2,0	0,3 to 0,6	—
1Ni	1,4	—	0,6 to 1,2
2Ni	1,4	—	1,8 to 2,6
3Ni	1,4	—	2,6 to 3,8
Mn1Ni	1,4 to 2,0	—	0,6 to 1,2
1NiMo	1,4	0,3 to 0,6	0,6 to 1,2
Z	Any other agreed composition		

<sup>a</sup> If not specified, Mo < 0,2; Ni < 0,3; Cr < 0,2; V < 0,05; Nb < 0,05; Cu < 0,3.  
<sup>b</sup> Single values shown in the table mean maximum values.  
<sup>c</sup> The results shall be rounded to the same number of significant figures as in the specified value using the rules according to ISO 31-0:1992, Annex B, Rule A.

**Table 3B — Symbol for chemical composition of all-weld metal** (Classification by tensile strength and 27 J impact energy)

Alloy symbol	Chemical composition	
	Principal alloy element(s)	Nominal level mass %
No symbol, -1, or -P1	Mn	1
-1M3	Mo	0,5
-3M2	Mn	1,5
	Mo	0,4
-3M3	Mn	1,5
	Mo	0,5
-N1	Ni	0,5
-N2	Ni	1
-N3	Ni	1,5
-3N3	Mn	1,5
	Ni	1,5
-N5	Ni	2,5
-N7	Ni	3,5
-N13	Ni	6,5
-N2M3	Ni	1
	Mo	0,5
-NC	Ni	0,5
	Cu	0,4
-CC	Cr	0,5
	Cu	0,4
-NCC	Ni	0,2
	Cr	0,6
	Cu	0,5
-NCC1	Ni	0,6
	Cr	0,6
	Cu	0,5
-NCC2	Ni	0,3
	Cr	0,2
	Cu	0,5
-G	Any other agreed composition	

## 4.5 Symbol for type of electrode covering

### 4.5A Classification by yield strength and 47 J impact energy

The type of covering of a covered electrode depends substantially on the type of slag-forming components. The symbols indicating the type shall be formed by the following letters or groups of letters:

- A = acid covering
- C = cellulosic covering
- R = rutile covering
- RR = rutile thick covering
- RC = rutile-cellulosic covering
- RA = rutile-acid covering
- RB = rutile-basic covering
- B = basic covering.

NOTE A description of the characteristics of each of the types of covering is given in annex B.

### 4.5B Classification by tensile strength and 27 J impact energy

The type of covering of a covered electrode depends substantially on the type of slag-forming components. The type of covering also determines the positions suitable for welding and the type of current, according to Table 4B.

**Table 4B — Symbol for type of covering**  
(classification by tensile strength and 27 J impact energy)

Symbol	Type of covering	Welding positions <sup>a</sup>	Type of current
03	Rutile basic	All <sup>b</sup>	a.c. and d.c. (±)
10	Cellulosic	All	d.c. (+)
11	Cellulosic	All	a.c. and d.c. (+)
12	Rutile	All <sup>b</sup>	a.c. and d.c. (-)
13	Rutile	All <sup>b</sup>	a.c. and d.c. (±)
14	Rutile + iron powder	All <sup>b</sup>	a.c. and d.c. (±)
15	Basic	All <sup>b</sup>	d.c. (+)
16	Basic	All <sup>b</sup>	a.c. and d.c. (+)
18	Basic + iron powder	All <sup>b</sup>	a.c. and d.c. (+)
19	Ilmenite	All <sup>b</sup>	a.c. and d.c. (±)
20	Iron oxide	PA, PB	a.c. and d.c. (-)
24	Rutile + iron powder	PA, PB	a.c. and d.c. (±)
27	Iron oxide + iron powder	PA, PB	a.c. and d.c. (-)
28	Basic + iron powder	PA, PB, PC	a.c. and d.c. (+)
40	Not specified	Manufacturer's recommendations	
48	Basic	All	a.c. and d.c. (+)

NOTE A description of the characteristics of each of the types of covering is given in annex C.

<sup>a</sup> Positions are defined in ISO 6947. PA = flat, PB = horizontal vertical fillet, PC = horizontal, PG = vertical down.

<sup>b</sup> All position may or may not include vertical down welding. This shall be specified in the manufacturer's trade literature.

#### 4.6 Symbol for condition of post-weld heat-treatment of all-weld metal

##### 4.6A Classification by yield strength and 47 J impact energy

Classification is based upon mechanical properties of the all-weld metal in the as-welded condition only. There is no symbol for condition of post-weld heat treatment.

##### 4.6B Classification by tensile strength and 27 J impact energy

If the electrode has been classified in the as-welded condition, the symbol A shall be added to the classification. If the electrode has been classified in the post-weld heat-treated condition, the temperature of post-weld heat-treatment shall be  $620\text{ °C} \pm 15\text{ °C}$  ( $605\text{ °C} \pm 15\text{ °C}$  in the cases of chemical compositions N5 and N7, and  $600\text{ °C} \pm 15\text{ °C}$  in the case of chemical composition N13), and the symbol P shall be added to the classification. Postweld heat treatment time shall be 1 h ( $^{+15}_0$  min) at temperature. If the electrode has been classified in both conditions, the symbol AP shall be added to the classification.



## 4.7 Symbol for nominal electrode efficiency and type of current

### 4.7A Classification by yield strength and 47 J impact energy

The symbols in Table 5A indicate nominal electrode efficiency, determined in accordance with ISO 2401 with the type of current shown in Table 5A.

**Table 5A — Symbol for nominal electrode efficiency and type of current** (Classification by yield strength and 47 J impact energy)

Symbol	Nominal electrode efficiency, %	Type of current <sup>a, b</sup>
1	≤ 105	a.c. + d.c.
2	≤ 105	d.c.
3	> 105 but ≤ 125	a.c. + d.c.
4	> 105 but ≤ 125	d.c.
5	> 125 but ≤ 160	a.c. + d.c.
6	> 125 but ≤ 160	d.c.
7	> 160	a.c. + d.c.
8	> 160	d.c.

<sup>a</sup> In order to demonstrate operability on a.c., tests shall be carried out with no load voltage higher than 65 V.

<sup>b</sup> a.c. = alternating current; d.c. = direct current.

### 4.7B Classification by tensile strength and 27 J impact energy

There is no specific symbol for nominal electrode efficiency and type of current. Type of current is included in the symbol for type of covering (Table 4B). Nominal electrode efficiency is not addressed.

## 4.8 Symbol for welding position

### 4.8A Classification by yield strength and 47 J impact energy

The symbols in table 6A for welding positions indicates the positions for which the electrode is tested in accordance with ISO 15792-3.

**Table 6A — Symbol for welding position** (classification by yield strength and 47 J impact energy)

Symbol	Positions
1	PA, PB, PC, PD, PE, PF, PG
2	PA, PB, PC, PD, PE, PF
3	PA, PB
4	PA
5	PA, PB, PG

### 4.8B Classification by tensile strength and 27 J impact energy

There is no specific symbol for welding position. The welding position requirements are included with the symbol for type of covering (Table 4B).

#### 4.9 Symbol for hydrogen content of deposited metal

The symbols in Table 7 indicate the hydrogen content determined in deposited metal from electrode size 4 mm in accordance with the method given in ISO 3690. The current used shall be 70 % to 90 % of the maximum value recommended by the manufacturer. Electrodes recommended for use with a.c. shall be tested using a.c. Electrodes recommended for d.c. only shall be tested using d.c. with electrode positive.

The manufacturer shall provide information on the recommended type of current and drying conditions for achieving the hydrogen levels.

**Table 7 — Symbol for hydrogen content of deposited metal**

Symbol	Hydrogen content max. ml/100 g of deposited weld metal
H5	5
H10	10
H15	15

See annex D for additional information about diffusible hydrogen.

### 5 Mechanical tests

#### 5A Classification by yield strength and 47 J impact energy

Tensile and impact tests and any required retests shall be carried out in the as-welded condition using an all-weld metal test assembly type 1.3 in accordance with ISO 15792-1:2000 using 4 mm electrodes and welding conditions as described below in 5.1 and 5.2.

#### 5.1 Preheating and interpass temperatures

The preheating and interpass temperatures shall be measured using temperature indicator crayons, surface thermometers or thermocouples (see ISO 13916).

#### 5.1A Classification by yield strength and 47 J impact energy

Preheating is not required; welding may start from room temperature. The interpass temperature shall not exceed 250 °C. If, after any pass, the interpass temperature is exceeded, the test assembly shall be cooled in air to a temperature below that limit.

#### 5B Classification by tensile strength and 27 J impact energy

Tensile and impact tests and any required retests shall be carried out in the as-welded condition and/or in the post-weld heat-treated condition, using an all-weld metal test assembly type 1.3 in accordance with ISO 15792-1:2000 using 4 mm electrodes and welding conditions as described below in 5.1 and 5.2.

#### 5.1B Classification by tensile strength and 27 J impact energy

Preheating and interpass temperature for electrodes with no chemical composition symbol or with the -1 symbol in Tables 3B and 8B shall be 100 °C to 150 °C. Preheating and interpass temperatures for all other compositions shall be 90 °C to 110 °C.

**Table 8B — Mechanical test requirements**  
(classification by tensile strength and 27 J impact energy)

Classification	Tensile strength <sup>a</sup>	Yield strength <sup>a</sup>	Elongation <sup>a</sup>	Charpy V-notch temperature <sup>b</sup>
	N/mm <sup>2</sup>	N/mm <sup>2</sup>	$A_5$ %	°C
E4303	430	330	20	0
E4310	430	330	20	– 30
E4311	430	330	20	– 30
E4312	430	330	16	NS <sup>b</sup>
E4313	430	330	16	NS
E4316	430	330	20	– 30
E4318	430	330	20	– 30
E4319	430	330	20	– 20
E4320	430	330	20	NS
E4324	430	330	16	NS
E4327	430	330	20	– 30
E4340	430	330	20	0
E4903	490	400	20	0
E4910	480 to 650	400	20	– 30
E4911	480 to 650	400	20	– 30
E4912	490	400	16	NS
E4913	490	400	16	NS
E4914	490	400	16	NS
E4915	490	400	20	– 30
E4916	490	400	20	– 30
E4916-1	490	400	20	– 45
E4918	490	400	20	– 30
E4918-1	490	400	20	– 45
E4919	490	400	20	– 20
E4924	490	400	16	NS
E4924-1	490	400	20	– 20
E4927	490	400	20	– 30
E4928	490	400	20	– 30
E4948	490	400	20	– 30
E5716	570	490	16	– 20
E5728	570	490	16	– 20
E4910-P1	490	420	20	– 30
E5510-P1	550	460	19	– 30
E4910-1M3	490	420	20	NS
E4911-1M3	490	400	20	NS
E4915-1M3	490	400	20	NS
E4916-1M3	490	400	20	NS
E4918-1M3	490	400	20	NS

Table 8B (continued)

Classification	Tensile strength <sup>a</sup>	Yield strength <sup>a</sup>	Elongation <sup>a</sup>	Charpy V-notch temperature <sup>b</sup>
	N/mm <sup>2</sup>	N/mm <sup>2</sup>	A <sub>5</sub> %	°C
E4919-1M3	490	400	20	NS
E4920-1M3	490	400	20	NS
E4927-1M3	490	400	20	NS
E5518-3M2	550	460	17	- 50
E5516-3M3	550	460	17	- 50
E5518-3M3	550	460	17	- 50
E4916-N1	490	390	20	- 40
E4928-N1	490	390	20	- 40
E5516-N1	550	460	17	- 40
E5528-N1	550	460	17	- 40
E4916-N2	490	390	20	- 40
E4918-N2	490	390	20	- 50
E5516-N2	550	470 to 550	20	- 40
E5518-N2	550	470 to 550	20	- 40
E4916-N3	490	390	20	- 40
E5516-N3	550	460	17	- 50
E5516-3N3	550	460	17	- 50
E5518-N3	550	460	17	- 50
E4915-N5	490	390	20	- 75
E4916-N5	490	390	20	- 75
E4918-N5	490	390	20	- 75
E4928-N5	490	390	20	- 60
E5516-N5	550	460	17	- 60
E5518-N5	550	460	17	- 60
E4915-N7	490	390	20	- 100
E4916-N7	490	390	20	- 100
E4918-N7	490	390	20	- 100
E5516-N7	550	460	17	- 75
E5518-N7	550	460	17	- 75
E5516-N13	550	460	17	- 100
E5518-N2M3	550	460	17	- 40
E4903-NC	490	390	20	0
E4916-NC	490	390	20	0
E4928-NC	490	390	20	0
E5716-NC	570	490	16	0
E5728-NC	570	490	16	0
E4903-CC	490	390	20	0
E4916-CC	490	390	20	0

Table 8B (continued)

Classification	Tensile strength <sup>a</sup>	Yield strength <sup>a</sup>	Elongation <sup>a</sup>	Charpy V-notch temperature <sup>b</sup>
	N/mm <sup>2</sup>	N/mm <sup>2</sup>	A <sub>5</sub> %	°C
E4928-CC	490	390	20	0
E5716-CC	570	490	16	0
E5728-CC	570	490	16	0
E4903-NCC	490	390	20	0
E4916-NCC	490	390	20	0
E4928-NCC	490	390	20	0
E5716-NCC	570	490	16	0
E5728-NCC	570	490	16	0
E4903-NCC1	490	390	20	0
E4916-NCC1	490	390	20	0
E4928-NCC1	490	390	20	0
E5516-NCC1	550	460	17	-20
E5518-NCC1	550	460	17	-20
E5716-NCC1	570	490	16	0
E5728-NCC1	570	490	16	0
E4916-NCC2	490	420	20	-20
E4918-NCC2	490	420	20	-20
E49XX-G	490	400	20	NS
E55XX-G	550	460	17	NS
E57XX-G	570	490	16	NS

<sup>a</sup> Single values are minimum requirements.

<sup>b</sup> NS = not specified.

## 5.2 Pass sequence

The pass sequence shall be as indicated in Table 9.

The direction of welding to complete a pass shall not vary. Each pass shall be welded with a welding current of 70 % to 90 % of the maximum current recommended by the manufacturer. Regardless of the type of covering, welding shall be performed with a.c. when both a.c. and d.c. are recommended and with d.c. using the recommended polarity when only d.c. is claimed.

Table 9 — Pass sequence

Electrode diameter mm	Split weave		
	Layer No.	Passes per layer	Number of layers
4, 0	1 to top	2 <sup>a</sup>	7 – 9

<sup>a</sup> The top two layers may be completed with 3 passes per layer.

## 6 Chemical analysis

Chemical analysis may be performed on any suitable test piece. In case of dispute specimens in accordance with ISO 6847 shall be used. Any analytical technique may be used but in case of dispute reference shall be made to established published methods.

### 6A Classification by yield strength and 47 J impact energy

The results of the chemical analysis shall fulfil the requirements given in Table 3A above.

### 6B Classification by tensile strength and 27 J impact energy

The results of the chemical analysis shall fulfil the requirements given in Table 10B for the classification under test.

**Table 10B — All-weld metal deposit composition requirements**  
(classification by tensile strength and 27 J impact energy)<sup>a, b</sup>

Classification	C	Mn	Si	P	S	Ni	Cr	Mo	V	Cu	Al
E4303	0,20	1,20	1,00	NS	NS	0,30	0,20	0,30	0,08	NS	NS
E4310	0,20	1,20	1,00	NS	NS	0,30	0,20	0,30	0,08	NS	NS
E4311	0,20	1,20	1,00	NS	NS	0,30	0,20	0,30	0,08	NS	NS
E4312	0,20	1,20	1,00	NS	NS	0,30	0,20	0,30	0,08	NS	NS
E4313	0,20	1,20	1,00	NS	NS	0,30	0,20	0,30	0,08	NS	NS
E4316	0,20	1,20	1,00	NS	NS	0,30	0,20	0,30	0,08	NS	NS
E4318	0,03	0,60	0,40	0,025	0,015	0,30	0,20	0,30	0,08	NS	NS
E4319	0,20	1,20	1,00	NS	NS	0,30	0,20	0,30	0,08	NS	NS
E4320	0,20	1,20	1,00	NS	NS	0,30	0,20	0,30	0,08	NS	NS
E4324	0,20	1,20	1,00	NS	NS	0,30	0,20	0,30	0,08	NS	NS
E4327	0,20	1,20	1,00	NS	NS	0,30	0,20	0,30	0,08	NS	NS
E4340	NS	NS	NS	NS	NS	NS	NS	NS	NS	NS	NS
E4903	0,15	1,25	0,90	NS	NS	0,30	0,20	0,30	0,08	NS	NS
E4910	0,20	1,25	0,90	NS	NS	0,30	0,20	0,30	0,08	NS	NS
E4911	0,20	1,25	0,90	NS	NS	0,30	0,20	0,30	0,08	NS	NS
E4912	0,20	1,20	1,00	0,035	0,035	0,30	0,20	0,30	0,08	NS	NS
E4913	0,20	1,20	1,00	0,035	0,035	0,30	0,20	0,30	0,08	NS	NS
E4914	0,15	1,25	0,90	0,035	0,035	0,30	0,20	0,30	0,08	NS	NS
E4915	0,15	1,25	0,75	0,035	0,035	0,30	0,20	0,30	0,08	NS	NS
E4916	0,15	1,60	0,75	0,035	0,035	0,30	0,20	0,30	0,08	NS	NS
E4916-1	0,15	1,60	0,75	0,035	0,035	0,30	0,20	0,30	0,08	NS	NS
E4918	0,15	1,60	0,90	0,035	0,035	0,30	0,20	0,30	0,08	NS	NS
E4918-1	0,15	1,60	0,90	0,035	0,035	0,30	0,20	0,30	0,08	NS	NS
E4919	0,15	1,25	0,90	0,035	0,035	0,30	0,20	0,30	0,08	NS	NS
E4924	0,15	1,25	0,90	0,035	0,035	0,30	0,20	0,30	0,08	NS	NS
E4924-1	0,15	1,25	0,90	0,035	0,035	0,30	0,20	0,30	0,08	NS	NS
E4927	0,15	1,60	0,75	0,035	0,035	0,30	0,20	0,30	0,08	NS	NS
E4928	0,15	1,60	0,90	0,035	0,035	0,30	0,20	0,30	0,08	NS	NS
E4948	0,15	1,60	0,90	0,035	0,035	0,30	0,20	0,30	0,08	NS	NS
E5716	0,12	1,60	0,90	0,03	0,03	1,00	0,30	0,35	NS	NS	NS
E5728	0,12	1,60	0,90	0,03	0,03	1,00	0,30	0,35	NS	NS	NS
E4910-P1	0,20	1,20	0,60	0,03	0,03	1,00	0,30	0,50	0,10	NS	NS

Table 10B (continued)

Classification	C	Mn	Si	P	S	Ni	Cr	Mo	V	Cu	Al
E5510-P1	0,20	1,20	0,60	0,03	0,03	1,00	0,30	0,50	0,10	NS	NS
E4910-1M3	0,12	0,60	0,40	0,03	0,03	NS	NS	0,40 to 0,65	NS	NS	NS
E4911-1M3	0,12	0,60	0,40	0,03	0,03	NS	NS	0,40 to 0,65	NS	NS	NS
E4915-1M3	0,12	0,90	0,60	0,03	0,03	NS	NS	0,40 to 0,65	NS	NS	NS
E4916-1M3	0,12	0,90	0,60	0,03	0,03	NS	NS	0,40 to 0,65	NS	NS	NS
E4918-1M3	0,12	0,90	0,80	0,03	0,03	NS	NS	0,40 to 0,65	NS	NS	NS
E4919-1M3	0,12	0,90	0,40	0,03	0,03	NS	NS	0,40 to 0,65	NS	NS	NS
E4920-1M3	0,12	0,60	0,40	0,03	0,03	NS	NS	0,40 to 0,65	NS	NS	NS
E4927-1M3	0,12	1,00	0,40	0,03	0,03	NS	NS	0,40 to 0,65	NS	NS	NS
E5518-3M2	0,12	1,00 to 1,75	0,80	0,03	0,03	0,90	NS	0,25 to 0,45	NS	NS	NS
E5516-3M3	0,12	1,00 to 1,80	0,80	0,03	0,03	0,90	NS	0,40 to 0,65	NS	NS	NS
E5518-3M3	0,12	1,00 to 1,80	0,80	0,03	0,03	0,90	NS	0,40 to 0,65	NS	NS	NS
E4916-N1	0,12	0,60 to 1,60	0,90	0,03	0,03	0,30 to 1,00	NS	0,35	0,05	NS	NS
E4928-N1	0,12	0,60 to 1,60	0,90	0,03	0,03	0,30 to 1,00	NS	0,35	0,05	NS	NS
E5516-N1	0,12	0,60 to 1,60	0,90	0,03	0,03	0,30 to 1,00	NS	0,35	0,05	NS	NS
E5528-N1	0,12	0,60 to 1,60	0,90	0,03	0,03	0,30 to 1,00	NS	0,35	0,05	NS	NS
E4916-N2	0,08	0,40 to 1,40	0,50	0,03	0,03	0,80 to 1,10	0,15	0,35	0,05	NS	NS
E4918-N2	0,08	0,40 to 1,40	0,50	0,03	0,03	0,80 to 1,10	0,15	0,35	0,05	NS	NS
E5516-N2	0,12	0,40 to 1,25	0,80	0,03	0,03	0,80 to 1,10	0,15	0,35	0,05	NS	NS
E5518-N2	0,12	0,40 to 1,25	0,80	0,03	0,03	0,80 to 1,10	0,15	0,35	0,05	NS	NS
E4916-N3	0,10	1,25	0,60	0,03	0,03	1,10 to 2,00	NS	0,35	NS	NS	NS
E5516-N3	0,10	1,25	0,60	0,03	0,03	1,10 to 2,00	NS	0,35	NS	NS	NS
E5516-3N3	0,10	1,60	0,60	0,03	0,03	1,10 to 2,00	NS	NS	NS	NS	NS
E5518-N3	0,10	1,25	0,80	0,03	0,03	1,10 to 2,00	NS	NS	NS	NS	NS
E4915-N5	0,05	1,25	0,50	0,03	0,03	2,00 to 2,75	NS	NS	NS	NS	NS
E4916-N5	0,05	1,25	0,50	0,03	0,03	2,00 to 2,75	NS	NS	NS	NS	NS
E4918-N5	0,05	1,25	0,50	0,03	0,03	2,00 to 2,75	NS	NS	NS	NS	NS
E4928-N5	0,10	1,00	0,80	0,025	0,020	2,00 to 2,75	NS	NS	NS	NS	NS
E5516-N5	0,12	1,25	0,60	0,03	0,03	2,00 to 2,75	NS	NS	NS	NS	NS
E5518-N5	0,12	1,25	0,80	0,03	0,03	2,00 to 2,75	NS	NS	NS	NS	NS
E4915-N7	0,05	1,25	0,50	0,03	0,03	3,00 to 3,75	NS	NS	NS	NS	NS
E4916-N7	0,05	1,25	0,50	0,03	0,03	3,00 to 3,75	NS	NS	NS	NS	NS
E4918-N7	0,05	1,25	0,50	0,03	0,03	3,00 to 3,75	NS	NS	NS	NS	NS
E5516-N7	0,12	1,25	0,80	0,03	0,03	3,00 to 3,75	NS	NS	NS	NS	NS
E5518-N7	0,12	1,25	0,80	0,03	0,03	3,00 to 3,75	NS	NS	NS	NS	NS
E5516-N13	0,06	1,00	0,60	0,025	0,020	6,00 to 7,00	NS	NS	NS	NS	NS
E5518-N2M3	0,10	0,80 to 1,25	0,60	0,02	0,02	0,80 to 1,10	0,10	0,40 to 0,65	0,02	0,10	0,05
E4903-NC	0,12	0,30 to 1,40	0,90	0,03	0,03	0,25 to 0,70	0,30	NS	NS	0,20 to 0,60	NS
E4916-NC	0,12	0,30 to 1,40	0,90	0,03	0,03	0,25 to 0,70	0,30	NS	NS	0,20 to 0,60	NS
E4928-NC	0,12	0,30 to 1,40	0,90	0,03	0,03	0,25 to 0,70	0,30	NS	NS	0,20 to 0,60	NS
E5716-NC	0,12	0,30 to 1,40	0,90	0,03	0,03	0,25 to 0,70	0,30	NS	NS	0,20 to 0,60	NS
E5728-NC	0,12	0,30 to 1,40	0,90	0,03	0,03	0,25 to 0,70	0,30	NS	NS	0,20 to 0,60	NS
E4903-CC	0,12	0,30 to 1,40	0,90	0,03	0,03	NS	0,30 to 0,70	NS	NS	0,20 to 0,60	NS
E4916-CC	0,12	0,30 to 1,40	0,90	0,03	0,03	NS	0,30 to 0,70	NS	NS	0,20 to 0,60	NS
E4928-CC	0,12	0,30 to 1,40	0,90	0,03	0,03	NS	0,30 to 0,70	NS	NS	0,20 to 0,60	NS
E5716-CC	0,12	0,30 to 1,40	0,90	0,03	0,03	NS	0,30 to 0,70	NS	NS	0,20 to 0,60	NS

Table 10B (continued)

Classification	C	Mn	Si	P	S	Ni	Cr	Mo	V	Cu	Al
E5728-CC	0,12	0,30 to 1,40	0,90	0,03	0,03	NS	0,30 to 0,70	NS	NS	0,20 to 0,60	NS
E4903-NCC	0,12	0,30 to 1,40	0,90	0,03	0,03	0,05 to 0,45	0,45 to 0,75	NS	NS	0,30 to 0,70	NS
E4916-NCC	0,12	0,30 to 1,40	0,90	0,03	0,03	0,05 to 0,45	0,45 to 0,75	NS	NS	0,30 to 0,70	NS
E4928-NCC	0,12	0,30 to 1,40	0,90	0,03	0,03	0,05 to 0,45	0,45 to 0,75	NS	NS	0,30 to 0,70	NS
E5716-NCC	0,12	0,30 to 1,40	0,90	0,03	0,03	0,05 to 0,45	0,45 to 0,75	NS	NS	0,30 to 0,70	NS
E5728-NCC	0,12	0,30 to 1,40	0,90	0,03	0,03	0,05 to 0,45	0,45 to 0,75	NS	NS	0,30 to 0,70	NS
E4903-NCC1	0,12	0,50 to 1,30	0,35 to 0,80	0,03	0,03	0,40 to 0,80	0,45 to 0,70	NS	NS	0,30 to 0,75	NS
E4916-NCC1	0,12	0,50 to 1,30	0,35 to 0,80	0,03	0,03	0,40 to 0,80	0,45 to 0,70	NS	NS	0,30 to 0,75	NS
E4928-NCC1	0,12	0,50 to 1,30	0,80	0,03	0,03	0,40 to 0,80	0,45 to 0,70	NS	NS	0,30 to 0,75	NS
E5516-NCC1	0,12	0,50 to 1,30	0,35 to 0,80	0,03	0,03	0,40 to 0,80	0,45 to 0,70	NS	NS	0,30 to 0,75	NS
E5518-NCC1	0,12	0,50 to 1,30	0,35 to 0,80	0,03	0,03	0,40 to 0,80	0,45 to 0,70	NS	NS	0,30 to 0,75	NS
E5716-NCC1	0,12	0,50 to 1,30	0,35 to 0,80	0,03	0,03	0,40 to 0,80	0,45 to 0,70	NS	NS	0,30 to 0,75	NS
E5728-NCC1	0,12	0,50 to 1,30	0,80	0,03	0,03	0,40 to 0,80	0,45 to 0,70	NS	NS	0,30 to 0,75	NS
E4916-NCC2	0,12	0,40 to 0,70	0,40 to 0,70	0,025	0,025	0,20 to 0,40	0,15 to 0,30	NS	0,08	0,30 to 0,60	NS
E4918-NCC2	0,12	0,40 to 0,70	0,40 to 0,70	0,025	0,025	0,20 to 0,40	0,15 to 0,30	NS	0,08	0,30 to 0,60	NS
E49XX-G	NS	NS	NS	NS	NS	NS	NS	NS	NS	NS	NS
E55XX-G	NS	NS	NS	NS	NS	NS	NS	NS	NS	NS	NS
E57XX-G	NS	NS	NS	NS	NS	NS	NS	NS	NS	NS	NS

<sup>a</sup> Single values are maximum.

<sup>b</sup> NS = not specified.

## 7 Fillet weld test

The fillet weld test assembly shall be as shown in Figure 1 of ISO 15792-3:2000.

### 7A Classification by yield strength and 47 J impact energy

The plate material shall be selected from the range of materials for which the electrode is recommended by the manufacturer. The surface shall be free of scale, rust and other contaminants. The plate thickness ( $t$ ) shall be 10 mm to 12 mm, the width ( $w$ ) shall be 75 mm minimum and the length ( $l$ ) shall be 300 mm minimum. The electrode sizes to be tested for each coating type, the test positions and the required test results are given in Table 11A.

### 7B Classification by tensile strength and 27 J impact energy

The plate material shall be unalloyed steel of 0,30 % C maximum. The surfaces to be welded shall be clean. The test plate thickness ( $t$ ), width ( $w$ ) and length ( $l$ ), the test positions for each coating type, and the required test results are given in Table 11B.



**Table 11A — Test requirements for fillet welds <sup>a</sup>**  
(classification by yield strength and 47 J impact energy)

Symbol of position for classification	Coating type	Test position	Electrode size <sup>a</sup> mm	Fillet theoretical throat mm	Leg length difference mm	Convexity mm
1 or 2	C	PB	6,0	4,5 min.	1,5 max.	2,5 max.
	RX <sup>b</sup>			5,0 min.	2,0 max.	3,0 max.
	B			5,0 min.	2,0 max.	3,0 max.
3	A	PB	6,0	5,0 min.	2,0 max.	3,0 max.
	RR					
5	R	PB	6,0	4,5 min.	1,5 max.	2,5 max.
	B		5,0			
1 or 2	C	PF	4,0	4,5 max.	—	2,0 max.
	RX <sup>b</sup>			4,5 max.		
	B			5,5 max.		
1, 2 or 5	C	PD	4,0	4,5 max.	1,5 max.	2,5 max.
	RX <sup>b</sup>			4,5 max.	1,5 max.	2,5 max.
	B			5,5 max.	2,0 max.	3,0 max.
5	B	PG	4,0	5,0 min.	—	1,5 max. <sup>c</sup>

<sup>a</sup> Where the largest size claimed for positional welding is smaller than that specified, use the largest size and adjust criteria pro rata. Otherwise, electrode sizes not shown are not required to be tested.

<sup>b</sup> RX includes R, RC, RA and RB.

<sup>c</sup> Maximum concavity.

**Table 11B — Test requirements for fillet welds**  
(classification by tensile strength and 27 J impact energy)

Coating type	Current and polarity	Electrode size <sup>a</sup>	Test position	Nominal plate thickness	Minimum plate width	Minimum plate length	Fillet weld size	Maximum leg length difference	Maximum convexity
		mm		<i>t</i> mm	<i>w</i> mm	<i>l</i> mm			
03	a.c. and d.c. (+)	5,0	PF, PD	12	75	300	10,0 max.	2,0	1,5
		6,0	PB	12		400	8,0 min.	3,5	2,0
10	d.c. (+)	5,0	PF, PD	10	75	300	8,0 max.	3,5	1,5
		6,0	PB	12		400	6,5 min.	2,5	2,0
11	a.c. and d.c. (+)	5,0	PF, PD	10	75	300	8,0 max.	3,5	1,5
		6,0	PB	12		400	6,5 min.	2,5	2,0
12	a.c. and d.c. (-)	5,0	PF, PD	12	75	300	10,0 max.	2,0	1,5
		6,0	PB	12		400	8,0 min.	3,5	2,0
13	a.c., d.c. (-) and d.c. (+)	5,0	PF, PD	12	75	300	10,0 max.	2,0	1,5
		6,0	PB	12		400	8,0 min.	3,5	2,0
14	a.c., d.c. (-) and d.c. (+)	4,0	PF, PD	10	75	300	8,0 max.	3,5	2,0
		6,0	PB	12		400	8,0 min.	3,5	2,0
15	d.c. (+)	4,0	PF, PD	10	75	300	8,0 max.	3,5	2,0
		6,0	PB	12		400	8,0 min.	3,5	2,0
16	a.c. and d.c. (+)	4,0	PF, PD	10	75	300	8,0 max.	3,5	2,0
		6,0	PB	12		400	8,0 min.	3,5	2,0
18	a.c. and d.c. (+)	4,0	PF, PD	10	75	300	8,0 max.	3,5	2,0
		6,0	PB	12		400	8,0 min.	3,5	2,0
19	a.c. and d.c. (+)	5,0	PF, PD	12	75	300	10,0 max.	2,0	1,5
		6,0	PB	12		400	8,0 min.	3,5	2,0
20	a.c. and d.c. (-)	6,0	PB	12	75	400	8,0 min.	3,5	2,0
24	a.c., d.c. (-) and d.c. (+)	6,0	PB	12	75	400 or 650 <sup>b</sup>	8,0 min.	3,5	2,0
27	a.c. and d.c. (-)	6,0	PB	12	75	400 or 650 <sup>b</sup>	8,0 min.	3,5	2,0
28	a.c. and d.c. (+)	6,0	PB	12	75	400 or 650 <sup>b</sup>	8,0 min.	3,5	2,0
40	NS <sup>c</sup>	NS <sup>c</sup>	NS <sup>c</sup>	NS <sup>c</sup>	75	NS <sup>c</sup>	NS <sup>c</sup>	NS <sup>c</sup>	NS <sup>c</sup>
48	a.c. and d.c. (+)	4,0	PD	10	75	300	8,0 max.	3,5	2,0
		5,0	PB, PG	10		300 or 400 <sup>d</sup>	6,5 min.	2,5	2,0

<sup>a</sup> Where the largest size claimed for positional welding is smaller than that specified, use the largest size and adjust criteria pro rata. Otherwise, electrode sizes not shown are not required to be tested.

<sup>b</sup> For 450 mm electrode length, *l* shall be 400 minimum; for 700 mm electrode length, *l* shall be 650 mm minimum.

<sup>c</sup> NS = not specified. Requirements shall be agreed between purchaser and supplier.

<sup>d</sup> For 350 mm electrode length, *l* shall be 300 mm minimum; for 450 mm or 460 mm electrode length, *l* shall be 400 mm minimum.

## **8 Retest**

If any test fails to meet the requirement, that test shall be repeated twice. The results of both retests shall meet the requirement. Specimens for the retest may be taken from the original test assembly or from a new test assembly. For chemical analysis, retesting need be only for those specific elements that failed to meet their test requirement. If the results of one or both retests fail to meet the requirement, the material under test shall be considered as not meeting the requirements of this specification for that classification.

In the event that, during preparation or after completion of any test, it is clearly determined that prescribed or proper procedures were not followed in preparing the weld test assembly or test specimen(s), or in conducting the tests, the test shall be considered invalid, without regard to whether the test was actually completed, or whether the test results met, or failed to meet, the requirement. That test shall be repeated, following properly prescribed procedures. In this case, the requirement for doubling the number of test specimens does not apply.

## **9 Technical delivery conditions**

Technical delivery conditions shall meet the requirements in ISO 544 and in ISO 14344.

## 10 Examples of designation

### 10A Classification by yield strength and 47 J impact energy

The designation of the covered electrode is indicated by the suffix letter A given after the number of this International Standard and shall follow the principle given in the example below.

#### EXAMPLE 1A:

A covered electrode for manual metal arc welding which deposits a weld metal with a minimum yield strength of 460 N/mm<sup>2</sup> (46) and a minimum average impact energy of 47 J at - 30 °C (3) with a chemical composition of 1,1 % Mn and 0,7 % Ni (1Ni) having a basic covering (B) and a nominal electrode efficiency recovery of 140 % and which may be used with a.c. and d.c. (5) in flat butt and flat fillet welds (4) and whose hydrogen content is determined in accordance with ISO 3690 and does not exceed 5 ml/100 g of deposited metal (H5) is designated as follows:

**ISO 2560-A - E 46 3 1Ni B 54 H5**

Compulsory section:

**ISO 2560-A - E 46 3 1Ni B**

where:

ISO 2560-A = the number of this International Standard, classification by yield strength and 47 J impact energy;

E = covered electrode/manual metal arc welding (see 4.1);

46 = strength and elongation (see Table 1A);

3 = impact properties (see Table 2A);

1Ni = chemical composition of all-weld metal (see Table 3A);

B = type of electrode covering (see 4.5A);

5 = nominal electrode efficiency and type of current (see Table 5A);

4 = welding position (see Table 6A);

H5 = hydrogen content (see Table 7).

### 10B Classification by tensile strength and 27 J impact energy

The designation of the covered electrode is indicated by the suffix letter B given after the number of this International Standard and shall follow the principle given in the example below.

#### EXAMPLE 1B:

A covered electrode for manual metal arc welding which deposits a weld metal with a minimum tensile strength of 550 N/mm<sup>2</sup> (55) and which meets a 47 J impact requirement at - 40 °C (U) in the as-welded condition and also exceeds 27 J at - 40 °C in the as-welded condition (A) with a chemical composition of 1,1 % Mn and 1 % Ni (-N2) having a basic covering including iron powder and which may be used with a.c. and d.c. + in all positions except vertical down (18) and whose hydrogen content is determined in accordance with ISO 3690 and does not exceed 5 ml/100 g of deposited metal (H5) is designated as follows:

**ISO 2560-B - E55 18-N2 A U H5**

Compulsory section:

**ISO 2560-B - E55 18-N2 A**

where:

ISO 2560-B = the number of this International Standard, classification by tensile strength and 27 J impact energy;

E = covered electrode/manual metal arc welding (see 4.1);

55 = tensile strength (see Table 1B);

18 = basic iron powder coating suitable for a.c. and d.c. (+), in all positions except vertical down (see Table 4B);

-N2 = 1% Ni as the principle alloying element (see Table 3B);

E5518-N2 A = complete specification of composition limits and mechanical property requirements (see Tables 8B and 10B) in the as-welded condition;

U = supplemental impact requirement of 47 J at the basic 27 J impact test temperature;

H5 = hydrogen content (see Table 7).

**Annex A**  
(informative)

**Classification systems**


**A.1 ISO 2560-A**

The ISO 2560-A classification system for covered electrodes for non-alloy and fine grain steels, based upon yield strength and 47 J minimum impact energy, is shown in Figure A.1.

**A.2 ISO 2560-B**

The ISO 2560-B classification system for covered electrodes for non-alloy and fine grain steels, based upon tensile strength and 27 J minimum impact energy, is shown in Figure A.2.

**Compulsory classification designators<sup>a</sup>**

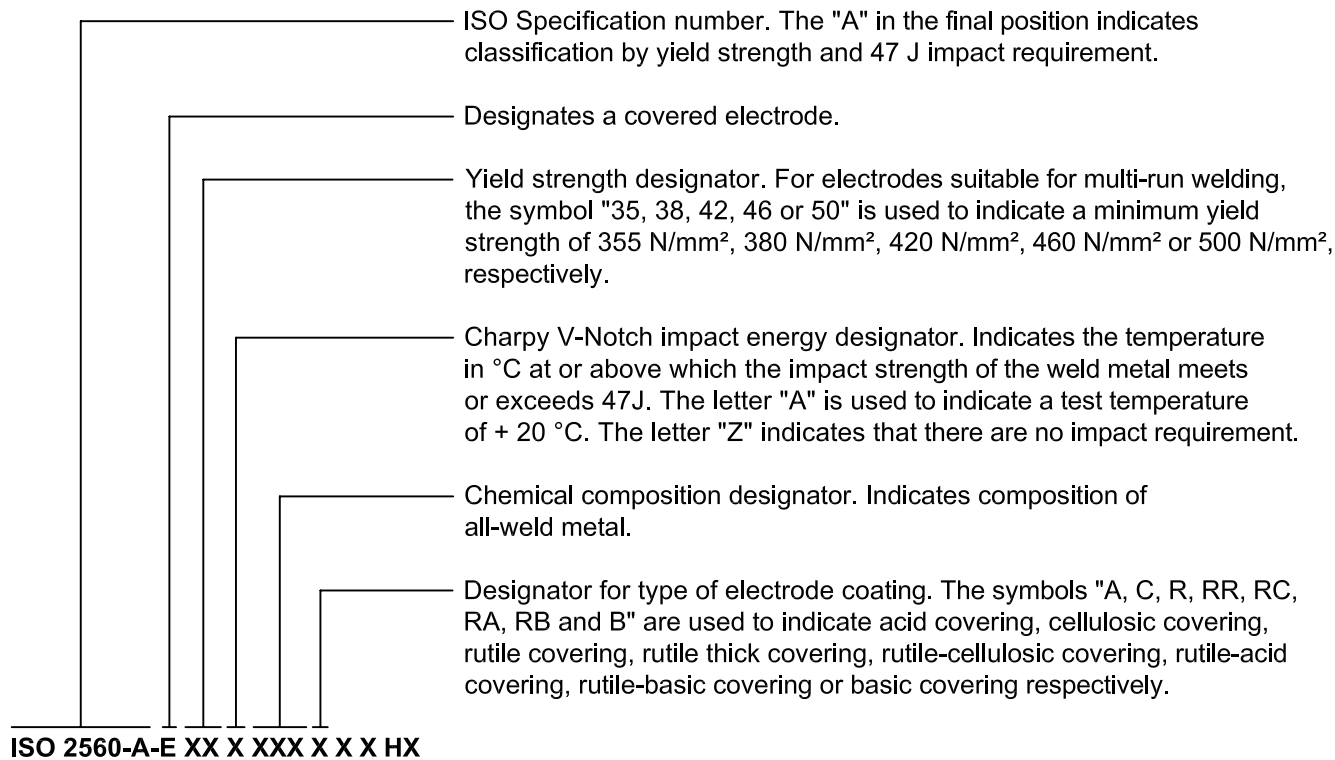

**Optional supplemental designators<sup>b</sup>**


- Optional supplemental diffusible hydrogen designator:** "H5, H10 or H15" is used to indicate a maximum diffusible hydrogen content of 5 ml/100 g, 10 ml/100 g or 15 ml/100 g of deposited metal, respectively.
- Positionality designator:** The symbol "1, 2, 3, 4 or 5" indicates the welding position(s) for which the electrode is suitable.
- Metal recovery and type of current indicator:** The symbol "1, 2, 3, 4, 5, 6, 7 or 8" indicates the weld metal recovery and type of current.

<sup>a</sup> The combination of these designators constitutes the covered electrode classification.

<sup>b</sup> These designators are optional and do not constitute part of the covered electrode classification.

**Figure A.1 — ISO 2560-A designation of electrodes (classification by yield strength and 47 J impact energy)**

**Compulsory classification designators<sup>a</sup>**

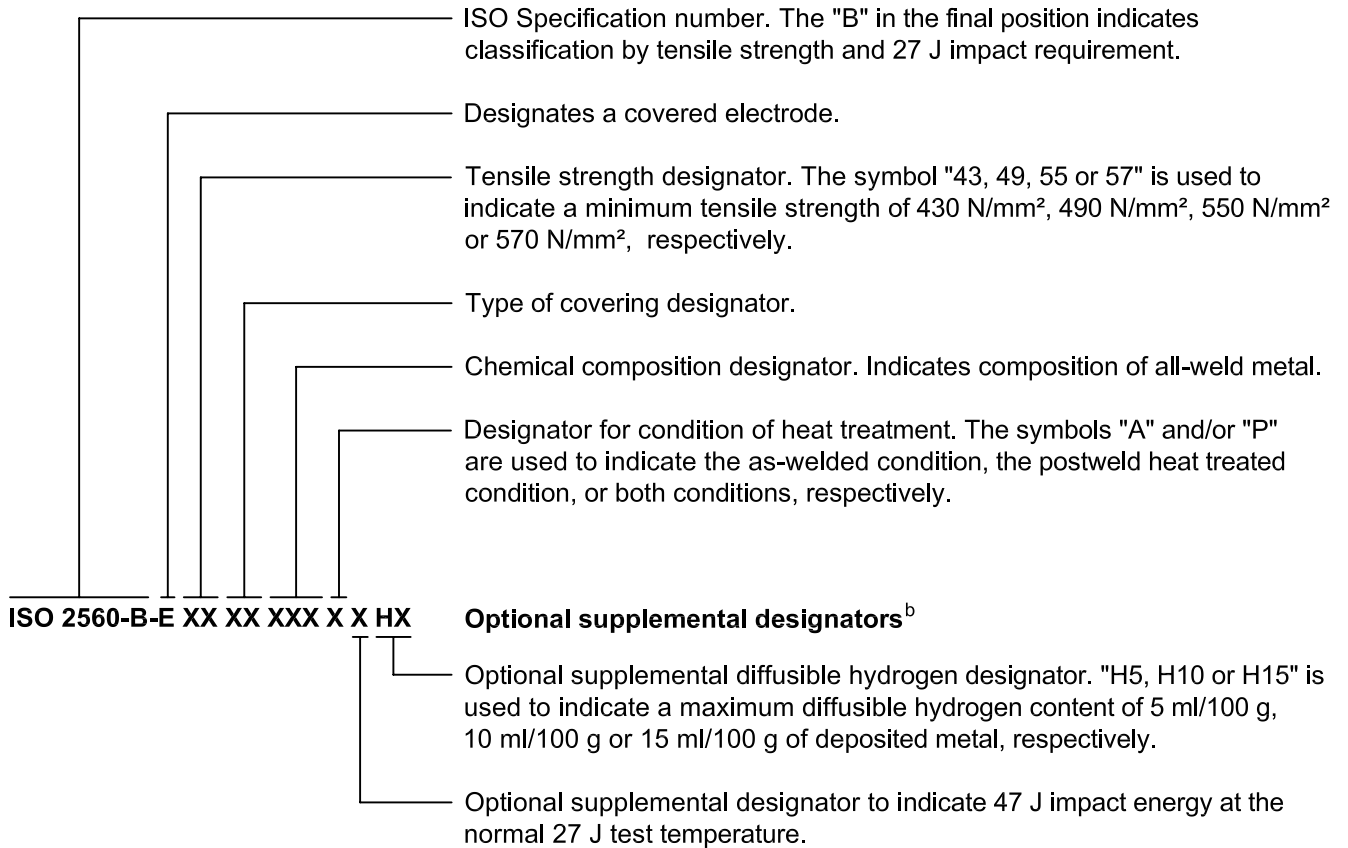

<sup>a</sup> The combination of these designators constitutes the covered electrode classification.

<sup>b</sup> These designators are optional and do not constitute part of the covered electrode classification.

**Figure A.2 — ISO 2560-B designation of electrodes (classification by tensile strength and 27 J impact energy)**

## Annex B (informative)

### Description of types of electrode covering — Classification by yield strength and 47 J impact energy

#### B.1 General

The properties of a covered electrode, i.e., both its welding characteristics and mechanical properties of the weld metal are decisively influenced by the covering. This homogeneous mixture of substances generally contains the following six main components:

- slag-forming materials;
- deoxidants;
- shielding gas-forming materials;
- ionizing agents;
- binders;
- alloying elements (if necessary).

In addition, iron powder may be added to increase the nominal electrode efficiency (see 4.6A), which may affect the positional welding properties.

In the following, "thick covering" means a diameter ratio of covering to core wire greater than or equal to 1:6.

#### B.2 Acid-covered electrodes

The covering of this type is characterized by large proportions of iron oxides and, as a result of the high oxygen potential, of deoxidants (ferro-manganese). With a thick covering, the acid slag causes a very fine droplet transfer and produces flat and smooth welds. Electrodes with acid covering only have a limited application for positional welding and are more susceptible to solidification cracking than other types.

#### B.3 Cellulosic-covered electrodes

Electrodes of this type contain a large quantity of combustible organic substances, particularly cellulose, in the covering. Owing to the intensive arc, such electrodes are especially suitable for welding in the vertical downward position.

#### B.4 Rutile-covered electrodes

Electrodes of this type will give a coarse droplet transfer which ensures that these electrodes are suitable for welding sheet metal. Rutile type electrodes are suitable for all welding positions, except the vertical downward position.



## B.5 Rutile-thick-covered electrodes

Electrodes of this type have a diameter ratio of covering to core wire greater than or equal to 1:6. Characteristic features are the high rutile content of their covering, their good restriking characteristics and their finely rippled regular welds.

## B.6 Rutile-cellulosic-covered electrodes

The composition of the covering of these electrodes is similar to that of rutile-type electrodes, containing, however, larger quantities of cellulose. Electrodes of this type are therefore suitable for welding in the vertical downward position.

## B.7 Rutile-acid-covered electrodes

Concerning welding characteristics, electrodes of this mixed type are comparable to electrodes having an acid covering.

However, in the covering of these electrodes a substantial proportion of iron oxide has been replaced by rutile. Therefore, these electrodes, having mostly a thick covering, are suitable for all positions, except the vertical downward position.

## B.8 Rutile-basic-covered electrodes

Characteristic features of this type of covering are a large quantity of rutile and an increased proportion of basic components. These electrodes, having mostly a thick covering, are characterized by good mechanical properties. They possess uniformly good welding properties in all positions except the vertical downward position.

## B.9 Basic-covered electrodes

A characteristic feature of the thick covering of these electrodes is the large quantity of carbonates of the alkaline earth metals, e.g. calcium carbonate (lime) and fluorspar. To improve the welding properties, particularly with a.c. welding, higher concentrations of non-basic components (e.g. rutile and/or quartz) may be required.

Basic-covered electrodes have two outstanding properties: a) the impact energy of the weld metal is higher, particularly at low temperatures; b) they are more resistant to cracking than all other types.

Their resistance to solidification cracking results from the high metallurgical purity of the weld metal, whilst the low risk of cold cracking, provided dry electrodes are used, is attributable to the low hydrogen content. It is lower than with all other types and should not exceed an upper permissible limit of  $H = 15 \text{ ml/100 g}$  of deposited metal.

Generally, electrodes of the basic type are suitable for all welding positions, except the vertical downward position. Basic-type electrodes especially suited for the vertical downward position have a particular composition.

## Annex C (informative)

### Description of types of electrode covering — Classification by tensile strength and 27 J impact energy

#### C.1 General

The properties of a covered electrode, i.e., both its welding characteristics and mechanical properties of the weld metal are decisively influenced by the covering. This homogeneous mixture of substances generally contains the following six main components:

- slag-forming materials;
- deoxidants;
- shielding gas-forming materials;
- ionizing agents;
- binders;
- alloying elements (if necessary).

In addition, iron powder may be added to increase the nominal electrode efficiency, which may affect the positional welding properties.

Certain electrode designs, while usable on both a.c. and d.c. (either or both polarities) may be optimized by their manufacturer for one particular current type for a particular market need.

#### C.2 Covering type 03

Electrodes of this type contain a mixture of titanium dioxide (rutile) and calcium carbonate (lime), so they share some characteristics of rutile electrodes with some characteristics of basic electrodes. See C.6 and C.9 below.

#### C.3 Covering type 10

Electrodes of this type contain a large quantity of combustible organic substances, particularly cellulose, in the covering. Owing to the intensive arc, such electrodes are especially suitable for welding in the vertical downward position. Arc stabilization is primarily by sodium, so the electrodes are mainly suitable for d.c. welding, normally with electrode positive.

#### C.4 Covering type 11

Electrodes of this type contain a large quantity of combustible organic substances, particularly cellulose, in the covering. Owing to the intensive arc, such electrodes are especially suitable for welding in the vertical downward position. Arc stabilization is primarily by potassium, so the electrodes are suitable for both a.c. and d.c., electrode positive, welding.

### **C.5 Covering type 12**

Electrodes of this type contain a large quantity of titanium dioxide (usually in the form of the mineral rutile) in the covering. Their soft arc makes them suitable for bridging wide root gaps under conditions of poor fit.

### **C.6 Covering type 13**

Electrodes of this type contain a large quantity of titanium dioxide (rutile) and are heavily stabilized with potassium. They produce a soft quiet arc at lower currents than electrodes with covering type 12, and are especially suitable for sheet metal.

### **C.7 Covering type 14**

Electrodes of this type have covering similar to types 12 and 13, but with the addition of a small amount of iron powder. The iron powder permits higher current and provides higher deposition rate. Nevertheless, they are suitable for use in all welding positions.

### **C.8 Covering type 15**

Electrodes of this type have a covering that is highly basic, consisting largely of lime and fluorspar. Arc stabilization is provided mainly by sodium, and they are generally suitable for use on d.c. (+) only. They produce weld metal of high metallurgical quality with low diffusible hydrogen.

### **C.9 Covering type 16**

Electrodes of this type have a covering that is highly basic, consisting largely of lime and fluorspar. Arc stabilization with potassium is responsible for their ability to weld with alternating current. They produce weld metal of high metallurgical quality with low diffusible hydrogen.

### **C.10 Covering type 18**

Electrodes of this type are similar to electrodes of covering type 16, except that they have a somewhat thicker coating with the addition of iron powder. The iron powder increases their current-carrying capacity and deposition rate, as compared to electrodes of covering type 16.

### **C.11 Covering type 19**

Electrodes of this type contain oxides of titanium and iron, usually combined in the form of the mineral ilmenite. Although they are not low-hydrogen basic electrodes, they are capable of producing weld metal of relatively high toughness.

### **C.12 Covering type 20**

Electrodes of this type contain large amounts of iron oxide. The slag is very fluid, so that welding is generally suitable only in flat and horizontal positions. They are primarily designed for fillet and lap welds.

### **C.13 Covering type 24**

Electrodes of this type are similar to electrodes of covering type 14, except that the covering is thicker and contains a higher portion of iron powder. They are generally only suitable for flat and horizontal welding positions. Principal applications are in fillet and lap welds.

### **C.14 Covering type 27**

Electrodes of this type are similar to electrodes of covering type 20, except that the covering is thicker and contains large amounts of iron powder in addition to the iron oxide of covering type 20. Electrodes of covering type 27 are primarily designed for high speed fillet and lap welds.

### **C.15 Covering type 28**

Electrodes of this type are similar to electrodes of covering type 18, except that the covering is thicker and contains more iron powder. As such, they are generally limited to use in the flat and horizontal positions. The resulting weld metal is of high metallurgical quality with low hydrogen content.

### **C.16 Covering type 40**

Electrodes having this type of covering cannot be classified as having any other covering type in this specification. They are manufactured to meet very specific usability or application requirements of the purchaser. Welding position is a matter of agreement between supplier and purchaser. A specific example might be an electrode specially designed for welding inside holes ("plug welding") or inside slots. Since covering type 40 is non-specific, a given electrode identified as having this covering type might be very different from another electrode identified as having this covering type.

### **C.17 Covering type 48**

Electrodes of this type are similar to electrodes of covering type 18, except that the covering is specifically designed for vertical downward welding.

## **Annex D** (informative)

### **Notes on diffusible hydrogen**

**D.1** Other methods of collection and measurement of diffusible hydrogen may be used for batch testing provided they possess equal reproducibility with, and are calibrated against the method given in ISO 3690. The hydrogen is influenced by the type of current.

**D.2** Cracks in welded joints may be caused or significantly influenced by hydrogen. The risk of hydrogen-induced cracks increases with rising alloy content and stress level. Such cracks generally develop after the joint has become cold and are therefore termed cold cracks.

**D.3** Assuming that the external conditions are satisfactory (i.e. weld areas clean and dry) the hydrogen in the weld metal stems from hydrogen-containing compounds in the consumables; in the case of basic covered electrodes the water taken up by the covering is the main source. The water dissociates in the arc and gives rise to atomic hydrogen which is absorbed by the weld metal. Under given material and stress conditions the risk of cold cracking diminishes with decreasing hydrogen content of the weld metal.

**D.4** In practice, the appropriate hydrogen level will depend on the particular application and, to ensure that this is achieved, the relevant handling, storage and drying conditions recommended by the electrode manufacturer should be followed.

## Bibliography

- [1] EN 499, *Welding consumables — Covered electrodes for manual metal arc welding of non alloy and fine grain steels — Classification*



---

---

## BSI — British Standards Institution

BSI is the independent national body responsible for preparing British Standards. It presents the UK view on standards in Europe and at the international level. It is incorporated by Royal Charter.

### Revisions

British Standards are updated by amendment or revision. Users of British Standards should make sure that they possess the latest amendments or editions.

It is the constant aim of BSI to improve the quality of our products and services. We would be grateful if anyone finding an inaccuracy or ambiguity while using this British Standard would inform the Secretary of the technical committee responsible, the identity of which can be found on the inside front cover. Tel: +44 (0)20 8996 9000. Fax: +44 (0)20 8996 7400.

BSI offers members an individual updating service called PLUS which ensures that subscribers automatically receive the latest editions of standards.

### Buying standards

Orders for all BSI, international and foreign standards publications should be addressed to Customer Services. Tel: +44 (0)20 8996 9001. Fax: +44 (0)20 8996 7001. Email: [orders@bsi-global.com](mailto:orders@bsi-global.com). Standards are also available from the BSI website at <http://www.bsi-global.com>.

In response to orders for international standards, it is BSI policy to supply the BSI implementation of those that have been published as British Standards, unless otherwise requested.

### Information on standards

BSI provides a wide range of information on national, European and international standards through its Library and its Technical Help to Exporters Service. Various BSI electronic information services are also available which give details on all its products and services. Contact the Information Centre. Tel: +44 (0)20 8996 7111. Fax: +44 (0)20 8996 7048. Email: [info@bsi-global.com](mailto:info@bsi-global.com).

Subscribing members of BSI are kept up to date with standards developments and receive substantial discounts on the purchase price of standards. For details of these and other benefits contact Membership Administration. Tel: +44 (0)20 8996 7002. Fax: +44 (0)20 8996 7001. Email: [membership@bsi-global.com](mailto:membership@bsi-global.com).

Information regarding online access to British Standards via British Standards Online can be found at <http://www.bsi-global.com/bsonline>.

Further information about BSI is available on the BSI website at <http://www.bsi-global.com>.

### Copyright

Copyright subsists in all BSI publications. BSI also holds the copyright, in the UK, of the publications of the international standardization bodies. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI.

This does not preclude the free use, in the course of implementing the standard, of necessary details such as symbols, and size, type or grade designations. If these details are to be used for any other purpose than implementation then the prior written permission of BSI must be obtained.

Details and advice can be obtained from the Copyright & Licensing Manager. Tel: +44 (0)20 8996 7070. Fax: +44 (0)20 8996 7553. Email: [copyright@bsi-global.com](mailto:copyright@bsi-global.com).