

Sintered metal materials, excluding hardmetals — Tensile test pieces (ISO 2740:2009)

ICS 77.040.10; 77.160

National foreword

This British Standard is the UK implementation of EN ISO 2740:2009. It supersedes BS EN ISO 2740:2007 which is withdrawn.

The UK participation in its preparation was entrusted to Technical Committee ISE/65, Sintered metal components.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 30 November 2009.

© BSI 2009

ISBN 978 0 580 62212 0

Amendments/corrigenda issued since publication

Date	Comments

English Version

**Sintered metal materials, excluding hardmetals - Tensile test
pieces (ISO 2740:2009)**

Matériaux en métal fritté, à l'exclusion des métaux-durs -
Éprouvettes pour essai de traction (ISO 2740:2009)

Sintermetalle, ausgenommen Hartmetalle - Zugprobestäbe
(ISO 2740:2009)

This European Standard was approved by CEN on 13 April 2009.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

Management Centre: Avenue Marnix 17, B-1000 Brussels

Foreword

This document (EN ISO 2740:2009) has been prepared by Technical Committee ISO/TC 119 "Powder metallurgy" in collaboration with Technical Committee CEN/SS M11 "Powder metallurgy" the secretariat of which is held by CMC.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by November 2009, and conflicting national standards shall be withdrawn at the latest by November 2009.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN [and/or CENELEC] shall not be held responsible for identifying any or all such patent rights.

This document supersedes EN ISO 2740:2007.

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland and the United Kingdom.

Endorsement notice

The text of ISO 2740:2009 has been approved by CEN as a EN ISO 2740:2009 without any modification.

Contents

Page

Foreword..... iv

1 Scope1

2 Normative references1

3 Method of testing1

4 Manufacture of test pieces1

5 Metal injection-moulded test pieces2

6 Machined test pieces2

7 Identification of test pieces3

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 2740 was prepared by Technical Committee ISO/TC 119, *Powder metallurgy*, Subcommittee SC 3, *Sampling and testing methods for sintered metal materials (excluding hardmetals)*.

This fifth edition cancels and replaces the fourth edition (ISO 2740:2007), of which it constitutes a minor revision.

Sintered metal materials, excluding hardmetals — Tensile test pieces

1 Scope

This International Standard is applicable to all sintered metals and alloys, excluding hardmetals.

This International Standard specifies:

- the die cavity dimensions used for making tensile test pieces by pressing and sintering, and by Metal Injection Moulding (MIM) and sintering;
- the dimensions of tensile test pieces machined from sintered and powder forged materials.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 6892, *Metallic materials — Tensile testing at ambient temperature*

ISO 7500-1, *Metallic materials — Verification of static uniaxial testing machines — Part 1: Tension/compression testing machines — Verification and calibration of the force-measuring system*

3 Method of testing

3.1 Test pieces shall be tested in accordance with ISO 6892, and the tensile test machine shall be calibrated to Class 1, in accordance with ISO 7500-1.

3.2 Data are to be reported for three or more test pieces.

4 Manufacture of test pieces

4.1 Pressed and sintered test pieces

The tensile test pieces shall have thicknesses from 5 mm to 6,5 mm. A thickness tolerance of 1,5 mm accommodates varying apparent densities in metal powders. During testing, the thinner pieces have less grip slippage and are more likely to break near the centre of the gauge length.

If necessary for measuring elongation, marks may be lightly scribed 25 mm apart and symmetrically about the centre line [see Figures 1 a) and 2 a)]. Between the scribed marks, the thickness shall not vary by more than 0,04 mm. The gauge length shall be scribed in such a way that the tensile properties are not affected.

Because of the possibility of creating microlaminations in the corners of test pieces compacted under laboratory conditions, representative sintered test pieces shall be examined metallographically to show that there are no microlaminations longer than 0,25 mm.

4.2 Die specifications

The dimensions of the two permitted die cavities are shown in Figures 1 b) and 2 b). The dies should preferably be of hardmetal and their surface finish shall be such as to allow compression of the test pieces under normal conditions. Dies may include a small exit taper to facilitate ejection and to avoid cracks or microlaminations in the test pieces. A die cavity tapered 0,01 per side, to aid ejection, may be enlarged by 0,5 % for tooling to be used for repressing. The dies should be well supported with shrink rings, so as to minimize lateral expansion during compacting. Such a support decreases the possibility of cracking of the specimen at ejection. To reduce the incidence of cracks in the specimen, it is recommended to use top-punch hold-down during ejection.

The die in Figure 1 b) is recommended for as-sintered test pieces. Gripping is readily accomplished by sliding the 20° wedge faces of the test piece into matching pockets machined in the grips. Figure 1 a) shows the test piece.

The die in Figure 2 b) is recommended for as-sintered test pieces. The test piece is gripped on the raised serrations compacted on its gripping ends, to prevent slippage during testing. It is important for testing that the grips fit properly into the clevis. Alternatively, the test piece is compacted without serrations and gripped on the flat faces.

Test pieces made from the dies in Figure 1 b) or 2 b) are recommended for materials to be tested in the as-sintered condition. When testing relatively brittle, heat-treated materials, the constraint of the test piece's sharp corners can result in tensile values that are lower than those obtained with machined tensile test pieces (see Figure 5).

5 Metal injection-moulded test pieces

Figure 3 shows a larger diameter of the die cavity for Metal Injection Moulding (MIM) tensile test pieces of type A. Figure 4 shows a smaller die cavity for MIM tensile test pieces of type B. During testing, the through-holes are intended to surround hardened steel pins. The pins are gripped in a clevis, and mounted on a testing machine in a self-aligning manner. The holes may optionally be drilled after sintering, rather than moulded with no draft permitted. These optional hole diameters should be: a diameter of $6,5 \text{ mm} +_{0}^{0,25} \text{ mm}$ for a large bar or a diameter of $4,77 \text{ mm} +_{0}^{0,25} \text{ mm}$ for a small bar, after sintering. The die dimensions assume about 17 % shrinkage during sintering, but variations in shrinkage are permitted. Either bar design may be used. Gauge marks may be scribed as noted in 4.1.

The gate, manufacturer's identification and ejector location are optional, but shall not be in the gauge length L_C and not in the gripping area.

6 Machined test pieces

6.1 Figure 5 shows the dimensions of a machined button-head tensile test piece. This is conveniently machined from a standard 10 mm × 10 mm × 75 mm impact bar. The taper of 0,1 mm in the nominal diameters, over the gauge length, generally results in fracture occurring within the gauge region, even for relatively brittle materials.

If a material is to be carburized after grinding, the surface pores in the gauge region shall be left open to allow carburizing gases to enter. Final polishing shall be in the longitudinal direction (no circumferential scratch lines shall be visible).

The test piece is gripped by a split collet, closely surrounding the 20° tapered region. During testing, the test piece is supported on the same taper. The test piece may have a 25 mm gauge length lightly scribed as in 4.1.

This test piece is primarily recommended for testing materials in the heat-treated condition, where elongations at fracture may be < 0,5 % in 25 mm. This test piece is recommended for use when the volume fraction of martensite is > 20 %, regardless of whether the test piece is as-sintered or heat-treated. Some work-hardening occurs during machining, and if the test piece is tested in the sintered and machined condition, the work-hardening can lower elongation and raise yield strength. This is particularly true for stainless steels.

During austenitizing and oil quenching, the usual sintered alloy steels may not fully harden to the centre of the machined test pieces. Such test pieces may be further qualified in the report, by indicating the hardness from the surface to the core.

6.2 Other cylindrical machined test pieces are possible and should conform to ISO 6892.

When the diameter of the useful part of the test pieces is less than 4 mm, its value shall be stated together with the fact that the results of the test may not be comparable with those obtained from test pieces of larger diameters.

For sintered products, it is recommended that a test piece having two shoulders at each end be used. The radius of the inner shoulder shall be between 1,5 mm and 2,5 mm (see Figure 5).

7 Identification of test pieces

For the identification of test pieces, the following shall be stated:

- a) a reference to this International Standard, i.e. ISO 2740;
- b) type of material;
- c) density of test piece;
- d) dimensions of test piece (thickness);
- e) when pressed and sintered test pieces are made according to 4.1, the nature of any finishing treatment and also, preferably, the material and the surface finish of the compacting tool;
- f) form of test piece, i.e. figure number of this International Standard;
- g) die material, i.e. tool steel or hardmetal/carbide;
- h) whether as-sintered or heat-treated;
- i) hardness of test piece according to the heat treatment.

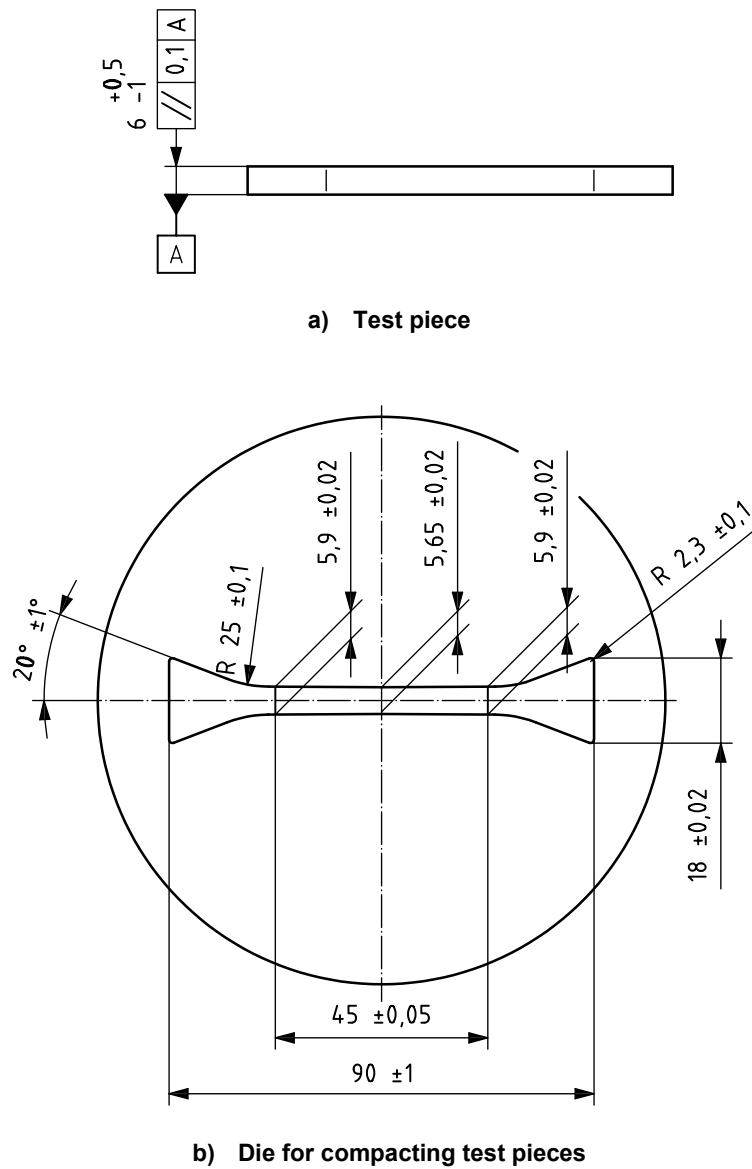


Figure 1 — Test piece and die for tensile testing — Smooth grips

Dimensions in millimetres



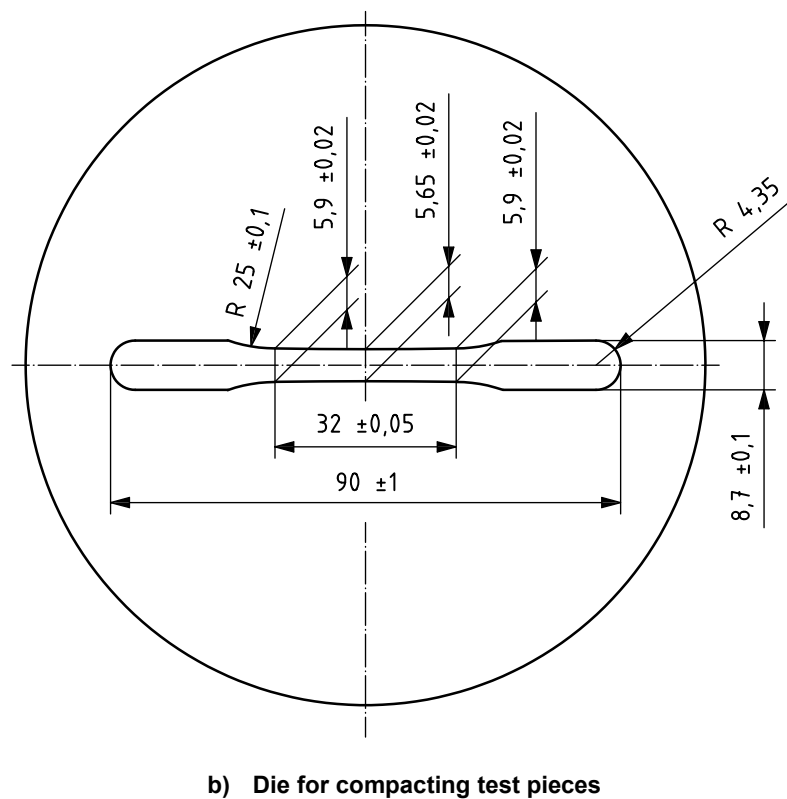



Figure 2 — Test piece and die for tensile testing — Serrated grips

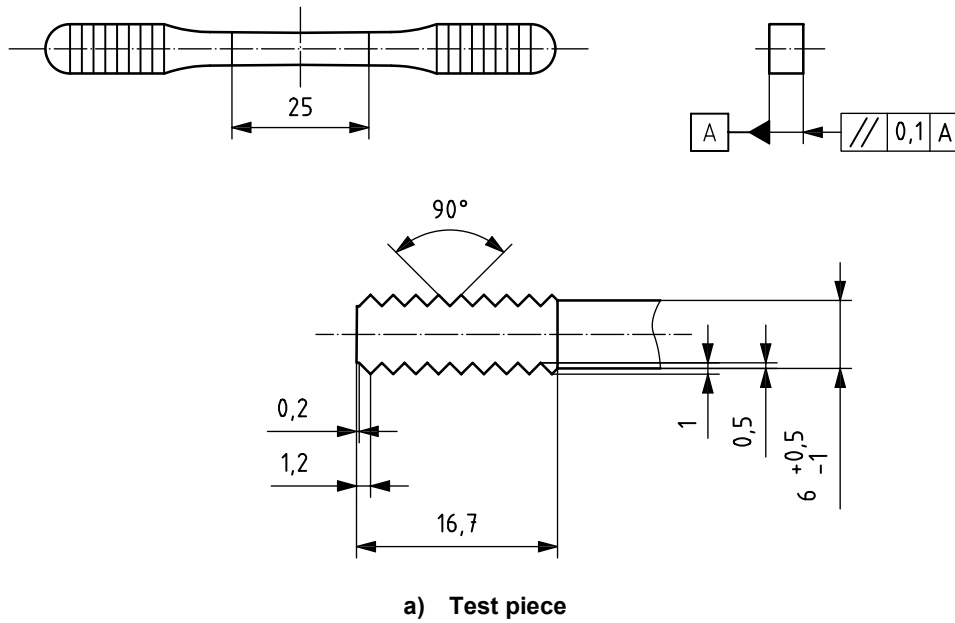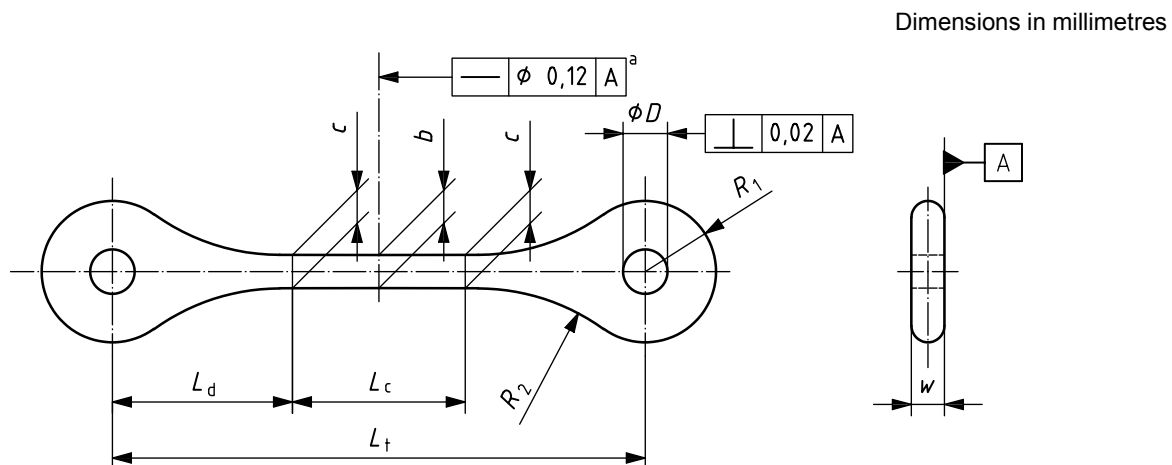

^a Applies to gauge length L_c .

Type	b	c	L_c	L_d	L_t	w	R_1	R_2	D
		$\pm 0,1$	$\pm 0,1$	$\pm 0,2$	$\pm 0,2$	$\pm 0,5$	0,1	$\pm 0,5$	$\pm 0,5$
A1	$\varnothing 5,82$	$\varnothing 5,87$	30,5	31,75	94	5,85	R 25	R 38	$\varnothing 7,85$
A2	$\varnothing 3,8$	$\varnothing 3,85$	30,5	27,5	85,5	3,85	R 23	R 23	$\varnothing 6$

Figure 3 — Die cavity for MIM tensile test pieces of type A

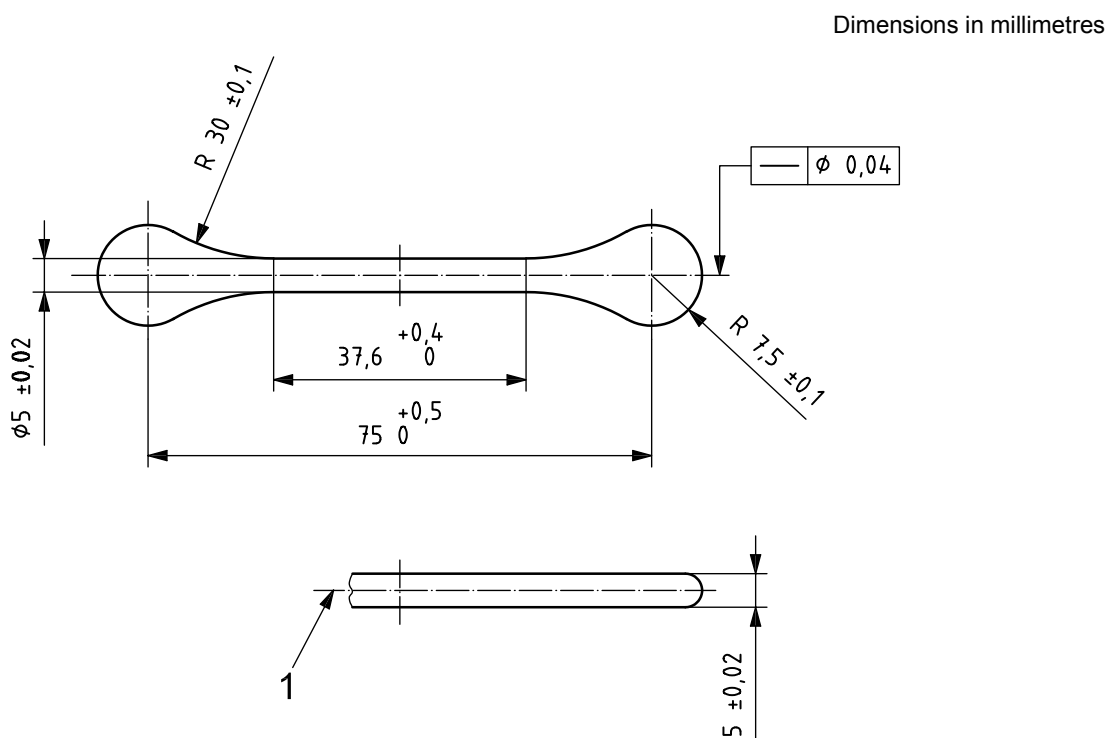


Key

1 mould-division plane

Figure 4 — Die cavity for MIM tensile test pieces of type B

Dimensions in millimetres

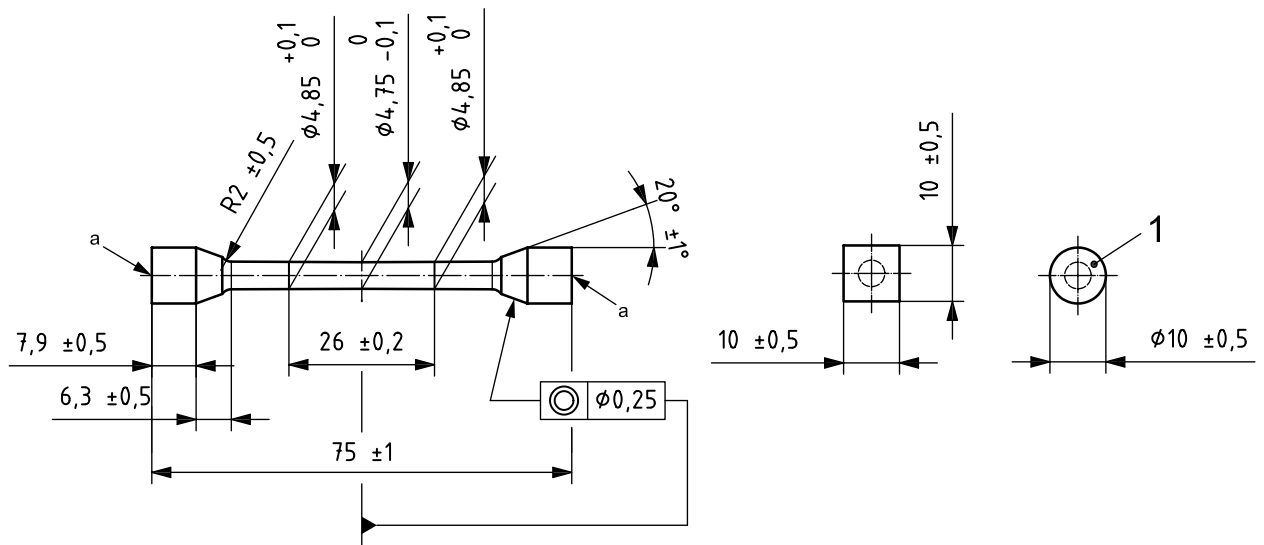

Key

- 1 alternative end
- a Centering holes are acceptable.

Figure 5 — Machined tensile test piece

BSI - British Standards Institution

BSI is the independent national body responsible for preparing British Standards. It presents the UK view on standards in Europe and at the international level. It is incorporated by Royal Charter.

Revisions

British Standards are updated by amendment or revision. Users of British Standards should make sure that they possess the latest amendments or editions.

It is the constant aim of BSI to improve the quality of our products and services. We would be grateful if anyone finding an inaccuracy or ambiguity while using this British Standard would inform the Secretary of the technical committee responsible, the identity of which can be found on the inside front cover. Tel: +44 (0)20 8996 9000. Fax: +44 (0)20 8996 7400.

BSI offers members an individual updating service called PLUS which ensures that subscribers automatically receive the latest editions of standards.

Buying standards

Orders for all BSI, international and foreign standards publications should be addressed to Customer Services. Tel: +44 (0)20 8996 9001. Fax: +44 (0)20 8996 7001 Email: orders@bsigroup.com You may also buy directly using a debit/credit card from the BSI Shop on the Website <http://www.bsigroup.com/shop>

In response to orders for international standards, it is BSI policy to supply the BSI implementation of those that have been published as British Standards, unless otherwise requested.

Information on standards

BSI provides a wide range of information on national, European and international standards through its Library and its Technical Help to Exporters Service. Various BSI electronic information services are also available which give details on all its products and services. Contact Information Centre. Tel: +44 (0)20 8996 7111 Fax: +44 (0)20 8996 7048 Email: info@bsigroup.com

Subscribing members of BSI are kept up to date with standards developments and receive substantial discounts on the purchase price of standards. For details of these and other benefits contact Membership Administration. Tel: +44 (0)20 8996 7002 Fax: +44 (0)20 8996 7001 Email: membership@bsigroup.com

Information regarding online access to British Standards via British Standards Online can be found at <http://www.bsigroup.com/BSOL>

Further information about BSI is available on the BSI website at <http://www.bsigroup.com>.

Copyright

Copyright subsists in all BSI publications. BSI also holds the copyright, in the UK, of the publications of the international standardization bodies. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI.

This does not preclude the free use, in the course of implementing the standard, of necessary details such as symbols, and size, type or grade designations. If these details are to be used for any other purpose than implementation then the prior written permission of BSI must be obtained.

Details and advice can be obtained from the Copyright and Licensing Manager. Tel: +44 (0)20 8996 7070 Email: copyright@bsigroup.com