

BS EN ISO 3458:2015



BSI Standards Publication

**Plastics piping systems —
Mechanical joints between
fittings and pressure pipes —
Test method for leaktightness
under internal pressure**

bsi.

...making excellence a habit.™

National foreword

This British Standard is the UK implementation of EN ISO 3458:2015. It supersedes BS EN 715:1995 which is withdrawn.

The UK participation in its preparation was entrusted to Technical Committee PRI/88/4, Test Methods - Plastic Piping.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© The British Standards Institution 2015. Published by BSI Standards Limited 2015

ISBN 978 0 580 81754 0

ICS 23.040.60

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 30 April 2015.

Amendments issued since publication

Date	Text affected
------	---------------

English Version

Plastics piping systems - Mechanical joints between fittings and pressure pipes - Test method for leaktightness under internal pressure (ISO 3458:2015)

Systèmes de canalisations en plastique - Assemblages mécaniques entre raccords et tubes sous pression - Méthode d'essai pour l'étanchéité sous pression interne (ISO 3458:2015)

Kunststoff-Rohrleitungssysteme - Mechanische Verbindungen zwischen Fittings und Druckrohren - Prüfung der Dichtheit bei Innendruck (ISO 3458:2015)

This European Standard was approved by CEN on 14 November 2014.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN-CENELEC Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

CEN-CENELEC Management Centre: Avenue Marnix 17, B-1000 Brussels

Foreword

This document (EN ISO 3458:2015) has been prepared by Technical Committee ISO/TC 138 "Plastics pipes, fittings and valves for the transport of fluids" in collaboration with Technical Committee CEN/TC 155 "Plastics piping systems and ducting systems" the secretariat of which is held by NEN.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by October 2015, and conflicting national standards shall be withdrawn at the latest by October 2015.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN [and/or CENELEC] shall not be held responsible for identifying any or all such patent rights.

This document supersedes EN 715:1994.

According to the CEN-CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and the United Kingdom.

Endorsement notice

The text of ISO 3458:2015 has been approved by CEN as EN ISO 3458:2015 without any modification.

Contents

	Page
Foreword	iv
1 Scope	1
2 Principle	1
3 Test parameters and requirements	1
4 Apparatus	1
5 Test pieces	3
6 Procedure	3
7 Test report	3
Annex A (normative) Test parameters	5

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the WTO principles in the Technical Barriers to Trade (TBT), see the following URL: [Foreword — Supplementary information](#).

The committee responsible for this document is ISO/TC 138, *Plastics pipes, fittings and valves for the transport of fluids*, Subcommittee SC 5, *General properties of pipes, fittings and valves of plastics materials and their accessories — Test methods and basic specifications*.

This second edition cancels and replaces the first edition (ISO 3458:1976), which has been technically revised. The reason for modification is for applicability to other plastics materials, other sizes and/or other test conditions and alignment with texts of other International Standards on test methods. This edition of ISO 3458 is prepared under Vienna Agreement, so that the content is also aligned with the EN 715:1994, which will be replaced.

The modifications are the following:

- no material is mentioned;
- test parameters are omitted, although the original test parameters can be found in [Annex A](#);
- the diameter limit is removed;
- no requirements are given;
- editorial changes have been introduced.

Plastics piping systems — Mechanical joints between fittings and pressure pipes — Test method for leaktightness under internal pressure

WARNING — Users of this International Standard should be familiar with normal laboratory practice, if applicable. The use of this International Standard might involve hazardous materials, operations, and equipment. This International Standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this International Standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.

1 Scope

This International Standard specifies the method of test for checking the leak tightness of assembled joints between mechanical fittings and plastic pressure pipes. The test applies regardless of the design and material of the fitting used for jointing plastic pipe.

This test method is not applicable to fusion-welded joints.

2 Principle

The leak tightness of an assembled joint is checked while the joint is subjected to an internal test pressure greater than the nominal pressure for which the pipe is rated with the pieces joined subject to the longitudinal force, induced by the hydrostatic end thrust.

3 Test parameters and requirements

The test parameters of the standard which refers to this test standard shall be used and the requirements shall be fulfilled. If one or more parameters are not given in the referring International Standard, the ones given in [Annex A](#) shall apply.

The following test parameters should be given by the standard which refers to this test standard:


- a) test medium;
- b) test pressure (bar or MPa);
- c) test duration (h);
- d) test temperature (°C);
- e) free length (mm).

4 Apparatus

4.1 A suitable apparatus is shown in [Figure 1](#).

4.2 Pressure source connected to the test specimens, capable of maintaining for at least 1 h a minimum water or air pressure to an accuracy of $\pm 2\%$.

4.3 Pressure measuring device (7), capable of checking performance of the test pressure with [4.2](#).

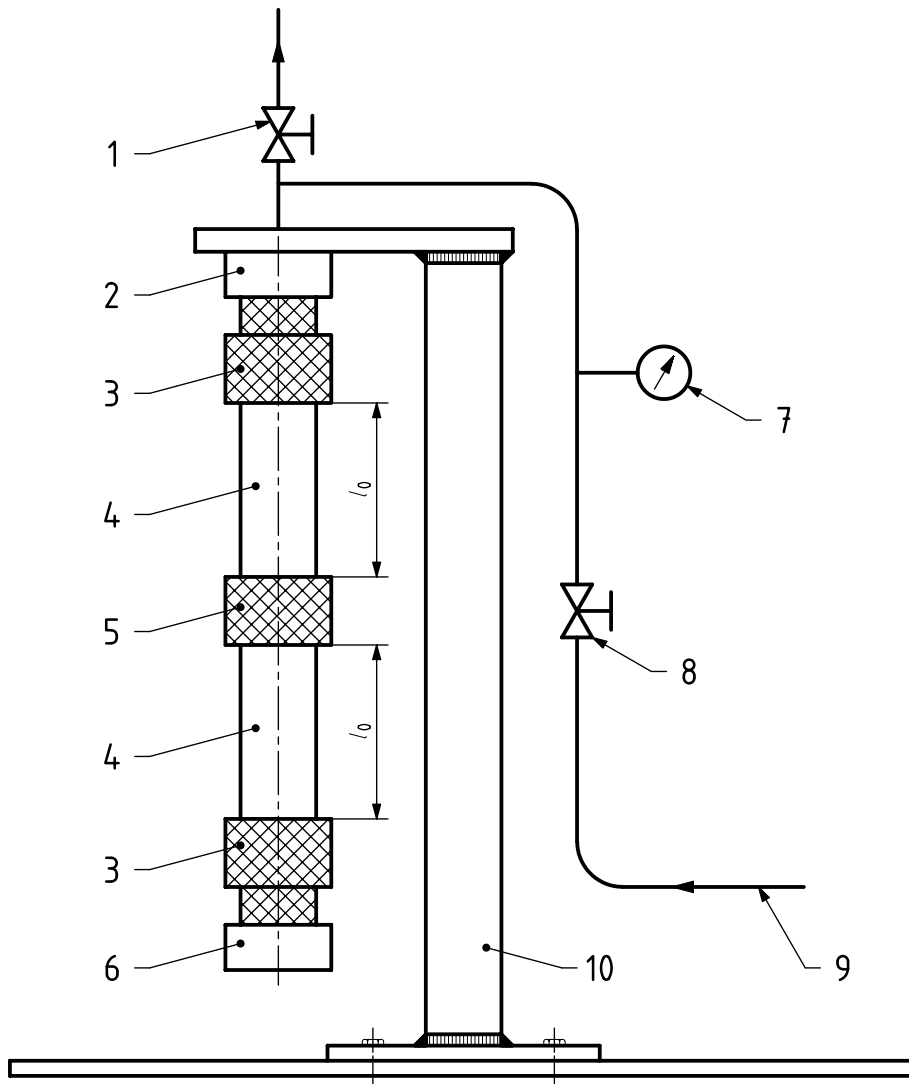

Key

- 1 air release valve
- 2 connecting element
- 3 fitting to be tested
- 4 pipe piece
- 5 fitting (option) to be tested
- 6 endcap
- 7 pressure measuring device
- 8 valve
- 9 connection pressure source
- 10 supporting frame
- l_0 pipe free length

Figure 1 — Diagram of typical apparatus

NOTE If the test is performed in a water bath, pressure equipment for detecting leakage is optional.

5 Test pieces

The test specimen shall consist of one or more joints formed by the assembly of at least one fitting and one or more pieces of plastic pressure pipe of the size and quality for which the fitting is designed.

The fittings and pipes shall not be tested until 24 h after their production. For practical reasons, the manufacturer can wait a shorter time before testing. In case of dispute, a duration of 24 h shall apply.

One end of the test specimen shall be connected to the pressure source. The other end(s) shall be sealed off in such a way that, when the test pressure is applied, longitudinal stresses are exerted within the pipe wall due to the pressure acting on the end fittings.

The assembly of the joint should be carried out in accordance with the manufacturer's instructions.

6 Procedure

Fill the test specimen with water or air at the specified test temperature. If water is used as test medium ensure all air is removed and excluded from the test piece for the remainder of the procedure.

Secure the test specimen to the apparatus. Minimum conditioning times are given in [Table 1](#).

Table 1 — Conditioning periods

Nominal wall thickness of the pipe mm	Minimum conditioning period min
$e \leq 10$	20
$10 < e \leq 20$	60
$20 < e$	120

If water is used as test medium and the test is carried out in air, ensure that the outside of the test specimen is completely dry.

After conditioning, progressively and smoothly apply the specified test pressure in the shortest time practicable. The test starts on achieving the required test pressure.

Maintain the specified temperature within ± 2 °C, and pressure within ± 2 %, while monitoring the apparatus for any indication of a loss of pressure and the test piece for any signs of leakage for the specified time or until failure as follows:

- a) terminate the test and record the observations if during the period the pressure cannot be maintained and the losses occurred at the joint, or within a distance of one pipe diameter from the joint under test;
- b) repeat the test if the pipe(s) fail(s) at a position further than one diameter from the joint(s) under test.

If air is used as test medium, leakage can be detected with leak detection fluid.

7 Test report

The test report shall include the following information:

- a) a reference to this International Standard (e.g. ISO 3458) and to the referring International standard;
- b) the nominal pressure class or S series of the components [e.g. fitting(s), pipe] comprising the joint(s) under test;
- c) all details necessary for identification of the test pieces, including the nominal size of the pipes and fittings used to produce the test pieces, the type of material and the manufacturer's code;

- d) the free length;
- e) the test medium;
- f) the test period;
- g) the test pressure;
- h) the test temperature;
- i) the information on the leak tightness of the joint including the pressure at which a leakage occurred (if any);
- j) any factors which may have affected the results, such as any incidents or any operating details not specified in this International Standard;
- k) the date of test.

Annex A (normative)

Test parameters

The test parameters in [Table A.1](#) shall be used, if applicable.

Table A.1 — Test Parameters

Test medium	Test duration h	Test temperature °C	Test pressure MPa
Water	1	20	Three times the nominal design pressure of the lowest rated component in the assembly

The free length, l_0 , of each pipe shall be at least three times the nominal outside diameter, d_n , with a minimum of 250 mm.

If, for pipes with d_n greater than 315 mm, the specified minimum free length cannot be achieved, a shorter free length may be chosen with a minimum of two times d_n , unless otherwise specified in the referring International Standard or specification.

British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at bsigroup.com/standards or contacting our Customer Services team or Knowledge Centre.

Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at bsigroup.com/shop, where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to bsigroup.com/subscriptions.

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

PLUS is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit bsigroup.com/shop.

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email bsmusales@bsigroup.com.

BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK

Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

Copyright

All the data, software and documentation set out in all British Standards and other BSI publications are the property of and copyrighted by BSI, or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI. Details and advice can be obtained from the Copyright & Licensing Department.

Useful Contacts:

Customer Services

Tel: +44 845 086 9001

Email (orders): orders@bsigroup.com

Email (enquiries): cservices@bsigroup.com

Subscriptions

Tel: +44 845 086 9001

Email: subscriptions@bsigroup.com

Knowledge Centre

Tel: +44 20 8996 7004

Email: knowledgecentre@bsigroup.com

Copyright & Licensing

Tel: +44 20 8996 7070

Email: copyright@bsigroup.com



...making excellence a habit.™