

# Hardmetals — Determination of total carbon — Gravimetric method (ISO 3907:2009)

ICS 77.160

## National foreword

This British Standard is the UK implementation of EN ISO 3907:2009. It supersedes BS EN 23907:1993 which is withdrawn.

The UK participation in its preparation was entrusted to Technical Committee ISE/65, Sintered metal components.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

**Compliance with a British Standard cannot confer immunity from legal obligations.**

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 30 November 2009.

© BSI 2009

ISBN 978 0 580 56454 3

### Amendments/corrigenda issued since publication

Date	Comments

EUROPEAN STANDARD

**EN ISO 3907**

NORME EUROPÉENNE

EUROPÄISCHE NORM

October 2009

ICS 77.160

Supersedes EN 23907:1993

English Version

## Hardmetals - Determination of total carbon - Gravimetric method (ISO 3907:2009)

Métaux-durs - Dosage du carbone total - Méthode  
gravimétrique (ISO 3907:2009)

Hartmetalle - Bestimmung des Gesamtkohlenstoff-  
Gehaltes - Gravimetrisches Verfahren (ISO 3907:2009)

This European Standard was approved by CEN on 29 September 2009.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION  
COMITÉ EUROPÉEN DE NORMALISATION  
EUROPÄISCHES KOMITEE FÜR NORMUNG

**Management Centre: Avenue Marnix 17, B-1000 Brussels**

## Foreword

This document (EN ISO 3907:2009) has been prepared by Technical Committee ISO/TC 119 "Powder metallurgy".

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by April 2010, and conflicting national standards shall be withdrawn at the latest by April 2010.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN [and/or CENELEC] shall not be held responsible for identifying any or all such patent rights.

This document supersedes EN 23907:1993.

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland and the United Kingdom.

### Endorsement notice

The text of ISO 3907:2009 has been approved by CEN as a EN ISO 3907:2009 without any modification.

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 3907 was prepared by Technical Committee ISO/TC 119, *Powder metallurgy*, Subcommittee SC 4, *Sampling and testing methods for hardmetal*.

This third edition cancels and replaces the second edition (ISO 3907:1985), which has been technically revised.



# Hardmetals — Determination of total carbon — Gravimetric method

## 1 Scope

This International Standard specifies a gravimetric method for the determination of the mass fraction of total carbon in carbides and hardmetals.



This method is applicable to

- carbides of chromium, hafnium, molybdenum, niobium, tantalum, titanium, vanadium, tungsten and zirconium,
- mixtures of these carbides and binder metals, free of lubricant,
- all grade of presintered or sintered hardmetals, produced from these carbides, and having a mass fraction of total carbon exceeding 4 %.

## 2 Principle

Oxidation of carbon to carbon dioxide at a high temperature in a stream of pure oxygen, with the addition of a flux, if necessary.

Absorption of the carbon dioxide, carried by oxygen, by Ascarite<sup>1)</sup> in a tared bulb. Determination of the increase in mass of the Ascarite<sup>1)</sup> which corresponds to the quantity of carbon dioxide formed.



## 3 Reagents

During the analysis, use only reagents of recognized analytical grade, and only distilled water or water of equivalent purity.

**3.1 Oxygen**, with a limitation of carbon-containing impurities of  $\leq 0,6$  ml of carbon per cubic metre of oxygen.

---

1) Ascarite is the trade name of a product supplied by Arthur H. Thomas Co. This information is given for the convenience of users of the International Standard and does not constitute an endorsement by ISO of the product named. Equivalent products may be used if they can be shown to lead to the same results.

**3.2 Magnesium perchlorate**, anhydrous.

**CAUTION** — To prevent the possibility of explosion, contact of this reagent with organic materials must be avoided, especially when discarding it.

**3.3 Flux**, for example tin metal, copper metal or oxide, iron metal.

**3.4 Ascarite**<sup>1)</sup>.

## 4 Apparatus

Ordinary laboratory apparatus and the following.

**4.1 Apparatus**, consisting of an electric furnace with a combustion tube, a purification train and a system to absorb carbon dioxide. If it is necessary to obtain oxygen of adequate purity, an oxygen purification train may also be used.

Successive parts of the apparatus shall be joined together with connecting tubes forming an airtight seal.

The apparatus is shown schematically in Figure 1.

**4.1.1 Source of oxygen** (3.1), with a pressure-regulating valve.

**4.1.2** Flow meter.

**4.1.3 Electric furnace**, capable of operation at up to 1 350 °C, with a suitable device for temperature control.

**4.1.4 Combustion tube**, made of a non-porous refractory material. The internal diameter of the tube should be 18 mm to 30 mm and its length should be at least 650 mm, so that the ends of the tube do not reach a temperature higher than 60 °C during the operation.

**4.1.5 Boat**, made of a refractory material, pretreated in an oxygen stream at the test temperature for 10 min or alternatively at 800 °C to 1 000 °C for 1 h.

The boat shall be of suitable dimensions, for example of length 80 mm to 100 mm, width 12 mm to 14 mm and depth 8 mm to 9 mm.

The pretreated boats shall be kept in a desiccator. The ground surfaces of the desiccator and its lid shall not be greased.

**4.1.6 Plug of silica wool**.

**4.1.7 Drying bulb**, containing anhydrous magnesium perchlorate (3.2).


**4.1.8 Absorption bulbs**, containing Ascarite<sup>1)</sup> (3.4) and a small amount of anhydrous magnesium perchlorate (3.2).

An example of an absorption bulb is shown in Figure 2.

**4.1.9 Additional absorption bulb**, facing the opposite way to the absorption bulb in 4.1.8 (see Figure 1, item reference 8) to avoid introduction of carbon dioxide and moisture from the air.

**4.2 Hook**, made from heat-resisting metal wire with a mass fraction of carbon less than 0,05 %. Its diameter should be approximately 3 mm and its length should be 500 mm to 600 mm.




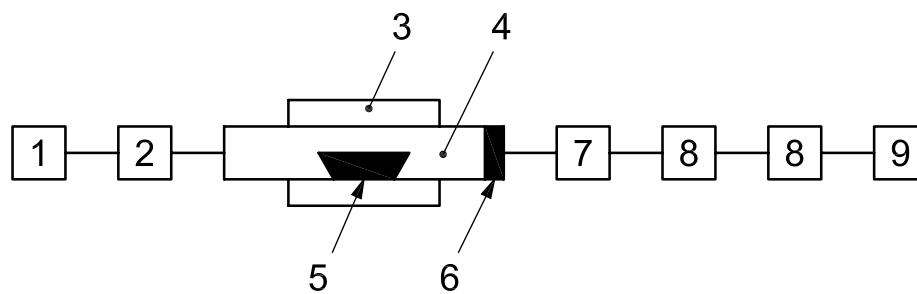

**Key**

- 1 source of oxygen
- 2 flow meter
- 3 electric furnace
- 4 combustion tube
- 5 boat
- 6 plug of silica wool
- 7 drying bulb
- 8 absorption bulbs
- 9 additional absorption bulb

**Figure 1 — Apparatus**

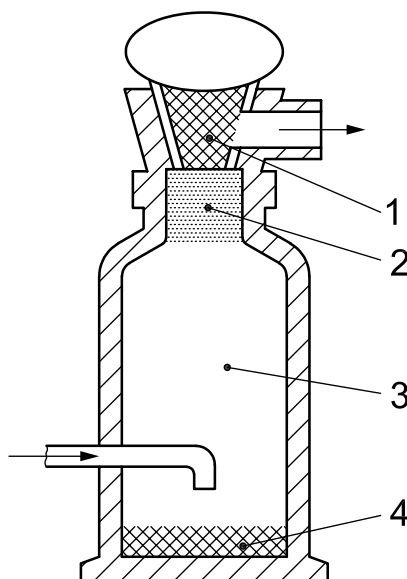

**Key**

- 1 glass wool in stopper
- 2 anhydrous magnesium perchlorate (3.2)
- 3 Ascarite<sup>1)</sup> (3.4), not too compressed
- 4 bottom layer of glass wool to protect inside of tube

**Figure 2 — Absorption bulb**

## 5 Sampling

5.1 The sample shall be crushed to a powder in a mortar made of a material which does not alter the sample composition. The powder shall pass through a 180  $\mu\text{m}$  sieve.

5.2 The analysis shall be carried out on two or three test portions.

## 6 Procedure

### 6.1 General

Check the temperature in the combustion zone (1 200 °C to 1 350 °C, and not less than 1 300 °C if chromium carbide is present), the gastightness of the apparatus and the efficiency of the oxygen purification. Pass oxygen through the apparatus for 10 min to 15 min at a rate of 300  $\text{cm}^3/\text{min}$  to 500  $\text{cm}^3/\text{min}$  depending on the diameter of the tube used. Then disconnect the absorption bulbs (see Figure 1, item reference 8), weigh them at ambient temperature and place them in position again.

### 6.2 Test portion

The mass of the test portion ( $m_0$ ) shall be such that it contains approximately 0,03 g of carbon, and shall be determined to the nearest 0,000 1 g.

If necessary, add 0,2 g to 1 g of the flux (3.3) to the test portion.

### 6.3 Blank test

Carry out the blank test by combustion (proceed as described in 6.4 and 6.5) in the presence of the quantity of flux used in the analysis, and carefully determine the increase in mass ( $m_1$ ) of the absorption bulbs.

### 6.4 Combustion

Open the combustion tube at the oxygen inlet end and, using the hook (4.2), place the boat (see Figure 1, item reference 5) containing the test portion (6.2) in the centre of the heated zone of the tube. Quickly close the tube and immediately pass a stream of oxygen at a rate of 300  $\text{cm}^3/\text{min}$  to 500  $\text{cm}^3/\text{min}$ , depending on the diameter of the tube used. Continue to pass oxygen for 10 min to 20 min, so that the carbon dioxide is completely removed from the combustion tube and the purifying bulb.

### 6.5 Determination

Close the tap of the absorption bulbs (see Figure 1, item reference 8) and immediately remove the bulbs from the apparatus. After 5 min, weigh the bulbs to the nearest 0,000 1 g. It is recommended that the fused mass in the boat be visually examined to verify that combustion has been completed. The increase in mass represents the carbon dioxide absorbed ( $m_2$ ).

## 7 Expression of results

### 7.1 Calculation

The mass fraction of carbon, expressed as a percentage, is given by the formula

**Error! Objects cannot be created from editing field codes.**

where

$m_0$  is the mass, in grams (g), of the test portion;

$m_1$  is the mass, in grams (g), of carbon dioxide obtained from the blank test;

$m_2$  is the mass, in grams (g), of the carbon dioxide obtained from the combustion of the test portion;

27,29 is the carbon dioxide to carbon conversion factor, multiplied by 100.

### 7.2 Tolerances

The deviation between two or three independent determinations shall not exceed the values shown in Table 1.

**Table 1 — Tolerances**

Total carbon mass fraction %	Range for two determinations %	Range for three determinations %
from 4 to 10	0,05	0,06
over 10	0,07	0,08

### 7.3 Final result

Report the arithmetical mean of acceptable determinations rounded to the nearest 0,01 % (mass fraction).

## 8 Test report

The test report shall include the following information:

- a) a reference to this International Standard;
- b) all details necessary for the identification of the test sample;
- c) the result obtained;
- d) all operations not specified in this International Standard, or regarded as optional;
- e) details of any occurrence which may have affected the result.

---

## BSI - British Standards Institution

BSI is the independent national body responsible for preparing British Standards. It presents the UK view on standards in Europe and at the international level. It is incorporated by Royal Charter.

### Revisions

British Standards are updated by amendment or revision. Users of British Standards should make sure that they possess the latest amendments or editions.

It is the constant aim of BSI to improve the quality of our products and services. We would be grateful if anyone finding an inaccuracy or ambiguity while using this British Standard would inform the Secretary of the technical committee responsible, the identity of which can be found on the inside front cover. Tel: +44 (0)20 8996 9000. Fax: +44 (0)20 8996 7400.

BSI offers members an individual updating service called PLUS which ensures that subscribers automatically receive the latest editions of standards.

### Buying standards

Orders for all BSI, international and foreign standards publications should be addressed to Customer Services. Tel: +44 (0)20 8996 9001. Fax: +44 (0)20 8996 7001 Email: [orders@bsigroup.com](mailto:orders@bsigroup.com) You may also buy directly using a debit/credit card from the BSI Shop on the Website <http://www.bsigroup.com/shop>

In response to orders for international standards, it is BSI policy to supply the BSI implementation of those that have been published as British Standards, unless otherwise requested.

### Information on standards

BSI provides a wide range of information on national, European and international standards through its Library and its Technical Help to Exporters Service. Various BSI electronic information services are also available which give details on all its products and services. Contact Information Centre. Tel: +44 (0)20 8996 7111 Fax: +44 (0)20 8996 7048 Email: [info@bsigroup.com](mailto:info@bsigroup.com)

Subscribing members of BSI are kept up to date with standards developments and receive substantial discounts on the purchase price of standards. For details of these and other benefits contact Membership Administration. Tel: +44 (0)20 8996 7002 Fax: +44 (0)20 8996 7001 Email: [membership@bsigroup.com](mailto:membership@bsigroup.com)

Information regarding online access to British Standards via British Standards Online can be found at <http://www.bsigroup.com/BSOL>

Further information about BSI is available on the BSI website at <http://www.bsigroup.com>.

### Copyright

Copyright subsists in all BSI publications. BSI also holds the copyright, in the UK, of the publications of the international standardization bodies. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI.

This does not preclude the free use, in the course of implementing the standard, of necessary details such as symbols, and size, type or grade designations. If these details are to be used for any other purpose than implementation then the prior written permission of BSI must be obtained.

Details and advice can be obtained from the Copyright and Licensing Manager. Tel: +44 (0)20 8996 7070 Email: [copyright@bsigroup.com](mailto:copyright@bsigroup.com)