

BS EN ISO 3953:2011



BSI Standards Publication

Metallic powders — Determination of tap density (ISO 3953:2011)

bsi.

...making excellence a habit.™

National foreword

This British Standard is the UK implementation of EN ISO 3953:2011. It supersedes BS EN ISO 3953:1995 which is withdrawn.

The UK participation in its preparation was entrusted to Technical Committee ISE/65, Sintered metal components.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© BSI 2011

ISBN 978 0 580 71218 0

ICS 77.160

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 28 February 2011.

Amendments issued since publication

Date	Text affected
------	---------------

English Version

Metallic powders - Determination of tap density (ISO 3953:2011)Poudres métalliques - Détermination de la masse
volumique après tassement (ISO 3953:2011)Metallpulver - Bestimmung der Klopfdichte (ISO
3953:2011)

This European Standard was approved by CEN on 31 January 2011.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN-CENELEC Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland and United Kingdom.

EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG**Management Centre: Avenue Marnix 17, B-1000 Brussels**

Foreword

This document (EN ISO 3953:2011) has been prepared by Technical Committee ISO/TC 119 "Powder metallurgy".

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by August 2011, and conflicting national standards shall be withdrawn at the latest by August 2011.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN [and/or CENELEC] shall not be held responsible for identifying any or all such patent rights.

This document supersedes EN ISO 3953:1995.

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland and the United Kingdom.

Endorsement notice

The text of ISO 3953:2011 has been approved by CEN as a EN ISO 3953:2011 without any modification.

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 3953 was prepared by Technical Committee ISO/TC 119, *Powder metallurgy*, Subcommittee SC 2, *Sampling and testing methods for powders (including powders for hardmetals)*.

This fourth edition cancels and replaces the third edition (ISO 3953:1993), of which it constitutes a minor revision.

Metallic powders — Determination of tap density

1 Scope

This International Standard specifies a method for the determination of tap density, i.e. the density of a powder that has been tapped into a container under specified conditions.

2 Principle

A specified amount of powder in a container is tapped by means of a tapping apparatus until no further decrease in the volume of the powder takes place. The mass of the powder divided by its volume after the test gives its tap density.

3 Symbols

For the purposes of this document, the symbols in Table 1 apply.

Table 1 — Symbols

Symbol	Meaning	Unit
ρ_t	Tap density	g/cm^3
m	Mass of the powder	g
V	Volume of the tapped powder	cm^3

4 Apparatus

4.1 Balance, of appropriate capacity to satisfy the requirements shown in Table 2 and of an accuracy to weigh to the nearest 0,1 g.


4.2 Graduated glass cylinder, calibrated to contain 100 cm^3 , the height of the graduated portion being approximately 175 mm. The graduations shall be at 1 cm^3 intervals, thus allowing a measuring accuracy of $\pm 0,5 \text{ cm}^3$.

Alternatively:

Graduated glass cylinder, calibrated to contain 25 cm^3 , the height of the graduated portion being approximately 135 mm. The graduations shall be at $0,2 \text{ cm}^3$ intervals.

A 25 cm^3 cylinder shall be used for powders of apparent density higher than 4 g/cm^3 , in particular for refractory metal powders, but may also be used for powders of lower apparent density.

4.3 Tapping apparatus, which permits the tapping of the graduated cylinder against a firm base. The tapping shall be such that a densification of the powder can take place without any loosening of its surface layers. The stroke shall be 3 mm and the tapping frequency shall be between 100 and 300 taps/min. An example of a tapping apparatus is shown in Figure 1.

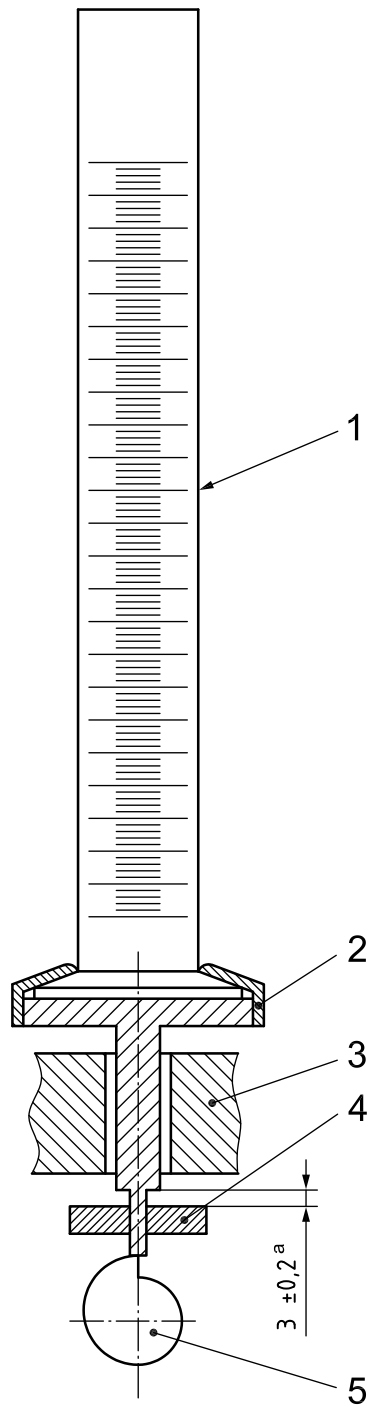

Key

- 1 graduated measuring cylinder
- 2 holder with guide-pin
- 3 guide-bearing
- 4 anvil (steel)
- 5 cam

^a Height of stroke.

Figure 1 — Example of tapping apparatus

5 Sampling

5.1 For the quantities of powder required for each test, see Table 2.

Table 2 — Required sample quantities

Apparent density g/cm ³	Cylinder capacity cm ³	Mass of test portion g
1 to 4	100	100 ± 0,5
< 1	100	50 ± 0,2
> 7	25	100 ± 0,5
> 2 to 7	25	50 ± 0,2
0,8 to 2	25	20 ± 0,1
< 0,8	25	10 ± 0,1

5.2 In general, the powder should be tested in the as-received condition. In certain instances, the powder may be dried. However, if the powder is susceptible to oxidation, the drying shall take place in a vacuum or in an inert gas. If the powder contains volatile substances, it shall not be dried.

5.3 The test shall be carried out on three test portions, if possible.

6 Procedure

6.1 Clean the inside wall of the graduated cylinder (4.2) with a suitable clean brush or, if necessary, by rinsing with a solvent, such as acetone. If a solvent is used, thoroughly dry the cylinder before re-use.

6.2 Weigh, to the nearest 0,1 g, the mass of the test portion as indicated in Table 2, using the balance (4.1).

6.3 Pour the test portion into the graduated cylinder. Take care that a level surface of the powder is formed. Place the cylinder in the tapping apparatus (4.3). Tap the cylinder until no further decrease in the volume of the powder takes place (see Note).

NOTE In practice, the minimum number of taps, N , would be determined such that no further change in volume takes place. For all further tests on the same type of powder, the cylinder would be subjected to $2N$ taps, except where general experience and acceptance has established a specific number of taps (no less than N taps) as being satisfactory. For fine refractory metal powders, 3 000 taps has been found to be satisfactory for all sizes.

6.4 If the tapped surface is level, read the volume directly. If the tapped surface is not level, determine the tap volume by calculating the mean value between the highest and the lowest reading of the tapped surface. Read the final volume to the nearest 0,5 cm³ when using a 100 cm³ cylinder, and to the nearest 0,2 cm³ when using a 25 cm³ cylinder.

7 Expression of results

The tap density is given by the following equation:

$$\rho_t = \frac{m}{V}$$

where ρ_t , m and V are as defined in Table 1.

Report the arithmetical mean of the number of determinations rounded to the nearest 0,1 g/cm³ for values up to and including 4 g/cm³, and to the nearest 0,2 g/cm³ for values greater than 4 g/cm³.

8 Test report

The test report shall include the following information:

- a) a reference to this International Standard, i.e. ISO 3953:2011;
- b) all details necessary for identification of the test sample;
- c) the drying procedure, if the powder has been dried;
- d) the cylinder capacity, mass of the test portion and method used;
- e) the result obtained;
- f) all operations not specified in this International Standard or regarded as optional;
- g) details of any occurrence which may have affected the result.

British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at bsigroup.com/standards or contacting our Customer Services team or Knowledge Centre.

Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at bsigroup.com/shop, where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to bsigroup.com/subscriptions.

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

PLUS is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit bsigroup.com/shop.

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email bsmusales@bsigroup.com.

BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK

Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

Copyright

All the data, software and documentation set out in all British Standards and other BSI publications are the property of and copyrighted by BSI, or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI. Details and advice can be obtained from the Copyright & Licensing Department.

Useful Contacts:

Customer Services

Tel: +44 845 086 9001

Email (orders): orders@bsigroup.com

Email (enquiries): cservices@bsigroup.com

Subscriptions

Tel: +44 845 086 9001

Email: subscriptions@bsigroup.com

Knowledge Centre

Tel: +44 20 8996 7004

Email: knowledgecentre@bsigroup.com

Copyright & Licensing

Tel: +44 20 8996 7070

Email: copyright@bsigroup.com



...making excellence a habit.™