

BS EN ISO 4534:2010

Incorporating corrigendum November 2014



BSI Standards Publication

**Vitreous and porcelain enamels
— Determination of fluidity
behaviour — Fusion flow test
(ISO 4534:2010)**

bsi.

...making excellence a habit.™

National foreword

This British Standard is the UK implementation of EN ISO 4534:2010. It supersedes BS 1344-18:1981, which is withdrawn.

The UK participation in its preparation was entrusted to Technical Committee STI/36, Vitreous enamel coatings.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© The British Standards Institution 2014.

Published by BSI Standards Limited 2014

ISBN 978 0 580 88637 9

ICS 25.220.50

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 31 January 2011.

Amendments/corrigenda issued since publication

Date	Text affected
30 November 2014	Correction to supersession details in national foreword

ICS 25.220.50

English Version

Vitreous and porcelain enamels - Determination of fluidity behaviour - Fusion flow test (ISO 4534:2010)

Émaux vitrifiés - Détermination du comportement de fluidité
- Essai d'écoulement (ISO 4534:2010)

Emails und Emailierungen - Prüfung des Fließverhaltens -
Ablaufversuch (ISO 4534:2010)

This European Standard was approved by CEN on 14 December 2010.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN-CENELEC Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

Management Centre: Avenue Marnix 17, B-1000 Brussels

Foreword

This document (EN ISO 4534:2010) has been prepared by Technical Committee ISO/TC 107 “Metallic and other inorganic coatings” in collaboration with Technical Committee CEN/TC 262 “Metallic and other inorganic coatings” the secretariat of which is held by BSI.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by June 2011, and conflicting national standards shall be withdrawn at the latest by June 2011.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN [and/or CENELEC] shall not be held responsible for identifying any or all such patent rights.

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland and the United Kingdom.

Endorsement notice

The text of ISO 4534:2010 has been approved by CEN as a EN ISO 4534:2010 without any modification.

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 4534 was prepared by Technical Committee ISO/TC 107, *Metallic and other inorganic coatings*.

This second edition cancels and replaces the first edition (ISO 4534:1980), which has been technically revised. The revised edition allows for the use of flow plates, other than unglazed ceramic tiles, such as enamelled steel or cast iron which is common practice in some countries.

Introduction

The fusion flow test specified in this International Standard is a comparative method which can be carried out with simplified equipment to provide data on the fluidity behaviour of molten enamel. The results from this test allow conclusions on the flow properties of the enamel to be inferred in a much simpler manner than is possible from the results of the much more expensive measurements made using the usual viscosity-measuring instruments.

The results of extensive tests¹⁾ have shown that there is a well-defined relationship between the results of the flow test and the viscosity-temperature curve, so that the flow test could also be used as an absolute method. However, more effort would be required to enable the various laboratories to obtain comparable results of similar quality than when using the method for comparative purposes.

When using this method, the reference (comparison) enamel must be similar to the enamel to be tested, as the fluidity behaviour of the various types of enamel might vary considerably from one type to another.

1) Dekker, P. Calculation of viscosity-temperature curves for porcelain enamels from the flow-button test. *Journal of the American Ceramic Society*, **48** (1965), 6, pp. 319 to 327.

Vitreous and porcelain enamels — Determination of fluidity behaviour — Fusion flow test

WARNING — This International Standard calls for the use of substances and/or procedures that may be injurious to health if adequate safety measures are not taken. This International Standard does not address any health hazards, safety or environmental matters associated with its use. It is the responsibility of the user of this International Standard to establish appropriate health, safety and environmentally acceptable practices and take suitable actions for any national and international regulations. Compliance with this International Standard does not in itself confer immunity from legal obligations.

1 Scope

This International Standard specifies a comparative method of determining the fluidity behaviour of vitreous and porcelain enamels in the viscous condition during firing. It is not intended for use as an absolute method.

2 Principle

The test samples are dried or wet-ground in accordance with the processing conditions. Cylindrical specimens of specified mass are pressed from the enamel powder, or the dried enamel slip, and from the reference enamel agreed upon between the parties concerned.

The test specimens are placed in a laboratory furnace at an agreed temperature on an unglazed ceramic tile in the horizontal position and melted to hemispherical shape. The tile is tilted to permit the enamel to flow at a specified angle and for an agreed time period.

The length flow number, F_l , and the breadth flow number, F_b , are calculated on the basis of the flow lengths and flow breadths of the test specimens.

3 Material and apparatus

3.1 Reference enamel, to be agreed upon by the parties concerned, having similar fluidity behaviour to the enamel to be tested.

3.2 Ball mill.

3.3 Evaporation device, for example, a hot-air oven, a hot plate, a sand bath.

3.4 Mortar.

3.5 Pestle.

3.6 Balance, with an accuracy of 0,01 g.

3.7 Press, able to generate a pressure of at least 5 N/mm², with a cylindrical mould having an internal diameter of 8 mm to 10 mm for preparation of the test specimens.

3.8 Flow plate, consisting preferably of a smooth unglazed ceramic tile, with side lengths of approximately 75 mm and a thickness of 5 mm to 6 mm, prefired at a temperature of at least 1 100 °C. It shall have a water absorption at atmospheric pressure $\leq 25\%$ and a homogeneous fine ceramic body. Flow plates may also be cut from a larger plate (see A.1).

3.9 Tilting frame, (see Figures 1 and 2), for placing a flow plate inside a laboratory furnace in a horizontal position and tilting the plate to an angle between 30° and 90°.

NOTE For very viscous samples, it can be favourable to increase the slope; for samples of low viscosity, it can be favourable to decrease the slope.


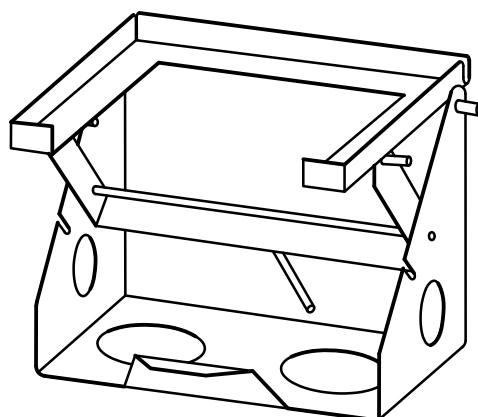


Figure 1 — Example of tilting frame set in a horizontal position for receiving the flow plate

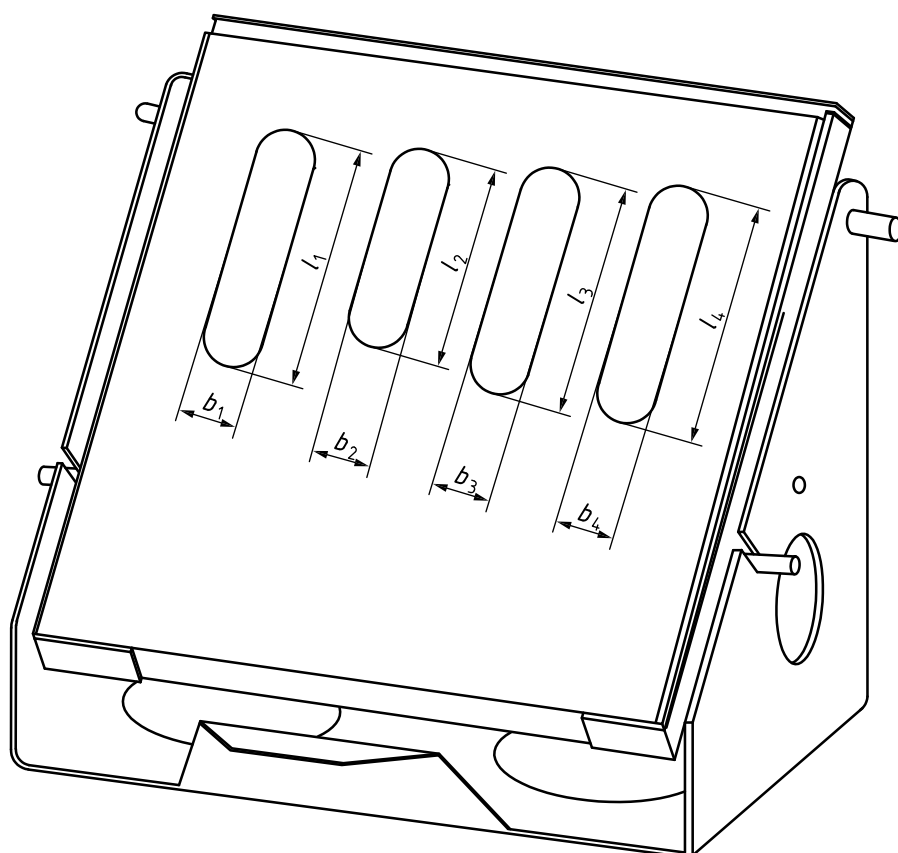

Key

l_1, l_2, l_3 and l_4 flow lengths of the four specimens

b_1, b_2, b_3 and b_4 maximum flow breadths of the four specimens (see Clause 6)

Figure 2 — Tilting frame tilted by 45° with flow plate and four specimens

3.10 Electrically heated laboratory furnace, capable of being controlled at (900 ± 10) °C.

3.11 Stop watch.

4 Test specimens

4.1 Preparation of enamel

The sample may be taken from the enamel powder readily ground or it may be ground separately in the ball mill (3.2). Mill additives and the fineness of grinding depend on the manufacturing conditions. In special cases, the complete grain-size distribution shall be taken into account.

Wet-ground enamels shall be evaporated to dryness in an evaporation dish. After cooling, the dried enamel shall be loosened and again pulverized using the pestle (3.5) and mortar (3.4).

If agreed, mill additives, which are completely or partially soluble in water and are only used as a setting-up agent, may be omitted.

Where the fluidity of frits only is to be determined, they should be milled dry.

4.2 Preparation of test specimens

The enamel shall have a mass of 1 g to 2 g, with a relative deviation of maximum 3 %. As specified in 4.1, the enamel powder shall be mixed with a defined amount of water in an empty mould (see 3.7 and A.2). Immediately press the specimen at a pressure of at least 5 N/mm². It is important to prepare all test specimens in the same manner with the same number of water drops.

4.3 Number of tests

Each flow test shall be performed with an agreed number of specimens made of the test enamel and at least one specimen made of the reference enamel (see Clause 5).

5 Procedure

Place the agreed number of test specimens and at least one specimen of the reference enamel on the flow plate (3.8) within the supporting area (see Figure 3). If various flow tests are carried out, interchange the positions of the test specimens and the specimen made of the reference enamel (see A.3).

It is recommended to have one reference in the side position and to have another reference in the middle of the plate.

Predetermine, by one or more pre-tests, the holding time, i.e. the time required from placing the flow plate in the laboratory furnace (3.10), maintained at the agreed temperature for the test enamel, until the reference specimen softens sufficiently to form an approximate hemisphere.

The test specimens shall be completely dry before the flow test is carried out. Carefully place the flow plate in the laboratory furnace, horizontally on the tilting frame (3.9), and at the end of the holding time, then tilt it (see A.3).

At the end of the flow period, i.e. the agreed period over which the enamel is allowed to flow, remove the flow plate from the furnace.

Measure the flow lengths and maximum flow breadths of the test specimens, in millimetres (see Figure 2).

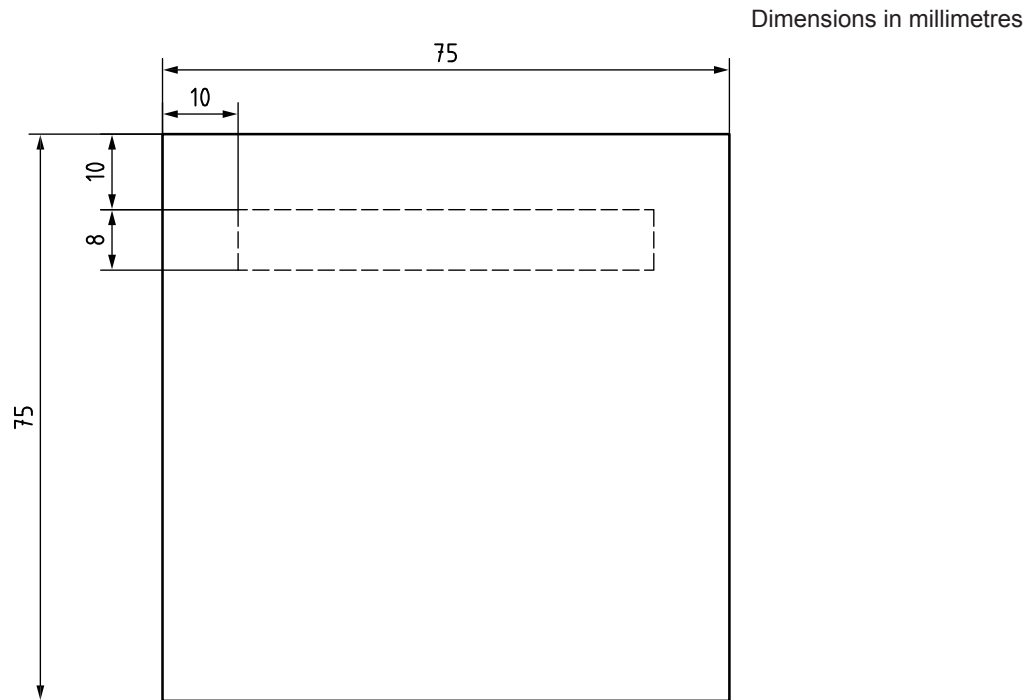


Figure 3 — Example of supporting area of specimens on flow plate

6 Calculation and expression of results

Calculate the length and breadth flow numbers, F_l and F_b , from Equations (1) and (2):

Length flow number:

$$F_l = \frac{l_t}{l_r} \quad (1)$$

where

l_t is the flow length of the test enamel;

l_r is the flow length of the reference enamel.

Breadth flow number:

$$F_b = \frac{b_t}{b_r} \quad (2)$$

where

b_t is the maximum flow breadth of the test enamel;

b_r is the maximum flow breadth of the reference enamel.

If several test specimens or reference specimens are used, use the mean flow length and the mean maximum flow breadth for the calculation.

7 Test report

The test report shall include the following information:

- a) a reference to this International Standard, ISO 4534:2010;
- b) name of testing establishment;
- c) designations of the test enamel and the reference enamel;
- d) temperature in the laboratory furnace;
- e) flow period;
- f) number of specimens used in the test;
- g) number of tests;
- h) length flow number, F_l , and breadth flow number, F_b , as individual values and arithmetic means;
- i) any deviations from the procedure specified;
- j) any unusual features observed during the test;
- k) date of test.

Annex A (informative)

Additional information

A.1 Flow plate (see 3.8)

Unglazed ceramic tiles have proven their value as flow plates. They can also be used for powder enamel (dry-process enamelling), wet-cast enamel, and sheet-steel porcelain enamel.

Plates made of a casting or of sheet metal, shall be enamelled first with a ground enamel matching the enamel to be tested. Ground enamel on sheet metal and fusible ground enamel on castings would, of necessity, be brought back into the fused, molten condition during the fusion flow test and might thereby influence the flow of the specimen. Another inhibiting factor during reheating of the previously fired ground enamel would be the possibility of reactions between the ground enamel and the specimen. As this is a comparative test, carriers other than ceramic plates are principally allowed.

The side walls of porcelain boats would obstruct the enamel in its spread, which provides an indication of the wetting properties of the enamel in relation to the ceramic bases used for enamelling. Therefore, porcelain boats should not be used.

A.2 Mass of test sample for moulding (see 4.2)

A given quantity has been specified for the specimens as, otherwise, density and fineness of grinding of the enamel would have to be considered.

A.3 Procedure (see Clause 5)

In the tests for each set of specimens, the positions on the flow plate of the test and reference specimens are interchanged so that the influence of any temperature gradients which might be present in the furnace is eliminated.

The start of the flow period has been defined as occurring when the reference specimen has attained roughly a hemispherical shape. If the specimen has proceeded beyond the hemispherical shape prior to tilting, that is if the specimen has spread too far, it will contract again during the flow process and become narrower from the top to the bottom. If the specimen has not attained the hemispherical shape, it will effectively roll down the flow plate instead of flowing. If the flow plate is tilted while the specimen is still in its cylindrical shape, perfect results cannot be expected, since the sintering and melting processes, occurring inside the specimen, may prevent reproducible flow.

British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at bsigroup.com/standards or contacting our Customer Services team or Knowledge Centre.

Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at bsigroup.com/shop, where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to bsigroup.com/subscriptions.

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

PLUS is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit bsigroup.com/shop.

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email bsmusales@bsigroup.com.

BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK

Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

Copyright

All the data, software and documentation set out in all British Standards and other BSI publications are the property of and copyrighted by BSI, or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI. Details and advice can be obtained from the Copyright & Licensing Department.

Useful Contacts:

Customer Services

Tel: +44 845 086 9001

Email (orders): orders@bsigroup.com

Email (enquiries): cservices@bsigroup.com

Subscriptions

Tel: +44 845 086 9001

Email: subscriptions@bsigroup.com

Knowledge Centre

Tel: +44 20 8996 7004

Email: knowledgecentre@bsigroup.com

Copyright & Licensing

Tel: +44 20 8996 7070

Email: copyright@bsigroup.com



...making excellence a habit.™