

BS EN ISO 6847:2013



BSI Standards Publication

Welding consumables — Deposition of a weld metal pad for chemical analysis

bsi.

...making excellence a habit.™

National foreword

This British Standard is the UK implementation of EN ISO 6847:2013. It supersedes BS EN ISO 6847:2001 which is withdrawn.

The UK participation in its preparation was entrusted to Technical Committee WEE/39, Welding consumables.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© The British Standards Institution 2013. Published by BSI Standards Limited 2013

ISBN 978 0 580 83713 5

ICS 25.160.20

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 31 July 2013.

Amendments issued since publication

Date	Text affected
------	---------------

English Version

Welding consumables - Deposition of a weld metal pad for chemical analysis (ISO 6847:2013)

Produits consommables pour le soudage - Exécution d'un
dépôt de métal fondu pour l'analyse chimique (ISO
6847:2013)

Schweißzusätze - Auftragung von Schweißgut zur
Bestimmung der chemischen Zusammensetzung (ISO
6847:2013)

This European Standard was approved by CEN on 21 April 2013.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN-CENELEC Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

Management Centre: Avenue Marnix 17, B-1000 Brussels

Foreword

This document (EN ISO 6847:2013) has been prepared by Technical Committee IIW “International Institute of Welding” in collaboration with Technical Committee CEN/TC 121 “Welding and allied processes” the secretariat of which is held by DIN.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by December 2013, and conflicting national standards shall be withdrawn at the latest by December 2013.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN [and/or CENELEC] shall not be held responsible for identifying any or all such patent rights.

This document supersedes EN ISO 6847:2001.

According to the CEN-CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and the United Kingdom.

Endorsement notice

The text of ISO 6847:2013 has been approved by CEN as EN ISO 6847:2013 without any modification.

Contents

	Page
Foreword	iv
Introduction	v
1 Scope	1
2 Normative references	1
3 Base metal	1
3.1 Type.....	1
3.2 Dimensions.....	1
3.3 Surface condition.....	1
4 Method for preparing the weld metal pad	2
4.1 Drying of the welding consumables.....	2
4.2 Welding position.....	2
4.3 Type of current.....	2
4.4 Welding conditions.....	2
4.5 Welding method.....	2
5 Weld metal pad size	3
6 Sampling	4

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

International Standard ISO 6847 was prepared by the International Institute of Welding, which has been approved as an international standardizing body in the field of welding by the ISO Council.

This third edition cancels and replaces the second edition (ISO 6847:2000), of which it constitutes a minor revision.

Requests for official interpretations of any aspect of this International Standard should be directed to the ISO Central Secretariat, who will forward them to the IIW Secretariat for an official response.

Introduction

ISO 6847:1985 addressed only the deposition of a weld metal pad for chemical analysis using covered electrodes for manual arc welding. This pad preparation was expensive to execute. IIW Commission II conducted testing of several methods of weld pad preparation that were less costly to execute than that of ISO 6847:1985 and yet produced equivalent results. Further, these methods were applicable to solid wires for gas shielded welding, to tubular cored wires for arc welding with or without gas shielding, and to wires and fluxes for submerged arc welding, as well as being applicable to covered electrodes. Accordingly, this revision simplifies weld pad preparation and broadens the range of welding processes and filler metals.

Welding consumables — Deposition of a weld metal pad for chemical analysis

1 Scope

This International Standard specifies the procedure to be used for deposition of a weld metal pad for chemical analysis. This International Standard applies to deposition of a weld metal pad by use of covered electrodes, wire electrodes for gas shielded metal arc welding, tubular cored electrodes for gas shielded metal arc welding and for non-gas shielded metal arc welding, tubular cored rods for gas tungsten arc welding, and wire-flux combinations for submerged arc welding. This International Standard is applicable to welding consumables for non-alloy and fine grain steels, high strength steels, creep-resisting steels, stainless and heat-resisting steels, nickel and nickel alloys, and copper and copper alloys.

2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 6947, *Welds — Working positions — Definitions of angles of slope and rotation*

ISO 14175, *Welding consumables — Gases and gas mixtures for fusion welding and allied processes*

3 Base metal

3.1 Type

The base metal shall have a composition similar to that of the deposited metal or be a weldable carbon manganese structural steel with a carbon content of less than 0,2 %.

3.2 Dimensions

The minimum dimensions of the base metal are given in Table 1.

3.3 Surface condition

The surface of the base metal on to which the weld metal is to be deposited shall be cleaned by grinding or other means in order to remove any rust, scale, grease, or paint.

Table 1 — Minimum dimensions of the base metal

Dimensions in millimetres

Welding consumables	Size of welding consumables	Plate size ^a	
		Length	Thickness
Covered electrodes and tubular cored rods for gas tungsten arc welding	≥1,6 but ≤4 >4 but ≤8	55 65	10
Wire electrodes for gas shielded arc welding	≥0,6 but ≤2,5	100	10
Tubular cored electrodes for gas shielded or non-gas shielded arc welding	≥0,6 but ≤4	100	10
Wire-flux combinations for submerged arc welding	≥1,2 but ≤4 >4 but ≤6,4	200 300	15

^a Plate width should be appropriate for the pass sequence method chosen (see Figure 1).

4 Method for preparing the weld metal pad

4.1 Drying of the welding consumables

Drying of the welding consumables (covered electrodes, fluxes for submerged arc welding) shall be performed using conditions indicated by the manufacturer. Tubular cored electrodes on metal supports may be dried.

4.2 Welding position

The weld metal pad shall be welded in the flat position (PA position in ISO 6947).

4.3 Type of current

The weld metal shall be deposited using the type of current (and, if appropriate, the polarity) indicated by the manufacturer. However, if both DC operation and AC operation are claimed, then the test shall be performed using AC.

4.4 Welding conditions


The welding conditions used, such as current, voltage, welding speed, etc., shall be in accordance with the limits specified in the relevant standard. If the welding conditions are not specified in the relevant standard, each pass shall be welded with a welding current of 70 % to 90 % of the maximum current indicated by the manufacturer. The welding conditions used to produce the weld metal pad shall be reported.

4.5 Welding method

4.5.1 General

Various methods for building up a weld metal pad have been shown to be acceptable and the weld metal pad shall be prepared using one of the methods shown in Figure 1. After the welding of each pass, the test piece may be cooled in water for about 30 s, then dried sufficiently before proceeding with the

next pass. The slag shall be removed from each pass. The welding shall be performed by alternating the direction of welding for each layer.

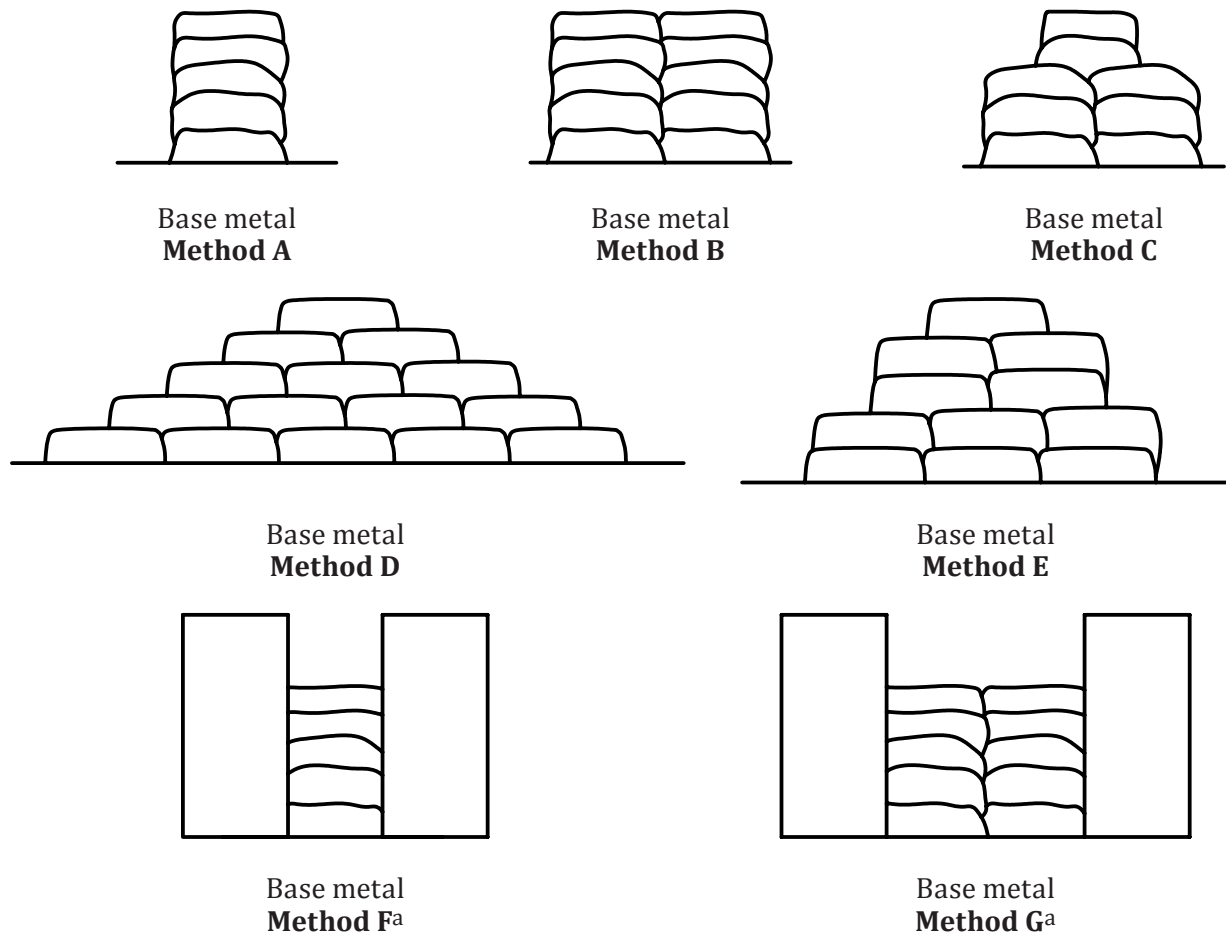

^a The blocks on both sides of the weld deposits of methods F and G are copper.

Figure 1 — Examples of pass sequence

4.5.2 Covered electrodes

The arc length shall be maintained as short as possible such that the arc remains stable. The maximum weave width shall be 2,5 times the diameter of the electrode core.

4.5.3 Solid wires and tubular cored wires

The number and size of the beads will vary according to the size of the electrodes and the width of the weave as well as the amperage employed. The electrode extension (stickout) shall be as indicated by the manufacturer ± 3 mm. The weld metal pad shall be deposited using the type of shielding gas indicated by the manufacturer; otherwise, the type of shielding gas used shall be selected from those specified in ISO 14175. In the case of submerged arc welding, the appropriate flux shall be used.

5 Weld metal pad size

The minimum dimensions of the weld metal pad shall be as given in Table 2.

6 Sampling

The surface oxide on the sampling portion of the specimen for chemical analysis shall be removed by machining or grinding. When taking chips by a milling, a shaping, or a drilling machine, the use of cutting fluid shall be avoided. The specimen for chemical analysis shall be taken from the weld metal of the fifth layer or higher. The specimen shall not include the start or the crater.

Table 2 — Minimum dimensions of the weld metal pad

Welding consumables	Size of welding consumables mm	Sampling portion		Minimum number of weld layers
		Width mm	Length mm	
Covered electrodes and tubular cored rods for gas tungsten arc welding	≥1,6 but ≤2,6	12	30	5
	>2,6 but ≤5	12	40	5
	>5 but ≤8	12	55	5
Wire electrodes for gas shielded arc welding	≥0,6 but ≤2,5	12	80	5
Tubular cored electrodes for gas shielded or non-gas shielded arc welding	≥0,6 but ≤4	12	80	5
Wire-flux combinations for submerged arc welding	≥1,2 but ≤6,4	12	150	5

British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at bsigroup.com/standards or contacting our Customer Services team or Knowledge Centre.

Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at bsigroup.com/shop, where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to bsigroup.com/subscriptions.

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

PLUS is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit bsigroup.com/shop.

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email bsmusales@bsigroup.com.

BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK

Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

Copyright

All the data, software and documentation set out in all British Standards and other BSI publications are the property of and copyrighted by BSI, or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI. Details and advice can be obtained from the Copyright & Licensing Department.

Useful Contacts:

Customer Services

Tel: +44 845 086 9001

Email (orders): orders@bsigroup.com

Email (enquiries): cservices@bsigroup.com

Subscriptions

Tel: +44 845 086 9001

Email: subscriptions@bsigroup.com

Knowledge Centre

Tel: +44 20 8996 7004

Email: knowledgecentre@bsigroup.com

Copyright & Licensing

Tel: +44 20 8996 7070

Email: copyright@bsigroup.com



...making excellence a habit.™