

BS EN ISO 7263:2011



BSI Standards Publication

Corrugating medium — Determination of the flat crush resistance after laboratory fluting (ISO 7263:2011)

bsi.

...making excellence a habit.™

National foreword

This British Standard is the UK implementation of EN ISO 7263:2011. It supersedes BS EN ISO 7263:2008, which is withdrawn.

The UK participation in its preparation was entrusted to Technical Committee PAI/11, Methods of test for paper, board and pulps.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© BSI 2011

ISBN 978 0 580 71677 5

ICS 85.060

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 30 April 2011.

Amendments issued since publication

Date	Text affected
------	---------------

English Version

Corrugating medium - Determination of the flat crush resistance after laboratory fluting (ISO 7263:2011)

Papier cannelure pour carton ondulé - Détermination de la
résistance à la compression à plat après cannelage en
laboratoire (ISO 7263:2011)

Wellenrohpapier - Bestimmung des
Flachstauchwiderstandes an labormäßig gewelltem
Wellenpapier (ISO 7263:2011)

This European Standard was approved by CEN on 14 February 2011.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN-CENELEC Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

Management Centre: Avenue Marnix 17, B-1000 Brussels

Foreword

This document (EN ISO 7263:2011) has been prepared by Technical Committee ISO/TC 6 "Paper, board and pulps" in collaboration with Technical Committee CEN/TC 172 "Pulp, paper and board" the secretariat of which is held by DIN.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by August 2011, and conflicting national standards shall be withdrawn at the latest by August 2011.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN [and/or CENELEC] shall not be held responsible for identifying any or all such patent rights.

This document supersedes EN ISO 7263:2008.

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland and the United Kingdom.

Endorsement notice

The text of ISO 7263:2011 has been approved by CEN as a EN ISO 7263:2011 without any modification.

Contents

Page

Foreword	iv
Introduction.....	v
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Principle	1
5 Apparatus	2
6 Sampling	4
7 Conditioning	4
8 Preparation of test pieces.....	4
9 Procedure	4
9.1 General	4
9.2 Testing immediately after fluting	4
9.3 Testing after 30 min of reconditioning	5
9.4 Fluting and testing	5
10 Expression of results	5
10.1 Flat crush resistance.....	5
10.2 Flat crush resistance index	6
11 Precision	6
12 Test report.....	6
Annex A (informative) Maintenance of fluting rolls (horizontal type).....	7
Bibliography.....	8

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 7263 was prepared by Technical Committee ISO/TC 6, *Paper board and pulps*, Subcommittee SC 2, *Test methods and quality specifications for paper and board*.

This fourth edition cancels and replaces the third edition (ISO 7263:2008), of which it constitutes a minor revision. A misprint in 5.3.1 (8,55 mm) has been corrected and the calculation of the flat crush resistance index has been included in 10.2.

Introduction

The flat crush resistance of laboratory-fluted corrugating medium is regarded as an important property because it is an indication of the potential flat crush resistance of corrugated fibreboard made from that medium. The corrugated medium is fluted by passing it between heated rollers. Two different test procedures are then widely used:

- a) the fluted corrugating medium is compressed immediately after fluting (i.e. 5 s to 8 s after fluting);
- b) the fluted corrugating medium is conditioned for 30 min to 35 min under standard laboratory test conditions before being compressed.

Procedure a) generally gives considerably higher results than those obtained with procedure b). The differences in results are claimed to be caused by

- the lower moisture content (and thus higher stiffness) of the unconditioned fluted corrugating medium, and/or
- the change in flute profile which occurs during the conditioning period.

Since considerable advantages are claimed for both procedures and both are widely used, this International Standard describes both procedures.

A method of determining the flat crush resistance of manufactured corrugated fibreboard is given in ISO 3035^[1].

Corrugating medium — Determination of the flat crush resistance after laboratory fluting

1 Scope

This International Standard specifies two methods for the determination of the flat crush resistance of a corrugating medium after laboratory fluting.

The procedures are applicable to any corrugating medium intended to be used, after fluting, in the manufacture of corrugated board.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 186, *Paper and board — Sampling to determine average quality*

ISO 187, *Paper, board and pulps — Standard atmosphere for conditioning and testing and procedure for monitoring the atmosphere and conditioning of samples*

ISO 536, *Paper and board — Determination of grammage*

ISO 13820, *Paper, board and corrugated fibreboard — Description and calibration of compression-testing equipment*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

3.1

flat crush resistance

maximum force that a corrugated test piece will withstand before the flutes collapse under an increasing force applied perpendicular to its surface

NOTE Flat crush resistance is expressed in newtons.

3.2

flat crush resistance index

flat crush resistance divided by the grammage

NOTE The result is expressed in newton square metres per gram (Nm²/g).

4 Principle

Fluting of the corrugating medium by passing it between heated rollers, and its formation into single-faced corrugated board using pressure-sensitive adhesive tape as the facing. Application of a crushing force, in the direction perpendicular to the plane of the flutes, and determination of the flat crush resistance.

5 Apparatus

5.1 **Cutting device**, for cutting the test pieces to the dimensions required.

5.2 **Fluter**, consisting of a pair of matched steel corrugating rolls.

The roll temperature shall be maintained at $175\text{ °C} \pm 8\text{ °C}$. The temperature is controlled by any suitable method. Check the temperature when the rolls are in motion.

One roll is motor-driven at $4,5\text{ r/min} \pm 1,0\text{ r/min}$ and the rolls are held in mesh by a force of $100\text{ N} \pm 10\text{ N}$ exerted between the rolls and distributed evenly across the teeth, under test conditions. In some instruments, the force between the rolls is applied by a spring acting in a slide. In such instruments, friction in this device can result in the force which acts upon the test piece being considerably less than the force required to displace the rolls initially. When verifying that an instrument conforms to the requirements given in this subclause, it is therefore necessary to measure the force required to just prevent the undriven roll from moving towards the driven roll, from a position about $200\text{ }\mu\text{m}$ away.

The essential characteristics of each roll are the following (see also Figure 1):

Roll diameter	$228,5\text{ mm} \pm 0,5\text{ mm}$
Roll face width	$16\text{ mm} \pm 1\text{ mm}$
Number of teeth	84 (see Note below)
Radius of teeth at peak	$1,5\text{ mm} \pm 0,1\text{ mm}$
Radius of teeth at base	$2,0\text{ mm} \pm 0,1\text{ mm}$
Depth of teeth	$4,75\text{ mm} \pm 0,05\text{ mm}$
Distance between teeth (peak-to-peak around the arc)	$8,55\text{ mm} \pm 0,05\text{ mm}$

In order to optimize the matching of pairs of rolls, pairs of rolls should be selected in which the differences in dimensions between the two are substantially less than the tolerances shown. A difference of $\pm 0,1\text{ mm}$ or better is recommended. Prior to first use, the rolls should be run at the operating temperature for about 6 h with a mild abrasive on the teeth. The two rolls should then be marked in some way so that, after removal for cleaning or maintenance, they can be reassembled with exactly the same teeth in mesh.

NOTE In some fluters, a full roll is not used.

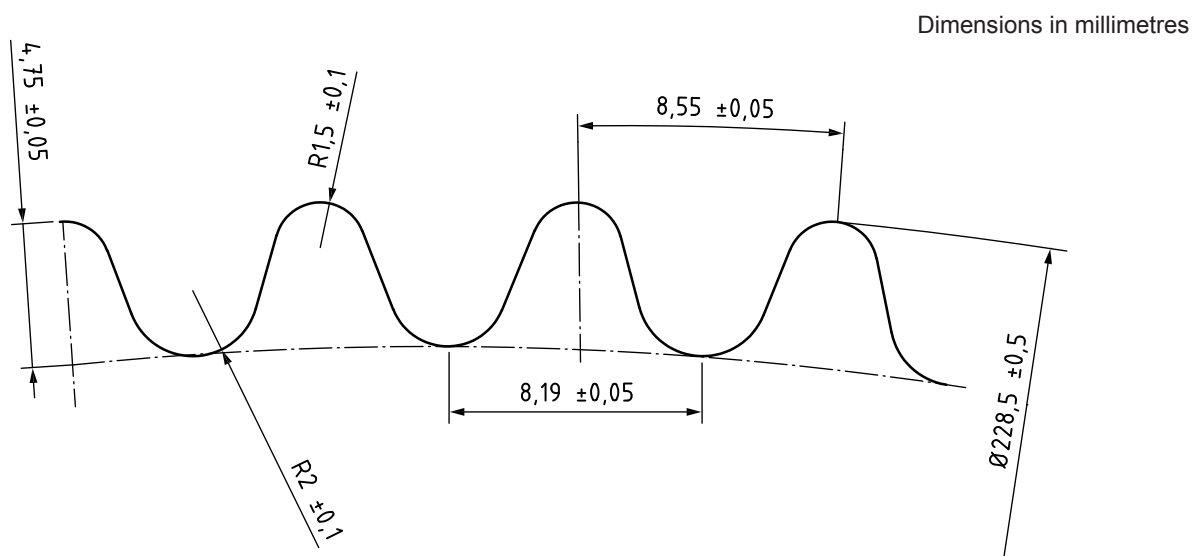


Figure 1 — Profile of corrugating rolls


5.3 Rack and comb.

5.3.1 Rack, at least 19 mm wide with a profile corresponding to the teeth of the corrugating rolls.

The rack has nine full teeth and one incomplete tooth at each end so as to form 10 valleys. The tooth spacing is $8,55 \pm 0,05$ mm and the height of the teeth is $4,75 \pm 0,05$ mm. (See 2 in Figures 2 and 3.)

5.3.2 Comb, at least 19 mm wide with 10 prongs, $3,4 \pm 0,1$ mm high. (See 1 in Figures 2 and 3.)


The rack (5.3.1) and comb may be replaced with an automatic device, provided it can be demonstrated that this device will produce the same results.

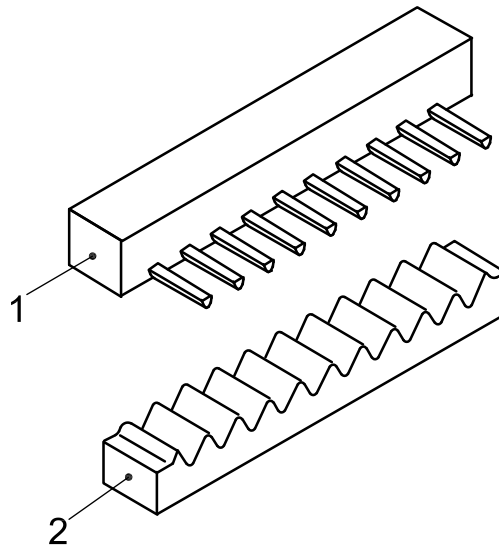

Key

- 1 comb
- 2 rack

Figure 2 — Profile of comb and rack

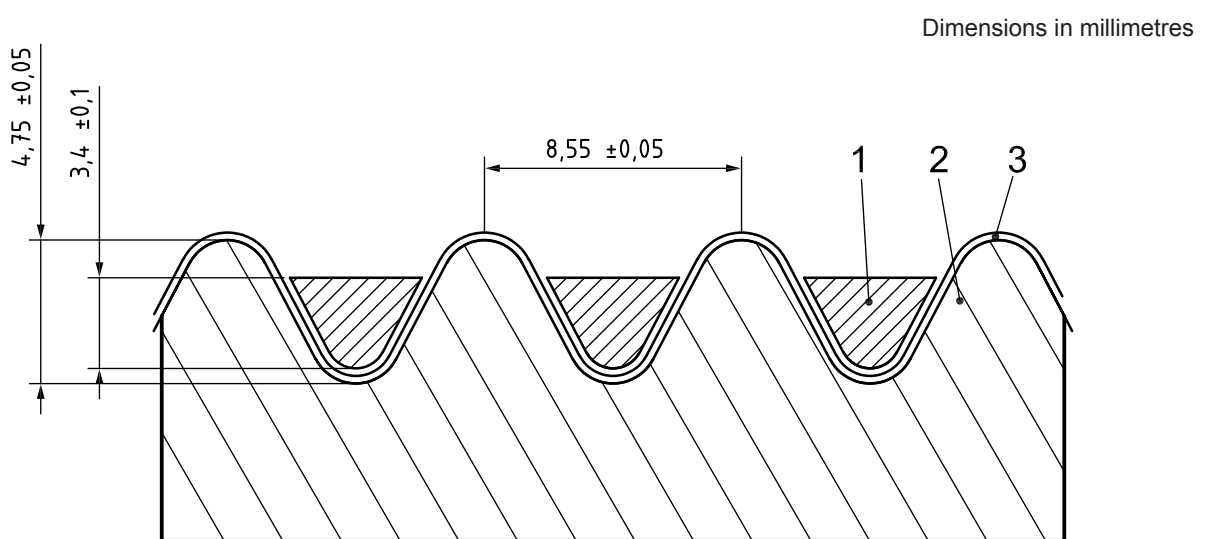

Key

- 1 comb
- 2 rack
- 3 paper

Figure 3 — Dimensions of comb and rack

5.4 Pressure-sensitive adhesive tap, for example 3M grade 410 tape¹⁾, at least 15 mm wide.

The tape shall be of low stretch and have good adhesion properties and it shall not transfer moisture to the substrate during the test.

5.5 Flat crush tester, motor-driven, fixed-platen type in accordance with ISO 13820.

6 Sampling

If the tests are being made to evaluate a lot, the sample shall be selected in accordance with ISO 186. If the tests are made on another type of sample, make sure that the specimens taken are representative of the sample received.

7 Conditioning

When using the reconditioning procedure (see 9.3), before preparation of the test pieces, condition the sample for at least 4 h in one of the conditioning atmospheres specified in ISO 187.

8 Preparation of test pieces

If the flat crush resistance index is required, determine the grammage of the conditioned specimens (before the preparation of test pieces) as described in ISO 536.

Cut at least 10 test pieces having a width of $12,7 \text{ mm} \pm 0,1 \text{ mm}$ and a length between 150 mm and 160 mm, the length being cut in the machine direction. Care should be taken not to damage the edges of the test pieces and they should not be handled more than is necessary.

A test piece width of $15,0 \text{ mm} \pm 0,1 \text{ mm}$ may be used, provided that the corrugating roll width is greater than the test piece width. If a test width of 15 mm is used, the force between the corrugating rolls, as defined in 5.2, is to be adjusted to $118 \text{ N} \pm 10 \text{ N}$. The use of a 15 mm test piece width is not to be considered as being in accordance with this International Standard and its use is to be stated in the test report.

9 Procedure

9.1 General

The compression test may be carried out immediately after fluting (see 9.2) or after reconditioning (see 9.3).

9.2 Testing immediately after fluting

If the test is to be carried out immediately after fluting, the total time between discharge of the fluted test piece from the fluting rolls and the initial application of the crushing force shall be 5 s to 8 s. Arrange all equipment to facilitate completing the operations in the specified time.

For the most reliable results, the times shall be maintained within the 5 s to 8 s time limit from the discharge of the fluted test piece from the fluter to the initial application of force in the compression tester. To do this expeditiously, pre-cut the adhesive tape (5.4) that is to serve as the facing to its prescribed length (at least 120 mm long) and adhere one end of each strip lightly to the workbench.

1) 3M grade 410 tape is an example of a suitable product available commercially. This information is given for the convenience of users of this International Standard and does not constitute an endorsement by ISO of this product.

9.3 Testing after 30 min of reconditioning

If the test is to be carried out after reconditioning, the composite test piece (i.e. the fluted test piece attached to the adhesive tape) shall be reconditioned for 30 min to 35 min in the conditioning atmosphere used to condition the samples (see Clause 7). If the test is carried out on reconditioned samples, all of the composite test pieces may be formed prior to testing.

9.4 Fluting and testing

Start the motor and heat the corrugating rolls (see 5.2) to $175\text{ °C} \pm 8\text{ °C}$. Taking care that one edge is flat on the guide, feed a test piece into the corrugating rolls with its longer side perpendicular to the nip. When the corrugated test piece emerges from the fluting rolls, place it on the rack (5.3.1) so that approximately equal lengths rest on the flat surfaces at each end of the rack.

Place the comb (5.3.2) over the corrugated test piece and press down so that it is held firmly in the valleys of the rack, ensuring that the test piece is bottomed uniformly in each of the flutes.

NOTE A rolling motion of the comb as it is placed on the test piece aids in forming the test pieces on the rack.

Flatten the ends of the corrugated test piece to facilitate the further removal of the test piece from the comb, then place a strip of the adhesive tape (5.4), at least 120 mm long, adhesive side down, along the tips of the flutes and apply pressure (preferably by means of a flat rigid block) to the tape in contact with the tips of the flutes and the test piece ends. Carefully withdraw the comb from the flutes, without damage to the test piece, and lift the resulting 10-flute composite test piece out of the rack. If more than 10 flutes are formed, crush the extra flute(s) by hand prior to testing.

Care should be taken to avoid distortion of the flutes caused by applying too great a pressure when adhering the tape to the tips of the flutes.

Perform the flat crush tests either immediately or after reconditioning (in the same conditioning atmosphere used to condition the samples).

Place the composite test piece centrally on the lower platen of the crush tester (5.5) with the uncovered flutes upwards. Start the compression and read, to the nearest 5 N, the maximum force registered when completely crushing the flutes.

If the flutes have been pressed askew during the compression or if they have come away from the tape at any point, reject the results.

Repeat the procedure for the remaining test pieces until a total of at least 10 valid results have been obtained.

10 Expression of results

10.1 Flat crush resistance

Calculate the mean flat crush resistance, to the nearest 5 N, from the valid results.

Calculate the standard deviation from the mean of the valid results.

To assist in the immediate identification of the results, for many purposes, it may be most convenient to express the results in the form

$$\text{CMT}_0 = 350\text{ N}$$

$$\text{CMT}_{30} = 250\text{ N}$$

where CMT denotes “corrugated medium test” and the subscript denotes the time, in minutes, for reconditioning.

10.2 Flat crush resistance index

If required, calculate the flat crush resistance index, X , in newton square metres per gram, using the equation:

$$X = \frac{\bar{F}}{g}$$

where

\bar{F} is the mean flat crush resistance, in newtons;

g is the grammage, in grams per square metre, determined in accordance with ISO 536.

Report the flat crush resistance index to three significant figures.

11 Precision

Where a rigid platen tester is used and crushing commences 5 s to 8 s after the emergence from fluting, a repeatability of 5 % and a reproducibility of 11 % have been found for the test results, each of which is an average of 10 determinations. These data were obtained in an interlaboratory trial among 53 laboratories using rigid platen testers (Reference [2]).

Where the test specimen is conditioned before fluting and reconditioned 30 min after fluting, a repeatability of 9 % and a reproducibility of 11 % have been found for test results, each of which is an average of 10 determinations. These data were obtained in an interlaboratory trial among 14 laboratories (Reference [3]).

12 Test report

The test report shall include the following information:

- a) a reference to this International Standard, i.e. ISO 7263:2011;
- b) the date and place of testing;
- c) the type of tester used (see 5.5) and, where applicable, the rate of loading;
- d) a description and identification of the product tested;
- e) if tested after reconditioning, the conditioning atmosphere used;
- f) the time, to the nearest minute, between fluting and crushing (or reconditioning after fluting);
- g) the number of valid tests, the arithmetic mean and the standard deviation of all replicate test results, to the nearest 5 N;
- h) if required, the flat crush resistance index, in newton square metres per gram, to three significant figures;
- i) details of any deviation from this International Standard, including if a test width of 15 mm has been used;
- j) any other information that may assist in the interpretation of the test results.

Annex A (informative)

Maintenance of fluting rolls (horizontal type)

Uniform meshing of fluting rolls can be checked by using, for example, National Cash Register Tape²⁾, (CB white NCR paper and CR green tinted NCR paper C2R).

Run a 12,7 mm wide strip of each type of paper through the fluting rolls. The pressure pattern will appear on the green tinted strip. The pressure lines should be uniform and extend the full 12,7 mm width of the strip. If there is more impression at the top or bottom of the rolls, they are not in the same plane. This means that the heating plate has warped, is worn unevenly, or that the bearings are worn. In any case, the fluter should go back to the manufacturer for repair.

The rolls should ride flat on the heating plate. If the drive roll is not flat on the heating plate, loosen the collar directly above the bottom-bearing housing and tap the roll lightly until it is lying flat. It may be necessary to loosen the bottom bearing also. Make this adjustment only when the fluter is up to normal operating temperature. When the roll is flat, tighten all bolts and set screws. Remove the driven roll by taking out the centre bolt and lifting the roll up by bolts inserted in the thread holes provided. Inspect the heating plate for wear of the chrome plating. If worn, a new heating plate should be installed by the manufacturer. The roll can also be inspected for smoothness and wear on the bottom. The spring-loaded post slide can be checked for freeness of movement and lubricated with powdered graphite, if necessary. When the roll is replaced, powdered graphite should be added to the lubricating hole while the roll is turning. Graphite should be added until the grooves under the roll are completely filled. The same holds true for the drive roll.

2) National Cash Register Tape is an example of a suitable product available commercially. This information is given for the convenience of users of this International Standard and does not constitute an endorsement by ISO of this product.

Bibliography

- [1] ISO 3035, *Corrugated fibreboard — Determination of flat crush resistance*
- [2] TAPPI Test Method T 809 om-06, *Flat crush of corrugating medium (CMT test)*
- [3] CEPI-CTS (Confederation of European Paper Industries — Comparative Testing Service):
Round 2007-2, Report A

British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at bsigroup.com/standards or contacting our Customer Services team or Knowledge Centre.

Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at bsigroup.com/shop, where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to bsigroup.com/subscriptions.

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

PLUS is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit bsigroup.com/shop.

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email bsmusales@bsigroup.com.

BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK

Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

Copyright

All the data, software and documentation set out in all British Standards and other BSI publications are the property of and copyrighted by BSI, or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI. Details and advice can be obtained from the Copyright & Licensing Department.

Useful Contacts:

Customer Services

Tel: +44 845 086 9001

Email (orders): orders@bsigroup.com

Email (enquiries): cservices@bsigroup.com

Subscriptions

Tel: +44 845 086 9001

Email: subscriptions@bsigroup.com

Knowledge Centre

Tel: +44 20 8996 7004

Email: knowledgecentre@bsigroup.com

Copyright & Licensing

Tel: +44 20 8996 7070

Email: copyright@bsigroup.com



...making excellence a habit.™