

Rubber and plastics hoses and hose assemblies — Determination of electrical resistance

The European Standard EN ISO 8031 : 1997 has the status of a
British Standard

ICS 23.040.70

NO COPYING WITHOUT BSI PERMISSION EXCEPT AS PERMITTED BY COPYRIGHT LAW



S

National foreword

This British Standard is the English language version of EN ISO 8031 : 1997. It is identical with ISO 8031 : 1993. It supersedes BS EN 28031 : 1993 which is withdrawn.

The UK participation in its preparation was entrusted by Technical Committee PRI/66, Rubber and plastics tubing, hoses and hose assemblies, to Subcommittee PRI/66/4, Methods of test, which has the responsibility to:

- aid enquirers to understand the text;
- present to the responsible international/European committee any enquiries on the interpretation, or proposals for change, and keep the UK interests informed;
- monitor related international and European developments and promulgate them in the UK.

A list of organizations represented on this subcommittee can be obtained on request to its secretary.

Cross-references

Attention is drawn to the fact that CEN and CENELEC Standards normally include an annex which lists normative references to international publications with their corresponding or European publications. The British Standards which implement these international or European publications may be found in the BSI Standards Catalogue under the section entitled 'International Standards Correspondence Index', or by using the 'Find' facility of the BSI Standards Electronic Catalogue.

Compliance with a British Standard does not of itself confer immunity from legal obligations.

Summary of pages

This document comprises a front cover, an inside front cover, the EN ISO title page, the EN ISO foreword page, the ISO title page, page ii, pages 1 to 4, an inside back cover and a back cover.

Amendments issued since publication

Amd. No.	Date	Text affected

This British Standard, having been prepared under the direction of the Sector Board for Materials and Chemicals, was published under the authority of the Standards Board and comes into effect on 15 October 1997

© BSI 1997

ISBN 0 580 28091 8

EUROPEAN STANDARD

EN ISO 8031

NORME EUROPÉENNE

EUROPÄISCHE NORM

June 1997

ICS 23.040.70

Supersedes EN 28031:1993

Descriptors: See ISO document

English version

**Rubber and plastics hoses and hose assemblies
Determination of electrical resistance
(ISO 8031:1993)**

Tuyaux et flexibles en caoutchouc et en
plastique - Détermination de la résistance
électrique (ISO 8031:1993)

Gummi- und Kunststoffschläuche und
-schlauchleitungen - Bestimmung des
elektrischen Widerstandes (ISO 8031:1993)

This European Standard was approved by CEN on 1997-05-03. CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration.

Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Central Secretariat or to any CEN member.

The European Standards exist in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Central Secretariat has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and United Kingdom.

CEN

European Committee for Standardization
Comité Européen de Normalisation
Europäisches Komitee für Normung

Central Secretariat: rue de Stassart, 36 B-1050 Brussels

© 1997 CEN - All rights of exploitation in any form and by any means reserved worldwide for CEN national Members.

Ref. No. EN ISO 8031:1997 E

EN ISO 8031 : 1997**Foreword**

The text of the International Standard from Technical Committee ISO/TC 45 "Rubber and rubber products" of the International Organization for Standardization (ISO) has been taken over as an European Standard by Technical Committee CEN/TC 218 "Rubber and plastics hoses and hose assemblies", the secretariat of which is held by BSI.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by December 1997, and conflicting national standards shall be withdrawn at the latest by December 1997.

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and the United Kingdom.

Endorsement notice

The text of the International Standard ISO 8031:1993 has been approved by CEN as a European Standard without any modification.

INTERNATIONAL
STANDARD

ISO
8031

Second edition
1993-12-15

**Rubber and plastics hoses and hose
assemblies — Determination of electrical
resistance**

*Tuyaux et flexibles en caoutchouc et en plastique — Détermination de la
résistance électrique*



Reference number
ISO 8031:1993(E)

* 5 *

EN ISO 8031 : 1997**Foreword**

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

International Standard ISO 8031 was prepared by Technical Committee ISO/TC 45, *Rubber and rubber products*, Subcommittee SC 1, *Hoses (rubber and plastics)*.

This second edition cancels and replaces the first edition (ISO 8031:1987), of which it constitutes a minor revision.

Descriptors: rubber products, plastics products, hoses, rubber hoses, plastics hoses, tests, electrical tests, determination, electrical resistance.

Rubber and plastics hoses and hose assemblies — Determination of electrical resistance

1 Scope

This International Standard specifies methods for electrical tests on rubber and plastics hoses and hose assemblies to determine the resistance of conductive, antistatic and non-conductive hoses, the electrical continuity between fittings, and the electrical discontinuity.

2 Normative references

The following standards contain provisions which, through reference in this text, constitute provisions of this International Standard. At the time of publication, the editions indicated were valid. All standards are subject to revision, and parties to agreements based on this International Standard are encouraged to investigate the possibility of applying the most recent editions of the standards indicated below. Members of IEC and ISO maintain registers of currently valid International Standards.

ISO 291:1977, *Plastics — Standard atmospheres for conditioning and testing*.

ISO 471:—¹⁾, *Rubber — Times, temperatures and humidities for conditioning and testing*.

ISO 2878:1987, *Rubber, vulcanized — Antistatic and conductive products — Determination of electrical resistance*.

3 Measurement of resistance of conductive, antistatic and non-conductive hoses

Rubber hoses may have a conducting lining only or a conducting cover only, or may be manufactured from

conducting rubber compounds throughout. A method of test is specified for each of the three possible types of construction.

3.1 Apparatus

The following apparatus is required and shall be basically as described in ISO 2878.

3.1.1 Testing instruments

3.1.1.1 To determine the resistance of conductive, antistatic and non-conductive hose, the test should be made preferably with an instrument specifically designed for measuring insulation resistance, having a nominal open-circuit voltage of 500 V d.c., or with any other instrument known to give comparable results. The instrument shall be sufficiently accurate to determine the resistance to within $\pm 10\%$. During the test, not more than 3 W shall be dissipated in the specimen, to prevent erroneous results due to effects of temperature. The power dissipated shall be determined by the square of the open-circuit voltage divided by the measured resistance.

The resistance values obtained will vary with the applied voltage, and errors may occur when low test voltages are involved. In cases of dispute, the voltage applied to the test piece shall be not less than 40 V, except where this conflicts with the requirement not to dissipate more than 3 W in the test piece.

3.1.1.2 For tests requiring measurement of electrical continuity between end fittings or through continuous internal or external bonded wires, the instrument used shall be an ohmmeter sufficiently accurate to determine the resistance to within $\pm 10\%$.

1) To published. (Revision of ISO 471:1983 and ISO 1826:1981)

EN ISO 8031 : 1997**3.1.2 Electrodes and contacts**

Electrodes shall be formed on the surface as bands (25 ± 2) mm wide around the circumference by means of a conductive silver lacquer, colloidal graphite or a conductive liquid.

When a conductive liquid is used, the electrode contact area shall be completely wetted and shall remain so until the end of the test. The conductive liquid shall consist of

- anhydrous polyethylene glycol of relative molecular mass 600: 800 parts by mass
- water: 200 parts by mass
- wetting agent: 1 part by mass
- potassium chloride: 10 parts by mass

When a conductive silver lacquer or colloidal graphite is used, the surface resistance between any two points on a sample of the dried film shall not exceed 100 Ω .

Clean metal contacts shall be applied to the electrodes so that the contact area is approximately the same size as, but no greater than, the electrodes, except where otherwise stated.

In the case of hoses of less than 50 mm bore, it is difficult to apply the conducting liquid accurately to the hose bore, and it is preferable to use a brass plug of external diameter equal to or greater than the hose internal diameter, coated with conducting liquid, and then pushed 25 mm into the hose.

3.2 Preparation and cleaning for test

The surfaces of the hose or test piece shall be clean. If necessary, they may be cleaned by rubbing with fuller's earth (magnesium aluminium silicate) and water, washing with distilled water and allowing to dry. Do not use organic materials which attack or swell the rubber, and do not buff or abrade the test surfaces.

The surface of the hose shall not be deformed either during the application of the contacts or during test. When using test pieces, the supports shall be outside the test length. When using a long length of hose, the hose shall be uncoiled and laid straight on polyethylene or other insulating material. Care shall be taken to ensure that the hose is insulated from any leakage path along the length of hose.

3.3 Conditioning

The articles shall be conditioned for at least 16 h under one of the following standard conditions in accordance with ISO 291 or ISO 471:

23 °C \pm 2 °C and (50 \pm 5) % relative humidity

or

27 °C \pm 2 °C and (65 \pm 5) % relative humidity.

However, where very long lengths of hose are being tested, it is permissible, by agreement between supplier and customer, to use the conditions prevailing in the factory, warehouse or laboratory, provided that the relative humidity is not greater than 70 %.

3.4 Procedure for hoses with conducting lining (on full hose length)

Apply the electrodes as specified in 3.1.2 on the inside surface at each end of the hose. The edge of the electrode band shall be coincident with the end of the hose. When using a conductive liquid, care shall be taken to avoid creating a leakage path between the lining and the reinforcement or cover of the hose.

Apply the metal contacts to the electrodes.

Apply the test voltage and measure the resistance 5 s \pm 1 s after the application of that voltage.

3.5 Procedure for hoses with conducting cover**3.5.1 Method for full hose length**

Apply the electrodes as specified in 3.1.2 on the outside surface at each end of the hose.

Apply the metal contacts.

Apply the test voltage and measure the resistance 5 s \pm 1 s after the application of that voltage.

3.5.2 Method for test pieces**3.5.2.1 Test pieces**

Prepare the test pieces by cutting five lengths of hose approximately 300 mm long from samples taken at random from a production run. Condition the test pieces in accordance with 3.3.

Position the electrodes as specified in 3.1.2 symmetrically along the test piece so that the distance

between their nearest edges is $100 \text{ mm} \pm 1 \text{ mm}$. (See figure 1.)

Ensure that contact is maintained with the electrodes around the circumference and that the contact pieces are sufficiently long for the two free ends to be held securely by a tensioning clip (see figure 1) such that the fit of the electrodes is as tight as possible, consistent with the means employed.

3.5.2.2 Test procedure

Place the test piece on blocks of polyethylene, or other insulating material, to provide a resistance of greater than $10^{11} \Omega$ between the test piece and the surface on which the blocks are supported. Ensure that the leads from the instrument do not touch each other, the hose, or any part except the terminal to which each is connected. Connect the leads from the testing instrument to the appropriate contact piece.

Apply the test voltage and measure the resistance $5 \text{ s} \pm 1 \text{ s}$ after the application of that voltage.

Avoid breathing on the test surfaces and thus creating condensation that may lead to inaccuracies.

3.6 Procedure for hoses with conducting compounds throughout

3.6.1 Method for hoses up to 6 m in length

3.6.1.1 Apply the electrodes as specified in 3.1.2 on the inside surface at one end of the hose (end A) and on the outside surface at the other end (end B).

Apply the metal contacts to the electrodes.

Apply the test voltage and measure the resistance $5 \text{ s} \pm 1 \text{ s}$ after the application of that voltage.

3.6.1.2 Repeat the test, applying the electrodes to the outside surface at end A and to the inside surface at end B.

3.6.2 Method for hoses over 6 m in length

3.6.2.1 Apply the electrodes as specified in 3.1.2 on the inside surface at one end of the hose and on the outside surface at distances of 3 m and 6 m from the same end.

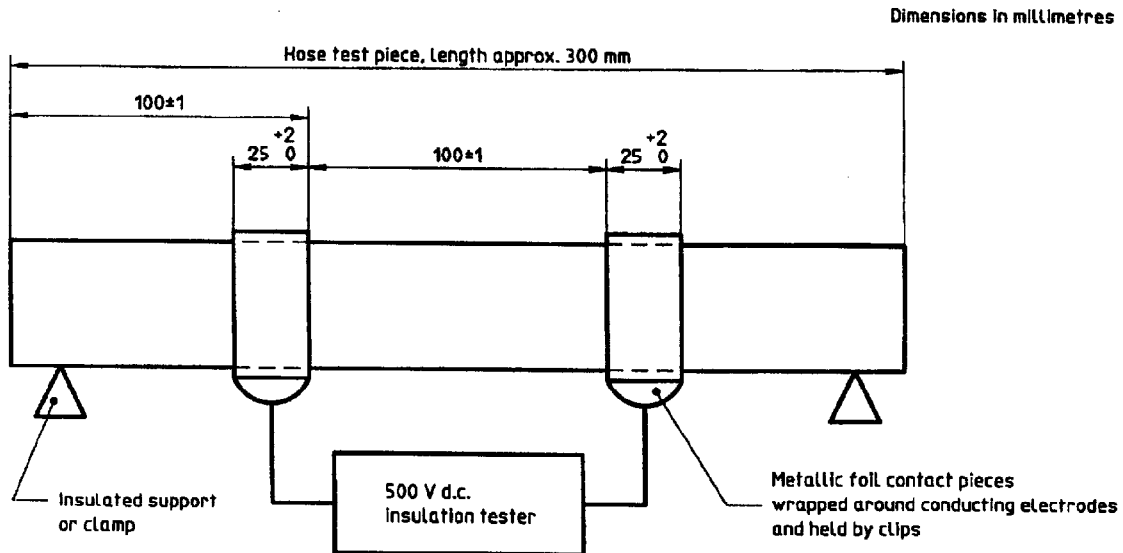


Figure 1 — Electrodes and contacts for testing as described in 3.5.2.1

EN ISO 8031 : 1997

Apply the metal contacts to the inside electrode and to the outside electrode at 3 m from the inside electrode.

Apply the test voltage and measure the resistance $5\text{ s} \pm 1\text{ s}$ after the application of that voltage.

3.6.2.2 Repeat the test between the inside electrode and the outside electrode at 6 m from the inside electrode. The difference between these resistance values shall be regarded as the resistance for 3 m of the hose.

3.6.2.3 Repeat the tests at the other end of the hose length.

NOTE 1 The purpose of this test is not only to measure and compare the resistance of the end 3 m of hose but to ensure that the homogeneity of the hose construction is maintained throughout during manufacture.

3.7 Hose assemblies fitted with metal end couplings

3.7.1 When it is required that the resistance of a hose assembly be measured, the leads of the test instrument shall be attached directly to the metal end couplings.

3.7.2 Some hoses, especially thermoplastics hoses, have conductive layers within the hose construction. These hoses shall be tested as assemblies made with fittings and assembly techniques specified by the hose and fitting manufacturer.

4 Measurement of electrical continuity

In certain types of hose construction, electrical continuity is provided between the end fittings by means of a continuous wire or wires bonded to each coupling. When the construction is such that there are internal and external wires, the electrical continuity of both wires shall be established using a suitable ohmmeter as described in 3.1.1.2.

It is essential that contact resistance between the end fittings and the meter is minimized.

5 Measurement of electrical discontinuity

In certain types of hose containing wire in the construction, it is required that such wire be insulated from the end fittings. In these cases, condition the hose in accordance with 3.3 and measure the resistance between the fittings as described in 3.7.

It is essential that contact resistance between the end fittings and the meter is minimized.

6 Test report

The test report shall include items a) to d) and, as appropriate, e) to k):

- a) the hose type and nominal bore;
- b) a reference to this International Standard;
- c) the conditioning and test atmosphere, i.e. the temperature and relative humidity;
- d) the distance between the electrodes;
- e) the electrode material used;
- f) the resistance, in ohms per metre, of the hose lining, and the test method used;
- g) the resistance, in ohms per metre, of the hose cover, and the test method used, detailing the individual readings;
- h) the resistance, in ohms per metre, of the hose from lining to cover, and the test method used, detailing the individual readings;
- i) the resistance, in ohms per metre, of the hose assembly between couplings, and the test method used;
- j) whether electrical continuity was established;
- k) the insulation resistance, in ohms, obtained when establishing electrical discontinuity.

BSI — British Standards Institution

BSI is the independent national body responsible for preparing British Standards. It presents the UK view on standards in Europe and at the international level. It is incorporated by Royal Charter.

Contract requirements

A British Standard does not purport to include all the necessary provisions of a contract. Users of British Standards are responsible for their correct application.

Revisions

British Standards are updated by amendment or revision. Users of British Standards should make sure that they possess the latest amendments or editions.

It is the constant aim of BSI to improve the quality of our products and services. We would be grateful if anyone finding an inaccuracy or ambiguity while using this British Standard would inform the Secretary of the responsible technical committee, the identity of which can be found on the inside front cover. Tel: 0181 996 9000; Fax: 0181 996 7400.

BSI offers members an individual updating service called PLUS which ensures that subscribers automatically receive the latest editions of standards.

Buying standards

Orders for all BSI, international and foreign standards publications should be addressed to Customer Services, Sales Department at Chiswick: Tel: 0181 996 7000; Fax: 0181 996 7001.

In response to orders for international standards, it is BSI policy to supply the BSI implementation of those that have been published as British Standards, unless otherwise requested.

Information on standards

BSI provides a wide range of information on national, European and international standards through its Library, the Standardline Database, the BSI Information Technology Service (BITS) and its Technical Help to Exporters Service. Contact the Information Department at Chiswick: Tel: 0181 996 7111; Fax: 0181 996 7048.

Subscribing members of BSI are kept up to date with standards developments and receive substantial discounts on the purchase price of standards. For details of these and other benefits contact Customer Services, Membership at Chiswick: Tel: 0181 996 7002; Fax: 0181 996 7001.

Copyright

Copyright subsists in all BSI publications. BSI also holds the copyright, in the UK, of the publications of the international standardization bodies. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI.

This does not preclude the free use, in the course of implementing the standard, of necessary details such as symbols, and size, type or grade designations. If these details are to be used for any other purpose than implementation then the prior written permission of BSI must be obtained.

If permission is granted, the terms may include royalty payments or a licensing agreement. Details and advice can be obtained from the Copyright Manager, BSI, 389 Chiswick High Road, London W4 4AL.

BSI
389 Chiswick High Road
London
W4 4AL