

BS EN ISO 8033:2017



BSI Standards Publication

**Rubber and plastics hoses —
Determination of adhesion
between components
(ISO 8033:2016)**

National foreword

This British Standard is the UK implementation of EN ISO 8033:2017. It is identical to ISO 8033:2016. It supersedes BS EN ISO 8033:2006 which is withdrawn.

The UK participation in its preparation was entrusted to Technical Committee PRI/66, Rubber and plastics tubing, hoses and hose assemblies.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© The British Standards Institution 2017.
Published by BSI Standards Limited 2017

ISBN 978 0 580 89089 5

ICS 23.040.70

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 31 January 2017.

Amendments/corrigendum issued since publication

Date	Text affected
------	---------------

EUROPEAN STANDARD

EN ISO 8033

NORME EUROPÉENNE

EUROPÄISCHE NORM

January 2017

ICS 23.040.70

Supersedes EN ISO 8033:2006

English Version

Rubber and plastics hoses - Determination of adhesion between components (ISO 8033:2016)

Tuyaux en caoutchouc et en plastique - Détermination
de l'adhérence entre éléments (ISO 8033:2016)

Gummi- und Kunststoffschläuche - Bestimmung der
Haftung zwischen den einzelnen Schichten (ISO
8033:2016)

This European Standard was approved by CEN on 24 September 2016.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN-CENELEC Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

CEN-CENELEC Management Centre: Avenue Marnix 17, B-1000 Brussels

European foreword

This document (EN ISO 8033:2017) has been prepared by Technical Committee ISO/TC 45 "Rubber and rubber products" in collaboration with Technical Committee CEN/TC 218 "Rubber and plastics hoses and hose assemblies" the secretariat of which is held by BSI.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by July 2017, and conflicting national standards shall be withdrawn at the latest by July 2017.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN [and/or CENELEC] shall not be held responsible for identifying any or all such patent rights.

This document supersedes EN ISO 8033:2006.

According to the CEN-CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and the United Kingdom.

Endorsement notice

The text of ISO 8033:2016 has been approved by CEN as EN ISO 8033:2017 without any modification.

Contents

Page

Foreword	iv
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Principle	2
5 Apparatus	2
5.1 General.....	2
5.2 Test machine.....	2
5.3 Grips.....	2
5.4 Mandrel.....	2
6 Test pieces	2
6.1 Types of test piece.....	2
6.1.1 General.....	2
6.1.2 Type 1.....	2
6.1.3 Type 2.....	2
6.1.4 Type 3.....	3
6.1.5 Type 4.....	3
6.1.6 Type 5.....	3
6.1.7 Type 6.....	3
6.1.8 Type 7.....	3
6.1.9 Type 8.....	3
6.2 Test piece selection.....	3
6.3 Test piece preparation.....	4
6.3.1 General.....	4
6.3.2 Type 1.....	4
6.3.3 Type 2.....	4
6.3.4 Type 3.....	4
6.3.5 Type 4.....	5
6.3.6 Type 5.....	5
6.3.7 Type 6.....	5
6.3.8 Type 7.....	5
6.3.9 Type 8.....	5
6.4 Conditioning of test pieces.....	6
6.5 Time interval between vulcanization and testing.....	6
7 Procedure	6
7.1 Preparation.....	6
7.2 Insertion of test pieces.....	6
7.3 Test speed.....	6
7.4 Measurement.....	6
8 Expression of results	6
9 Test report	7
Bibliography	13

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT) see the following URL: www.iso.org/iso/foreword.html.

The committee responsible for this document is ISO/TC 45, *Rubber and rubber products*, Subcommittee SC 1, *Rubber and plastics hoses and hose assemblies*.

This fourth edition cancels and replaces the third edition (ISO 8033:2006), which has been technically revised with the following changes:

- [Figure 3](#), [6.3.8](#) and [Figure 7](#) have been technically revised.

Rubber and plastics hoses — Determination of adhesion between components

1 Scope

This document specifies methods for the determination of the adhesion between lining and reinforcement, between cover and reinforcement, between reinforcement layers, between cover and outer lamination (thin layer of material outside the cover for protection) and between lining and inner lamination (thin layer of material inside the lining to reduce permeation of fluid into the lining). It covers all bore sizes and the following types of hose construction:

- woven textile fabric;
- braided textile fabric;
- knitted textile fabric;
- circular-woven textile fabric;
- textile spiral;
- textile cord;
- wire braid;
- wire spiral;
- hoses containing a supporting helix.

Adequate adhesion between the various components of a hose is essential if it is to perform satisfactorily in service.

2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 5893, *Rubber and plastics test equipment — Tensile, flexural and compression types (constant rate of traverse) — Specification*

ISO 6133, *Rubber and plastics — Analysis of multi-peak traces obtained in determinations of tear strength and adhesion strength*

ISO 23529, *Rubber — General procedures for preparing and conditioning test pieces for physical test methods*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 8330 apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- IEC Electropedia: available at <http://www.electropedia.org/>
- ISO Online browsing platform: available at <http://www.iso.org/obp>

4 Principle

Using test pieces of standard dimensions, the adhesion strength between lining and reinforcement, between cover and reinforcement, between reinforcement layers, between cover and outer lamination and between lining and inner lamination is measured under specified conditions.

5 Apparatus

5.1 General

A test machine having the following characteristics is required:

5.2 Test machine

The machine shall be power driven, equipped with a suitable dynamometer, capable of maintaining a substantially constant rate of traverse of the moving head during the test and fitted with an autographic recorder. It shall comply with the requirements for class 0,5 or 1 of ISO 5893.

An inertialess dynamometer shall be used.

5.3 Grips

The grips shall be capable of holding the test piece without slippage.

Self-tightening grips are recommended.

For strip test pieces, provision shall be made to maintain the strip in the appropriate plane of the grips during the test, for example, by attaching sufficient weights to the free end of the test piece or by fitting a supporting plate, coated with a low-friction material, such as polytetrafluoroethylene (PTFE), to the non-driven grip.

5.4 Mandrel

For testing ring test pieces (type 6 and type 8), a mandrel shall be provided that is a close sliding fit in the test piece. This mandrel shall be capable of being fitted into the driven head of the machine so that it will rotate freely during the test.

6 Test pieces

6.1 Types of test piece

6.1.1 General

Eight types of test piece are specified to cover the range of hose constructions and bore sizes normally encountered (see [Figures 1 to 8](#)).

6.1.2 Type 1

Strip, cut from the hose as a $25 \text{ mm} \pm 0,5 \text{ mm}$ wide ring which is then cut transversely to form a strip.

6.1.3 Type 2

Strip, $160 \text{ mm} \times$ half the hose circumference.

6.1.4 Type 3

Strip, cut from the hose as a 35 mm ± 2 mm wide ring which is then cut transversely to form a strip.

6.1.5 Type 4

Strip, 160 mm × half the hose circumference or 10 mm, whichever is smaller.

6.1.6 Type 5

Strip, 160 mm long × half the hose circumference.

6.1.7 Type 6

Ring, 35 mm ± 2 mm wide.

6.1.8 Type 7

Strip, cut along a reinforcing helix, 25 mm ± 0,5 mm wide or the maximum obtainable.

6.1.9 Type 8

Ring, 25 mm ± 0,5 mm wide.

6.2 Test piece selection

Unless specified in the particular product standard or otherwise agreed between the interested parties, the type of test piece shall be selected from [Table 1](#). Results obtained with different test pieces and/or hoses of the same construction but of different diameters are not comparable.

Table 1 — Test piece selection

Hose construction	Adhesion between	Hose nominal bore size, <i>d</i> mm		
		<i>d</i> ≤ 20	20 < <i>d</i> ≤ 50	50 < <i>d</i>
Woven textile fabric	Lining and reinforcement	Type 4 or 8	Type 1 or 8	Type 1 or 8
Braided textile fabric	Reinforcement layers	Type 4 or 8	Type 1 or 8	Type 1 or 8
Knitted textile fabric	Cover and reinforcement	Type 4 or 8	Type 1 or 8	Type 1 or 8
Circular-woven textile fabric				
Textile spiral	Lining and reinforcement	Type 2, 6 or 8	Type 3, 6 or 8	Type 3, 6 or 8
Textile cord	Reinforcement layers	Type 2 ^a , 6 or 8	Type 2, 3 ^a , 6 or 8	Type 3 ^a , 6 or 8
	Cover and reinforcement	Type 2, 6 or 8	Type 3, 6 or 8	Type 3, 6 or 8

^a If the determination of adhesion is affected by difficulty in obtaining a cleanly separating interface because of fraying of the yarns, indicate this in the test report.

^b Determination is impracticable below 12,5 mm bore size since insufficient test piece width is available.

^c Determination is impracticable since the wire braid or spiral layers tend to disintegrate and the result is in any case significantly affected by the forces required to bend the wires.

Table 1 (continued)

Hose construction	Adhesion between	Hose nominal bore size, <i>d</i>		
		mm		
		<i>d</i> ≤ 20	20 < <i>d</i> ≤ 50	50 < <i>d</i>
Wire braid	Lining and reinforcement	Type 5 ^b	Type 5	Type 5
Wire spiral	Reinforcement layers	— ^c	— ^c	— ^c
	Cover and reinforcement	Type 2, 6 or 8	Type 2, 6 or 8	Type 2, 6 or 8
Hoses containing a supporting helix	Lining and reinforcement	Type 7	Type 7	Type 7
	Reinforcement layers	Type 7	Type 7	Type 7
	Cover and reinforcement	Type 7	Type 7	Type 7
All constructions	Lining and inner lamination	Type 2, 4, 5 or 8	Type 2, 4, 5 or 8	Type 2, 4, 5 or 8
	Cover and outer lamination	Type 2, 4, 5 or 8	Type 2, 4, 5 or 8	Type 2, 4, 5 or 8

^a If the determination of adhesion is affected by difficulty in obtaining a cleanly separating interface because of fraying of the yarns, indicate this in the test report.

^b Determination is impracticable below 12,5 mm bore size since insufficient test piece width is available.

^c Determination is impracticable since the wire braid or spiral layers tend to disintegrate and the result is in any case significantly affected by the forces required to bend the wires.

6.3 Test piece preparation

6.3.1 General

Test pieces shall be prepared by a method that does not produce high temperatures due to the action of the cutting blade.

The thickness of test pieces shall be adjusted by buffing so that the separated faces are positioned as close as possible to the axis of traction of the grips.

Test pieces that contain foreign matter or have blisters or flaws shall not be used for tests.

6.3.2 Type 1

Cut a ring 25 mm ± 0,5 mm wide from the hose at right angles to its longitudinal axis. Cut the ring transversely and open it out to form a strip.

Separate a layer for a distance sufficient to enable the separated ends to be held in the grips of the test machine (see [Figure 1](#)).

Where heat build-up might cause deterioration of properties, use test pieces of type 2, 3, 5 or 6.

6.3.3 Type 2

Cut a suitable length of hose in half longitudinally. From one of the halves, make two cuts parallel to the axis of the test piece 25 mm ± 0,5 mm, 10 mm ± 0,5 mm or 5 mm ± 0,2 mm apart, depending on the width available, taking care not to cut through the yarns.

Separate a layer for a distance sufficient to enable the separated ends to be held in the grips of the test machine (see [Figure 2](#)).

6.3.4 Type 3

Cut a ring 35 mm ± 2 mm wide from the hose at right angles to its longitudinal axis. Cut the ring transversely and open it to form a strip.

Make two parallel cuts on the strip $25\text{ mm} \pm 0,5\text{ mm}$ apart, taking care not to cut through the yarns.

Separate a layer for a distance sufficient to enable the separated ends to be held in the grips of the test machine (see [Figure 3](#)).

6.3.5 Type 4

Cut a suitable length of hose in half longitudinally. From one of the halves, cut a strip $10\text{ mm} \pm 0,5\text{ mm}$ wide, or of the maximum width obtainable if the width is less than 10 mm.

Separate a layer for a distance sufficient to enable the separated ends to be held in the grips of the test machine (see [Figure 4](#)).

6.3.6 Type 5

Cut a suitable length of hose in half longitudinally. Using a twin-bladed tool, cut from one of the halves a centrally located longitudinal strip $5\text{ mm} \pm 0,2\text{ mm}$ wide through the lining and open up one end of the test piece to form a lip.

Separate a layer for a distance sufficient to enable the separated ends to be held in the grips of the test machine (see [Figure 5](#)).

6.3.7 Type 6

Cut a ring $35\text{ mm} \pm 2\text{ mm}$ wide from the hose at right angles to its longitudinal axis. Make two circumferential cuts through the cover $25\text{ mm} \pm 0,5\text{ mm}$ apart and located centrally on the test piece. Make a transverse cut across the 25 mm width through the cover and open up on one side of the cut to form a lip (see [Figure 6](#)).

NOTE When cutting ring-shaped test pieces from a hose, it is advisable to insert a wooden cylinder, or similar device, into the hose before cutting out the test piece.

6.3.8 Type 7

Obtain a strip from the hose wall by cutting along the reinforcing helix through the complete thickness of the hose wall and trim to 160 mm long and $25\text{ mm} \pm 0,5\text{ mm}$ wide or the maximum width obtainable if the width is less than 25 mm.

Separate a layer for a distance sufficient to enable the separated ends to be held in the grips of the test machine (see [Figure 7](#)).

This is an optional test for helix-reinforced hoses made in long lengths. It does not apply to hoses made to individual lengths, with special ends, built-in fittings, etc. If the spacing between adjacent coils of the helix is less than 10 mm, leaving an appropriate length (i.e. more than 160 mm or 25 mm) without applying reinforcing helix on one end of the hose is recommended during manufacturing, so that this end has the same process and state with the hose body which applied helix. Cut this part off and prepare the test piece according to type 4 or type 8.

6.3.9 Type 8

Cut a ring-shaped test piece $25\text{ mm} \pm 0,5\text{ mm}$ wide from the hose at right angles to its longitudinal axis. Make a transverse cut across the 25 mm width through the cover and open up on one side of the cut to form a lip (see [Figure 8](#)).

NOTE When cutting ring-shaped test pieces from a hose, it is advisable to insert a wooden cylinder, or similar device, into the hose before cutting out the test piece.

6.4 Conditioning of test pieces

No tests shall be carried out within 24 h of manufacture. Before testing, test pieces shall be conditioned at standard temperature and humidity (see ISO 23529) for at least 16 h; this may be part of the 24 h after manufacture.

6.5 Time interval between vulcanization and testing

For evaluations intended to be comparable, the tests should, as far as possible, be carried out after the same time interval after manufacture. ISO 23529 shall be followed for the time between sample manufacture and testing.

7 Procedure

7.1 Preparation

A separate test piece shall be used for each interface to be tested.

7.2 Insertion of test pieces

Take a test piece from the conditioning atmosphere and measure the actual width of the test piece. For types 1, 2, 3, 4, 5 and 7, fix the separated ends of the test piece in the grips of the test machine. For types 6 and 8, place the test piece on the mandrel (5.4) and the separated ends in the grips. Adjust so that the tension is distributed uniformly and that no twisting of the test piece occurs during the test. Place the test piece in the grips so that the angle of separation is approximately 180° for strip or 90° for ring test pieces.

It is important to ensure that the pulling force acts in the plane of separation.

7.3 Test speed

The rate of travel of the power-driven grip shall be such as to provide a rate of ply separation of 50 mm/min \pm 5 mm/min (for test pieces of types 1 to 7) or 25 mm/min \pm 2,5 mm/min (for type 8 test pieces).

7.4 Measurement

Start the machine and record the force, in newtons, over a length of separation of at least 100 mm or the maximum distance possible if the test piece is less than 100 mm long.

If separation occurs at any other point, for example, inside either component under test, note this failure and report the force at which it occurs.

8 Expression of results

The trace obtained from the graphical recorder shows the variations in the force at which the plies or layers have separated.

Determine the median peak force from the trace using the appropriate method specified in ISO 6133. Divide the median peak force by the effective width of the test piece and express the adhesion strength in kilonewtons per metre.

9 Test report

The test report shall contain the following information:

- a) the hose type and nominal bore;
- b) the date of manufacture and batch number or reference, as applicable;
- c) the method of manufacture and details of the reinforcement;
- d) a reference to this document, i.e. ISO 8033:2016;
- e) the type(s) of test piece used;
- f) the test speed;
- g) if appropriate, the adhesion strength, expressed in kilonewtons per metre of width, between lining and reinforcement;
- h) if appropriate, the adhesion strength, expressed in kilonewtons per metre of width, between layers of reinforcement, noting any difficulties (see [Table 1](#), footnote “a”);
- i) if appropriate, the adhesion strength, expressed in kilonewtons per metre of width, between cover and reinforcement;
- j) if appropriate, the adhesion strength, expressed in kilonewtons per metre of width, between cover and outer lamination and between lining and inner lamination;
- k) the date of test.

Dimensions in millimetres


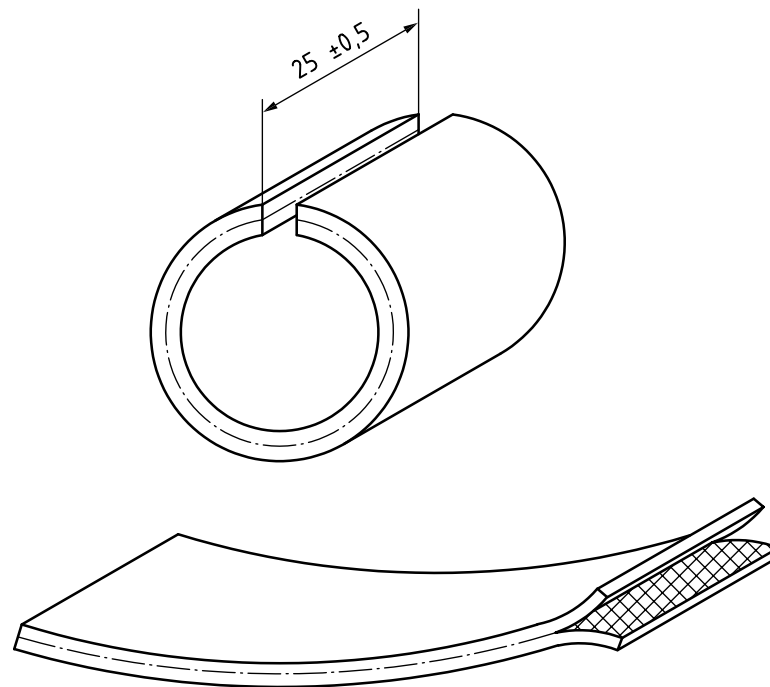


Figure 1 — Type 1 test piece

Dimensions in millimetres

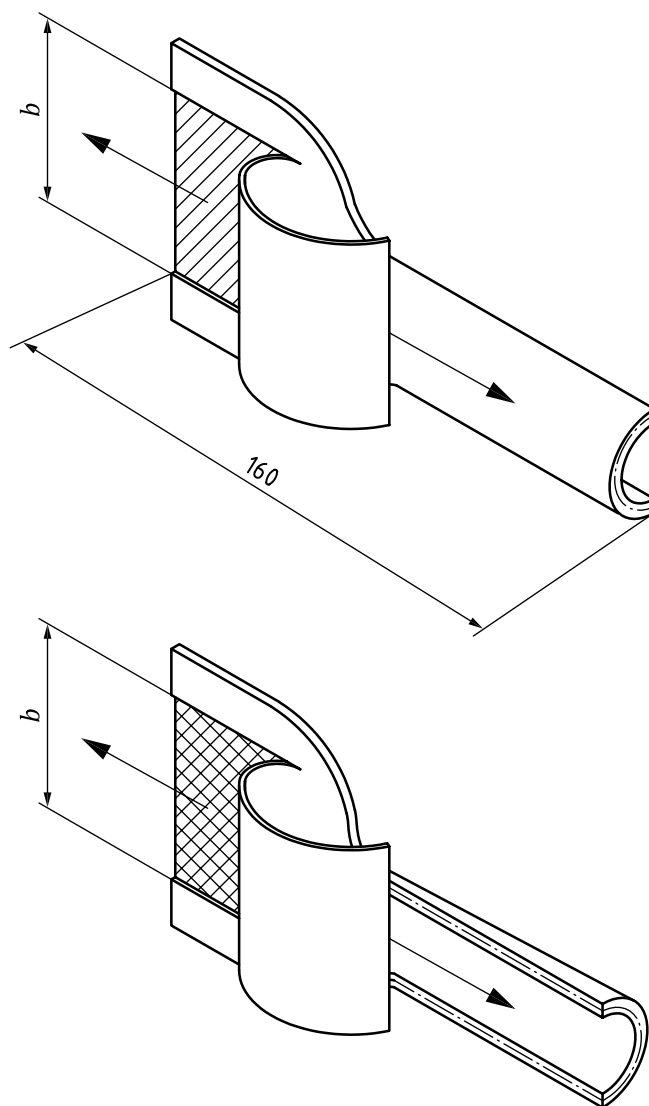

b 25 mm \pm 0,5 mm or 10 mm \pm 0,5 mm or 5 mm \pm 0,2 mm

Figure 2 — Type 2 test piece

Dimensions in millimetres

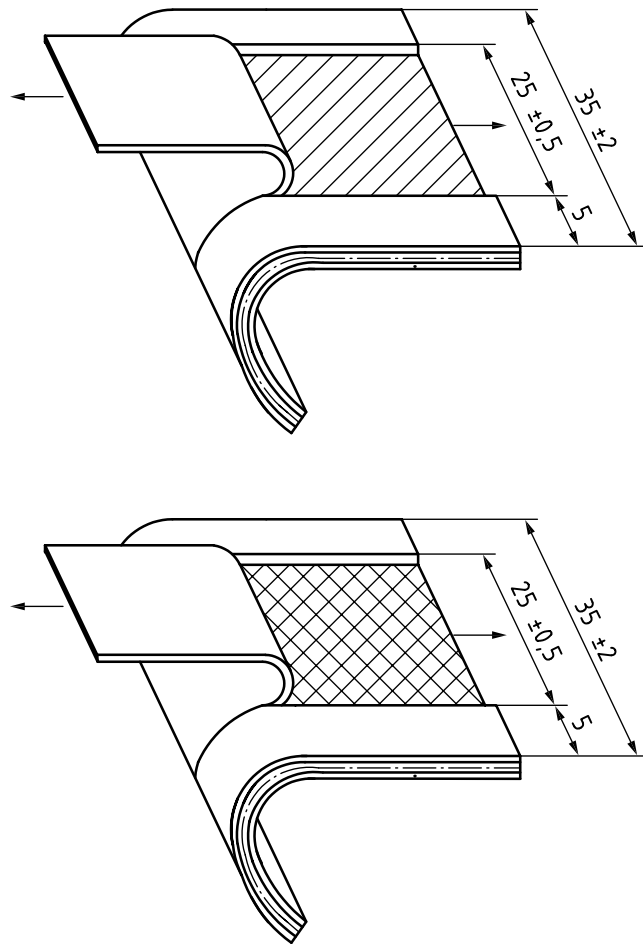


Figure 3 — Type 3 test piece

Dimensions in millimetres

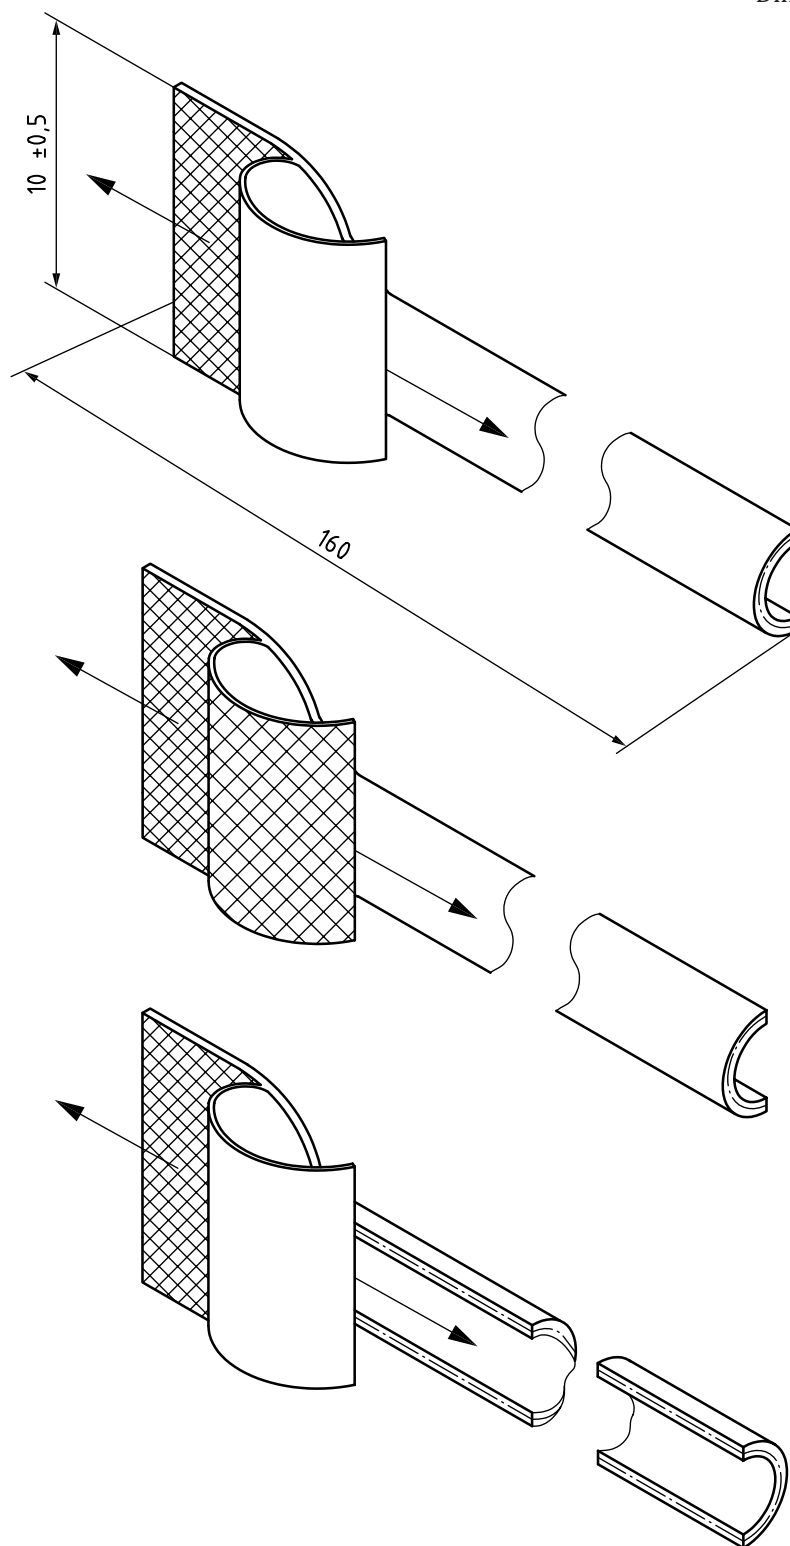


Figure 4 — Type 4 test piece

Dimensions in millimetres

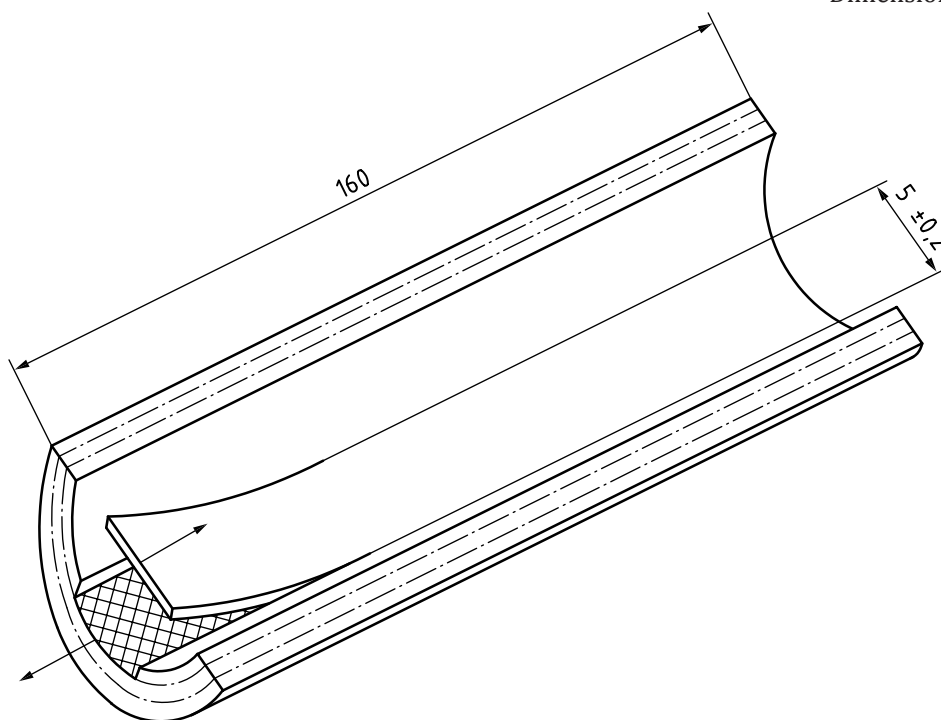


Figure 5 — Type 5 test piece

Dimensions in millimetres

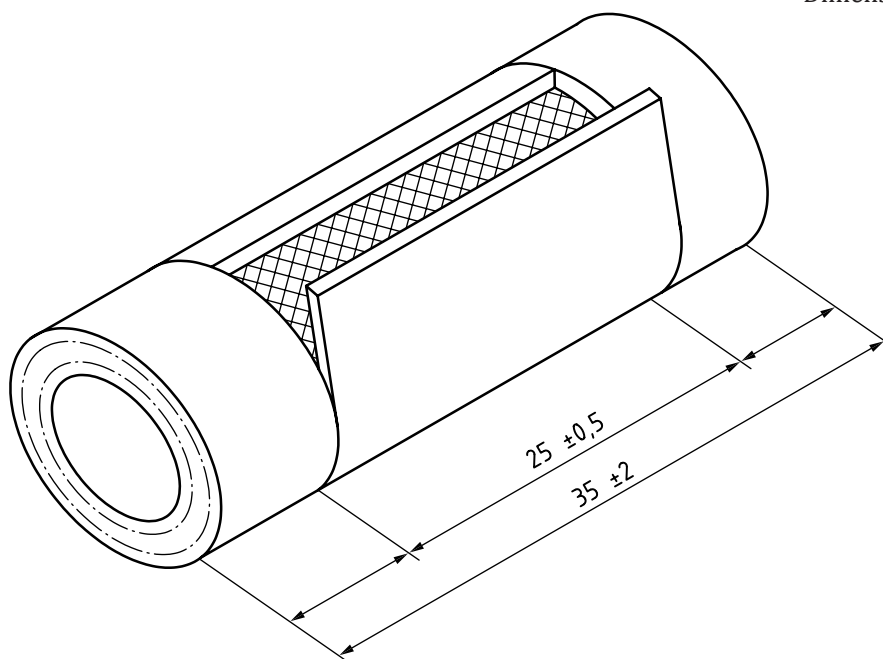


Figure 6 — Type 6 test piece

Dimensions in millimetres

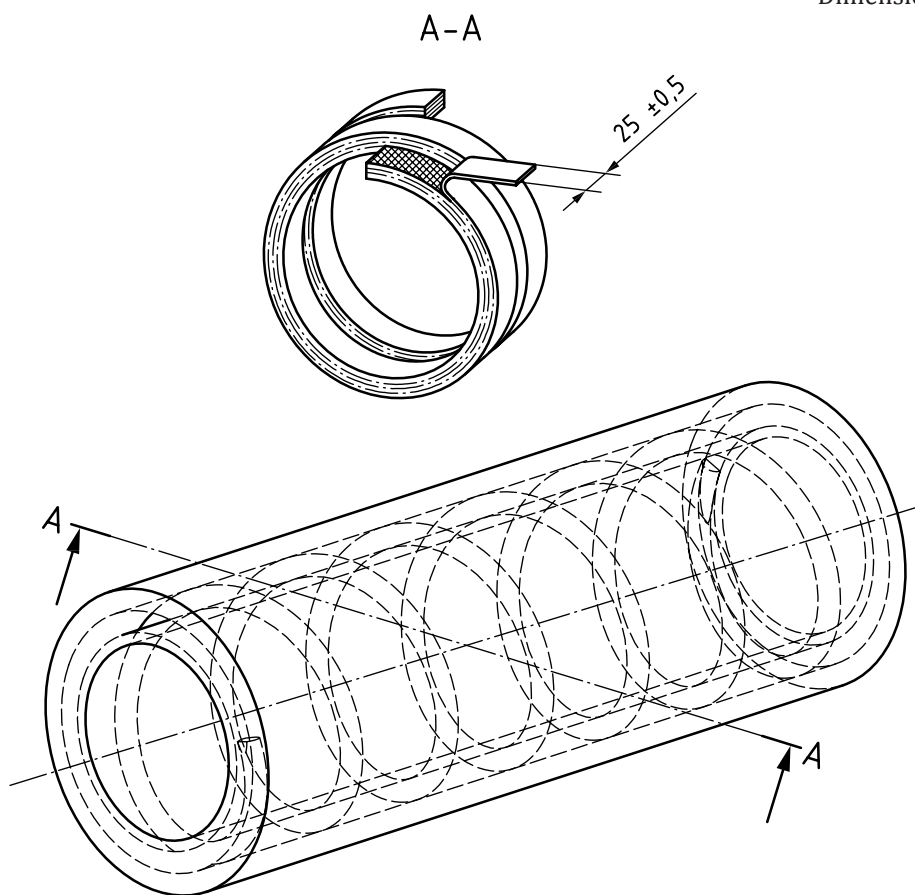


Figure 7 — Type 7 test piece for hoses containing a supporting helix

Dimensions in millimetres

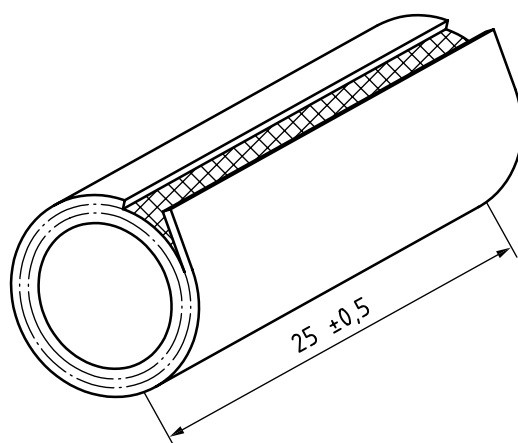


Figure 8 — Type 8 test piece

Bibliography

- [1] ISO 8330, *Rubber and plastics hoses and hose assemblies — Vocabulary*

British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at bsigroup.com/standards or contacting our Customer Services team or Knowledge Centre.

Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at bsigroup.com/shop, where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

Copyright in BSI publications

All the content in BSI publications, including British Standards, is the property of and copyrighted by BSI or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use.

Save for the provisions below, you may not transfer, share or disseminate any portion of the standard to any other person. You may not adapt, distribute, commercially exploit, or publicly display the standard or any portion thereof in any manner whatsoever without BSI's prior written consent.

Storing and using standards

Standards purchased in soft copy format:

- A British Standard purchased in soft copy format is licensed to a sole named user for personal or internal company use only.
- The standard may be stored on more than 1 device provided that it is accessible by the sole named user only and that only 1 copy is accessed at any one time.
- A single paper copy may be printed for personal or internal company use only.

Standards purchased in hard copy format:

- A British Standard purchased in hard copy format is for personal or internal company use only.
- It may not be further reproduced – in any format – to create an additional copy. This includes scanning of the document.

If you need more than 1 copy of the document, or if you wish to share the document on an internal network, you can save money by choosing a subscription product (see 'Subscriptions').

Reproducing extracts

For permission to reproduce content from BSI publications contact the BSI Copyright & Licensing team.

Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to bsigroup.com/subscriptions.

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

PLUS is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit bsigroup.com/shop.

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email subscriptions@bsigroup.com.

Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

Useful Contacts

Customer Services

Tel: +44 345 086 9001

Email (orders): orders@bsigroup.com

Email (enquiries): cservices@bsigroup.com

Subscriptions

Tel: +44 345 086 9001

Email: subscriptions@bsigroup.com

Knowledge Centre

Tel: +44 20 8996 7004

Email: knowledgecentre@bsigroup.com

Copyright & Licensing

Tel: +44 20 8996 7070

Email: copyright@bsigroup.com

BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK