



BSI Standards Publication

Preparation of steel substrates before application of paints and related products — Surface roughness characteristics of blast-cleaned steel substrates

Part 5: Replica tape method for the
determination of the surface profile
(ISO 8503-5:2017)

National foreword

This British Standard is the UK implementation of EN ISO 8503-5:2017. It supersedes BS EN ISO 8503-5:2004 which is withdrawn.

The UK participation in its preparation was entrusted to Technical Committee STI/21, Paint systems and surface preparation for metallic substrates.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© The British Standards Institution 2017.
Published by BSI Standards Limited 2017

ISBN 978 0 580 76136 2

ICS 25.220.10

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 31 March 2017.

Amendments/corrigenda issued since publication

Date	Text affected
------	---------------

EUROPEAN STANDARD

EN ISO 8503-5

NORME EUROPÉENNE

EUROPÄISCHE NORM

March 2017

ICS 25.220.10

Supersedes EN ISO 8503-5:2004

English Version

Preparation of steel substrates before application of paints
and related products - Surface roughness characteristics of
blast-cleaned steel substrates - Part 5: Replica tape
method for the determination of the surface profile (ISO
8503-5:2017)

Préparation des subjectiles d'acier avant application de
peintures et de produits assimilés - Caractéristiques de
rugosité des subjectiles d'acier décapés - Partie 5:
Méthode de l'empreinte sur ruban adhésif pour la
détermination du profil de surface (ISO 8503-5:2017)

Vorbereitung von Stahloberflächen vor dem Auftragen
von Beschichtungstoffen - Rauheitskenngrößen von
gestrahlten Stahloberflächen - Teil 5:
Abdruckverfahren zum Bestimmen der Rauheit (ISO
8503-5:2017)

This European Standard was approved by CEN on 3 February 2017.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN-CENELEC Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

CEN-CENELEC Management Centre: Avenue Marnix 17, B-1000 Brussels

European foreword

This document (EN ISO 8503-5:2017) has been prepared by Technical Committee ISO/TC 35 “Paints and varnishes” in collaboration with Technical Committee CEN/TC 139 “Paints and varnishes” the secretariat of which is held by DIN.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by September 2017, and conflicting national standards shall be withdrawn at the latest by September 2017.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN [and/or CENELEC] shall not be held responsible for identifying any or all such patent rights.

This document supersedes EN ISO 8503-5:2004.

According to the CEN-CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and the United Kingdom.

Endorsement notice

The text of ISO 8503-5:2017 has been approved by CEN as EN ISO 8503-5:2017 without any modification.

Contents		Page
Foreword		iv
Introduction		v
1 Scope		1
2 Normative references		1
3 Terms and definitions		1
4 Principle		1
5 Apparatus		2
6 Maintenance and assurance of calibration for the replica tape method		2
7 Procedure		3
8 Specification of acceptable error		3
9 Test report		3
Annex A (informative) Measurement errors associated with replica tape determination of profile height		5
Annex B (informative) Guidance on the correspondence between replica tape and ISO comparator determinations of profile height		6
Annex C (informative) Grades of replica tape		8
Annex D (informative) Service life and storage recommendations for replica tape		9
Bibliography		10

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT) see the following URL: www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 35, *Paints and varnishes*, Subcommittee SC 12, *Preparation of steel substrates before application of paints and related products*.

This second edition cancels and replaces the first edition (ISO 8503-5:2003), which has been technically revised.

A list of all parts in the ISO 8503 series can be found on the ISO website.

Introduction

The performance of protective coatings of paint and related products applied to steel is significantly affected by the state of the steel surface immediately prior to painting. The principal factors that are known to influence this performance are:

- a) the presence of rust and mill scale;
- b) the presence of surface contaminants, including salts, dust, oils and greases;
- c) the surface profile.

ISO 8501 (all parts), ISO 8502 (all parts) and ISO 8503 (all parts) have been prepared to provide methods of assessing these factors, while ISO 8504 (all parts) provides guidance on the preparation methods that are available for cleaning steel substrates, indicating the capabilities of each in attaining specified levels of cleanliness.

These International Standards do not contain recommendations for the protective coating systems to be applied to the steel surface. Neither do they contain recommendations for the surface quality requirements for specific situations, even though surface quality can have a direct influence on the choice of protective coating to be applied and on its performance. Such recommendations are found in other documents, such as national standards and codes of practice. It will be necessary for users of these International Standards to ensure that the qualities specified are:

- compatible and appropriate both for the environmental conditions to which the steel will be exposed and for the protective coating system to be used;
- within the capability of the cleaning procedure specified.

The International Standards referred to above deal with the following aspects of preparation of steel substrates:

- ISO 8501 — *Visual assessment of surface cleanliness*;
- ISO 8502 — *Tests for the assessment of surface cleanliness*;
- ISO 8503 — *Surface roughness characteristics of blast-cleaned steel substrates*;
- ISO 8504 — *Surface preparation methods*.

Each of these International Standards is in turn divided into separate parts.

It is important to note that numerical characterization of a surface profile is meaningful only when accompanied by an understanding of the errors of measurement and by the realization that different techniques may yield somewhat different numerical values for the profile. Estimates of measurement error associated with different techniques can be obtained from national or international standards or from the equipment manufacturers. As shown in [Annex B](#), values given by the replica tape method align well with those obtained using other parts of ISO 8503.

Information regarding the magnitude of errors associated with use of replica tape is given in [Annex A](#).

Advantages of the replica tape method include the fact that it affords numerical characterization, yields a permanent record, works well on curved surfaces and benefits from a geographically broad base of user experience over a period of several decades.

Preparation of steel substrates before application of paints and related products — Surface roughness characteristics of blast-cleaned steel substrates —

Part 5:

Replica tape method for the determination of the surface profile

1 Scope

This document describes a field method for measuring the surface profile produced by any of the abrasive blast-cleaning procedures given in ISO 8504-2. The method uses replica tape and a suitable gauge for measuring, on site, the roughness of a surface before the application of paint or another protective coating.

The method is applicable within the range of profile heights cited for a given grade (or thickness) of replica tape. The commercial grades currently available permit measurement of average peak-to-valley profiles of 20 µm to 115 µm. The method is valid for surfaces that have been cleaned with abrasives.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 4618, *Paints and varnishes — Terms and definitions*

ISO 8503-1, *Preparation of steel substrates before application of paints and related products — Surface roughness characteristics of blast-cleaned steel substrates — Part 1: Specifications and definitions for ISO surface profile comparators for the assessment of abrasive blast-cleaned surfaces*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 4618 and ISO 8503-1 apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- IEC Electropedia: available at <http://www.electropedia.org/>
- ISO Online browsing platform: available at <http://www.iso.org/obp>

4 Principle

The replica film in replica tape consists of a layer of crushable plastic microfoam coated onto a polyester substrate of highly uniform thickness ($50\ \mu\text{m} \pm 2\ \mu\text{m}$). When compressed against a hard surface, the microfoam collapses and acquires an impression of the surface. The thickness of the replica is a measure of the surface profile.

When the replica film is coated with a thin (80 nm) layer of a ductile and optically reflective metal, such as indium, the replicated surface can be studied with an optical interferometric profiler. When the film

is coated with a similarly thin layer of a ductile and electron-emissive metal, such as gold, platinum or palladium, the replica may be studied with an electron microscope.

NOTE This method measures an “average maximum peak-to-valley profile” because the anvils of the micrometer gauge flatten the replica profile slightly so that the reading equates to an average maximum value, though this is not the same as a mathematical average.

5 Apparatus

5.1 Replica tape, consisting of a square piece of replica film (measuring approximately 10 mm along each side) attached to adhesive-backed paper tape. The film shall be mounted over a hole (approximately 10 mm in diameter) in the centre of a section of the paper tape (approximately 53 mm × 19 mm in size), which is printed with the grade of tape and the corresponding range of profile heights.

NOTE Grades of replica tape are available for measurement of profiles between 20 µm and 64 µm (“Coarse” grade) and between 38 µm and 115 µm (“X-Coarse” grade). Additional grades permit checking measurements at or near the low (20 µm) and high (115 µm) ends of this range. See [Annex C](#).

The tape’s adhesive backing prevents movement of the replica film during the test and allows the sample identification and measured profile parameters to be recorded.

The crushed microfoam can be further compressed and should therefore be handled with care, especially when measuring its thickness.

5.2 Micrometer gauge, use a spring-loaded instrument specifically designed for use with replica tape, having a closing force of 1,0 N to 1,2 N and an accuracy of ±5 µm or better. The anvils shall be circular with the upper anvil (that touches the non-compressible polyester side of the replica film) having a diameter of 6,3 mm and the lower face being the same size or larger.

5.3 Compression tool, consisting of a hard, smooth, rounded, approximately spherical (nominal diameter 8 mm) surface that is used to compress the replica film against the surface to be measured. This tool sometimes takes the form of a rod with a compression ball at one end.

6 Maintenance and assurance of calibration for the replica tape method

Each component of the replica tape has its own storage life and effective operating temperature with the replica film being much more durable than the adhesive-backed paper tape.

Replica tape should be stored at room temperature, prolonged storage of replica tape outside the range 5 °C to 30 °C for more than two years is not recommended (see [Annex D](#)). Rolls of replica tape are marked with a batch number and date of manufacture. Both should be noted in the test report.

The measuring gauge, while rugged, should be treated with the usual level of care associated with a precision instrument.

The gauge shall be calibrated regularly (e.g. by the equipment manufacturer, their authorized agent or by an accredited calibration laboratory). A certificate of calibration showing traceability to a national measurement standard can be issued. There is no standard time interval for re-calibration, nor is one absolutely required, but a calibration interval can be established based on experience and the work environment. A one-year calibration interval is a typical frequency suggested by many gauge manufacturers.

Gauge accuracy shall then be checked by the operator at regular intervals using appropriate standards in accordance with the manufacturer’s instructions. If the results fall outside the limits of accuracy specified by the manufacturer, the instrument shall not be used.

Information on the correlation of ISO comparator measurements with those obtained by replica tape is given in [Annex B](#).

7 Procedure

Select a representative area of the surface for measurement.

Select a grade (thickness) of replica tape that includes the target profile.

Prepare the micrometer gauge by cleaning the anvils and adjusting the zero point to read $-50,8 \mu\text{m}$, the thickness of the non-compressible polyester substrate. This initial adjustment automatically subtracts the thickness of the substrate from all subsequent readings. Some digital micrometers automatically perform this initial adjustment.

Remove a single piece of replica tape from its release paper. Apply it to the blast-cleaned surface and rub the compression tool (5.3) over the replica film in the centre of the tape, using firm pressure, with a circular and/or x-y motion until the circular area of the replica tape is darkened uniformly.

Remove the tape from the surface and place the replica between the anvils of the measuring gauge, making sure that the tape is centred properly. Release the measuring gauge gently onto the replica and read the profile.

The average of two profile readings constitutes a profile measurement. Manufacturer recommendations provide guidance on whether these two readings should be obtained with the same grade or two different grades.

The number of measurements shall be agreed between the interested parties.

Before the surface under test is measured, the accuracy of this method may be checked by measuring a known profile, such as an ISO comparator.

NOTE The same procedure is used for measuring gauges that read in non-SI units, such as mil or thou (thousandths of an inch; 1 mil or thou approximately $25,4 \mu\text{m}$). Gauges calibrated in non-SI units are supplied with instructions appropriate to those units.

8 Specification of acceptable error

An essential part of any specification relating to surface profile is an explicit statement of how the surface profile was determined. Implicit in this specification is an understanding of both the precision and the accuracy associated with a given method of measuring the profile. A discussion of error associated with replica tape measurements is given in [Annex A](#).

The number of readings to be taken and the range of acceptable profiles shall be agreed between the interested parties before measurement starts.

9 Test report

The test report shall contain at least the following information:

- a) all the information needed for the identification of the sample tested;
- b) a reference to this document, including its year of publication, i.e. ISO 8503-5:2017;
- c) replica tape batch number and date of manufacture;
- d) measured profiles and location of measurement;
- e) micrometer calibration date and record of most recent micrometer accuracy check;
- f) the work site identification and project name (if applicable);
- g) the date of the test;
- h) the name of the operator;

- i) any deviations from the procedure;
- j) any unusual features observed.

Annex A (informative)

Measurement errors associated with replica tape determination of profile height

In 1987, a panel of experts convened by NACE International (formerly National Association of Corrosion Engineers) investigated the measurement properties of replica tape. NACE/Standard RP0287 addressed the issue of repeatability and accuracy of measurement and reported the results of round-robin tests in which 14 blasted panels were measured by seven observers. Replica tape and focusing microscope measurements agreed within their 95 % confidence limits (two standard deviations) in 11 of 14 cases. The average difference between the two types of measurement technique was 4,5 μm . It should be noted that some difference is to be expected, based on the fact that the techniques have differing maximum peak-to-valley evaluation distances, evaluation areas and approaches to averaging. This is further discussed in [Annex B](#).

The standard deviation for measurements made by the seven observers, averaged over all 14 panels, was 5,4 μm . The standard deviation for the corresponding focusing microscope profile determinations, averaged over all 14 panels, was 8,1 μm . Confidence intervals comprising two standard deviations (95 % confidence) are commonly specified. A standard deviation of 5,4 μm implies that a single replica tape measurement, by an arbitrary observer, has a 95 % probability of lying within 10,8 μm (two standard deviations) of the nominal replica tape profile.

More recent tests (2011) conducted by ASTM International are generally supportive of the error assessment arrived at by NACE. Measurements were obtained for five test surfaces having profiles in the range 33 μm to 107 μm by investigators at 11 laboratories. Analysis of the resulting data indicate a one standard deviation measurement reproducibility of 3 μm to 6 μm . Manufacturer tests in the 38 μm to 64 μm grade range overlap region suggest a somewhat lower accuracy in this range.

Annex B (informative)

Guidance on the correspondence between replica tape and ISO comparator determinations of profile height

B.1 Replica tape

A single replica tape measurement samples a circular patch 6,3 mm in diameter and 31 mm² in area. Flexing of the polyester substrate and the curvature of the compression ball cause the film to conform to the surface over distances greater than 0,4 mm. Within patches smaller than approximately 0,4 mm, the portion of the ball pressing the film against the surface is effectively flat. These patches constitute the sampling area for individual maximum peak-to-valley determinations. In fact, the evaluation areas overlap so there is multi-patch correlation and the sampling process is somewhat more complex. A measurement using the micrometer gauge approximates the average maximum peak-to-valley heights over all the sampling areas in the 31 mm² area evaluated.

B.2 Focusing microscope


A single maximum peak-to-valley measurement using a focusing microscope covers a sampling region with a diameter of 0,5 mm and an area of approximately 0,2 mm². Taking the average of the maximum peak-to-valley distances from 20 of these regions, as specified in ISO 8503-3, gives a total evaluation area of approximately 4 mm².

B.3 Stylus device

The sampling length for this method, i.e. the distance over which individual maximum peak-to-valley distances are measured, is 2,5 mm and there are five such lengths in a single traverse of the stylus. For a stylus point with a diameter of 10 µm, the area evaluated on each traverse will be 0,125 mm². Taking the average of the maximum peak-to-valley distances from (a minimum of) 10 traverses, as specified in ISO 8503-4, gives 50 sampling lengths with a total area of 1,25 mm².

B.4 Comparison of different methods

A comparison of profile readings obtained using various ISO methods is given in [Figure B.1](#).

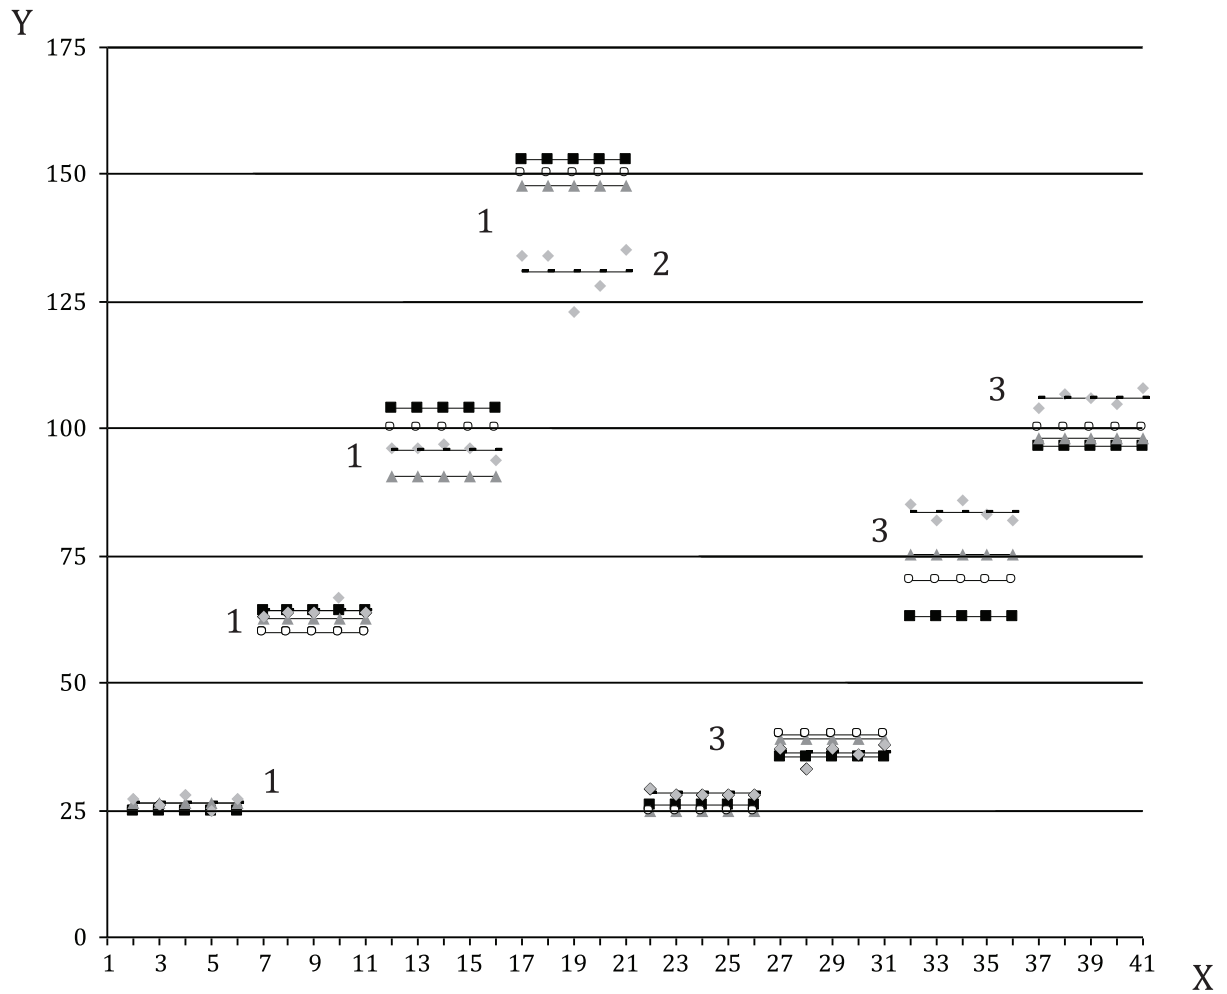

Key

- X measurement No.
- Y profile (μm)
- ◆ replica tape measurements
- replica tape averages
- comparator (nominal spec)
- comparator (microscope)
- ▲ comparator (stylus)
- 1 grit-blasted surfaces
- 2 upper limit for XC replica tape
- 3 shot-blasted surfaces

Figure B.1 — Comparison of profile readings using various ISO methods

Annex C (informative)

Grades of replica tape

The replica tape method is useful for measurement of profile in the 20 µm to 115 µm range. The low end of this range is covered by “Coarse” grade tape; the high end by “X-Coarse” grade, where the term “grade” refers to the thickness of the plastic foam that acquires the impression. “Coarse Minus” and “X-Coarse Plus” grades also exist but are recommended for use *only* to check measurements at the low and high end, respectively, of the 20 µm to 115 µm primary range.

[Table C.1](#) describes these grades.

Table C.1 — Description of grades

Grade description	Nominal foam thickness µm	Measurement range µm	Comment
“Medium”	10	Not Applicable	Measureable only with special instruments
“Coarse Minus”	38	12 to 25	Low end check grade
“Coarse”	75	20 to 64	Lower end of primary measurement range
“X-Coarse”	140	38 to 115	Upper end of primary measurement range
“X-Coarse Plus”	175	116 to 127	High end check grade

Annex D (informative)

Service life and storage recommendations for replica tape

Testing has shown that replica film is able to produce accurate replicas on surfaces with temperatures over at least the range between -10 °C and $+60\text{ °C}$. At typical room temperatures, it is believed that replicas will store well for years, while uncompressed film may be stored for decades. No failures to uncompressed film have been recorded, despite prolonged storage, at temperatures over the range between 5 °C to 30 °C .

By contrast, the adhesive backing on the paper tape can deteriorate with time. The effect of adhesion failure is that the replica film can slide with respect to the surface being replicated when the film is rubbed for the purpose of compressing it. Sliding will cause “smearing” of the replica. If sliding is observed during the replication process, the replica should be discarded and the adhesive considered suspect.

Bibliography

- [1] ISO 8503-3, *Preparation of steel substrates before application of paints and related products — Surface roughness characteristics of blast-cleaned steel substrates — Part 3: Method for the calibration of ISO surface profile comparators and for the determination of surface profile — Focusing microscope procedure*
- [2] ISO 8503-4, *Preparation of steel substrates before application of paints and related products — Surface roughness characteristics of blast-cleaned steel substrates — Part 4: Method for the calibration of ISO surface profile comparators and for the determination of surface profile — Stylus instrument procedure*
- [3] ISO 8504-2, *Preparation of steel substrates before application of paints and related products — Surface preparation methods — Part 2: Abrasive blast-cleaning*

British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at bsigroup.com/standards or contacting our Customer Services team or Knowledge Centre.

Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at bsigroup.com/shop, where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

Copyright in BSI publications

All the content in BSI publications, including British Standards, is the property of and copyrighted by BSI or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use.

Save for the provisions below, you may not transfer, share or disseminate any portion of the standard to any other person. You may not adapt, distribute, commercially exploit, or publicly display the standard or any portion thereof in any manner whatsoever without BSI's prior written consent.

Storing and using standards

Standards purchased in soft copy format:

- A British Standard purchased in soft copy format is licensed to a sole named user for personal or internal company use only.
- The standard may be stored on more than 1 device provided that it is accessible by the sole named user only and that only 1 copy is accessed at any one time.
- A single paper copy may be printed for personal or internal company use only.

Standards purchased in hard copy format:

- A British Standard purchased in hard copy format is for personal or internal company use only.
- It may not be further reproduced – in any format – to create an additional copy. This includes scanning of the document.

If you need more than 1 copy of the document, or if you wish to share the document on an internal network, you can save money by choosing a subscription product (see 'Subscriptions').

Reproducing extracts

For permission to reproduce content from BSI publications contact the BSI Copyright & Licensing team.

Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to bsigroup.com/subscriptions.

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

PLUS is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit bsigroup.com/shop.

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email subscriptions@bsigroup.com.

Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

Useful Contacts

Customer Services

Tel: +44 345 086 9001

Email (orders): orders@bsigroup.com

Email (enquiries): cservices@bsigroup.com

Subscriptions

Tel: +44 345 086 9001

Email: subscriptions@bsigroup.com

Knowledge Centre

Tel: +44 20 8996 7004

Email: knowledgecentre@bsigroup.com

Copyright & Licensing

Tel: +44 20 8996 7070

Email: copyright@bsigroup.com

BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK