

Soft soldering fluxes — Test methods —

Part 2: Determination of non-volatile matter, ebulliometric method

The European Standard EN ISO 9455-2:1995 has the status of a
British Standard

ICS 25.160.20; 25.160.50

UDC 621.791.35.048:543.714

Committees responsible for this British Standard

The preparation of this British Standard was entrusted to Technical Committee NFE/27, Tin and tin alloys, upon which the following bodies were represented:

Association of British Pewter Craftsmen
British Iron and Steel Producers' Association
Federation of the Electronics Industry
International Tin Research Institute
London Metal Exchange
Metal Packaging Manufacturers' Association
Solder Makers' Association
Co-opted members

The following bodies were also represented in the drafting of the standard, through subcommittees and panels.

British Plumbing Fittings Manufacturers' Association
Institute of Metal Finishing
Ministry of Defence
Co-opted members

This British Standard, having been prepared under the direction of the Engineering Sector Board, was published under the authority of the Standards Board and comes into effect on 15 February 1996

© BSI 01-2000

The following BSI references relate to the work on this standard:
Committee reference NFE/27
Draft for comment 92/38567 DC

ISBN 0 580 25229 9

Amendments issued since publication

Amd. No.	Date	Comments

Contents

	Page
Committees responsible	Inside front cover
National foreword	ii
<hr/>	
Foreword	2
1 Scope	3
2 Normative references	3
3 Principle	3
4 Apparatus	3
5 Procedure	3
6 Calculation of results	3
7 Precision	4
8 Test report	4
<hr/>	
Annex A (informative) Method for the preparation of standard reference rosin (colophony) based liquid fluxes, having 25 % (<i>m/m</i>) non-volatile content	7
Annex ZA (normative) Normative references to international publications with their relevant European publications	8
<hr/>	
Figure 1 — Martin ebulliometer with spherical distillation mask	5
Figure 2 — Typical distillation curve	6
<hr/>	
List of references	Inside back cover
<hr/>	

National foreword

This British Standard has been prepared by Technical Committee NFE/27 and is the English language version of EN ISO 9455-2:1995 *Soft soldering fluxes — Test methods — Part 2: Determination of non-volatile matter, ebulliometric method*, published by the European Committee for Standardization (CEN).

EN ISO 9455-2 is identical with ISO 9455-2:1993, published by the International Organization for Standardization (ISO).

Cross-references

Publication referred to	Corresponding British Standard
ISO 4791-1:1985	BS 6711 <i>Vocabulary relating to laboratory apparatus made essentially from glass, porcelain or vitreous silica</i> Part 1:1986 <i>Names for items of apparatus</i>
EN 29454-1:1993 (ISO 9454-1:1990)	BS EN 29454 <i>Soft soldering fluxes — Classification and requirements</i> Part 1:1994 <i>Classification, labelling and packaging</i>
IEC 68-2-20:1979	BS 2011 <i>Environmental testing</i> Part 2.1 <i>Tests</i> Part 2.1T:1981 <i>Test T. Soldering</i>

A British Standard does not purport to include all the necessary provisions of a contract. Users of British Standards are responsible for their correct application.

Compliance with a British Standard does not of itself confer immunity from legal obligations.

Summary of pages

This document comprises a front cover, an inside front cover, pages i and ii, the EN ISO title page, pages 2 to 8, an inside back cover and a back cover.

This standard has been updated (see copyright date) and may have had amendments incorporated. This will be indicated in the amendment table on the inside front cover.

ICS 25.160.20; 25.160.50

Descriptors: Soldering, soldering fluxes, tests, determination of content, non volatile matter, evaporation analysis

English version

Soft soldering fluxes — Test methods —
Part 2: Determination of non-volatile matter,
ebulliometric method

(ISO 9455-2:1993)

Flux de brasage tendre — Méthodes d'essai —
Partie 2: Dosage des matières non volatiles
par ébulliométrie
(ISO 9455-2:1993)

Flußmittel zum Weichlöten —
Prüfverfahren —
Teil 2: Bestimmung nichtflüchtiger Stoffe,
ebulliometrische Methode
(ISO 9455-2:1993)

This European Standard was approved by CEN on 1995-08-27. CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration.

Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Central Secretariat or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Central Secretariat has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and United Kingdom.

CEN

European Committee for Standardization
Comité Européen de Normalisation
Europäisches Komitee für Normung

Central Secretariat: rue de Stassart 36, B-1050 Brussels

Foreword

The text of the International Standard from ISO/TC 44, Welding and allied processes, of the International Organization for Standardization (ISO) has been taken over as a European Standard by the Technical Committee CEN/TC 121, Welding.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by March 1996, and conflicting national standards shall be withdrawn at the latest by March 1996.

According to the CEN/CENELEC Internal Regulations, the following countries are bound to implement this European Standard: Austria, Belgium, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland, United Kingdom.

NOTE Normative references to International Standards are listed in Annex ZA (normative).

1 Scope

This part of ISO 9455 specifies an ebulliometric method for the determination of the content of non-volatile matter in soft soldering fluxes. It is applicable to liquid fluxes of classes 1.1.1, 1.1.2 and 1.1.3, as defined in ISO 9454-1, and only those fluxes containing solvents of relatively high volatility, such as propan-2-ol. The method is applicable only to fluxes with a non-volatile content of 10 % or more.

NOTE 1 For the determination of the content of non-volatile matter of liquid fluxes of these classes, where the solvent has a lower volatility than propan-2-ol, the method given in ISO 9455-1 should be used.

2 Normative references

The following standards contain provisions which, through reference in this text, constitute provisions of this part of ISO 9455. At the time of publication, the editions indicated were valid. All standards are subject to revision, and parties to agreements based on this part of ISO 9455 are encouraged to investigate the possibility of applying the most recent editions of the standards indicated below. Members of IEC and ISO maintain registers of currently valid International Standards.

ISO 4791-1:1985, *Laboratory apparatus — Vocabulary relating to apparatus made essentially from glass, porcelain or vitreous silica — Part 1: Names for items of apparatus.*

ISO 9454-1:1990, *Soft soldering fluxes — Classification and requirements — Part 1: Classification, labelling and packaging.*

IEC 68-2-20:1979, *Environmental testing — Part 2: Tests — Test T: Soldering.*

3 Principle

A weighed amount of the flux sample is evaporated in an ebullimeter until the entire volatile part is driven off, which is determined by following the graph of distillation temperature against time. The flux residue is considered as the non-volatile content of flux.

4 Apparatus

Usual laboratory apparatus and, in particular, the following.

4.1 Martin ebullimeter (ISO 4791-1:1985, 5.04.10), but with a spherical distillation flask, as shown in Figure 1.

NOTE 2 It has been found that better heat exchange characteristics are obtained between the heater and the distillation flask if a spherical flask is used rather than the pear-shaped flask normally supplied with the Martin ebullimeter.

4.2 Thermostatically controlled heater, suitable for heating the distillation flask of the ebullimeter.

4.3 Laboratory thermometer, covering the range 50 °C to 150 °C with 0,5 °C graduations, for use with the ebullimeter.

NOTE 3 A corrosion-resistant thermocouple, connected to a digital indicator, or recorder, may be used in place of the laboratory thermometer.

4.4 Laboratory balance, accurate to 0,1 mg.

5 Procedure

Carry out the following procedure in duplicate.

All the glass apparatus used shall be clean and dry. Remove the distillation flask from the Martin ebullimeter (4.1) and weigh it to the nearest 0,001 g. Introduce between 40 g and 50 g of the flux sample into the flask and re-weigh the flask to the nearest 0,001 g. This weighing shall be carried out quickly, so as to avoid loss of solvent by evaporation.

Attach the flask to the ebullimeter and fit the thermometer, or thermocouple, (4.3) as shown in Figure 1, through a new rubber plug in the top of the distillation column.

Adjust the thermometer or thermocouple height so that its tip is on a level with the entry of the cross tube leading to the condenser. Turn on the water in the condenser. Turn the heater on. When the flux begins to boil, regulate the heat so as to collect the condensate at the rate of 1 drop per second for the first millilitre and 2 drops per second thereafter.

Record the temperature and time at approximately 2 min intervals and plot the distillation curve (temperature versus time) during the course of the distillation. A typical distillation curve is given in Figure 2.

NOTE 4 This curve may be obtained directly if a thermocouple (see 4.3) is used and connected to a suitable recorder.

Stop the distillation when the temperature drops back to 75 °C. Remove the distillation flask immediately and put it into a desiccator while it cools down to room temperature. Weigh the distillation flask containing the non-volatile residue.

6 Calculation of results

The non-volatile matter content for each determination, in % (*m/m*), is equal to

$$\frac{(P_3 - P_1)}{(P_2 - P_1)} \times 100$$

where

P_1 is the mass, in grams, of the empty distillation flask;

P_2 is the mass, in grams, of the flask and the flux sample;

P_3 is the mass, in grams, of the flask and the non-volatile residue.

The values calculated for the duplicate determinations on the flux sample should not differ by more than 0,2 % (*m/m*).

Calculate the mean of the two results, to obtain the result for the non-volatile matter content of the flux sample.

NOTE 5 The experimental technique may be verified by carrying out the procedure given in clause 5 on a standard flux, containing 25 % (*m/m*) non-volatile content, prepared as described in Annex A.

7 Precision

Interlaboratory tests were carried out on three fluxes containing non-volatile matter within the range 18 % (*m/m*) to 26 % (*m/m*). Six laboratories took part in the tests and the estimates for precision data, expressed as % (*m/m*) non-volatile matter, were as follows:

Standard deviations

— within laboratory s_w 0,32

— between laboratories s_b 1,29


Repeatability r 0,9

Reproducibility R 3,6

8 Test report

The test report shall include the following information:

- a) identification of the test sample;
- b) the test method used (i.e. reference to this part of ISO 9455);
- c) the results obtained;
- d) any unusual features noted during the determination;
- e) details of any operation not included in this part of ISO 9455, or regarded as optional.

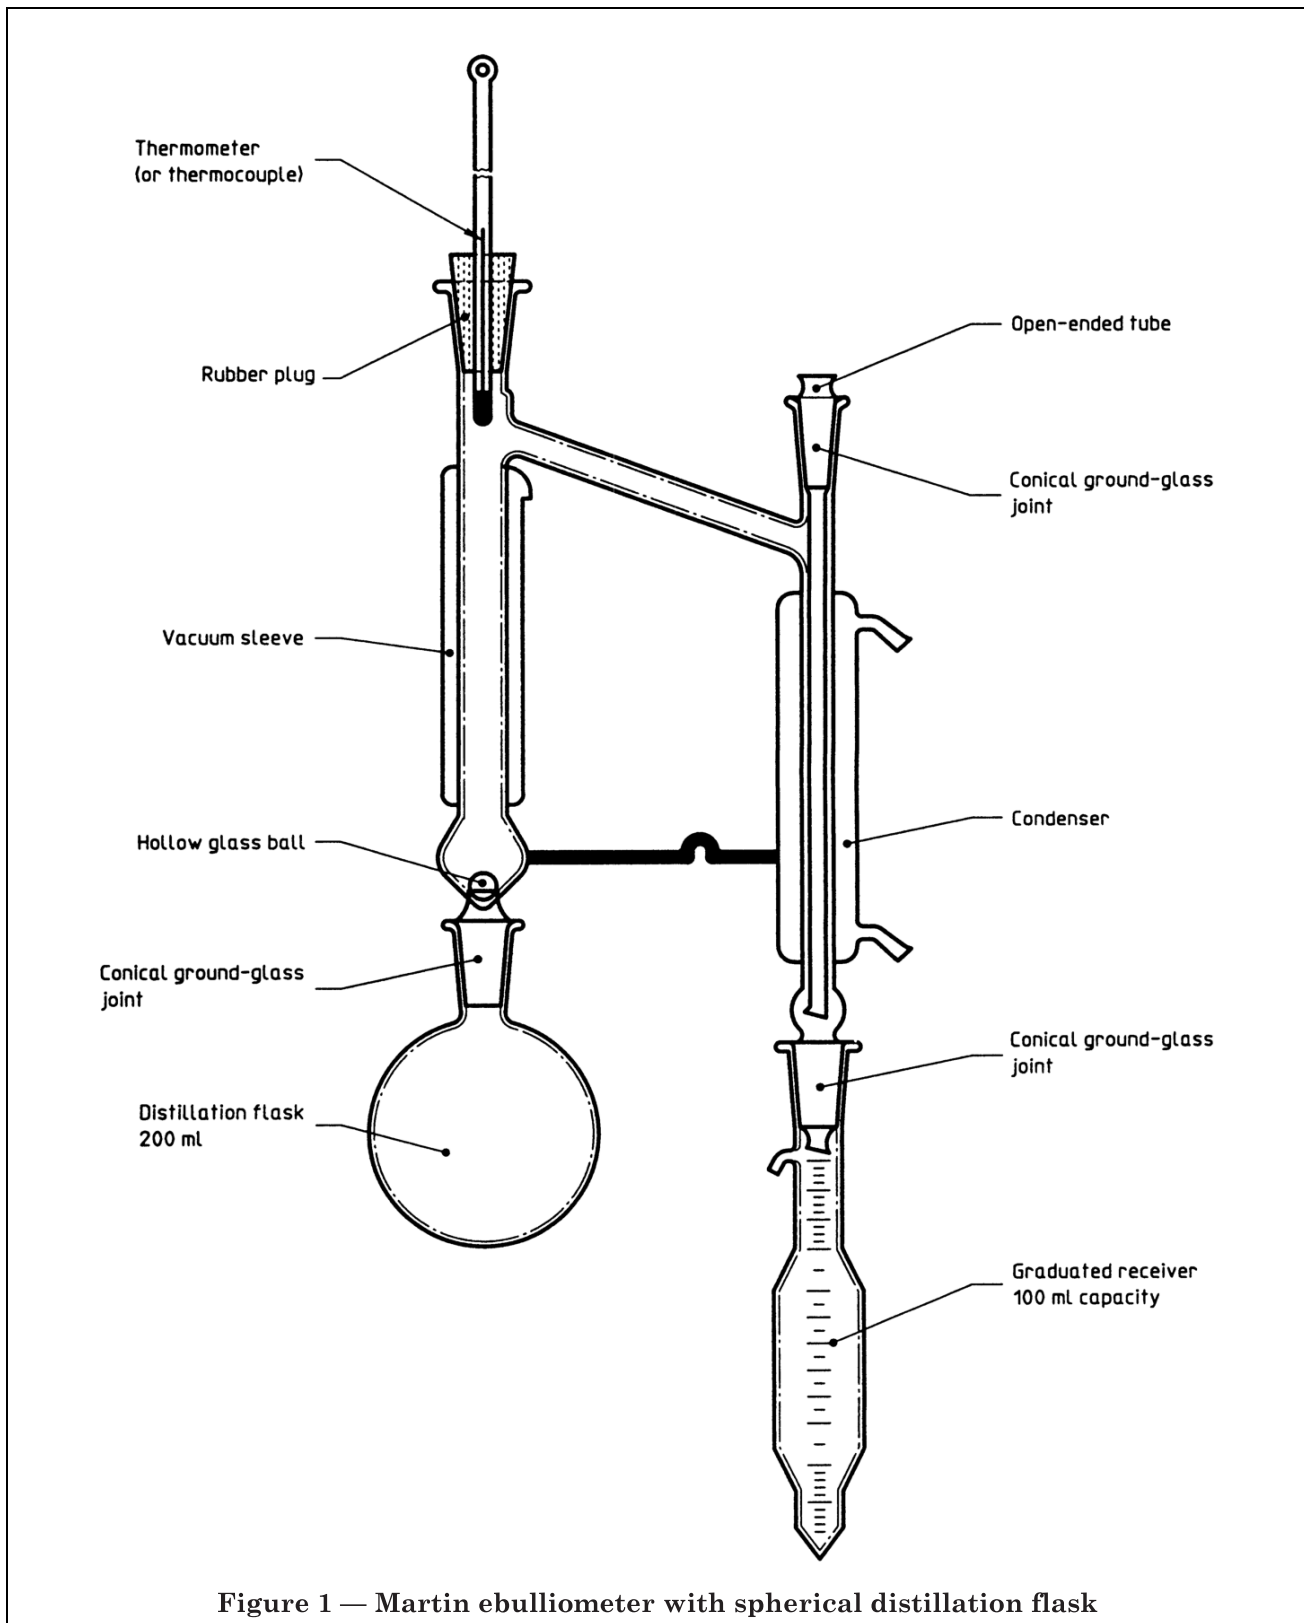

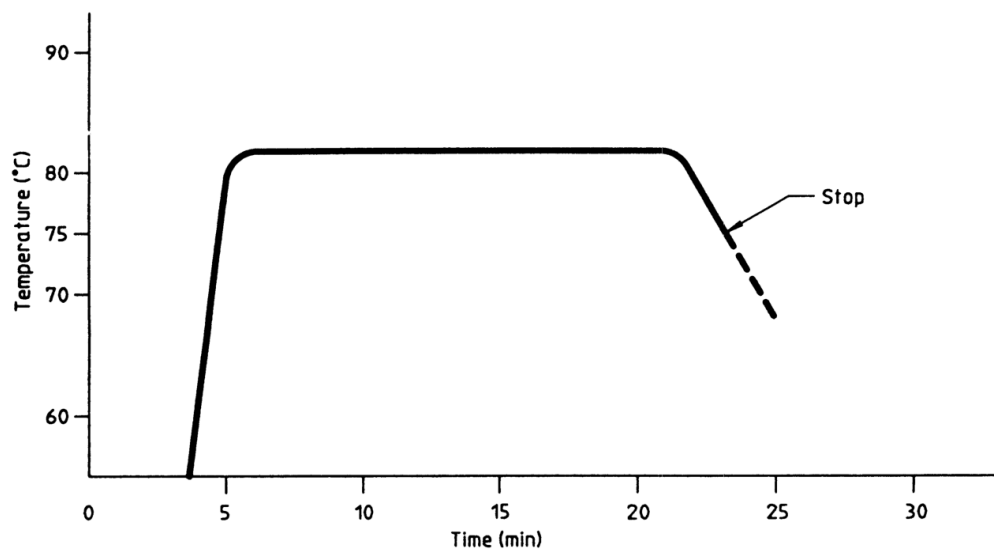


Figure 2 — Typical distillation curve

Annex A (informative)

Method for the preparation of standard reference rosin (colophony) based liquid fluxes, having 25 % (m/m) non-volatile content

A.1 General

This annex gives a method for the preparation of two standard rosin (colophony) based liquid fluxes having 25 % (m/m) non-volatile content, one non-activated and the other halogen-activated (i.e. being respectively class 1.1.1.A and class 1.1.2.A, as defined in ISO 9454-1). The specifications for the flux constituents are based on IEC 68-2-20:1979, Appendix C.

The standard flux may be used by a laboratory to verify its experimental procedure, in the method for the determination of non-volatile content, described in the main body of this part of ISO 9455.

A.2 Principle

The non-activated flux is prepared by dissolving a special grade of rosin (colophony) in propan-2-ol. The halogen-activated flux is prepared in a similar way, with the addition of diethylamine hydrochloride.

A.3 Apparatus

Usual laboratory apparatus and, in particular, the following.

A.3.1 *Oven*, capable of being maintained at $110\text{ °C} \pm 2\text{ °C}$.

A.4 Reagents

Use only reagents of recognized analytical grade.

A.4.1 *Gum rosin (colophony)*, water-white grade or equivalent, having the following properties:

Acid value:	155 mg KOH/g to 180 mg KOH/g
Softening point:	70 °C minimum
Flow point:	76 °C minimum
Ash:	0,05 % maximum
Solubility:	To give clear 1 + 1 solution in propan-2-ol

A.4.2 *Diethylamine hydrochloride*, dried for 2 h at $110\text{ °C} \pm 2\text{ °C}$.

A.4.3 *Propan-2-ol*, having the following composition:

Propan-2-ol:	99,5 % (m/m) minimum
Acid content:	0,002 % (m/m) maximum
Non-volatile content:	0,2 % (m/m) maximum

A.5 Procedure

A.5.1 *Non-activated rosin (colophony)*

Weigh $25\text{ g} \pm 0,1\text{ g}$ of rosin (A.4.1) and dissolve it with gentle mixing in $75\text{ g} \pm 0,1\text{ g}$ of propan-2-ol (A.4.3).

A.5.2 *Halogen-activated rosin (colophony)*

Weigh $0,39\text{ g} \pm 0,01\text{ g}$ of diethylamine hydrochloride (A.4.2) and dissolve it in $75\text{ g} \pm 0,1\text{ g}$ of propan-2-ol (A.4.3). Then add $25\text{ g} \pm 0,1\text{ g}$ of rosin (A.4.1) and dissolve it with gentle mixing. This flux solution contains 0,5 % (m/m) of active chloride.

A.6 Storage

The standard flux solutions, prepared as described in A.5 must be stored in a container, properly closed at all times, away from heat or extreme cold.

Annex ZA (normative)**Normative references to international publications with their relevant European publications**

This European Standard incorporates by dated or undated reference, provisions from other publications. These normative references are cited at the appropriate places in the text and the publications are listed hereafter. For dated references, subsequent amendments to or revisions of any of these publications apply to this European Standard only when incorporated in it by amendment or revision. For undated references the latest edition of the publication referred to applies (including amendments).

Publication	Year	Title	EN/HD	Year
ISO 9454-1	1990	<i>Soft soldering fluxes — Classification and requirements — Part 1: Classification, labelling and packaging</i>	EN 29454-1	1993

List of references

See national foreword.

BSI — British Standards Institution

BSI is the independent national body responsible for preparing British Standards. It presents the UK view on standards in Europe and at the international level. It is incorporated by Royal Charter.

Revisions

British Standards are updated by amendment or revision. Users of British Standards should make sure that they possess the latest amendments or editions.

It is the constant aim of BSI to improve the quality of our products and services. We would be grateful if anyone finding an inaccuracy or ambiguity while using this British Standard would inform the Secretary of the technical committee responsible, the identity of which can be found on the inside front cover.
Tel: 020 8996 9000. Fax: 020 8996 7400.

BSI offers members an individual updating service called PLUS which ensures that subscribers automatically receive the latest editions of standards.

Buying standards

Orders for all BSI, international and foreign standards publications should be addressed to Customer Services. Tel: 020 8996 9001. Fax: 020 8996 7001.

In response to orders for international standards, it is BSI policy to supply the BSI implementation of those that have been published as British Standards, unless otherwise requested.

Information on standards

BSI provides a wide range of information on national, European and international standards through its Library and its Technical Help to Exporters Service. Various BSI electronic information services are also available which give details on all its products and services. Contact the Information Centre.
Tel: 020 8996 7111. Fax: 020 8996 7048.

Subscribing members of BSI are kept up to date with standards developments and receive substantial discounts on the purchase price of standards. For details of these and other benefits contact Membership Administration.
Tel: 020 8996 7002. Fax: 020 8996 7001.

Copyright

Copyright subsists in all BSI publications. BSI also holds the copyright, in the UK, of the publications of the international standardization bodies. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI.

This does not preclude the free use, in the course of implementing the standard, of necessary details such as symbols, and size, type or grade designations. If these details are to be used for any other purpose than implementation then the prior written permission of BSI must be obtained.

If permission is granted, the terms may include royalty payments or a licensing agreement. Details and advice can be obtained from the Copyright Manager.
Tel: 020 8996 7070.