

Approval testing of welders — Fusion welding —

**Part 5: Titanium and titanium alloys,
zirconium and zirconium alloys**

The European Standard EN ISO 9606-5:2000 has the status of a
British Standard

ICS 25.160.10



050928041106

National foreword

This British Standard is the official English language version of EN ISO 9606-5:2000. It is identical with ISO 9606-5:1999.

The UK participation in its preparation was entrusted to Technical Committee WEE/36, Approval testing of welding procedures and welders, which has the responsibility to:

- aid enquirers to understand the text;
- present to the responsible international/European committee any enquiries on the interpretation, or proposals for change, and keep the UK interests informed;
- monitor related international and European developments and promulgate them in the UK.

A list of organizations represented on this committee can be obtained on request to its secretary.

Cross-references

Attention is drawn to the fact that CEN and CENELEC Standards normally include an annex which lists normative references to international publications with their corresponding European publications. The British Standards which implement these international or European publications may be found in the BSI Standards Catalogue under the section entitled "International Standards Correspondence Index", or by using the "Find" facility of the BSI Standards Electronic Catalogue.

A British Standard does not purport to include all the necessary provisions of a contract. Users of British Standards are responsible for their correct application.

Compliance with a British Standard does not of itself confer immunity from legal obligations.

Summary of pages

This document comprises a front cover, an inside front cover, the EN ISO title page, pages 2 to 21 and a back cover.

The BSI copyright notice displayed in this document indicates when the document was last issued.

This British Standard, having been prepared under the direction of the Engineering Sector Committee, was published under the authority of the Standards Committee and comes into effect on 15 April 2000

© BSI 04-2000

ISBN 0 580 35681 7

Amendments issued since publication

Amd. No.	Date	Comments

English version

Approval testing of welders - Fusion welding - Part 5: Titanium
and titanium alloys, zirconium and zirconium alloys (ISO 9606-
5:2000)

Epreuve de qualification des soudeurs - Soudage par
fusion - Partie 5: Titane et ses alliages, zirconium et ses
alliages (ISO 9606-5:2000)

Prüfung von Schweißern - Schmelzschweißen - Teil 5:
Titan und Titanlegierungen, Zirkonium und
Zirkoniumlegierungen (ISO 9606-5:2000)

This European Standard was approved by CEN on 29 October 1999.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Central Secretariat or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Central Secretariat has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

Central Secretariat: rue de Stassart, 36 B-1050 Brussels

Contents

	Page
Foreword	3
Introduction	4
1 Scope	4
2 Normative references	4
3 Terms and definitions	5
4 Symbols and abbreviations	5
4.1 General	5
4.2 Test piece	5
4.3 Consumables	5
4.4 Miscellaneous	5
5 Essential variables for approval testing	5
5.1 General	5
5.2 Welding processes	6
5.3 Joint types (butt and fillet welds)	6
5.4 Material groups	6
5.5 Consumables	6
5.6 Dimensions	6
5.7 Number of test pieces	6
5.8 Welding positions	7
6 Range of approval for the welder	7
6.1 General	7
6.2 Welding process	7
6.3 Joint types	7
6.4 Material groups (according to CR 12187)	8
6.5 Consumables	9
6.6 Dimensions	9
6.7 Welding positions	9
7 Examination and testing	11
7.1 Supervision	11
7.2 Shapes and dimensions of test pieces	11
7.3 Welding conditions	12
7.4 Test methods	12
7.5 Test piece and test specimens	13
8 Acceptance requirements for test pieces	15
9 Re-tests	15
10 Period of validity	16
10.1 Initial approval	16
10.2 Prolongation	16
11 Certificate	16
12 Designation	16
Annex A (informative) Job knowledge	18
Annex ZA (informative) Bibliography	20
Annex ZB (informative) Clauses of this European Standard addressing essential requirements or other provisions of EU Directives	21

Foreword

The text of EN ISO 9606-5:2000 has been prepared by Technical Committee CEN/TC 121 "Welding", the secretariat of which is held by DS, in collaboration with Technical Committee ISO/TC 44 "Welding and allied processes".

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by August 2000, and conflicting national standards shall be withdrawn at the latest by August 2000.

This European Standard has been prepared under a mandate given to CEN by the European Commission and the European Free Trade Association, and supports essential requirements of EU Directive(s).

For relationship with EU Directive(s), see informative Annex ZB, which is an integral part of this standard.

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and the United Kingdom.

Introduction

This standard covers the principles to be observed in the approval testing of welder performance for the fusion welding of titanium, zirconium and their weldable alloys.

The ability of the welder to follow verbal or written instructions and testing of his skill are important factors in ensuring the quality of the welded product.

Testing of skill to this standard depends on welding methods in which uniform rules and test conditions are complied with, and standard test pieces are used.

The test weld can be used to approve a welding procedure and a welder provided that all the relevant requirements, e.g. test piece dimensions, are satisfied (see EN 288-2).

1 Scope

This standard specifies essential requirements, ranges of approval, test conditions, acceptance requirements and certification for the approval testing of welder performance for the welding of titanium and zirconium.

This standard applies to the approval testing of welders for the fusion welding of titanium and zirconium.

This standard is intended to provide the basis for the mutual recognition by examining bodies for approval relating to welders' competence in the various fields of application. Tests will be carried out in accordance with this standard unless more severe tests are specified by the relevant application standard when these are applied.

During the approval test the welder should be required to show adequate practical experience and job knowledge (test non mandatory) of the welding processes, materials and safety requirements for which he is to be approved. Information on these aspects is given in Annex A.

This standard is applicable when the welder's approval testing is required by the purchaser, by inspection authorities or by other organizations.

The welding processes referred to in this standard include those fusion welding processes which are designated as manual or partly mechanized welding. It does not cover fully mechanized and automatic processes (see 5.2).

This standard covers approval testing of welders for work on semi-finished and finished products made from wrought, forged or cast material types listed in 5.4.

The certificate of approval testing is issued under the sole responsibility of the examiner or examining body.

2 Normative references

This European Standard incorporates by dated or undated reference, provisions from other publications. These normative references are cited at the appropriate places in the text and the publications are listed hereafter. For dated references, subsequent amendments to or revisions of any of these publications apply to this European Standard only when incorporated in it by amendment or revision. For undated references the latest edition of the publication referred to applies.

EN 287-1 : 1992

Approval testing of welders – Fusion welding – Part 1: Steels

EN 288-2 : 1992

Specification and approval of welding procedures for metallic materials – Part 2: Welding procedure specification for arc welding

EN 571-1

Non destructive testing – Penetrant testing – Part 1: General principles

EN 910

Destructive tests on welds in metallic materials – Bend tests

EN 970

Non-destructive examination of fusion welds – Visual examination

EN 1289

Non-destructive examination of welds – Penetrant testing of welds – Acceptance levels

EN 1320

Destructive tests on welds in metallic materials – Fracture test

EN 1321

Destructive tests on welds in metallic materials – Macroscopic and microscopic examination of welds

EN 1435

Non-destructive examination of welds – Radiographic examination of welded joints

EN ISO 4063

Welding and allied processes – Nomenclature of processes and reference numbers (ISO 4063 : 1998)

EN ISO 6520-1

Welding and applied processes - Classification of geometric imperfections in metallic materials - Part 1: Fusion welding (ISO 6520-1:1998)

EN 25817

Arc-welded joints in steel – Guidance on quality levels for imperfections (ISO 5817 : 1992)

EN ISO 6947

Welds – Working positions – Definitions of angles of slope and rotation (ISO 6947 : 1993)

CR 12187

Welding – Guidelines for a grouping system of materials for welding purposes

ISO 857

Welding, brazing and soldering processes – Vocabulary

3 Terms and definitions

For the purposes of this standard, the terms and definitions given in EN 287-1 apply.

4 Symbols and abbreviations

4.1 General

Where the full wording is not used, the following symbols and abbreviations shall be used when completing the test certificate (see Annex B of EN 287-1 : 1992).

4.2 Test piece

- a nominal throat thickness;
- BW butt weld;
- D outside diameter of pipe;
- FW fillet weld;
- P plate;
- t plate or pipe wall thickness;
- T pipe;
- z leg length of fillet weld.

4.3 Consumables

- nm no filler metal;
- wm with filler metal.

4.4 Miscellaneous

- bs welding from both sides;
- gg back grinding or back milling of welds;
- mb welding with backing;
- nb welding without backing;
- ng no back grinding or back milling of welds;
- ss single-side welding.

5 Essential variables for approval testing

5.1 General

The criteria specified in this clause shall be examined in order to identify the ability of the welder in these areas. Each criterion is considered to be a significant factor in the approval testing.

The welder's approval test shall be carried out on test pieces and is independent of the type of construction.

5.2 Welding processes

Welding processes are defined in accordance with ISO 857 and reference numbers of welding processes for symbolic representation are listed in accordance with EN ISO 4063.

This standard covers the following welding processes:

- 131 – metal-arc inert gas-welding (MIG welding);
- 141 – tungsten inert gas arc welding (TIG welding);
- 15 – plasma arc welding;

Other fusion welding processes by agreement.

5.3 Joint types (butt and fillet welds)

Test pieces shall be produced for butt weld (BW) and fillet weld (FW) in plates (P) or pipes¹⁾ (T) for approval tests in accordance with 7.2.

5.4 Material groups

An approval test carried out on any material in groups 51, 52, 53 or 54 according to CR 12187 or 61 or 62 according to CR 12187 covers all materials within these groups. In cases where the production work is predominantly zirconium welding, the welder shall carry out the approval test on zirconium.

5.5 Consumables

In the approval test, the filler metal and the shielding gas, including plasma gas, shall be compatible with the parent metal and the process used in accordance with the relevant pWPS or WPS (see EN 288-2).

5.6 Dimensions

The welder approval test should be based on the thickness of the material (i.e. plate thickness or wall thickness of pipe) and pipe diameters which the welder will use in production. A test is listed for each of the ranges of plate thickness and pipe wall thickness or pipe diameter as specified in tables 1 and 2.

Table 1 - Test piece thickness (plate or pipe) and range of approval

Test piece thickness <i>t</i> mm	Range approval
$t \leq 3$	t to $2,5 t$
$t > 3$	> 3

Table 2 - Test piece diameter and range of approval

Test piece diameter <i>D</i> mm	Range approval
$D \leq 25$	D to $2D$
$D > 25$	$\geq 0,5 D$ (25 mm min.)

5.7 Number of test pieces

Plate: One test piece per position.

Pipe: A minimum weld length of 150 mm is required, but not more than three test pieces.

¹⁾ The word "pipe" alone or in combination, is used to mean "pipe", "tube" or "hollow section".

5.8 Welding positions

The welding positions shall be taken from EN ISO 6947.

The test pieces shall be welded in accordance with the nominal angles of the positions according to EN ISO 6947.

6 Range of approval for the welder

6.1 General

As a general rule, the test piece approves the welder not only for the conditions used in the test, but also for all joints which are considered easier to weld. The range of approval for each type of test is given in the relevant sub-clauses and tables. In these tables the range of approval is indicated in the same horizontal line.

6.2 Welding process

Each test normally approves one process. A change of process requires a new approval test. However, it is possible for a welder to be approved for more than one welding process by a single test or by two separate approval tests to be used to cover a multi-process joint. For example in a case where approval is required for a single-side butt joint with the root to be welded by TIG (141) without backing and to be filled by MIG (131), the welder can be approved by either of the following routes:

- a) a successful completion of an approval test simulating the multi-process joint, i. e. the root run welded by TIG (141) without backing, subsequent runs or layers welded by MIG (131) within the limits of the range of approval for each welding process;
- b) successful completion of separate relevant approval tests one for TIG (141) without backing for the root run and a separate test for the fill by MIG (131) with backing or welded from both sides with or without back grinding or milling.

6.3 Joint types

Depending on the test piece, the range of welds for which the welder is approved is shown in table 3. The following criteria are applicable:

- a) approval for butt welds in pipes, diameter > 25 mm, includes butt welds in plates;
- b) approval for butt welds in plates in all relevant positions covers butt welds on pipes having an outside diameter ≥ 500 mm, except item c) also applies;
- c) approval for butt joints in plates welded in the flat (PA) or horizontal (PC) position shall include approval for butt joints in pipes of outside diameter ≥ 150 mm welded in similar positions according to table 6;
- d) butt welds approve fillet welds. In cases where the majority of production work is fillet welding, the welder shall *be approved also by an appropriate fillet welding test*;
- e) approval for butt welds in pipes without backing includes approval for branch connections within the same range of approval as in tables 3 to 6. For a branch weld the range of approval is based on the diameter of the branch;
- f) in cases where the majority of production work is predominantly branch welding or involves a complex branch connection, the welder should receive special training. In some cases a welder approval test on a branch connection can be necessary.

Table 3 - Range of approval for tests on butt joints (Details of the weld type)

Details of the weld type				Range of approval					
				Butt welds in plate				Butt welds in pipe	
				welded from one side ss		welded from both sides bs		welded from one side ss	
				with backing mb	no backing nb	with grinding gg	no grinding ng	with backing mb	no backing nb
Butt weld in plate	welded from one side ss	with backing	mb	*	—	x	—	1)	—
		no backing	nb	x	*	x	x	1)	1)
	welded from both sides bs	with grinding	gg	x	—	*	—	1)	—
		no grinding	ng	x	—	x	*	1)	—
Butt weld in pipe	welded from one side ss	with backing	mb	x	—	x	—	*	—
		no backing	nb	x	x	x	x	x	*

1) See 6.3b), and 6.3c)

* indicates the weld for which the welder is approved in the approval test
x indicates those welds for which the welder is also approved
— indicates those welds for which the welder is not approved

6.4 Material groups (according to CR 12187)

In tables 4 and 5 the grouping systems for titanium/titanium alloys and zirconium/zirconium alloys are given.

Table 4 - Grouping system for titanium and titanium alloys

Group	Type of titanium and titanium alloys
51	Pure titanium
52	Alpha alloys 1)
53	Alpha-beta alloys 2)
54	Near beta and beta alloys 3)

1) Alloys covered by group 52 are: Ti-0,2Pd; Ti-2,5Cu; Ti-5Al-2,5Sn; Ti-8Al-1Mo-1V; Ti-6Al-2Sn-4Zr-2Mo; Ti-6Al-2Nb-1Ta-0,8Mo.

2) Alloys covered by group 53 are: Ti-3Al-2,5V; Ti-6Al-4V; Ti-6Al-6V-2Sn; Ti-7Al-4Mo.

3) Alloys covered by group 54 are: Ti-10V-2Fe-3Al; Ti-13V-11Cr-3Al; Ti-11,5Mo-6Zr-4,5Sn; Ti-3Al-8V-6Cr-4Zr-4Mo.

Table 5 - Grouping system for zirconium and zirconium alloys

Group	Type of zirconium and zirconium alloys
61	Pure zirconium
62	Zirconium with 2,5 % Nb

6.5 Consumables

An approval test made with a specific filler metal and shielding gas shall give approval to weld with any other filler metal compatible with the parent metal group when using the same welding process.

6.6 Dimensions

The range of approval according to plate thickness or wall thickness of pipe and/or pipe diameter is shown in tables 1 and 2.

6.7 Welding positions

The range of approval for each welding position is given in table 6. The welding positions and codes refer to EN ISO 6947.

The welding position H-L045 for pipes approves for all pipe angles in production work. In pipes diameter $D \geq 150$ mm it is allowed to weld in two welding positions (PF 2/3 of circumference, PC 1/3 of circumference) using only one test piece.

Table 6 - Range of approval according to welding position

Welding position of approval test piece		Range of approval																								
		Plates								Pipes																
		Butt welds				Fillet welds				Butt welds				Fillet welds												
		rotating		fixed		rotating		fixed		rotating		fixed		rotating		fixed										
0°		90°		45°		H-L045		45°		90°		45°		0°		90°										
PA		PC		PF		PE		PA		PB		PF		PD		PA		PB		PF		PD ²⁾				
Plates	Butt welds	PA	*	-	-	-	X	X	-	-	-	-	X	X	-	-	X	X	-	-	-	-	-			
		PC	X	*	-	-	X	X	-	-	-	-	X	X	-	-	X	X	-	-	-	-	-	-		
		PF	X	-	*	-	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	
		PE	X	X	X	*	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	
	Fillet welds	PA	-	-	-	-	*	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	
		PB	-	-	-	-	X	*	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	
		PF	-	-	-	-	X	X	*	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	
		PD	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	
		Butt welds	0°	PA	X	-	-	-	-	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X
			fixed	90°	PC	X	X	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-
45°	H-L045	X		X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	
45°	PA	-		-	-	-	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X		
Fillet welds	1)	PB	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-	-		
	fixed	0°	PF	-	-	-	-	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X		

1) PB for pipes can be welded in two versions

(1) pipe: rotating; axis: horizontal; weld: horizontal vertical

(2) pipe: fixed; axis: vertical; weld: horizontal vertical

2) This is an approved position and is covered by the other related tests.

* indicates the welding position for which the welder is approved in the approval test

x indicates those welding positions for which the welder is also approved

- indicates those welding positions for which the welder is not approved

7 Examination and testing

7.1 Supervision

The welding and testing of test pieces shall be witnessed by an examiner or examining body acceptable to the contracting parties.

The test pieces shall be marked with the identification of the examiner and the welder before welding starts.

The examiner or examining body can stop the test if the welding conditions are not correct or if it appears that the welder does not have the technical competence to comply to the requirements of this standard, e.g. where there are excessive and/or systematic repairs.

7.2 Shapes and dimensions of test pieces

The shape and dimension of test pieces (see 5.6) required are shown in figures 1 to 4.

Dimensions in millimetres


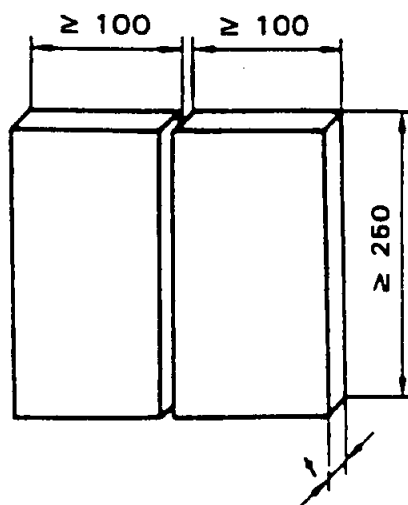


Figure 1 - Dimensions of test piece for a butt weld in plate

Dimensions in millimetres

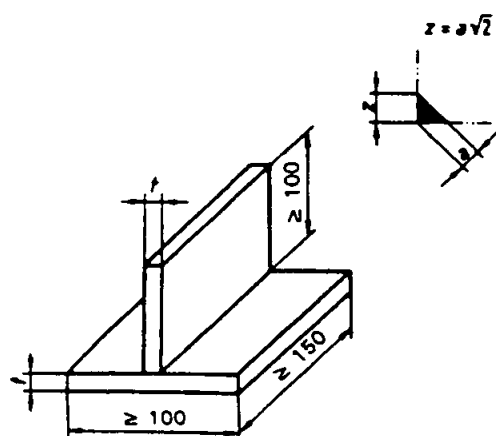

For $t \geq 6$ mm, $a \leq 0,5 t$
 For $t < 6$ mm, $0,5 t \leq a \leq t$
 ($z = 0,7 t$)

Figure 2 - Dimensions of test piece for fillet weld(s) on plate

Dimensions in millimetres


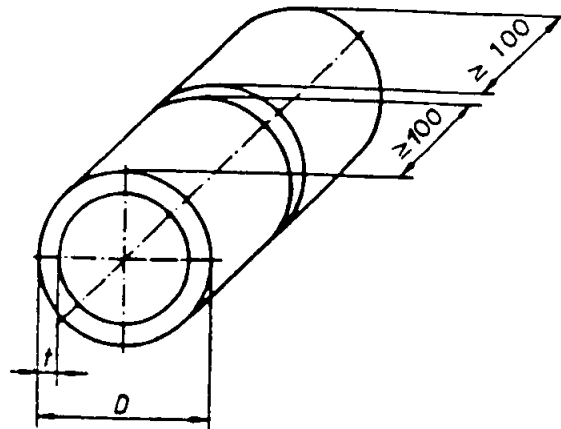


Figure 3 - Dimensions of test piece for a butt weld in pipe

Dimensions in millimetres

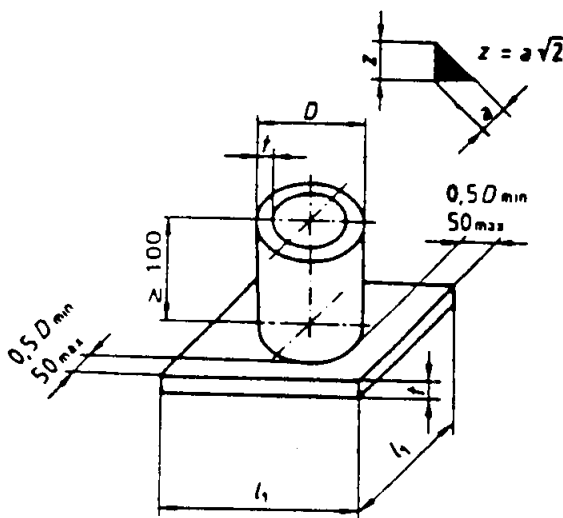

For $t \geq 6$ mm, $a \leq 0,5 t$
For $t < 6$ mm, $0,5 t \leq a \leq t$
($z = 0,7 t$)

t corresponds to the thinner part

Figure 4 - Dimensions of test piece for a fillet weld on pipe

7.3 Welding conditions

The approval test for the welder shall correspond to the conditions used in production and follow a WPS or pWPS prepared in accordance with EN 288-2.

The following conditions shall apply:

- the welding time for the test piece shall correspond to the working time under usual production conditions;
- the test piece shall have at least one stop and one re-start in the root run and in the top capping run and be identified in the inspection length to be examined;
- identification of the test piece;
- the welder shall be allowed to remove minor imperfections, except on the surface layer, by grinding or any other method used in production. The approval of the examiner or test body shall be obtained.

7.4 Test methods

Each completed weld shall be examined visually in accordance with EN 970 including temper colour on the root and face side in the as-welded condition. The visual examination shall be supplemented by penetrant testing in accordance with EN 571-1 or other test methods (see table 7).

For the root examination on pipes, the test piece shall be cut into two half pipes.

If accepted by visual examination with assessment of temper colours, the mandatory tests according to table 7 have to be carried out.

Prior to mechanical testing, backing strips, where used, shall be removed. The test piece can be sectioned by mechanical means discarding the first and the last 25 mm of the test piece at the end of the plates (figures 5 and 6).

Table 7 - Test methods

Test method	Butt weld plate	Butt weld pipe	Fillet weld
Visual	mandatory	mandatory	mandatory
Bend	mandatory	mandatory	–
Fracture	–	–	mandatory
Penetrant	not mandatory	not mandatory	not mandatory
Macroscopic incl. hardness	not mandatory	not mandatory	not mandatory
Radiography	not mandatory	not mandatory	–

7.5 Test piece and test specimens

7.5.1 General

In 7.5.2 to 7.5.5 details of the type, dimensions and preparation of test pieces and test specimens are given. In addition, the requirements for mechanical tests are indicated.

7.5.2 Butt weld

The transverse bend testing shall be carried out in accordance with EN 910, and the bending angle shall be 180°.

Two root and two face bend tests shall be performed as a minimum (for pipes, see figure 5). In general, the diameter of the former or the inner roller should be:

- 4 r for group 51;
- 6 r for groups 52, 53, 54 and 61, 62.

Depending on the ductility of the parent metal, larger diameter for the former or inner roller can be used by agreement.

For plate or wall thickness ≥ 10 mm, the transverse bend tests can be substituted by four side bend tests in accordance with EN 910.

When radiographic testing is used, the test piece shall be radiographed in the as-welded condition in accordance with EN 1435 using class B technique.

7.5.3 Fillet weld on plate


For fracture tests according to EN 1320 the test piece can be cut, if necessary, into several test specimens (see figure 6a). Each test specimen shall be positioned for breaking as shown in figure 6b, and examined after fracture.

When macroscopic examination is used, at least four test specimens shall be taken equally spaced in the inspection length. Macroscopic tests shall be carried out in accordance with EN 1321.

Dimensions in millimetres

Position 1 + 3:
Each position one root transverse bend
or one side bend test specimen

Position 2 + 4:
Each position one face transverse bend
or one side bend test specimen

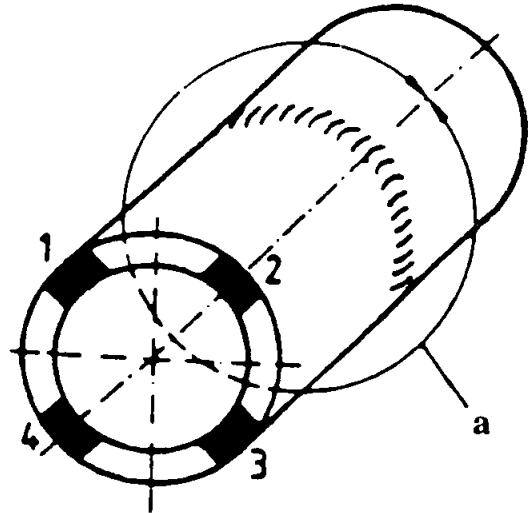



^a Inspection length of the test piece

Sectioning into at least four test specimens

Figure 5 - Preparation of bend test specimens for a butt weld in pipe

Dimensions in millimetres

^a Inspection length of the
test piece

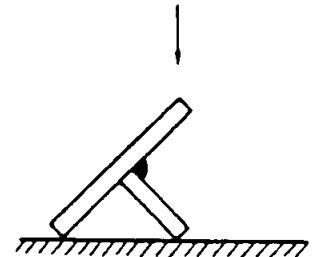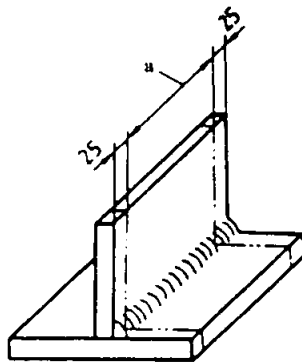

a) Inspection length of the fillet welds

b) Fracture testing
(The fillet weld can be notched, if necessary)

Figure 6 - Preparation and fracture testing of test specimens for a fillet weld on plate

7.5.4 Fillet weld on pipe

For fracture tests in accordance with EN 1320, the test piece shall be cut into four or more test specimens and fractured as shown on figure 7.

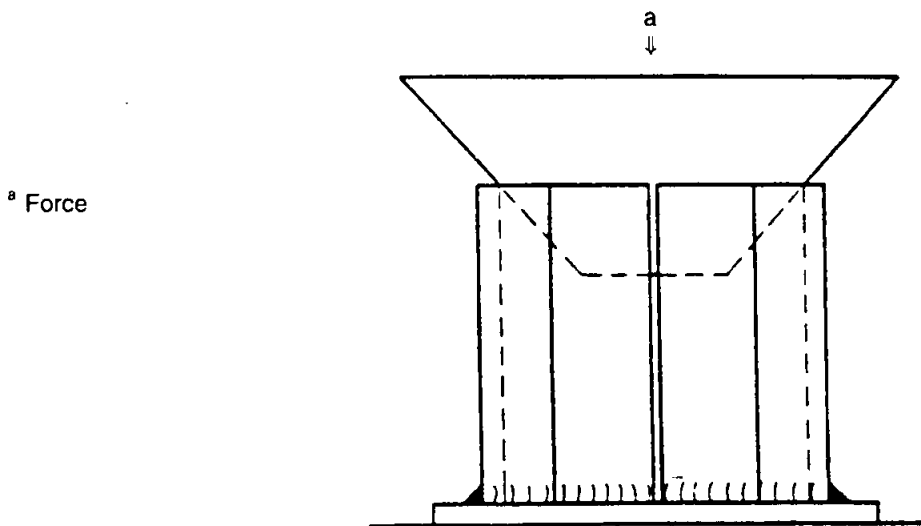


Figure 7 - Preparation and fracture testing of test specimens for fillet welds on pipe

When macroscopic examination in accordance with EN 1321 is used, at least four test specimens shall be taken equally spaced around the pipe.

8 Acceptance requirements for test pieces

Test pieces shall be evaluated according to the acceptance requirements specified for relevant types of imperfections. A full explanation of these imperfections is given in accordance with EN ISO 6520-1. The acceptance requirements for imperfections found by test methods according to this standard shall, unless otherwise specified, be assessed in accordance with EN 25817. A welder is approved if the imperfections in the test piece are within the specified limits of level B in accordance with EN 25817, except for imperfection types as follows: excess weld metal, excessive convexity, excessive throat thickness and excessive penetration, for which level C shall apply.

If the imperfections in the welder's test piece exceed the permitted maximum specified, then the welder shall not be approved.

Reference should also be made to the corresponding acceptance criteria for non-destructive examination. Specified procedures shall be used for all destructive and non-destructive examinations.

Colouration: Accepted colours on the weld metal surface: silver and straw. A narrow band of intensive colours close to the limits of the gas shielding is acceptable. Darker brown, purple and blue colours and grey or flaky white are not acceptable.

Bend test: The test specimens shall bend uniformly and the weld, HAZ and parent metal areas will each conform closely to the radius of the forming tool. This will indicate that any gas pick-up during welding has not reduced the ductility of the weld and that the welding has not adversely affected the formability of the parent metal.

9 Re-tests

If any test piece fails to comply with the requirements of this standard, the welder shall produce a new test piece.

If it is established that failure is attributed to the welder's lack of skill, the welder shall be regarded as incapable of complying with the requirements of this standard without further training before re-testing.

If it is established that failure is due to metallurgical or other extraneous causes and cannot be directly attributed to the welder's lack of skill, an additional test is required in order to assess the quality and integrity of the new test material and/or new test conditions.

10 Period of validity

10.1 Initial approval

The validity of the welder's approval begins from the date the required tests are satisfactorily completed. This date can be different to the date of issue marked on the certificate.

A welder's approval is valid for a period of two years provided that the relevant certificate is confirmed at six months intervals by the welding coordinator or the employer, and that all the following conditions are fulfilled:

- a) The welder shall be engaged with reasonable continuity on welding work within the current range of approval. An interruption for a period no longer than six months is permitted;
- b) There shall be no specific reason to question the welder's skill and knowledge.

If any of these conditions are not fulfilled, the approval shall be revoked.

10.2 Prolongation

The validity of the approval on the certificate can be prolonged for further periods of two years, within the original range of approval, provided each of the following conditions according to 10.1 are fulfilled:

- a) the production welds made by the welder have been of the required quality;
- b) records of tests, e.g. either half yearly documentation about radiographic testing or test reports about destructive testing, shall be maintained on file with the welder's approval certificate.

The examiner or examining body shall verify compliance with the above conditions and sign the prolongation of the welder's approval test certificate.

11 Certificate

It shall be verified that the welder has successfully passed the performance approval test. All relevant test conditions shall be recorded on the certificate. If the welder fails any of the prescribed tests, no certificate shall be issued.

The certificate shall be issued under the sole responsibility of the examiner or examining body and shall contain all the information detailed in Annex A of 287-1:1992. The format of this Annex A of EN 287-1:1992 is recommended to be used as the welder's approval test certificate. If any other form of welder's approval test certificate is used, it shall contain the information required in Annex A of EN 287-1:1992.

The manufacturer's pWPS or WPS as shown in Annex A of EN 288-2:1992 shall give information about materials, welding positions, welding processes, range of approval etc., in accordance with this standard.

The welder's approval test certificate shall be issued at least in one of the official CEN languages (English, French, German).

The practical test and the examination of job knowledge (see Annex A) shall be designated by "Accepted" or "Not tested".

Each change of the essential variables for the approval testing beyond the permitted ranges requires a new test and a new approval certificate.

12 Designation

The designation of a welder approval shall comprise the following items in the order given (the system is arranged so that it can be used for computerization):

- a) the number of this standard;
- b) the essential variables:
 - 1) welding processes: refer to 5.2 and EN ISO 4063;
 - 2) semi-finished product: plate (P), pipe (T), refer to 5.3;
 - 3) joint type: butt weld (BW), fillet weld (FW), refer to 5.3;
 - 4) material group: refer to 5.4 and 6.4;
 - 5) consumables: refer to 5.5;
 - 6) dimension of test piece: thickness (t) and pipe diameter (D), refer to 5.6;
 - 7) welding positions: refer to 5.8 and EN ISO 6947;
 - 8) details of the joint type: refer to 6.3 and table 3, for abbreviations to 4.4.

DESIGNATION EXAMPLE 1:

Welder approval EN ISO 9606-5 141 T BW W61 wm t03 D50 PA ss nb

EXPLANATION

Welding process: TIG-welding	141
Pipe:	T
Butt weld:	BW
Material group: pure zirconium	W61
Consumables: with filler metal	wm
Dimension of test piece:	
– thickness 3 mm	t03
– pipe diameter 50 mm	D50
Welding position: butt weld in pipe, rotating pipe, horizontal axis, flat	PA
Details of the weld type:	
– single side	ss
– without backing	nb

DESIGNATION EXAMPLE 2:

Welder approval EN ISO 9606-5 131 P FW W51 wm t10 PB

EXPLANATION

Welding process: MIG welding	131
Plate:	P
Fillet weld:	FW
Material group: pure titanium	W51
Consumables: with filler metal	wm
Dimension of test piece: thickness 10 mm	t10
Welding position: fillet weld on plate, horizontal vertical	PB

NOTE: For explanation of abbreviations used in the designation examples, see clause 4.

Annex A (informative)

Job knowledge

A.1 General

The test of job knowledge is recommended, but it is not mandatory.

However, some countries can require that the welder undergoes a test of job knowledge. If the job knowledge test is carried out, it should be recorded on the welder's certificate.

This annex outlines the job knowledge that a welder should have to ensure that procedures are followed and common practices are complied with. The job knowledge indicated in this annex is only pitched at the most basic level.

Owing to different training programmes in various countries, it is only proposed to standardize general objectives or categories of job knowledge. The actual questions used should be drawn up by the individual country, but should include questions on areas covered in A.2, relevant to the welders approval test.

The actual tests of a welder's job knowledge can be given by any of the following methods or combinations of these methods:

- a) written objective tests (multiple choice);
- b) oral questioning following a set of written questions;
- c) computer testing;
- d) demonstration/observation testing following a written set of criteria.

The test of job knowledge is limited to the matters related to the welding process used in the test.

A.2 Requirements

A.2.1 Arc welding

A.2.1.1 Welding equipment

- a) Identification and assembly of essential components and equipment;
- b) Type of welding current;
- c) Correct connection of the welding return cable.

A.2.2 Welding process

A.2.1.2 Gas shielded arc welding (131, 141, 15) ¹⁾

- a) Types and size of electrodes;
- b) Identification of shielding gas and flow rate;
- c) Type, size and maintenance of nozzles/contact tip;
- d) Selection and limitations of mode of metal transfer;
- e) Protection of the welding arc from draughts.

A.2.3 Parent metals

- a) Identification of material;
- b) Behaviour under higher temperature

A.2.4 Consumables

- a) Identification of consumables;
- b) Storage, handling and conditions of consumables;
- c) Selection of correct size;
- d) Cleanliness of electrodes and filler wires;
- e) Control of wire spooling;
- f) Control and monitoring of gas flow rates and quality.

¹⁾ The numbers refer to EN ISO 4063.

A.2.5 Safety and accident prevention

A.2.5.1 General

- a) Safe assembly, setting up and closing down procedures;
- b) Safe control of welding fumes and gases;
- c) Personal protection;
- d) Fire hazards;
- e) Welding in confined spaces;
- f) Awareness of welding environment.

A.2.5.2 Gas-shielded arc welding

- a) Environment of increase hazard of electric shock;
- b) Radiation from the arc;
- c) Effects of stray arcing;
- d) Safe storage, handling and use of compressed gases;
- e) Leak detection on gas hoses and fittings.

A.2.6 Welding sequences/procedures

Appreciation of welding procedure requirements and the influence of welding parameters.

A.2.7 Joint preparation and weld representation

- a) Conformance of joint preparation to procedure specification (WPS);
- b) Cleanliness of fusion faces.

A.2.8 Weld imperfections

- a) Identification of imperfections;
- b) Causes;
- c) Prevention and remedial action.

A.2.9 Welder approval

The welder shall be aware of the range of the approval.

Annex ZA (informative)

Bibliography

Table ZA.1 - ISO standards conforming to the European Standards quoted in clause 2

European Standard quoted in clause 2	Corresponding ISO standard	Title of the ISO standard
EN 287-1 :1992	ISO 9606-1 : 1994	Approval testing of welders – Fusion welding – Part 1: Steels
EN 288-2 : 1992	ISO 9956-2 : 1995	Specification and approval of welding procedures for metallic materials – Part 2: Welding procedure specification for arc welding
EN 571-1	–	
EN 910	ISO/DIS 5173.2 : 1996	Destructive tests on welds in metallic materials – Bend test (Revision of ISO 5173:1981 and ISO 5177:1981)
EN 970	–	
EN 1289	–	
EN 1320	ISO/DIS 9017.3 : 1996	Destructive tests on welds in metallic materials – Fracture test
EN 1321	–	
EN 1435	ISO 1106-1 : 1984	Recommended practice for radiographic examination of fusion welded joints – Part 1 : Fusion welded butt joints in steel plates up to 50 mm thick
	ISO 1106-2 : 1985	Recommended practice for radiographic examination of fusion welded joints – Part 2: Fusion welded butt joints in steel plates thicker than 50 mm and up to and including 200 mm in thickness
EN ISO 4063	ISO 4063 : 1998	Welding and allied processes – Nomenclature of processes
EN 25817	ISO 5817 : 1992	Arc-welded joints in steel – Guidance on quality levels for imperfections
EN ISO 6520-1	ISO 6520-1 : 1998	Welding and allied processes - Classification of geometric imperfections in metallic fusion welds, with explanations - Part 1: Fusion welding
EN ISO 6947	ISO 6947 : 1990	Welds – Working positions – Definitions of angles of slope and rotation (Revision of ISO 6947:1980)
CR 12187	–	

Annex ZB (informative)

Clauses of this European Standard addressing essential requirements or other provisions of EU Directives

This European Standard has been prepared under a mandate given to CEN by the European Commission and the European Free Trade Association and supports essential requirements of Directive 97/23/EEC of the European Parliament and of the Council of 29 May 1997 on the approximation of the laws of the Member States concerning pressure equipment.

WARNING: Other requirements and other EU Directives may be applicable to the product(s) falling within the scope of this standard.

The following clauses of this standard as detailed in Table ZB.1, are likely to support requirements of the Directive 97/23/EEC.

Compliance with these clauses of this standard provides one means of conforming with the specific essential requirements of the Directive concerned and associated EFTA regulations.

Table ZB.1 - Correspondence between this European Standard and Directive 97/23/EEC

Clauses/sub-clauses of this European Standard	Essential requirements of Directive 97/23/EEC	Qualifying remarks/Notes
All clauses	Annex I, 3.1.2	Permanent joining

BSI — British Standards Institution

BSI is the independent national body responsible for preparing British Standards. It presents the UK view on standards in Europe and at the international level. It is incorporated by Royal Charter.

Revisions

British Standards are updated by amendment or revision. Users of British Standards should make sure that they possess the latest amendments or editions.

It is the constant aim of BSI to improve the quality of our products and services. We would be grateful if anyone finding an inaccuracy or ambiguity while using this British Standard would inform the Secretary of the technical committee responsible, the identity of which can be found on the inside front cover. Tel: 020 8996 9000. Fax: 020 8996 7400.

BSI offers members an individual updating service called PLUS which ensures that subscribers automatically receive the latest editions of standards.

Buying standards

Orders for all BSI, international and foreign standards publications should be addressed to Customer Services. Tel: 020 8996 9001. Fax: 020 8996 7001.

In response to orders for international standards, it is BSI policy to supply the BSI implementation of those that have been published as British Standards, unless otherwise requested.

Information on standards

BSI provides a wide range of information on national, European and international standards through its Library and its Technical Help to Exporters Service. Various BSI electronic information services are also available which give details on all its products and services. Contact the Information Centre. Tel: 020 8996 7111. Fax: 020 8996 7048.

Subscribing members of BSI are kept up to date with standards developments and receive substantial discounts on the purchase price of standards. For details of these and other benefits contact Membership Administration. Tel: 020 8996 7002. Fax: 020 8996 7001.

Copyright

Copyright subsists in all BSI publications. BSI also holds the copyright, in the UK, of the publications of the international standardization bodies. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI.

This does not preclude the free use, in the course of implementing the standard, of necessary details such as symbols, and size, type or grade designations. If these details are to be used for any other purpose than implementation then the prior written permission of BSI must be obtained.

If permission is granted, the terms may include royalty payments or a licensing agreement. Details and advice can be obtained from the Copyright Manager. Tel: 020 8996 7070.