

Adhesives — Determination of shear strength of adhesive bonds between rigid substrates by the block-shear method

The European Standard EN ISO 13445:2006 has the status of a
British Standard

ICS 83.180

National foreword

This British Standard is the official English language version of EN ISO 13445:2006. It is identical with ISO 13445:2003.

The UK participation in its preparation was entrusted to Technical Committee PRI/52, Adhesives, which has the responsibility to:

- aid enquirers to understand the text;
- present to the responsible international/European committee any enquiries on the interpretation, or proposals for change, and keep UK interests informed;
- monitor related international and European developments and promulgate them in the UK.

A list of organizations represented on this committee can be obtained on request to its secretary.

Cross-references

The British Standards which implement international or European publications referred to in this document may be found in the *BSI Catalogue* under the section entitled “International Standards Correspondence Index”, or by using the “Search” facility of the *BSI Electronic Catalogue* or of British Standards Online.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

Compliance with a British Standard does not of itself confer immunity from legal obligations.

Summary of pages

This document comprises a front cover, an inside front cover, the EN ISO title page, the EN ISO foreword page, the ISO title page, pages ii to iv, pages 1 to 5 and a back cover.

The BSI copyright notice displayed in this document indicates when the document was last issued.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 31 August 2006

© BSI 2006

ISBN 0 580 48924 8

Amendments issued since publication

Amd. No.	Date	Comments

English Version

**Adhesives - Determination of shear strength of adhesive bonds
between rigid substrates by the block-shear method (ISO
13445:2003)**

Adhésifs - Détermination de la résistance au cisaillement
de joints collés entre éléments rigides par la méthode de
cisaillement entre blocs massifs (ISO 13445:2003)

Klebstoffe - Bestimmung der Scherfestigkeit von
Klebungen zwischen starren Werkstoffen nach dem
Blockscherverfahren (ISO 13445:2003)

This European Standard was approved by CEN on 25 May 2006.

CEN members are bound to comply with the CEN/GENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Central Secretariat or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Central Secretariat has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

Management Centre: rue de Stassart, 36 B-1050 Brussels

Foreword

The text of ISO 13445:2003 has been prepared by Technical Committee ISO/TC 61 "Plastics" of the International Organization for Standardization (ISO) and has been taken over as EN ISO 13445:2006 by Technical Committee CEN/TC 193 "Adhesives", the secretariat of which is held by AENOR.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by December 2006, and conflicting national standards shall be withdrawn at the latest by December 2006.

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland and United Kingdom.

Endorsement notice

The text of ISO 13445:2003 has been approved by CEN as EN ISO 13445:2006 without any modifications.

INTERNATIONAL
STANDARD

ISO
13445

Second edition
2003-04-01

**Adhesives — Determination of shear
strength of adhesive bonds between rigid
substrates by the block-shear method**

*Adhésifs — Détermination de la résistance au cisaillement de joints
collés entre éléments rigides par la méthode de cisaillement entre blocs
massifs*



Reference number
ISO 13445:2003(E)

Contents

Page

Foreword..... iv

1 **Scope**..... 1

2 **Normative references** 1

3 **Terms and definitions** 1

4 **Principle** 2

5 **Apparatus**..... 2

6 **Test specimens** 3

7 **Conditioning** 4

8 **Procedure**..... 4

9 **Expression of results**..... 4

10 **Precision** 4

11 **Test report**..... 4

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 13445 was prepared by Technical Committee ISO/TC 61, *Plastics*, Subcommittee SC 11, *Products*.

This second edition cancels and replaces the first edition (ISO 13445:1995), which has been technically revised.

Adhesives — Determination of shear strength of adhesive bonds between rigid substrates by the block-shear method

1 Scope

This International Standard specifies a method for the determination of the shear strength of adhesives used to bond materials with elastic moduli higher than the elastic modulus of the adhesive. The method provides an estimate of the shear strength of an adhesive on various machinable and non-machinable substrate materials.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 291:1997, *Plastics — Standard atmospheres for conditioning and testing*

ISO 7500-1:—¹⁾, *Metallic materials — Verification of static uniaxial testing machines — Part 1: Tension/compression testing machines — Verification and calibration of the force-measuring system*

ISO 10365:1992, *Adhesives — Designation of main failure patterns*

EN 13887:—²⁾, *Structural adhesives — Guidelines for surface preparation of metals and plastics prior to adhesive bonding*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

3.1

shear stress

force applied parallel to a flat adhesive joint, divided by the bond area of the joint

3.2

shear strength

maximum shear stress sustained by an adhesive joint during a shear test

1) To be published. (Revision of ISO 7500-1:1999)

2) To be published.

4 Principle

Blocks, plates or discs are bonded together, and the maximum force required to shear them apart is determined. The method is particularly applicable to the testing of bonds between ceramic parts, glass parts, magnet mouldings and plastic parts having one flat face where machining would be difficult or impractical.

5 Apparatus

5.1 Tensile-testing machine, with a capacity of not less than 45 kN in tension. The machine shall conform to the requirements of ISO 7500-1.

5.2 Shearing fixture, consisting of a specimen-holding block and a shearing tool (see Figures 1 and 2). Adherends measuring up to 80 mm × 80 mm × 13 mm can be held in the block, while the shearing tool can be used with adherends measuring up to 30 mm × 30 mm × 13 mm. A test specimen with adherends approximating to these dimensions is shown in Figure 3a). For test specimens having two smaller adherends as shown in Figure 3b), an adapter plate can be inserted into the specimen-holding block (see Figure 4) to keep the shearing tool in its guides and to ensure the specimen is located under the clamp.

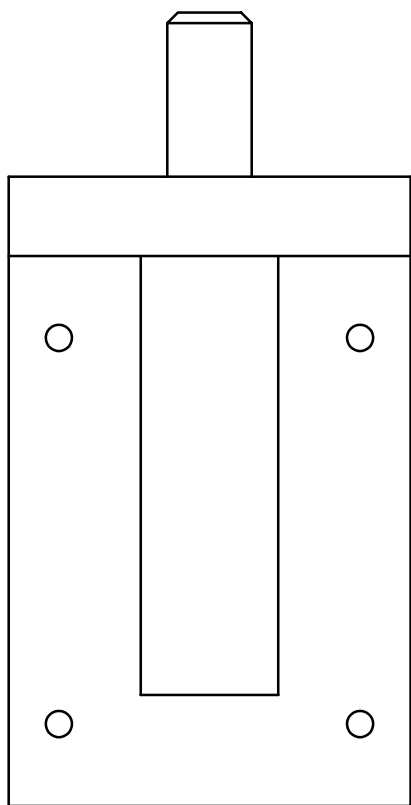


Figure 1 — Specimen-holding block



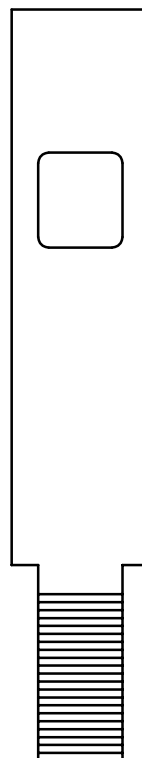


Figure 2 — Shearing tool

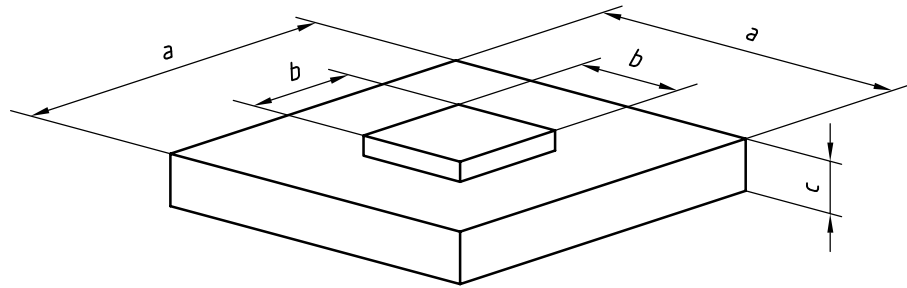

a) Plastic, metal, ceramic or wood to glass

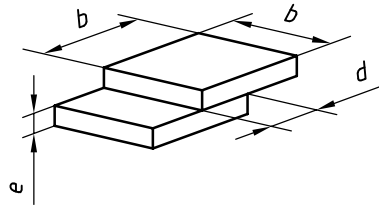

b) Plastic, metal, ceramic or wood to the same material or to one of the other materials

Key

- a* 75 mm ± 1 mm
- b* 25 mm ± 0,2 mm
- c* 13 mm ± 1 mm
- d* 12 mm < *d* ± 0,2 mm < 13 mm
- e* 6 mm for metals, 13 mm for others

Figure 3 — Typical specimens after assembly

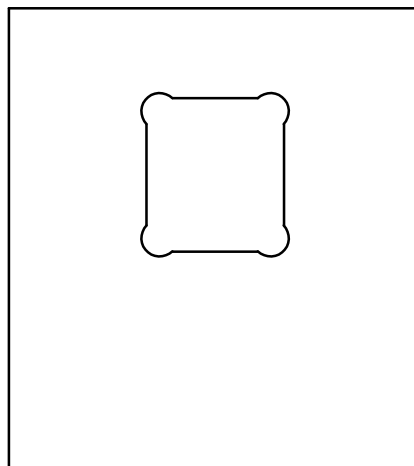


Figure 4 — Adapter for small specimens of the size shown in Figure 3b)

6 Test specimens

6.1 Adherend sizes shall be as follows:

- a) metal blocks: 25 mm × 25 mm × 6 mm;
- b) glass plates: 75 mm × 75 mm × 13 mm;
- c) other materials: 25 mm × 25 mm × 13 mm.

EN ISO 13445:2006

NOTE 1 Other adherend dimensions, within the limits of the shearing-fixture capacity, may be used depending on the application, provided the specimens are thick enough to avoid deformation occurring.

NOTE 2 This method is not applicable to thin adherends with which deformation of the specimen would occur.

6.2 Prepare the surface of the specimen in accordance with EN 13887.

6.3 Prepare the adhesive and apply it in accordance with the adhesive manufacturer's recommendations. Bond the adhesive-coated adherends in accordance with the procedure under investigation. Assemble straight-sided adherends such that the thrust surfaces of the specimen are parallel to within $\pm 5 \mu\text{m}/\text{mm}$. Determine the thickness of the adhesive layer to within 0,02 mm using suitable equipment.

6.4 Remove immediately any excess adhesive squeezed out during assembly. Figure 3 shows typical specimens after bonding.

6.5 Test a minimum of five specimens.

7 Conditioning

The specimens shall be conditioned and tested in one of the standard conditioning atmospheres specified in ISO 291.

8 Procedure

8.1 Mount the shearing fixture in the test machine with the specimen-holding block on top.

8.2 Place an assembled specimen in the shearing fixture in such a way that one of the adherends is held by the holding block and the other engaged by the shearing tool (see Figure 5). Centre the specimen in the shearing tool so that no turning moment is applied to the specimen during shearing. Close the toggle clamp on the rear of the specimen-holding block to keep the specimen (or adapter) located against the shearing tool.

8.3 Test the specimen using a crosshead speed of 1,5 mm/min. Record the maximum force sustained by the specimen.

8.4 Examine the adherends after the test to determine the failure pattern in accordance with ISO 10365.

8.5 Repeat the procedure for the remaining specimens.

9 Expression of results

Calculate the maximum shear stress for each specimen by dividing the maximum force by the bond area. Average the maximum shear stresses for all replicates to determine the average shear strength. Express the shear stress and shear strength in megapascals.

10 Precision


The precision of this test method is not known because interlaboratory data are not available. When interlaboratory data are obtained, a precision statement will be added at the following revision.

11 Test report

The test report shall include the following information:

- a) a reference to this International Standard;
- b) all details necessary for complete identification of the adhesive tested, including type, source and manufacturer's code number;

- c) all details necessary for complete identification of the adherends used, including dimensions and orientation in the shearing fixture, conditioning of specimens, and the method of cleaning and preparing the surfaces prior to bonding;
- d) the quantity of adhesive applied and the bonding conditions used;
- e) the average thickness of the adhesive layer after formation of the bond, to within 0,02 mm, and the way in which the thickness was measured;
- f) the temperature at which the test was performed;
- g) the number of specimens tested;
- h) the maximum shear stress for each specimen;
- i) the average shear strength;
- j) the failure-pattern designation for each specimen, in accordance with ISO 10365.

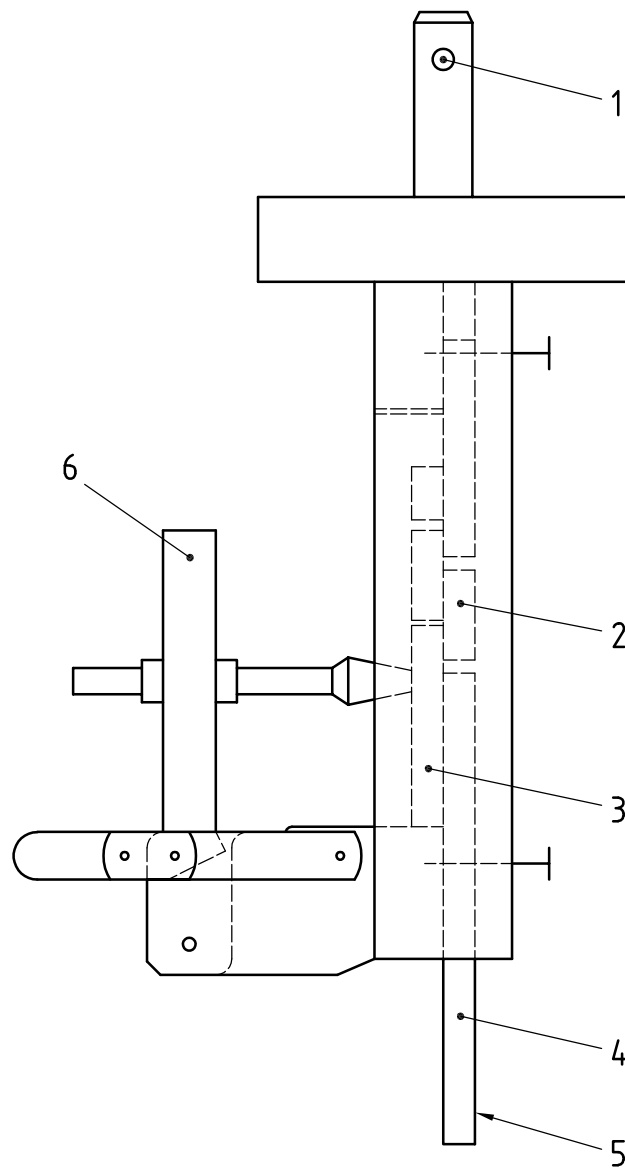

Key

- | | |
|------------------------|--------------------|
| 1 pinhole for mounting | 4 shearing tool |
| 2 specimen | 5 end for clamping |
| 3 adapter | 6 toggle clamp |

Figure 5 — Side view of shearing fixture with specimen

BSI — British Standards Institution

BSI is the independent national body responsible for preparing British Standards. It presents the UK view on standards in Europe and at the international level. It is incorporated by Royal Charter.

Revisions

British Standards are updated by amendment or revision. Users of British Standards should make sure that they possess the latest amendments or editions.

It is the constant aim of BSI to improve the quality of our products and services. We would be grateful if anyone finding an inaccuracy or ambiguity while using this British Standard would inform the Secretary of the technical committee responsible, the identity of which can be found on the inside front cover.
Tel: +44 (0)20 8996 9000. Fax: +44 (0)20 8996 7400.

BSI offers members an individual updating service called PLUS which ensures that subscribers automatically receive the latest editions of standards.

Buying standards

Orders for all BSI, international and foreign standards publications should be addressed to Customer Services. Tel: +44 (0)20 8996 9001.
Fax: +44 (0)20 8996 7001. Email: orders@bsi-global.com. Standards are also available from the BSI website at <http://www.bsi-global.com>.

In response to orders for international standards, it is BSI policy to supply the BSI implementation of those that have been published as British Standards, unless otherwise requested.

Information on standards

BSI provides a wide range of information on national, European and international standards through its Library and its Technical Help to Exporters Service. Various BSI electronic information services are also available which give details on all its products and services. Contact the Information Centre.
Tel: +44 (0)20 8996 7111. Fax: +44 (0)20 8996 7048. Email: info@bsi-global.com.

Subscribing members of BSI are kept up to date with standards developments and receive substantial discounts on the purchase price of standards. For details of these and other benefits contact Membership Administration.
Tel: +44 (0)20 8996 7002. Fax: +44 (0)20 8996 7001.
Email: membership@bsi-global.com.

Information regarding online access to British Standards via British Standards Online can be found at <http://www.bsi-global.com/bsonline>.

Further information about BSI is available on the BSI website at <http://www.bsi-global.com>.

Copyright

Copyright subsists in all BSI publications. BSI also holds the copyright, in the UK, of the publications of the international standardization bodies. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI.

This does not preclude the free use, in the course of implementing the standard, of necessary details such as symbols, and size, type or grade designations. If these details are to be used for any other purpose than implementation then the prior written permission of BSI must be obtained.

Details and advice can be obtained from the Copyright & Licensing Manager.
Tel: +44 (0)20 8996 7070. Fax: +44 (0)20 8996 7553.
Email: copyright@bsi-global.com.