BRITISH STANDARD

BS EN ISO 13468-2:2006

Incorporating Amendment No. 1 (renumbers BS ISO 13468-2:1999 as BS EN ISO 13468-2:2006)

Plastics — Determination of the total luminous transmittance of transparent materials —

Part 2: Double-beam instrument

The European Standard EN ISO 13468-2:2006 has the status of a British Standard

ICS 83.080.01



National foreword

This British Standard is the official English language version of EN ISO 13468-2:2006. It is identical with ISO 13468-2:1999.

The UK participation in its preparation was entrusted to Technical Committee PRI/21, Testing of plastics, which has the responsibility to:

- aid enquirers to understand the text;
- present to the responsible international/European committee any enquiries on the interpretation, or proposals for change, and keep UK interests informed;
- monitor related international and European developments and promulgate them in the UK.

A list of organizations represented on this committee can be obtained on request to its secretary.

Cross-references

The British Standards which implement international or European publications referred to in this document may be found in the *BSI Catalogue* under the section entitled "International Standards Correspondence Index", or by using the "Search" facility of the *BSI Electronic Catalogue* or of British Standards Online.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

Compliance with a British Standard does not of itself confer immunity from legal obligations.

Summary of pages

This document comprises a front cover, an inside front cover, pages i and ii, the EN ISO title page, the EN ISO foreword page, the ISO title page, pages ii to iv, pages 1 to 4, an inside back cover and a back cover.

The BSI copyright notice displayed in this document indicates when the document was last issued.

This British Standard, having been prepared under the direction of the Sector Committee for Materials and Chemicals, was published under the authority of the Standards Committee and comes into effect on 15 August 1999

© BSI 2006

Amendments issued since publication

Amd. No.	Date	Comments
16335	31 July 2006	Renumbers BS ISO 13468-2:1999 as BS EN ISO 13468-2:2006

ISBN 0 580 32872 4

Contents

	Page
National foreword	Inside front cover
Foreword	iii
Text of ISO 13468-2	1

© BSI 2006 i

 $\it ii$ $\it blank$

EUROPEAN STANDARD NORME EUROPÉENNE EUROPÄISCHE NORM

EN ISO 13468-2

April 2006

ICS 83.080.01

English Version

Plastics - Determination of the total luminous transmittance of transparent materials - Part 2: Double-beam instrument (ISO 13468-2:1999)

Plastiques - Détermination du facteur de transmission du flux lumineux total des matériaux transparents - Partie 2: Instrument à double faisceau (ISO 13468-2:1999)

Kunststoffe - Bestimmung des totalen Lichttransmissionsgrades von transparenten Materialien -Teil 2: Zweistrahlinstrument (ISO 13468-2:1999)

This European Standard was approved by CEN on 16 March 2006.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Central Secretariat or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Central Secretariat has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION COMITÉ EUROPÉEN DE NORMALISATION EUROPÄISCHES KOMITEE FÜR NORMUNG

Management Centre: rue de Stassart, 36 B-1050 Brussels

Foreword

The text of ISO 13468-2:1999 has been prepared by Technical Committee ISO/TC 61 "Plastics" of the International Organization for Standardization (ISO) and has been taken over as EN ISO 13468-2:2006 by Technical Committee CEN/TC 249 "Plastics", the secretariat of which is held by IBN.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by October 2006, and conflicting national standards shall be withdrawn at the latest by October 2006.

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland and United Kingdom.

Endorsement notice

The text of ISO 13468-2:1999 has been approved by CEN as EN ISO 13468-2:2006 without any modifications.

INTERNATIONAL STANDARD

ISO 13468-2

> First edition 1999-05-01

Plastics — Determination of the total luminous transmittance of transparent materials —

Part 2:

Double-beam instrument

Plastiques — Détermination du facteur de transmission du flux lumineux total des matériaux transparents —

Partie 2: Instrument à double faisceau



Contents

		Page
Foreword		iii
1	Scope	1
2	Normative references	1
3	Terms and definitions	1
4	Apparatus	1
5	Test specimens	3
6	Conditioning	3
7	Procedure	3
8	Expression of results	4
9	Precision	4
10	Test report	4
Figu	are 1 — Schematic arrangement of the integrating sphere	2
Tab	le 1 — Measurements	3

ii © BSI 2006

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 3.

Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

International Standard ISO 13468-2 was prepared by Technical Committee ISO/TC 61, *Plastics*, Subcommittee SC 5, *Physical-chemical properties*.

ISO 13468 consists of the following parts, under the general title *Plastics* — *Determination of the total luminous transmittance of transparent materials*:

- Part 1: Single-beam instrument;
- Part 2: Double-beam instrument.

© BSI 2006

iv blank

1 Scope

This part of ISO 13468 covers the determination of the total luminous transmittance, in the visible region of the spectrum, of planar transparent and substantially colourless plastics, using a double-beam scanning spectro-photometer. This part of ISO 13468 cannot be used for plastics which contain fluorescent materials.

This part of ISO 13468 is applicable to transparent moulding materials, films and sheets not exceeding 10 mm in thickness.

NOTE 1 Total luminous transmittance can also be determined by a single-beam instrument as in part 1 of this International Standard.

NOTE 2 Substantially colourless plastics include those which are faintly tinted.

NOTE 3 Specimens more than 10 mm thick may be measured provided the instrument can accommodate them, but the results may not be comparable with those obtained using specimens less than 10 mm thick.

2 Normative references

The following normative documents contain provisions which, through reference in this text, constitute provisions of this part of ISO 13468. For dated references, subsequent amendments to, or revisions of, any of these publications do not apply. However, parties to agreements based on this part of ISO 13468 are encouraged to investigate the possibility of applying the most recent editions of the normative documents indicated below. For undated references, the latest edition of the normative document referred to applies. Members of ISO and IEC maintain registers of currently valid International Standards.

ISO 291:1997, Plastics — Standard atmospheres for conditioning and testing.

ISO 5725-1:1994, Accuracy (trueness and precision) of measurement methods and results — Part 1: General principles and definitions.

ISO 5725-2:1994, Accuracy (trueness and precision) of measurement methods and results — Part 2: Basic method for the determination of repeatability and reproducibility of a standard measurement method.

ISO 5725-3:1994, Accuracy (trueness and precision) of measurement methods and results —

Part 3: Intermediate measures of the precision of a standard measurement method.

ISO/CIE 10526:1999, CIE standard illuminants for colorimetry.

ISO/CIE 10527:1991, CIE standard colorimetric observers.

CIE Publication No. 15.2:1986, Colorimetry.

CIE Publication No. 17.4:1987, International lighting vocabulary [also published as IEC 50(845):1987, International electrotechnical vocabulary — Chapter 845: Lighting].

3 Terms and definitions

For the purposes of this part of ISO 13468, the terms and definitions given in CIE Publication No. 17.4 for "transparent medium", "transmittance", "regular transmittance", "radiant flux" and "luminous flux" apply, together with the

3.1

following:

transparent plastics

plastics in which the transmission of light is essentially regular and which have a high transmittance in the visible region of the spectrum

NOTE Provided their geometrical shape is suitable, objects will be seen distinctly through plastic which is transparent in the visible region.

3.2

total spectral transmittance

the ratio of the transmitted radiant flux (regular and diffuse) to the incident radiant flux when a parallel beam of monochromatic radiation of a given wavelength passes through a specimen

3.3

total luminous transmittance


the ratio of the transmitted luminous flux to the incident luminous flux when a parallel beam of light passes through a specimen

4 Apparatus

- **4.1** The apparatus shall consist of the following elements:
 - a stabilized light source;
 - a monochromator;
 - an optical system that forms two parallel beams of monochromatic radiation of equal wavelength λ and approximately equal radiant flux from the output of the monochromator (called the sample and the reference beam);
 - and an integrating sphere fitted with ports and a photodetector.

The sample beam enters the sphere through the entrance port. The reference beam enters the sphere through the reference port. The photodetector is mounted on the photodetector port in a manner that allows it to view with equal efficiency all parts of the sphere. Ingress of external light into the integrating sphere shall be prevented. A schematic arrangement of the integrating sphere is shown in Figure 1.

© BSI 2006 1

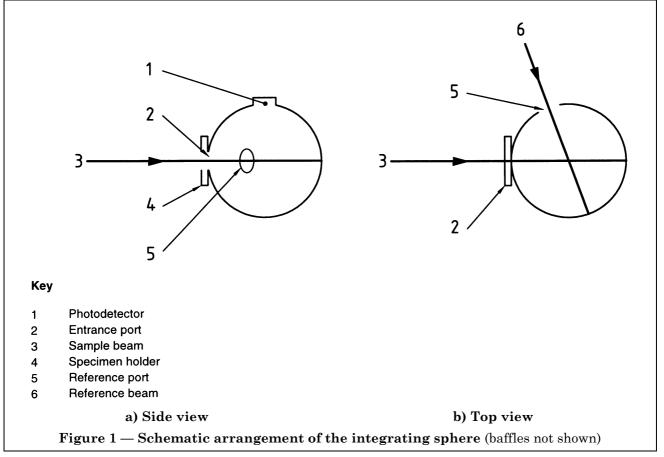

- **4.2** The value of the total luminous transmittance determined by the instrument shall be accurate to \pm 1,0 %. To fulfill this requirement, the response of the photodetector must be sufficiently linear in the visible region of the spectrum and the spectral bandwidth at half power of the monochromator must be sufficiently small. The measurement conditions shall be such that the specimen temperature does not increase while measurements are made.
- **4.3** The optical system shall produce two parallel beams; the angle which any ray of either of these beams makes with the axis of the beam shall not exceed 0,087 rad (5°). The beams shall not be vignetted at either port of the sphere.

The diameter of each beam shall be 0,5 to 0,8 times the diameter of its respective port.

4.4 Using this instrument, the repeatability standard deviation shall be 0,2 % or less. The within-laboratory reproducibility over long time intervals shall not exceed the repeatability by a factor of more than 3.

- **4.5** The design of the instrument shall be such that the total spectral transmittance is zero when the radiant flux incident on the specimen is zero.
- **4.6** The integrating sphere may be of any diameter as long as the total port area does not exceed 3,0% of the internal area of the sphere.
- NOTE 1 $\,$ It is recommended that the diameter of the integrating sphere is not less than 150 mm so that specimens of a reasonable size can be used.
- NOTE 2 When the diameter of the integrating sphere is 150 mm and the diameters of the entrance, reference and photodetector ports are 30 mm, the ratio of the total port area to the internal area of the sphere is 3,0 %.
- 4.7 The entrance and reference ports of the integrating sphere shall be circular and of the same size (see the note below). The angle between the straight line defined by the centre of the entrance port and the centre of the sphere and the straight line defined by the centre of the reference port and the centre of the sphere shall be less than or equal to 90°. The angle between each of these straight lines and the straight line defined by the centre of the photodetector port and the centre of the sphere shall be 90°.

 $NOTE\ \ The entrance$ and reference ports may have other shapes provided they give the same total luminous transmittance values.

2 © BSI 2006

- **4.8** The photodetector shall be fitted with baffles to prevent light falling on it directly from the specimen. It shall also be shielded from light reflected from the internal surface of the sphere.
- **4.9** The surfaces of the interior of the integrating sphere and the baffles shall be of substantially equal luminous reflectance which, determined in accordance to ISO 7724-2, shall be 90 % or more and shall not vary by more than \pm 3 %. When direct measurement of the reflectance of the internal surface of an integrating sphere is difficult, the measurement may be carried out instead on a surface prepared from the same material in the same way as the internal surface.
- **4.10** The apparatus shall be contained in a light-tight box. No radiant flux other than the sample and reference beams may enter the sphere.
- **4.11** The specimen holder shall be such as to hold the specimen rigidly in a plane normal \pm 2° to the sample beam and as close as possible to the entrance port of the integrating sphere to ensure that all light which passes through the specimen, including scattered light, is collected.

The holder shall be designed so that it keeps flexible specimens, such as film, flat.

NOTE It is recommended that thin, flexible film is clamped round the edge in a double-ring-type holder or double-sided adhesive tape is used to stick it to the edge of the holder. The latter method is used for thicker specimens, which cannot be mounted in the double-ring-type holder.

- **4.12** Errors caused by inter-reflections between the optics and the sample shall be minimized by tilting sensitive components or by applying an anti-reflection coating to them.
- **4.13** The apparatus shall allow the wavelength λ to be varied over the range 380 nm $\leq \lambda \leq$ 780 nm in intervals of 5 nm.

NOTE In most cases, a bandwidth of 5 nm will be sufficiently small to fulfill the requirements of subclause **4.2**.

4.14 By blocking each of the beams in turn, the radiant flux of each beam can be made equal to zero. The apparatus includes provision for recording the ratio

$$\xi(\lambda) = I_{\text{sam}}(\lambda)/I_{\text{ref}}(\lambda)$$

of two photodetector signals $I_{\rm sam}(\lambda)$ and $I_{\rm ref}(\lambda)$ as a function of wavelength λ . $I_{\rm sam}(\lambda)$ is measured with the reference beam blocked, $I_{\rm ref}(\lambda)$ with the sample beam blocked.

5 Test specimens

5.1 Specimens shall be cut from film, sheet or injection-moulded or compression-moulded mouldings.

- **5.2** Specimens shall be free of defects, dust, grease, adhesive from protecting materials, scratches and blemishes, and shall be free from visibly distinct internal voids and particles.
- **5.3** Specimens shall be large enough to cover the entrance port of the integrating sphere.

NOTE 1 $\,$ For a 150 mm diameter sphere, a disc of 50 mm or 60 mm in diameter or a square with a side of the same length is recommended.

NOTE 2 Concerning specimen thickness, see note 3 to clause 1.

5.4 Three specimens shall be taken from each sample of a given material unless otherwise specified.

6 Conditioning

6.1 Prior to the test, condition the specimens in accordance with ISO 291, at 23 $^{\circ}$ C \pm 2 $^{\circ}$ C and (50 \pm 5) % relative humidity, for a length of time dependent on the specimen thickness and material such that the specimens reach thermal equilibrium.

NOTE $\,\,$ 16 h is usually sufficient for specimens less than 0,025 mm thick. For thicker material, more than 40 h is recommended.

6.2 Set up the test apparatus in an atmosphere maintained at 23 °C \pm 2 °C and (50 \pm 5) % relative humidity.

7 Procedure

- **7.1** Allow the apparatus sufficient time to reach thermal equilibrium before making any measurements.
- **7.2** Make the two readings described in Table 1. The specimen shall be mounted directly over the entrance port of the integrating sphere.

Table 1 — Measurements

Reading	Specimen over		
	entrance port	reference port	
$\xi_1(\lambda)$	No	No	
$\xi_2(\lambda)$	Yes	No	

Repeat the measurements of $\xi_1(\lambda)$ and $\xi_2(\lambda)$ at intervals of 5 nm to give a total of 81 spectral $\xi_1(\lambda)$ -values and 81 spectral $\xi_2(\lambda)$ -values at λ = 380 nm, 385 nm, 390 nm, ..., 775 nm, 780 nm.

Concerning the use of abridged or truncated data, CIE Publication No. 15.2:1986 applies.

- **7.3** Repeat the readings $\xi_1(\lambda)$ and $\xi_2(\lambda)$ with the specimen in positions selected to determine uniformity.
- 7.4 Measure the thickness of the specimen in three places to an accuracy of 0,02 mm for sheet and 1 μm for film.

© BSI 2006 3

7.5 Carry out the procedure on each of the three specimens in turn.

8 Expression of results

Calculate the total spectral transmittance, $\tau_t(\lambda)$, in percent, using the following equation:

$$\tau_{t}(\lambda) = \frac{\xi_{2}(\lambda)}{\xi_{1}(\lambda)} \times 100$$

Calculate the total luminous transmittance for CIE standard illuminant D_{65} , using the following equation with

 $\lambda = 380 \text{ nm}, 385 \text{ nm}, 390 \text{ nm}, ..., 775 \text{ nm}, 780 \text{ nm}$:

$$\tau_{t} = \frac{\sum_{\lambda = 380 \text{ nm}}^{780 \text{ nm}} S(\lambda) \times \tau_{t}(\lambda) \times V(\lambda)}{\sum_{\lambda = 380 \text{ nm}}^{780 \text{ nm}} S(\lambda) \times V(\lambda)}$$

where

- $S(\lambda)$ is the relative spectral power distribution of CIE standard illuminant D_{65} as given in Table 1 in ISO/CIE 10526:1999;
- $V(\lambda)$ represents the spectral luminous efficiency and is identical to the colour-matching function $\bar{y}(\lambda)$ as given in Table 1 in ISO/CIE 10527:1991.

9 Precision

The precision of this test method is not known because inter-laboratory data are not available yet. As soon as inter-laboratory data are obtained, a precision statement in accordance with ISO 5725-1, ISO 5725-2 and ISO 5725-3 will be added at the next revision.

10 Test report

The test report shall include the following:

- a) all details necessary for identification of the test specimens and the source of the specimens;
- b) the thickness of the specimens (the average of the three measurements);
- c) the total luminous transmittance $\tau_{\rm t}$ for CIE standard illuminant D_{65} (the average of the three calculated results to the nearest 0,1 %).

4 © BSI 2006

BS EN ISO 13468-2:2006

BSI — British Standards Institution

BSI is the independent national body responsible for preparing British Standards. It presents the UK view on standards in Europe and at the international level. It is incorporated by Royal Charter.

Revisions

British Standards are updated by amendment or revision. Users of British Standards should make sure that they possess the latest amendments or editions.

It is the constant aim of BSI to improve the quality of our products and services. We would be grateful if anyone finding an inaccuracy or ambiguity while using this British Standard would inform the Secretary of the technical committee responsible, the identity of which can be found on the inside front cover. Tel: +44 (0)20 8996 9000. Fax: +44 (0)20 8996 7400.

BSI offers members an individual updating service called PLUS which ensures that subscribers automatically receive the latest editions of standards.

Buying standards

Orders for all BSI, international and foreign standards publications should be addressed to Customer Services. Tel: +44 (0)20 8996 9001. Fax: +44 (0)20 8996 7001. Email: orders@bsi-global.com. Standards are also available from the BSI website at $\frac{\text{http://www.bsi-global.com}}{\text{http://www.bsi-global.com}}.$

In response to orders for international standards, it is BSI policy to supply the BSI implementation of those that have been published as British Standards, unless otherwise requested.

Information on standards

BSI provides a wide range of information on national, European and international standards through its Library and its Technical Help to Exporters Service. Various BSI electronic information services are also available which give details on all its products and services. Contact the Information Centre. Tel: +44 (0)20 8996 7111. Fax: +44 (0)20 8996 7048. Email: info@bsi-global.com.

Subscribing members of BSI are kept up to date with standards developments and receive substantial discounts on the purchase price of standards. For details of these and other benefits contact Membership Administration.

Tel: +44 (0)20 8996 7002. Fax: +44 (0)20 8996 7001.

Email: membership@bsi-global.com.

Information regarding online access to British Standards via British Standards Online can be found at http://www.bsi-global.com/bsonline.

Further information about BSI is available on the BSI website at http://www.bsi-global.com.

Copyright

Copyright subsists in all BSI publications. BSI also holds the copyright, in the UK, of the publications of the international standardization bodies. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means — electronic, photocopying, recording or otherwise — without prior written permission from BSI.

This does not preclude the free use, in the course of implementing the standard, of necessary details such as symbols, and size, type or grade designations. If these details are to be used for any other purpose than implementation then the prior written permission of BSI must be obtained.

Details and advice can be obtained from the Copyright & Licensing Manager. Tel: +44 (0)20 8996 7070. Fax: +44 (0)20 8996 7553. Email: copyright@bsi-global.com.

BSI 389 Chiswick High Road London

W4 4AL