

Fibre-reinforced plastic composites — Determination of apparent interlaminar shear strength by short-beam method

The European Standard EN ISO 14130:1997 has the status of a
British Standard

ICS 83.120

National foreword

This British Standard is the English language version of EN ISO 14130:1997. It is identical with ISO 14130:1997, including Technical Corrigendum November 2003.

The UK participation in its preparation was entrusted to Technical Committee PRI/42, Fibre reinforced thermosetting plastics and prepregs, which has the responsibility to:

- aid enquirers to understand the text;
- present to the responsible international/European committee any enquiries on the interpretation, or proposals for change, and keep the UK interests informed;
- monitor related international and European developments and promulgate them in the UK.

A list of organizations represented on this committee can be obtained on request to its secretary.

Cross-references

The British Standards which implement international or European publications referred to in this document may be found in the *BSI Catalogue* under the section entitled “International Standards Correspondence Index”, or by using the “Search” facility of the *BSI Electronic Catalogue* or of British Standards Online.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

Compliance with a British Standard does not of itself confer immunity from legal obligations.

This British Standard, having been prepared under the direction of the Sector Board for Materials and Chemicals, was published under the authority of the Standards Board and comes into effect on 15 April 1998

© BSI 7 May 2004

Summary of pages

This document comprises a front cover, an inside front cover, the EN ISO title page, the EN ISO foreword page, the ISO title page, page ii, pages 1 to 8, an inside back cover and a back cover.

The copyright notice displayed in this document indicates when the document was last issued.

Amendments issued since publication

| Amd. No. | Date | Comments |
|----------|------------|---|
| 15091 | 7 May 2004 | Changes to 2, 4.1, 4.2, 6.2, 9.2, 9.7, 10.1, 10.3 and Figure 4 |
| | | |
| | | |
| | | |

ICS 83.120
Descriptors: see ISO document

English version

Fibre-reinforced plastic composites — Determination of apparent interlaminar shear strength by short-beam method

(ISO 14130:1997)

Composites plastiques renforcés de fibres —
Détermination de la résistance au cisaillement
interlaminaire apparent par essai de flexion sur
appuis rapprochés (ISO 14130:1997)

Faserverstärkte Kunststoffe — Bestimmung
der scheinbaren interlaminaren Scherfestigkeit
nach dem Dreipunktverfahren mit kurzem
Balken (ISO 14130:1997)

This European Standard was approved by CEN on 23 November 1997.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Central Secretariat or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Central Secretariat has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and United Kingdom.

CEN

European Committee for Standardization
Comité Européen de Normalisation
Europäisches Komitee für Normung

Central Secretariat: rue de Stassart 36, B-1050 Brussels

Foreword

The text of the International Standard ISO 14130:1997 has been prepared by Technical Committee ISO/TC 61 "Plastics" in collaboration with Technical Committee CEN/TC 249 "Plastics", the secretariat of which is held by IBN.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by June 1998, and conflicting national standards shall be withdrawn at the latest by June 1998.

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and the United Kingdom.

Endorsement notice

The text of the International Standard ISO 14130:1997 was approved by CEN as a European Standard without any modification.

NOTE Normative references to International Standards are listed in Annex ZA (normative).

INTERNATIONAL
STANDARD

ISO
14130

First edition
1997-12-15

Incorporating Technical Corrigendum
2003-11-01

**Fibre-reinforced plastic composites —
Determination of apparent interlaminar
shear strength by short-beam method**

*Composites plastiques renforcés de fibres — Détermination de
la résistance au cisaillement interlaminaire apparent par essai de flexion
sur appuis rapprochés*



Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

International Standard ISO 14130 was prepared by Technical Committee ISO/TC 61, *Plastics*, Subcommittee SC 13, *Composites and reinforcement fibres*.

It cancels and replaces International Standard ISO 4585:1989. The main changes are as follows:

The scope of ISO 4585 has been extended to include all current and future textile-diameter fibre-reinforced plastic composites which fail in the required manner, with an additional requirement for a standard specimen thickness of 2 mm. The 3 mm thick specimen is still available as an alternative using the specimen scaling rules given in 6.1.2, but, although the test span at 15 mm is the same as previously, the width is now 15 mm (cf. 10 mm previously).

Descriptors: plastics, reinforced plastics, tests, shear tests, determination, shear strength, test specimens.

1 Scope

1.1 This International Standard specifies a procedure for determining the apparent interlaminar shear strength of fibre-reinforced plastic composites by the short-beam method.

1.2 The method is suitable for use with fibre-reinforced plastic composites with a thermoset or a thermoplastic matrix, providing interlaminar shear failure is obtained.

NOTE When using other than laminated materials which are not symmetrical and balanced, the results may be affected by various couplings such as extension/bending, bending/twisting, etc.

1.3 The method is not suitable for the determination of design parameters, but may be used for screening materials, or as a quality-control test.

2 Normative references

The following standards contain provisions which, through reference in this text, constitute provisions of this International Standard. At the time of publication, the editions indicated were valid. All standards are subject to revision, and parties to agreements based on this International Standard are encouraged to investigate the possibility of applying the most recent editions of the standards indicated below. Members of IEC and ISO maintain registers of currently valid International Standards.

ISO 291:1997, *Plastics — Standard atmospheres for conditioning and testing*.

ISO 1268 (all parts), *Fibre-reinforced plastics — Methods of producing test plates*.

ISO 2602:1980, *Statistical interpretation of test results — Estimation of the mean — Confidence interval*.

ISO 2818:1994, *Plastics — Preparation of test specimens by machining*.

ISO 5893:2002, *Rubber and plastics test equipment — Tensile, flexural and compression types (constant rate of traverse) — Specification*.

3 Principle

A bar of rectangular cross-section is loaded as a simple beam in flexure so that interlaminar shear failure occurs. The bar rests on two supports and the load is applied by means of a loading member midway between the supports.

NOTE 1 The test is similar in nature to the three-point loading method used to determine the flexural properties of plastics (ISO 14125, *Fibre-reinforced plastic composites — Determination of flexural properties*). However, a smaller test span/specimen thickness ratio is adopted to increase the level of shear stress relative to the flexural stress in the test specimen to encourage interlaminar shear failure.

NOTE 2 It is emphasized that the result obtained is not an absolute value. For this reason the term “apparent interlaminar shear strength” is used to define the quantity measured. Test results from different-sized specimens, or from specimens tested under different conditions, are not directly comparable.

4 Definitions

For the purposes of this International Standard, the following definitions apply:

4.1

apparent interlaminar shear stress, τ

the interlaminar shear stress acting on the neutral plane of the specimen

It is calculated from Equation (1) in 10.1 and is expressed in megapascals (MPa).

4.2

apparent interlaminar shear strength, τ_M

the value of the apparent interlaminar shear stress at failure or when the load reaches a maximum value

It is calculated from Equation (2) in 10.1 and is expressed in megapascals (MPa).

4.3

span, L

the distance between the two specimen supports in the test machine

It is expressed in millimetres (mm).

4.4

specimen coordinate axes (for aligned materials)

the coordinate axes for the material under test are defined in Figure 1. The direction parallel to the fibre axes is defined as the “1” direction and the direction perpendicular to it the “2” direction.

For other materials, the 1, 2 and 3 directions are generally described by the x, y, z system of coordinates

NOTE 1 The “1” direction is also referred to as the 0 degree (0°) or longitudinal direction, and the “2” direction as the 90 degree (90°) or transverse direction.

NOTE 2 A similar definition can be used for material with a preferred fibre lay-up or in cases where a direction (e.g. the lengthwise direction) can be related to the production process (i.e. directions A and B in Figure 3).

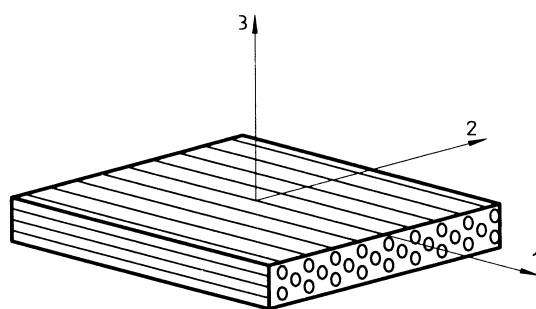


Figure 1 — Unidirectional reinforced composite plate element showing symmetry axes

5 Apparatus

5.1 Test machine

5.1.1 General

The machine shall conform to ISO 5893 as appropriate to the requirements given in 5.1.2 and 5.1.3.

5.1.2 Speed of testing

The speed of testing v shall be kept constant in accordance with ISO 5893.

5.1.3 Load indicator

The load indicator shall be such that the error in the indicated load is less than $\pm 1\%$ of full scale (see ISO 5893).


5.2 Loading member and supports

The radius of the loading member r_1 shall be $5\text{ mm} \pm 0,2\text{ mm}$ and that of the supports r_2 shall be $2\text{ mm} \pm 0,2\text{ mm}$ (see Figure 2).

The width of the loading member and the supports shall be greater than the test specimen width. The loading member shall apply the load mid-way between the supports. The span (distance between the supports) shall be adjustable.

5.3 Micrometer, or equivalent, capable of reading to $0,01\text{ mm}$ or less, and suitable for measuring the width b and thickness h of the test specimen.

The micrometer shall have contact faces appropriate to the surface being measured (i.e. flat faces for flat, polished surfaces and hemispherical faces for irregular surfaces).

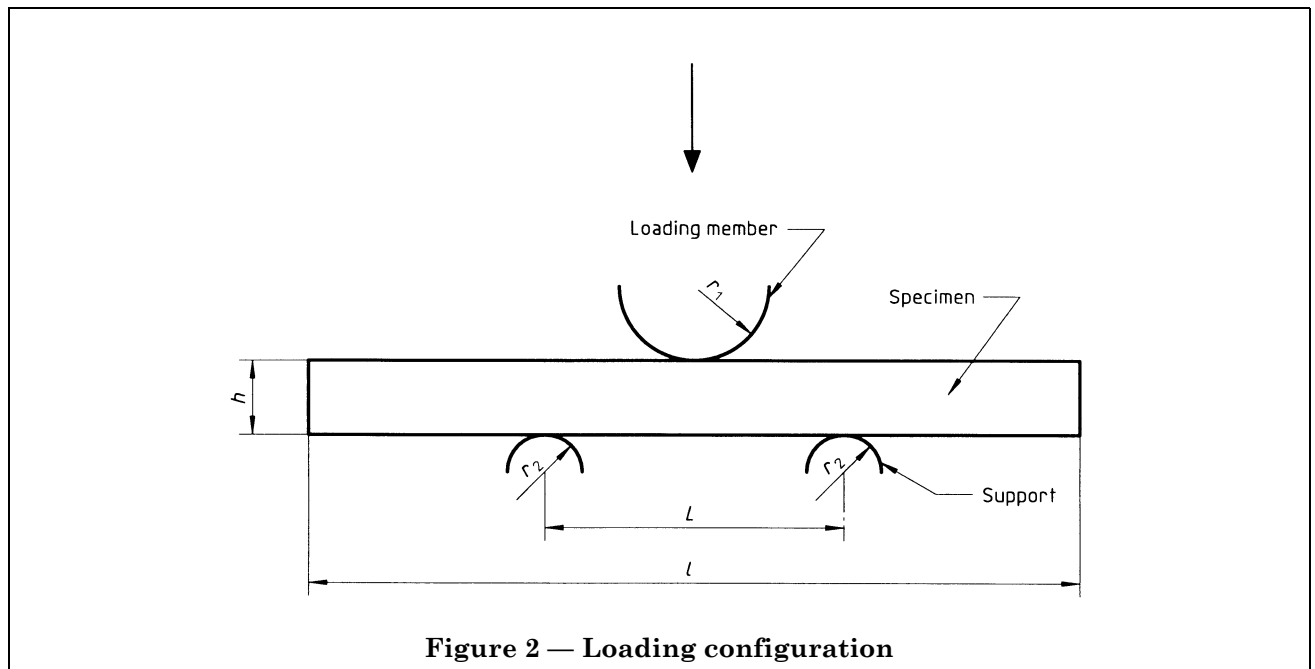

6 Test specimens

6.1 Shape and dimensions

6.1.1 Standard specimen size

Unless 6.1.2 applies, test specimens shall comprise rectangular bars of uniform thickness with the dimensions given in Table 1.

Table 1

| Thickness, h mm | Overall length, l mm | Width, b mm |
|----------------------|---------------------------|------------------|
| $2 \pm 0,2$ | 20 ± 1 | $10 \pm 0,2$ |

6.1.2 Other test specimens

When it is not possible or not desirable to use the standard specimen, the following rules shall be observed:

- the length and the thickness of the test specimen shall be in the same ratio as in the standard specimen, i.e.

$$l = 10h$$

- the width shall be chosen in the same ratio to the thickness as in the standard specimen, i.e.

$$b = 5h$$

NOTE Depending upon the material being tested, specimens of 2 mm thickness may fail by shear or experience compression failure under load or exhibit extreme deflection without shear failure. As specimen thickness (height) is increased, the probability of compression failure under load increases and the probability of extreme deflection with no failure decreases. As specimen thickness is decreased, the reverse is true. It is important to select a specimen thickness that will cause specimens to fail by horizontal shear (see 9.7).

6.2 Preparation of specimens

Machine the test specimens from a moulded blank or sheet, prepared in accordance with the relevant part of ISO 1268 or another specified/agreed procedure. Some parameters for machining are given in ISO 2818.

6.3 Checking the test specimens

The specimens shall be flat and free of twist. The surfaces and edges shall be free from defects. The thickness along the whole length shall be within $\pm 5\%$ of the mean thickness. The width of individual specimens shall be constant to within 0,2 mm.

Specimens showing measurable or observable departure from one or more of these requirements shall be rejected or machined to the required size and shape before testing.

7 Number of test specimens

7.1 At least five test specimens shall be tested.

7.2 When the fibre orientation and distribution in the material to be tested does not differ significantly between the two principal directions, shear specimens shall be taken in each of these two directions (see Figure 3, specimens A and B). When the material has a preferred orientation, the specimens shall be taken in this direction.

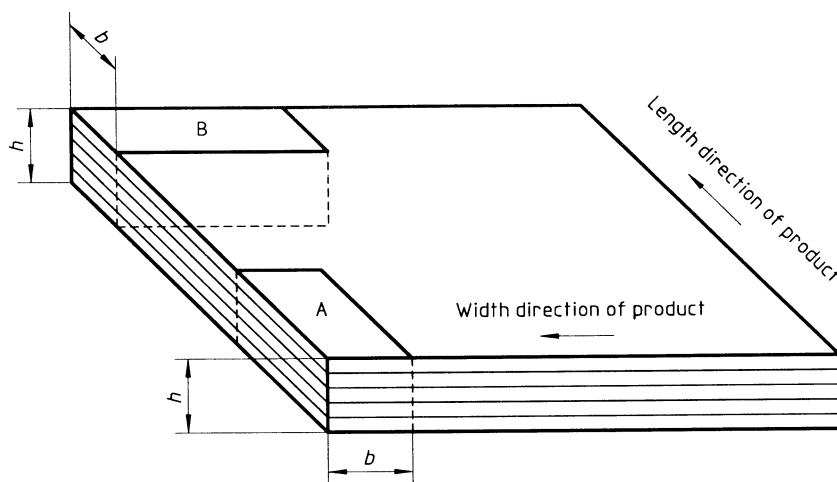


Figure 3 — Location of specimens

8 Conditioning

Where applicable, condition the test specimens as specified in the standard for the material under test. In the absence of such information, select the most appropriate conditions from ISO 291, unless agreed otherwise by the interested parties.

9 Procedure

9.1 Test atmosphere

Conduct the test in the same atmosphere as that used for conditioning unless agreed otherwise by the interested parties (e.g. for testing at elevated or reduced temperatures).

9.2 Measurement of specimen dimensions

Measure, at the mid-point of each test specimen, the width b and the thickness h of the specimen to the nearest 0,02 mm.

9.3 Span

Set the span L to $5h \pm 0,3$ mm, where h is the mean thickness of the set of specimens (see Figure 2).

NOTE For some materials, a shorter span may be necessary to produce interlaminar shear failure (see 9.7).

9.4 Speed of testing

Where applicable, set the speed of testing as given in the standard for the material being tested. In the absence of this information, the speed of testing v shall be $1 \text{ mm/min} \pm 0,2 \text{ mm/min}$.

9.5 Actual testing

Place the test specimen symmetrically across the two parallel supports with an unmachined surface in contact with the supports (see Figure 2). Apply the force uniformly across the width of the test piece by means of the loading member, parallel to and midway between the supports.

9.6 Data collection

Record the force throughout the test.

9.7 Mode of failure

Record the mode of failure using the following classification:

Acceptable interlaminar shear failure modes:

- a) single shear, multiple shear [see Figure 4a)].

Unacceptable failure modes:

- b) mixed modes of failure [see Figure 4b)]: shear and tension, shear and compression;
- c) non-shear modes of failure [see Figure 4c)]: tension, compression;
- d) plastic shear [see Figure 4d)].

NOTE There are two possible failure cases:

- for failure by mode “a”, approximately in the plane of the neutral axis, the apparent interlaminar shear stress can be calculated as shown in 10.1;
- for failure by modes “b” and “c”, the result calculated in accordance with 10.1 is not an apparent interlaminar shear stress and may only be used to compare test specimens taken from the same material.

10 Calculation and expression of results

10.1 Calculate the apparent interlaminar shear stress τ , expressed in megapascals, using the following equation:

$$\tau = \frac{3}{4} \times \frac{F}{bh} \quad (1)$$

where

- F is the load, in newtons;
- b is the width, in millimetres, of the test specimen;
- h is the thickness, in millimetres, of the test specimen.

Calculate the apparent interlaminar shear strength τ_M , expressed in megapascals, using the following equation:

$$\tau_M = \frac{3}{4} \times \frac{F_M}{bh} \quad (2)$$

where


- F_M is the failure or maximum load, in newtons;
- b is the width, in millimetres, of the test specimen;
- h is the thickness, in millimetres, of the test specimen.

10.2 Calculate the arithmetic mean of the individual determinations and, if required, the standard deviation using the procedure given in ISO 2602.

10.3 Calculate the apparent interlaminar shear stress and shear strength to three significant figures.

11 Precision

The precision of this test method is not known because interlaboratory data are not available. When interlaboratory data are obtained, a precision statement will be added at the following revision. This method may not be suitable for use in specifications or in the case of disputed results as long as these data are not available.

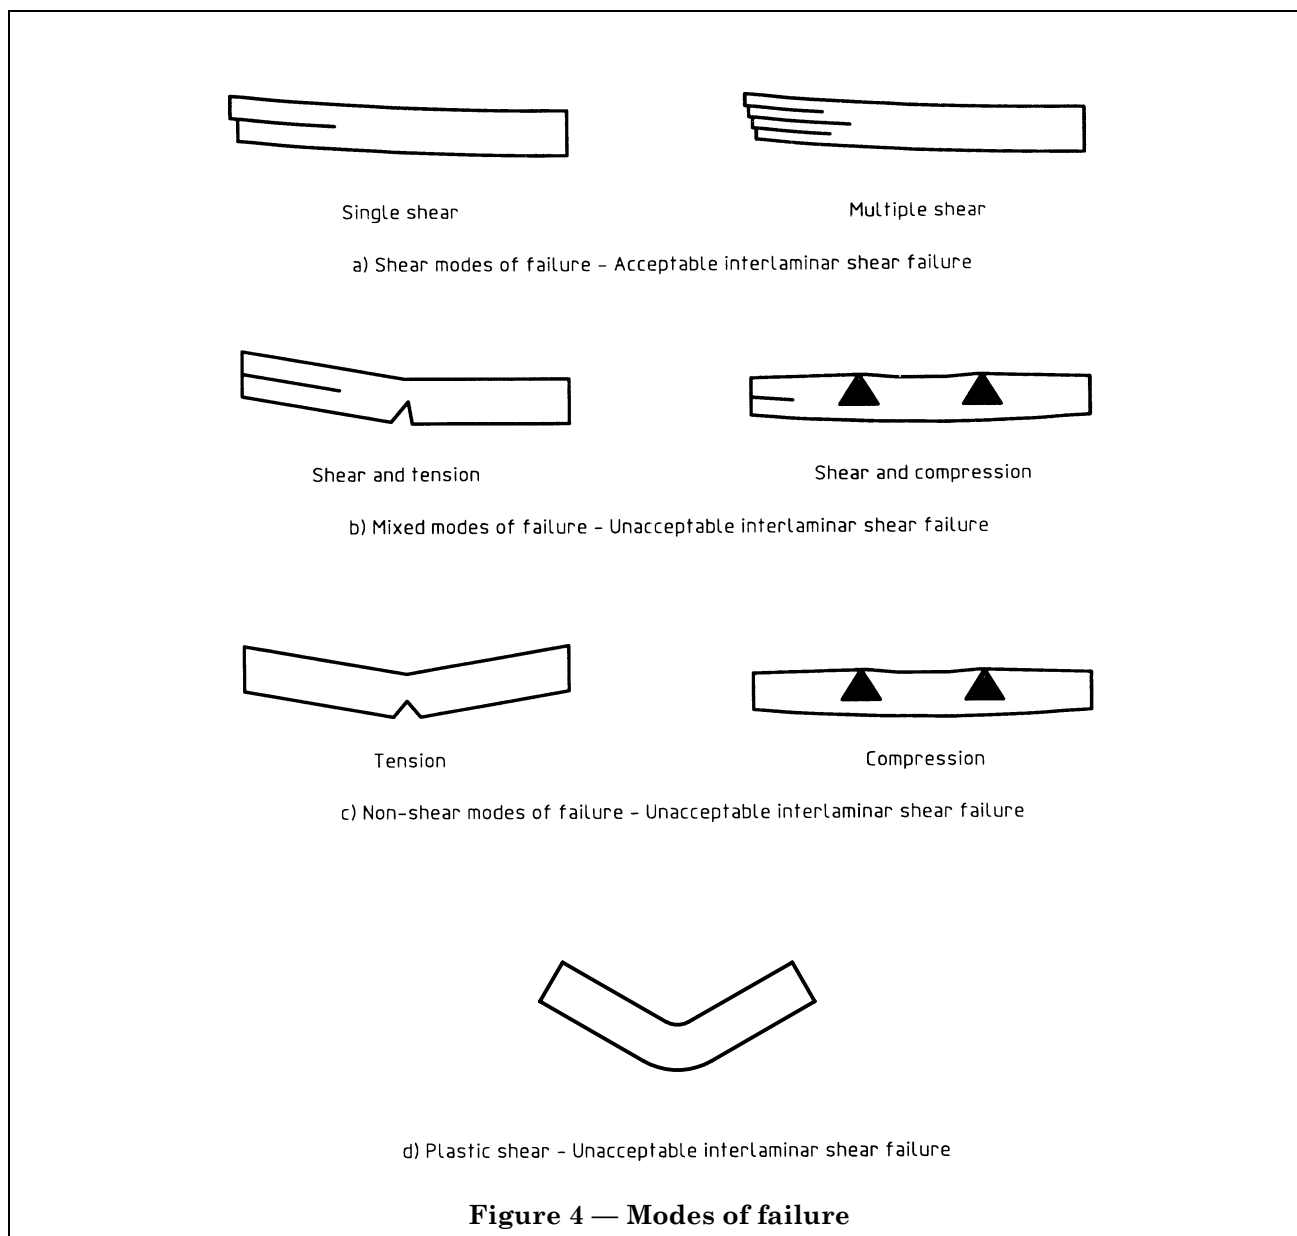

12 Test report

The test report shall include the following information:

- a) a reference to this International Standard and the test speed (e.g. ISO 14130/1);
- b) all details necessary for complete identification of the material tested, including type, source, manufacturer's code number, form and previous history, where these are known;
- c) the accuracy grading of the test machine (see ISO 5893);
- d) the radius of the loading member and that of the supports;
- e) all relevant information on the preparation of the test specimens, including information on the direction of cutting/testing (e.g. specimen A or B in Figure 3, or direction 1 or 2);
- f) the dimensions of the test specimens;
- g) the number of specimens tested;
- h) the test conditions and the conditioning procedures, if applicable;
- i) the span used;
- j) the specimen surface in contact with the loading member;
- k) for test specimens which failed by interlaminar shear [see 9.7 and Figure 4a)], the mode of failure (single or multiple shear), plus the individual apparent interlaminar shear strength values, their arithmetic mean and, if required, the standard deviation;
- l) for test specimens which did not fail by interlaminar shear [see 9.7 and Figure 4b), Figure 4c) and Figure 4d)], a full description of the mode of failure together with the statement that the calculated values are not apparent interlaminar shear strengths, plus the individual values, their arithmetic mean and, if required, the standard deviation;
- m) any operation not specified in this International Standard, as well as any incident likely to have affected the results;
- n) the date of the test.

Annex ZA (normative)**Normative references to international publications with their relevant European publications**

This European Standard incorporates by dated or undated reference, provisions from other publications.

These normative references are cited at the appropriate places in the text and the publications are listed hereafter. For dated references, subsequent amendments to or revisions of any of these publications apply to this European Standard only when incorporated in it by amendment or revision. For undated references the latest edition of the publication referred to applies.

| <u>Publication</u> | <u>Year</u> | <u>Title</u> | <u>EN</u> | <u>Year</u> |
|--------------------|-------------|--|-------------|-------------|
| ISO 291 | 1997 | Plastics — Standard atmospheres for conditioning and testing | EN ISO 291 | 1997 |
| ISO 2818 | 1994 | Plastics — Preparation of test specimens by machining | EN ISO 2818 | 1996 |

BSI — British Standards Institution

BSI is the independent national body responsible for preparing British Standards. It presents the UK view on standards in Europe and at the international level. It is incorporated by Royal Charter.

Revisions

British Standards are updated by amendment or revision. Users of British Standards should make sure that they possess the latest amendments or editions.

It is the constant aim of BSI to improve the quality of our products and services. We would be grateful if anyone finding an inaccuracy or ambiguity while using this British Standard would inform the Secretary of the technical committee responsible, the identity of which can be found on the inside front cover.
Tel: 020 8996 9000. Fax: 020 8996 7400.

BSI offers members an individual updating service called PLUS which ensures that subscribers automatically receive the latest editions of standards.

Buying standards

Orders for all BSI, international and foreign standards publications should be addressed to Customer Services. Tel: 020 8996 9001. Fax: 020 8996 7001.

In response to orders for international standards, it is BSI policy to supply the BSI implementation of those that have been published as British Standards, unless otherwise requested.

Information on standards

BSI provides a wide range of information on national, European and international standards through its Library and its Technical Help to Exporters Service. Various BSI electronic information services are also available which give details on all its products and services. Contact the Information Centre.
Tel: 020 8996 7111. Fax: 020 8996 7048.

Subscribing members of BSI are kept up to date with standards developments and receive substantial discounts on the purchase price of standards. For details of these and other benefits contact Membership Administration.
Tel: 020 8996 7002. Fax: 020 8996 7001.

Copyright

Copyright subsists in all BSI publications. BSI also holds the copyright, in the UK, of the publications of the international standardization bodies. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI.

This does not preclude the free use, in the course of implementing the standard, of necessary details such as symbols, and size, type or grade designations. If these details are to be used for any other purpose than implementation then the prior written permission of BSI must be obtained.

If permission is granted, the terms may include royalty payments or a licensing agreement. Details and advice can be obtained from the Copyright Manager.
Tel: 020 8996 7070.