

BS EN ISO 14372:2011



BSI Standards Publication

**Welding consumables —
Determination of moisture
resistance of manual metal
arc welding electrodes by
measurement of diffusible
hydrogen (ISO 14372:2011)**

bsi.

...making excellence a habit.™

National foreword

This British Standard is the UK implementation of EN ISO 14372:2011. It supersedes BS EN ISO 14372:2001 which is withdrawn.

The UK participation in its preparation was entrusted to Technical Committee WEE/39, Welding consumables.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© BSI 2011

ISBN 978 0 580 68395 4

ICS 25.160.20

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 31 July 2011.

Amendments issued since publication

Date	Text affected
------	---------------

English Version

Welding consumables - Determination of moisture resistance of
manual metal arc welding electrodes by measurement of
diffusible hydrogen (ISO 14372:2011)

Produits consommables pour le soudage - Détermination
de la reprise d'humidité des électrodes utilisées en
soudage manuel à l'arc avec électrode enrobée, par
mesurage de l'hydrogène diffusible (ISO 14372:2011)

Schweißzusätze - Bestimmung der Feuchteresistenz von
Elektroden für das Lichtbogenhandschweißen durch
Messung des diffusiblen Wasserstoffs (ISO 14372:2011)

This European Standard was approved by CEN on 30 June 2011.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN-CENELEC Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

Management Centre: Avenue Marnix 17, B-1000 Brussels

Foreword

This document (EN ISO 14372:2011) has been prepared by IIW "International Institute of Welding" in collaboration with Technical Committee CEN/TC 121 "Welding" the secretariat of which is held by DIN.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by January 2012, and conflicting national standards shall be withdrawn at the latest by January 2012.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN [and/or CENELEC] shall not be held responsible for identifying any or all such patent rights.

This document supersedes EN ISO 14372:2001.

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland and the United Kingdom.

Endorsement notice

The text of ISO 14372:2011 has been approved by CEN as a EN ISO 14372:2011 without any modification.

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 14372 was prepared by the International Institute of Welding, recognized as an international standardizing body in the field of welding in accordance with Council Resolution 42/1999.

This second edition cancels and replaces the first edition (ISO 14372:2000), which has been technically revised.

Requests for official interpretations of any aspect of this International Standard should be directed to the ISO Central Secretariat, who will forward them to the IIW Secretariat for an official response.

Introduction

This test method is based on procedures originally put forward within Sub-commission II-A of the International Institute of Welding (IIW) by the delegation from Argentina. It was subsequently evaluated in a round robin exercise within IIW Sub-commission II-A, and served as the basis for ISO 14372:2000. This International Standard was developed with Sub-commissions II-A and II-E of the International Institute of Welding (IIW).

Welding consumables — Determination of moisture resistance of manual metal arc welding electrodes by measurement of diffusible hydrogen

1 Scope

This International Standard specifies a method for the relative ranking, by 24 h exposure to humid air and subsequent diffusible hydrogen testing, of manual metal arc electrode coatings related to their tendency to absorb moisture. This test method has limited potential applicability since it is unlikely to be capable of being scaled up for large volumes of testing.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 3690, *Welding and allied processes — Determination of hydrogen content in arc weld metal*¹⁾

3 Principle

This procedure is presented as a standard method for exposure and control of welding consumables in preparation for, and during, diffusible hydrogen testing. After drying (if applicable), the electrodes are exposed to an air atmosphere of controlled temperature and humidity [27 °C, 80 % relative humidity²⁾ (RH)] by enclosing them in a box containing a saturated solution of ammonium sulfate.

4 Equipment

4.1 Humidity box, made of acrylic or similar inert material, consisting of a box within which test electrodes, a thermometer, and protecting tubes (maximum $\sim 1,5d$, where d is the overall diameter of the electrode, and appropriate length to fit) for holding the electrodes after exposure can be suspended over a saturated solution of ammonium sulfate (see Figure 1).



IMPORTANT — Any attempt to measure relative humidity, if used, shall not cause air circulation within the humidity box.

4.2 Temperature control cabinet, capable of being maintained at a temperature of $27\text{ °C} \pm 1\text{ °C}$. Good results have been achieved using a draught-proof enclosure heated by low-power (40 W) light bulbs, controlled by a calibrated thermostat, or by another suitable thermal source, with a fan for circulating air to maintain uniform air temperature.

1) To be published. (Revision of ISO 3690:2000.)

2) It is not necessary to measure relative humidity within the humidity box. The test conditions are the temperature and the presence of the saturated salt bath. Well-established physical principles relate the relative humidity to these two conditions.

Dimensions in millimetres

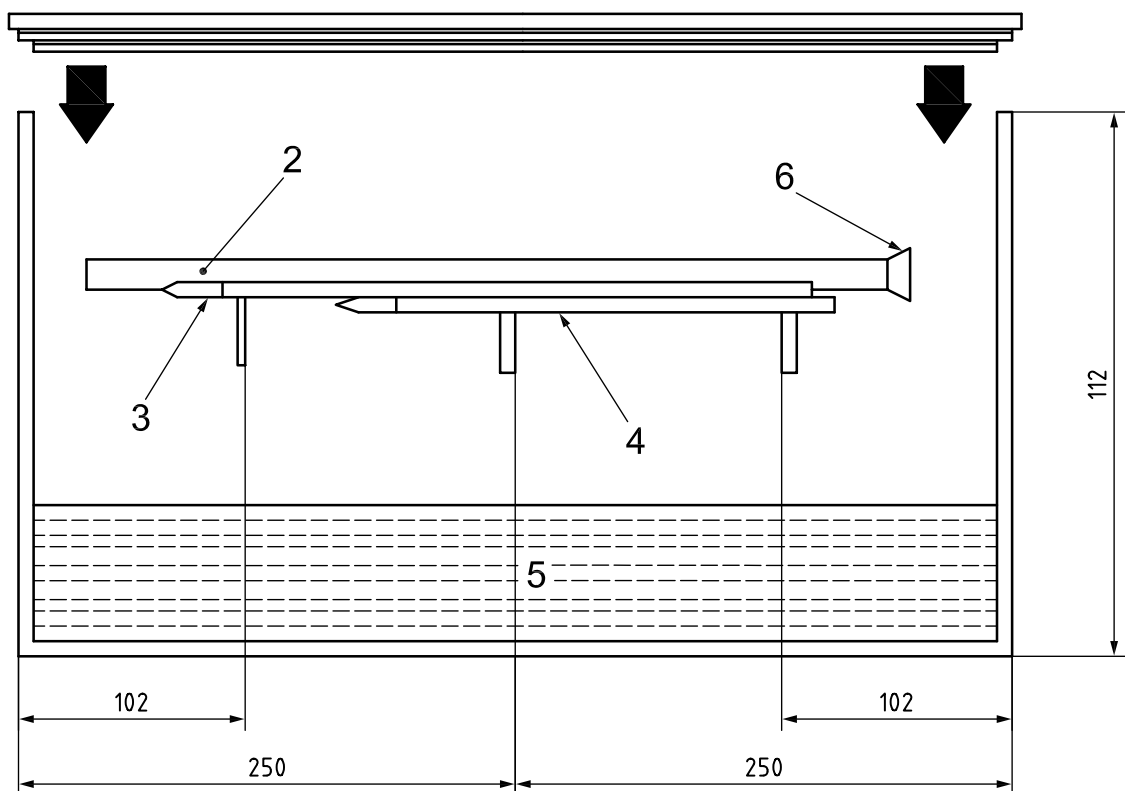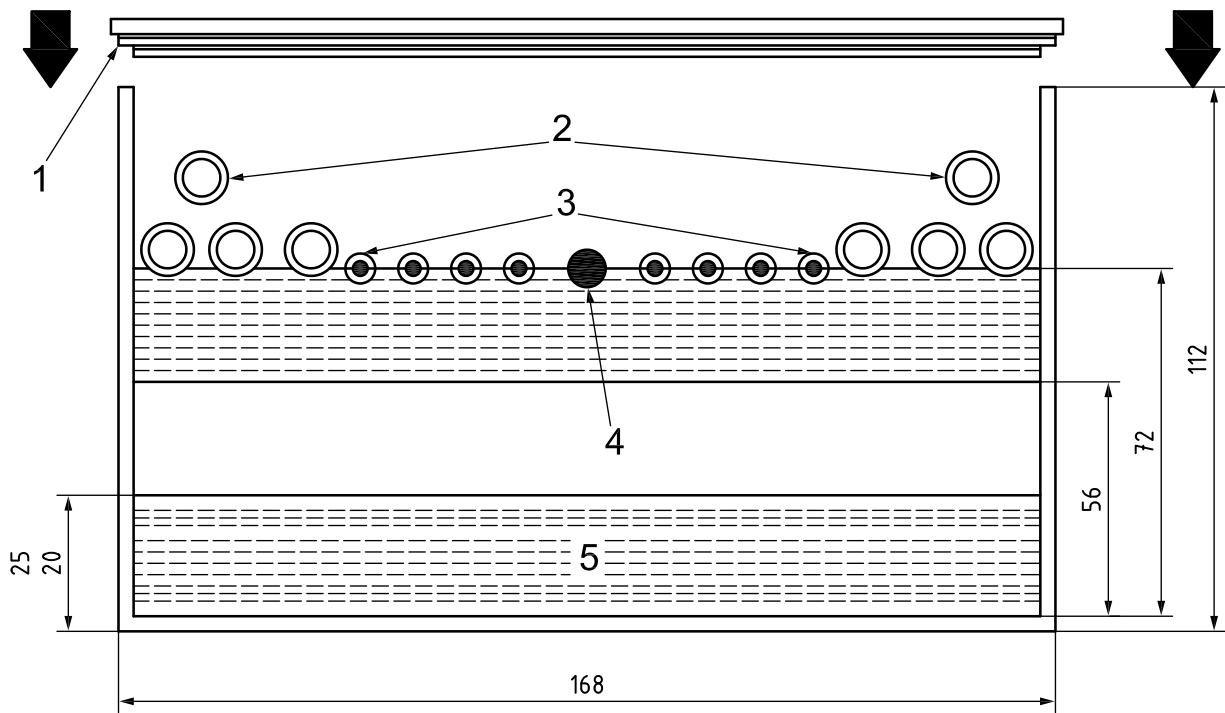

Key

- | | | | | | |
|---|------------------|---|-------------|---|-------------------------------------|
| 1 | packing | 3 | electrodes | 5 | saturated ammonium sulfate solution |
| 2 | protecting tubes | 4 | thermometer | 6 | plugs |

Figure 1 — Sketch of a humidity box

5 Procedure

5.1 Preparation of humidity box

5.1.1 Wash all tubes with distilled water.

5.1.2 Air dry tubes.

5.1.3 Seal one end of each tube with a plug.

5.1.4 Dissolve 1,3 kg anhydrous ammonium sulfate in 1 500 ml distilled water at 40 °C to 45 °C.

5.1.5 Fill the humidity box (4.1) with this solution (5.1.4) to a depth of 20 mm to 25 mm. If the height of solution drops, transfer solution to a mixing vessel, add further saturated solution or distilled water at 45 °C, mixing thoroughly. Refill the box to a depth of 25 mm, ensuring that undissolved ammonium sulfate is present, but does not reduce the surface area of the liquid when restored to the operating temperature of 27 °C.

5.1.6 A finger moistened with silicone oil may be run around the box just above solution level. (This helps prevent crystals creeping up the walls.)

5.1.7 Allow solution to cool to 27 °C ± 1 °C.

5.1.8 Insert protecting tubes, second end plugs (not fitted in tubes) and thermometer, and close lid on box.

5.2 Preparation of temperature control cabinet

5.2.1 Set the temperature to 27 °C ± 1 °C.

5.2.2 Hold the temperature at 27 °C ± 1 °C for at least 90 min.

5.3 Preconditioning of humidity box

Keep the prepared and sealed box in the temperature control cabinet for at least 4 h, with the temperature maintained at 27 °C ± 1 °C.

5.4 Electrode preparation

5.4.1 Mark coatings near the stub end with a unique identity.

5.4.2 Pre-dry (if appropriate) according to manufacturer's instructions.

5.4.3 If electrodes have been dried at elevated temperature, seal in glass tubes using tightly fitting rubber bungs or by melting the ends, or place in a desiccator to cool to room temperature.

5.5 Exposure of electrodes in humidity box

5.5.1 Open the temperature control cabinet (4.2) door.

5.5.2 Open humidity box lid.

5.5.3 Transfer electrodes from glass tubes, desiccator, or manufacturer's packaging, as appropriate, to the humidity box as indicated in Figure 1.

5.5.4 The procedures specified in 5.5.1 to 5.5.3 shall be completed within 90 s.

5.5.5 Replace humidity box lid.

5.5.6 Close temperature control cabinet door.

5.5.7 The procedures specified in 5.5.5 and 5.5.6 shall be completed within a further 30 s.

5.5.8 Expose electrodes at $27\text{ °C} \pm 1\text{ °C}$ for 24 h.

5.6 Measurement of weld deposit hydrogen

5.6.1 Open temperature control cabinet door.

5.6.2 Open humidity box lid.

5.6.3 Insert electrodes into protection tubes, seal ends with plugs, and remove from temperature control cabinet.

5.6.4 The procedures specified in 5.6.2 and 5.6.3 shall be completed within 60 s.

5.6.5 Close humidity box and temperature control cabinet door.

5.6.6 Transfer electrodes in sealed tubes to welding station.

Electrodes shall be welded within 24 h of removal from the humidity box.

5.6.7 Weld and analyse for hydrogen in accordance with ISO 3690.

Welding shall take place within 2 min of removal of electrodes from the sealed tubes.

5.6.8 Record ambient room temperature and relative humidity (RH) at the time of welding.

6 Test report

The test report shall contain at least the following information:

- a) the weld deposit hydrogen levels, expressed in millilitres per 100 g deposited metal, as measured;
- b) a reference to this International Standard (ISO 14372:2011);
- c) trade name of the electrodes tested;
- d) electrode designation;
- e) electrode size;
- f) electrode drying details (temperature and time at temperature);
- g) date and time of completion of exposure;
- h) date and time of beginning of test welding;
- i) measured temperature range during exposure;
- j) measured duration of exposure;
- k) information required by ISO 3690;
- l) temperature and relative humidity at time of welding.

British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at bsigroup.com/standards or contacting our Customer Services team or Knowledge Centre.

Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at bsigroup.com/shop, where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to bsigroup.com/subscriptions.

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

PLUS is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit bsigroup.com/shop.

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email bsmusales@bsigroup.com.

BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK

Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

Copyright

All the data, software and documentation set out in all British Standards and other BSI publications are the property of and copyrighted by BSI, or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI. Details and advice can be obtained from the Copyright & Licensing Department.

Useful Contacts:

Customer Services

Tel: +44 845 086 9001

Email (orders): orders@bsigroup.com

Email (enquiries): cservices@bsigroup.com

Subscriptions

Tel: +44 845 086 9001

Email: subscriptions@bsigroup.com

Knowledge Centre

Tel: +44 20 8996 7004

Email: knowledgecentre@bsigroup.com

Copyright & Licensing

Tel: +44 20 8996 7070

Email: copyright@bsigroup.com



...making excellence a habit.™