BS EN ISO 14921:2010



BSI Standards Publication

Thermal spraying — Procedures for the application of thermally sprayed coatings for engineering components (ISO 14921:2010)



National foreword

This British Standard is the UK implementation of EN ISO 14921:2010. It supersedes BS EN ISO 14921:2001 which is withdrawn.

The UK participation in its preparation was entrusted to Technical Committee STI/40, Thermally sprayed inorganic finishes.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© BSI 2011

ISBN 978 0 580 66613 1

ICS 25.220.20

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 31 January 2011.

Amendments issued since publication

Date Text affected

EUROPEAN STANDARD

EN ISO 14921

NORME EUROPÉENNE EUROPÄISCHE NORM

December 2010

ICS 25.220.20

Supersedes EN ISO 14921:2001

English Version

Thermal spraying - Procedures for the application of thermally sprayed coatings for engineering components (ISO 14921:2010)

Projection thermique - Mode opératoire d'application de revêtements obtenus par projection thermique pour les pièces mécaniques (ISO 14921:2010)

Thermisches Spritzen - Vorgehen für das Anwenden thermischer Spritzschichten für Bauteile im Maschinenbau (ISO 14921:2010)

This European Standard was approved by CEN on 10 December 2010.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN-CENELEC Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION COMITÉ EUROPÉEN DE NORMALISATION EUROPÄISCHES KOMITEE FÜR NORMUNG

Management Centre: Avenue Marnix 17, B-1000 Brussels

Foreword

This document (EN ISO 14921:2010) has been prepared by Technical Committee CEN/TC 240 "Thermal spraying and thermally sprayed coatings", the secretariat of which is held by DIN, in collaboration with Technical Committee ISO/TC 107 "Metallic and other inorganic coatings".

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by June 2011, and conflicting national standards shall be withdrawn at the latest by June 2011.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN [and/or CENELEC] shall not be held responsible for identifying any or all such patent rights.

This document supersedes EN ISO 14921:2001.

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland and the United Kingdom.

Contents Page

Forew	vord	iv
Introd	ductionduction	v
1	Scope	1
2	Normative references	1
3	Terms and definitions	1
4 4.1 4.2 4.3 4.4	Component and coating design considerations	1 2 2
5	Preliminary machining by turning, milling, or grinding	3
6	Masking	3
7	Methods of surface preparation	3
8	Thermal spraying	4
9	Inspection after spraying	4
10	Sealing	4
11	Finishing	4
12	Final inspection	4
13	Documentation	5
Anne	x A (informative) Flow chart for assessment of suitability of thermal spraying	6
Anne	x B (informative) Check list for evaluation of the most suitable coating system for the intended purpose	7
Anne	x C (informative) Record for the applied thermal spray procedure	8
Biblio	ography	12

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 14921 was prepared by Technical Committee CEN/TC 240, *Thermal spraying and thermally sprayed coatings* of the European Committee for Standardization (CEN) in collaboration with ISO Technical Committee ISO/TC 107, *Metallic and other inorganic coatings* in accordance with the Agreement on technical cooperation between ISO and CEN (Vienna Agreement).

This second edition cancels and replaces the first edition (ISO 14921:2001), which has been technically revised.

Introduction

Components might fail if the surface does not fulfil the physical, chemical, and/or technological requirements. For several applications, this deficiency can be avoided by a thermally sprayed coating.

Where appropriate, a coating may be applied to protect the component's surface or to improve its behaviour by increasing the resistance against wear and/or corrosion, or the electrical or thermal conductivity or insulation or by reducing the friction coefficient.

There are limits to the applicable thickness of some thermally sprayed coatings. However, several different coatings may be built up one upon another. In the case of extensive loss of material through corrosion or wear, an alternative suitable spraying material may be applied prior to the top coat or the bond and top coat.

Thermal spraying — Procedures for the application of thermally sprayed coatings for engineering components

1 Scope

This International Standard specifies the general procedure, when a thermally sprayed coating is applied to enhance the surface properties of a component or to reclaim worn and non-conforming parts.

This International Standard does not provide definitive methods for specific work due to the variety of the technological, physical and/or chemical requirements and of the component's shape.

This International Standard specifies the general conditions for the selection of the spraying procedure and materials for this purpose. It does not apply to thermally sprayed zinc and/or aluminium coatings for protection of steel structures against atmospheric corrosion, for which ISO 2063 applies.

This International Standard also does not apply to coatings of self-fluxing alloys which are subsequently fused. That procedure is covered by ISO 14920.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 14923, Thermal spraying — Characterization and testing of thermally sprayed coatings

EN 657:2005, Thermal spraying — Terminology, classification

EN 13507, Thermal spraying — Pre-treatment of surface of metallic parts and components for thermal spraying

EN 15520, Thermal spraying — Recommendations for constructional design of components with thermally sprayed coatings

3 Terms and definitions

For the purposes of this document, the terms and definitions given in EN 657:2005 apply.

4 Component and coating design considerations

4.1 General

If any of the considerations in 4.2 to 4.4 cannot be met satisfactorily, thermal spraying is not recommended. Factors which should be considered are illustrated in the flow chart shown in Annex A.

Judgements of the possibility for coating new parts may be carried out by assessing the drawing of the component and the area to be sprayed.

If a coating specification defines the spraying material, the factors to be considered are reduced.

4.2 Pre-inspection in the case of repair

Before carrying out a preparation procedure on the component, it shall be inspected to assess its suitability for spraying. Attention shall be given to the following:

- The concentricity and straightness of parts which rotate when operating and the shape and geometry of parts operated with a reciprocating or sliding motion shall be checked and, where necessary, corrected.
- The surface to be coated shall be inspected to check that it is free from cracks or other damage which can affect the performance of the coating. If any serious defects cannot be removed or repaired, spraying cannot be carried out satisfactorily.
- Establish dimensions of the area to be sprayed.
- The component shall be checked for any evidence of a previous coating, which, if present, shall usually be removed.
- Check and take into account the surface hardness of the work piece.

4.3 Component substrate

To establish whether a thermally sprayed coating is suitable for the intended purpose, consideration should be given to the following.

- Certain substrate materials are not suitable for thermal spraying or require special consideration in processing.
- Thermally sprayed coatings do not increase the strength of the part generally, and therefore the effects of any reduction in the dimensions of the original component shall be considered.
- The fatigue strength can be affected by the method of surface preparation, the spray material and the spray procedure.
- Certain processes to improve the surface condition, such as nitriding, can leave gaseous inclusions which
 can have a detrimental effect on the surface preparation, bonding, and porosity in the coating.
- Where hardened surfaces prevent a proper preparation, the limitations of the coating system which can be applied, and the properties subsequently derived, shall be considered.
- The area to be coated shall be accessible for applying the complete coating procedure. Therefore, the requirements for the processes of preparing, spraying and testing, spray gun with its electrical and/or gas connections, required distance and spray angle shall be considered.

4.4 Coating

The spray process and spray material can exert a tremendous influence on the coating properties. To determine the most suitable coating system, consideration of the following is required:

- bond strength requirement;
- thickness requirement;
- surface requirement (roughness);

- surface load; thermally sprayed coatings are sensitive to spot or line stress;
- the coating properties required, e.g. resistance to different types of wear mechanism, corrosion, chemical attack, temperature, thermal cycling, and other environmental conditions;
- where the level of porosity in the coating is unacceptable, it is to be checked, whether a suitable method
 of sealing, and type of sealant is available;
- is it possible to keep the oxide content within the accepted tolerance by control of process variables and the spray material?

Annex B gives a check list which details the information required to determine the most suitable coating system for the intended purpose.

5 Preliminary machining by turning, milling or grinding

Coatings which have to be renewed shall be removed completely. However, consideration shall be given to the condition of a surface treatment previously applied, e.g. for increasing fatigue strength.

Pre-machining shall be carried out to remove wear profiles, if applicable, and to ensure a uniform coating thickness. Sharp edges shall be avoided and shall be rounded or chamfered. Coatings shall be "inlaid" in the component, where possible, or continued around the rounded or chamfered edge. Recommendations for design are given in EN 15520.

The surface to be coated shall be machined concentrically to the relevant axis, to ensure a uniform thickness of the deposit.

Wherever possible, pre-machining shall be carried out without the use of a lubricant. This is particularly important in the case of porous substrate materials.

Where necessary, the component shall be degreased after preliminary machining.

6 Masking

Where appropriate, surfaces that shall not be sprayed can be masked with a suitable material. This material should be resistant to abrasive grit blasting and thermal spraying. Otherwise, separate masking for each operation shall be used.

Precautions shall be taken to ensure that the surface to be sprayed will not be contaminated by the masking material or otherwise at all times.

7 Methods of surface preparation

Contamination caused by pre-treatments shall be removed and the surface shall be cleaned immediately before the specific surface preparation commences.

A suitable surface preparation is required to achieve maximum bond strength to metallic substrates. Grit blasting is the normal method.

The surface preparation shall be in accordance with EN 13507. Deviations from this shall be agreed between the contracting parties.

8 Thermal spraying

The thermally sprayed coating should be applied as soon as possible after preparation, with parameters as given in the thermal spraying procedure specification. Reasonable precautions shall be taken to prevent contamination of the prepared surface during the time period between blasting and spraying.

Where appropriate, the surface to be sprayed may be pre-heated immediately prior to spraying. However, no contamination or local overheating (visible by tempering colour) of the prepared surface shall appear.

Before and during spraying, the surface shall be warm enough to prevent moisture by condensation.

During spraying, control of the temperature is necessary to avoid excessive residual stresses and impairment of the coating performance.

Dust entrapment in the coating shall be minimized.

The spraying equipment shall be operated in accordance with the manufacturer's instructions.

The thermal sprayer or operator should be qualified according to ISO 14918, or an equivalent qualification should be agreed upon by the parties concerned.

9 Inspection after spraying

Inspection of the thermally sprayed coating shall be carried out after cooling down to ambient temperature by

- visual inspection of the coating in accordiance with ISO 14923, and
- measurement of coating thickness.

If any defects are observed, such as de-bonding, cracking or other unacceptable imperfections and deviations from an agreed specification, the coating shall be removed completely and the complete spray procedure including the preparation shall be repeated, perhaps, using a revised spray procedure specification.

10 Sealing

Thermally sprayed coatings can be sealed, where required. For sealing, a range of different sealants and procedures are available. The supplier's instruction shall be followed.

The sealing should be carried out as soon as possible after spraying. If the sealant contains a solvent, this operation shall be carried out after the coating has cooled to an appropriate temperature.

11 Finishing

Coatings can be finished by surface finishing techniques, e.g. turning, milling or grinding. ISO 14924 presents recommendations for machining and other post-treatments of several thermally sprayed coatings.

12 Final inspection

The finished coating should be inspected with regard to the following aspects:

- dimensional accuracy within the required tolerances, as specified;
- specified surface roughness obtained;

- visible coating defects, for example, cavities, score marks, cracks, or spalling (see ISO 14923);
- overspray removal;
- cleanliness of the component;
- other specified requirements, e. g. on accompanying specimens.


13 Documentation

To meet the requirements of quality management, a record of the applied procedure should be established containing all manufacturing steps and, if required, any results of the inspections and measurements.

Annex C shows an example of a record for the applied thermal spray procedure. This record can also be used as a guideline for a spray procedure specification.

Annex A (informative)

Flow chart for assessment of suitability of thermal spraying

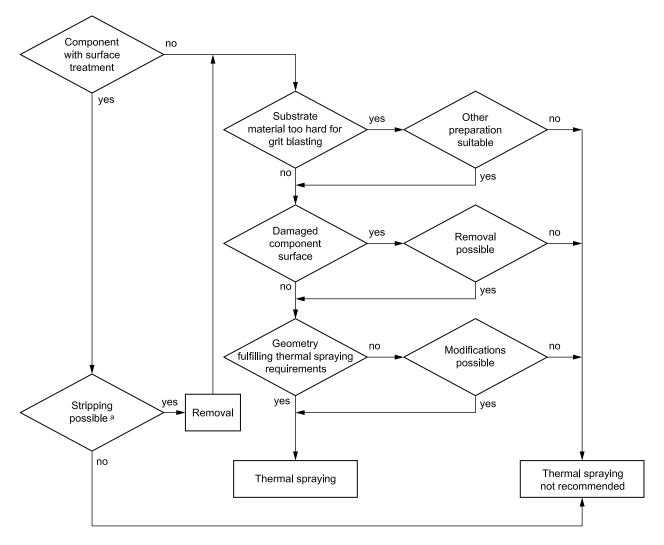

^a Stripping by grinding or chemical or electrochemical means possible.

Annex B

(informative)

Check list for evaluation of the most suitable coating system for the intended purpose

(The user of this form is allowed to copy it.)

1) Designation of the component. 2) Brief description of its function. 3) The area to be coated. 4) Areas to be masked off. 5) Any special precautions to be taken during handling or processing. 6) Function of the coating. Is it a running surface? Yes/No If "Yes", against what? Lubricated? Yes/No If "No", is it subject to abrasion? Yes/No If "Yes", state media. 7) Is it subject to chemical attack by liquids or gases? Yes/No If "Yes", state chemical and concentration. Yes/No 8) Is operating temperature similar to ambient temperature? If "No", state operating temperature. 9) Is any thermal shock applied? Yes/No If "Yes", give details. 10) State thickness requirement. 11) Is the coating to be finished? Yes/No

If "Yes", state finish technique, size, tolerance and roughness.

12) Where applicable, state concentricity requirement.

13) State any special requirement not covered by the above.

The following data should be determined:

© ISO 2010 – All rights reserved

Annex C

(informative)

Record for the applied thermal spray procedure

(The user of this form is allowed to copy it.)

Roughness, e.g. according to ISO 8503-1: Time period between blasting and spraying: Spray procedure, generally Spray material: Designation according to standard: Grain size/wire diameter: Other designation: Preheating: yes/no Preheating temperature: Cooling: yes/no Cooling medium: Coating thickness: as sprayed: Finished:							
Component description: Substrate material: Function of coating: Chemical analysis: Preliminary machined by: Chemical analysis: Preliminary machining Sketch (if applicable) Method of preparation and cleaning: Surface preparation: Program No.: Blasting procedure: Number of sequences: Type of grit: Grain size: Blasting pressure: bar Blasting distance/angle: Visual inspection: Cleanliness, uniformity, e.g. according to ISO 8503-1: Roughness, e.g. according to ISO 8503-1: Time period between blasting and spraying: Spray material: Designation according to standard: Grain size/wire diameter: Other designation: Preheating: yes/no Preheating temperature: °C Cooling: yes/no Cooling medium: Coating thickness: as sprayed: Finished:	Manufacturer:			Location (workshop, on site, client):			
Function of coating: Chemical analysis: Preliminary machined by: Preliminary machining Sketch (if applicable) Method of preparation and cleaning: Surface preparation: Program No: Blasting procedure: Number of sequences: Type of grit: Grain size: Blasting pressure: bar Blasting distance/angle: Visual inspection: Cleanliness, uniformity, e.g. according to ISO 8501-1: Roughness, e.g. according to ISO 8503-1: Time period between blasting and spraying: Spray procedure, generally Spray material: Designation according to standard: Grain size/wire diameter: Other designation: Preheating: yes/no Preheating temperature: °C Cooling: yes/no Cooling medium: Coating thickness: as sprayed: Finished:	Reason for repa	air:					
Preliminary machining Sketch (if applicable) Method of preparation and cleaning: Surface preparation: Program No.: Blasting procedure: Number of sequences: Type of grit: Grain size: Blasting pressure: bar Blasting distance/angle: Visual inspection: Cleanliness, uniformity, e.g. according to ISO 8501-1: Roughness, e.g. according to ISO 8503-1: Time period between blasting and spraying: Spray procedure, generally Spray material: Designation according to standard: Grain size/wire diameter: Other designation: Preheating: yes/no Cooling: yes/no Cooling medium: Coating thickness: as sprayed: Finished:	Component de	scription: .		Substrate material:			
Preliminary machining Sketch (if applicable) Method of preparation and cleaning: Surface preparation: Program No.: Blasting procedure: Number of sequences: Type of grit: Grain size: Blasting pressure: bar Blasting distance/angle: Visual inspection: Cleanliness, uniformity, e.g. according to ISO 8501-1: Roughness, e.g. according to ISO 8503-1: Time period between blasting and spraying: Spray procedure, generally Spray material: Designation according to standard: Grain size/wire diameter: Other designation: Preheating: yes/no Cooling: yes/no Cooling medium: Coating thickness: as sprayed: Finished:	Function of coa	ating:		Chemical analysis:			
Method of preparation and cleaning: Surface preparation: Program No.: Blasting procedure: Number of sequences: Type of grit: Blasting pressure: bar Blasting distance/angle: Visual inspection: Cleanliness, uniformity, e.g. according to ISO 8501-1: Roughness, e.g. according to ISO 8503-1: Time period between blasting and spraying: Spray procedure, generally Spray material: Designation according to standard: Grain size/wire diameter: Other designation: Preheating: yes/no Cooling: yes/no Cooling medium: Coating thickness: as sprayed: Finished:	Preliminary ma	chined by	<i>r</i>				
Method of preparation and cleaning: Surface preparation: Program No.: Blasting procedure: Number of sequences: Type of grit: Blasting pressure: bar Blasting distance/angle: Visual inspection: Cleanliness, uniformity, e.g. according to ISO 8501-1: Roughness, e.g. according to ISO 8503-1: Time period between blasting and spraying: Spray procedure, generally Spray material: Designation according to standard: Grain size/wire diameter: Other designation: Preheating: yes/no Cooling: yes/no Cooling medium: Coating thickness: as sprayed: Finished:	Preliminary ma	Preliminary machining Skotch (if applicable)					
Surface preparation: Program No.:	- 10		(ii applicable)				
Surface preparation: Program No.:							
Surface preparation: Program No.:							
Surface preparation: Program No.:							
Program No.:	Method of prep	aration ar	nd cleaning:				
Blasting procedure:	Surface prepa	ration:					
Type of grit:	Program No.: .						
Blasting pressure: bar Blasting distance/angle: Visual inspection: Cleanliness, uniformity, e.g. according to ISO 8501-1: Roughness, e.g. according to ISO 8503-1: Time period between blasting and spraying: Spray procedure, generally Spray material: Designation according to standard: Grain size/wire diameter: Other designation: Preheating: yes/no Preheating temperature: °C Cooling: yes/no Cooling medium: Coating thickness: as sprayed: Finished:	Blasting proced	dure:	N	Number of sequences:			
Visual inspection: Cleanliness, uniformity, e.g. according to ISO 8501-1: Roughness, e.g. according to ISO 8503-1: Time period between blasting and spraying: Spray procedure, generally Spray material: Designation according to standard: Grain size/wire diameter: Other designation: Preheating: yes/no Preheating temperature: Cooling: yes/no Cooling medium: Coating thickness: as sprayed: Finished:	Type of grit:		C	Grain size:			
Roughness, e.g. according to ISO 8503-1: Time period between blasting and spraying: Spray procedure, generally Spray material: Designation according to standard: Grain size/wire diameter: Other designation: Preheating: yes/no Preheating temperature: Cooling: yes/no Cooling medium: Coating thickness: as sprayed: Finished:	Blasting pressure:		bar E	bar Blasting distance/angle:			
Time period between blasting and spraying: Spray procedure, generally Spray material: Designation according to standard: Grain size/wire diameter: Other designation: Preheating: yes/no Preheating temperature: Cooling: yes/no Cooling medium: Coating thickness: as sprayed: Finished:	Visual inspection:		Cleanliness, uniformity, e.g. according to ISO 8501-1:				
Time period between blasting and spraying: Spray procedure, generally Spray material: Designation according to standard: Grain size/wire diameter: Other designation: Preheating: yes/no Preheating temperature: Cooling: yes/no Cooling medium: Coating thickness: as sprayed: Finished:			Roughness, e.g. according to ISO 8503-1:				
Spray procedure, generally Spray material: Designation according to standard: Grain size/wire diameter: Other designation: Preheating: yes/no Preheating temperature: Cooling: yes/no Cooling medium: Coating thickness: as sprayed: Finished:	Time period be	tween bla					
Spray material: Designation according to standard: Grain size/wire diameter: Other designation: Preheating: yes/no Preheating temperature: Cooling: yes/no Cooling medium: Coating thickness: as sprayed: Finished:							
Grain size/wire diameter: Other designation: Preheating: yes/no Cooling: yes/no Cooling medium: Coating thickness: as sprayed: Finished:		•					
Other designation: Preheating: yes/no Cooling: yes/no Coating thickness: as sprayed: Finished:	, ,						
Preheating: yes/no Preheating temperature: "C Cooling: yes/no Cooling medium: "C Coating thickness: as sprayed: Finished: "C							
Cooling: yes/no Cooling medium:	Preheating:	ves/no	G				
Coating thickness: as sprayed: Finished:	•	•					
Masking material: Device No.:	•	-	•	Device No.:			

Spray device, if applicable, No.:	
Motion: manually/mechanised: industrial robot/x-y-	z-manipulator/manipulator for rotating parts
Spraying program No.:Rev. index:	Movement program No.: Rev. index:
Spraying distance: mm	Surface speed:(m/min) (relative speed between spray torch and the part's surface)
Spraying sequences: (kind, number/ thickness of page 1)	asses)
Thermal sprayer/operator:	
Surface post-treatment:	Program No.:
Temperature/time period:	
Spray procedure, specific data applied (for sev	eral spray procedures)
Spraying procedure (according to EN 657):	Arc spraying
Arc spraying system:	
Type of nozzle: closed arc/open arc/arc jet	
Current: A	Voltage: V
Atomising gas pressure: (MPa)	
Arc jet pressure: (MPa)	
Spraying procedure (according to EN 657):	Wire flame spraying
Flame spraying system:	
Type of nozzle:	
Wire feed rate: m/min	
Oxygen flow rate ¹⁾ :NI/min	
Fuel type:	Fuel flow rate ¹⁾ : NI/min
Compressed air flow rate/setting:	
Spraying procedure (according to EN 657):	Powder flame spraying
Flame spraying system:	
Type of nozzle:	
Powder injector: diameter: mm	Position to nozzle: angle: degrees
Powder feed rate: g/min	
Powder carrier gas:	Carrier gas flow rate ¹⁾ : NI/min
Oxygen flow rate ¹⁾ : NI/min	
Fuel type:	Fuel flow rate ¹⁾ : NI/min
Compressed air flow rate/setting:	

© ISO 2010 – All rights reserved

^{1) 0 °}C (273,15 K) and 101,325 kPa.

Spraying procedure (according to EN 657):	High velocity flame spraying (HVOF)
HVOF spraying system:	
Nozzle, inner diameter: mm	
Powder injector: diameter: mm	Position to nozzle: angle: degrees
Powder feed rate: g/min	
Powder carrier gas:	Carrier gas flow rate ¹⁾ : NI/min
Oxygen flow rate ¹⁾ : NI/min	
Fuel type:	Fuel flow rate ¹⁾ : NI/min
Spraying procedure (according to EN 657):	Atmospheric plasma spraying (APS)
APS spraying system:	
Nozzle, inner diameter: mm	
Powder injector: diameter: mm	Position to nozzle: angle: degrees
Powder feed rate: g/min	
Powder carrier gas:	Carrier gas flow rate ¹⁾ : NI/min
Primary gas:	Primary gas flow rate ¹⁾ : NI/min
Secondary gas:	Secondary gas flow rate ¹⁾ NI/min
Current: A	Voltage nominal: V (new electrode/nozzle)
	Voltage min.: V (operated)
Electrical power, nominal: kW	Kept constant: yes / no
Voltage drop compensated: yes/no	Voltage drop to minimum compensated by:
Spraying procedure (according to EN 657):	Cold spraying (CGS)
Cold spraying system:	
Nozzle, inner diameter: mm	
Powder injector: diameter mm	
Powder feed rate: g/min	
Powder carrier gas:	Carrier gas flow rate ¹⁾ : NI/min
Gas type:	Gas flow rate ¹⁾ : NI/min
Gas temperature: °C	Gas pressure: MPa

Inspection and test results (Example)

Inspection/Test	Procedure/ Specification	Executed by:	Record No.	Test results		Remarks
inspection/rest				Passed	Failed	Remarks
Visual inspection	ISO 14923					
Coating thickness						
Penetrant test	EN 571-1					
Hardness test						
Roughness test						
Materialographic examination						
Determination of adhesive tensile strength	EN 582					

Date of issue:	Signature:
	Name:

Bibliography

- [1] ISO 2063, Thermal spraying Metallic and other inorganic coatings Zinc, aluminium and their alloys
- [2] ISO 8501-1, Preparation of steel substrates before application of paints and related products Visual assessment of surface cleanliness Part 1: Rust grades and preparation grades of uncoated steel substrates and of steel substrates after overall removal of previous coatings
- [3] ISO 8503-1, Preparation of steel substrates before application of paints and related products Surface roughness characteristics of blast-cleaned steel substrates Part 1: Specifications and definitions for ISO surface profile comparators for the assessment of abrasive blast-cleaned surfaces
- [4] ISO 14918, Thermal spraying Approval testing of thermal sprayers
- [5] ISO 14920, Thermal spraying Spraying and fusing of self-fluxing alloys
- [6] ISO 14924, Thermal spraying Post-treatment and finishing of thermally sprayed coatings
- [7] EN 571-1, Non destructive testing Penetrant testing Part 1: General principles
- [8] EN 582, Thermal spraying Determination of tensile adhesive strength





British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards -based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at bsigroup.com/standards or contacting our Customer Services team or Knowledge Centre.

Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at bsigroup.com/shop, where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to bsigroup.com/subscriptions.

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

PLUS is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit bsigroup.com/shop.

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email bsmusales@bsigroup.com.

BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK

Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

Copyright

All the data, software and documentation set out in all British Standards and other BSI publications are the property of and copyrighted by BSI, or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI. Details and advice can be obtained from the Copyright & Licensing Department.

Useful Contacts:

Customer Services

Tel: +44 845 086 9001

Email (orders): orders@bsigroup.com
Email (enquiries): cservices@bsigroup.com

Subscriptions

Tel: +44 845 086 9001

Email: subscriptions@bsigroup.com

Knowledge Centre

Tel: +44 20 8996 7004

Email: knowledgecentre@bsigroup.com

Copyright & Licensing

Tel: +44 20 8996 7070 Email: copyright@bsigroup.com

