

BS EN ISO 15614-8:2016



BSI Standards Publication

Specification and qualification of welding procedures for metallic materials — Welding procedure test

Part 8: Welding of tubes to tube-plate joints
(ISO 15614-8:2016)

bsi.

...making excellence a habit.TM

National foreword

This British Standard is the UK implementation of EN ISO 15614-8:2016. It supersedes BS EN ISO 15614-8:2002 which is withdrawn.

The UK participation in its preparation was entrusted to Technical Committee WEE/36, Qualification of welding personnel and welding procedures.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© The British Standards Institution 2016. Published by BSI Standards Limited 2016

ISBN 978 0 580 85698 3

ICS 25.160.10

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 30 April 2016.

Amendments issued since publication

Date	Text affected

EUROPEAN STANDARD
NORME EUROPÉENNE
EUROPÄISCHE NORM

EN ISO 15614-8

April 2016

ICS 25.160.10

Supersedes EN ISO 15614-8:2002

English Version

**Specification and qualification of welding procedures for
metallic materials - Welding procedure test - Part 8:
Welding of tubes to tube-plate joints (ISO 15614-8:2016)**

Descriptif et qualification d'un mode opératoire de
soudage sur les matériaux métalliques - Épreuve de
qualification d'un mode opératoire de soudage - Partie
8: Soudage de tubes sur plaques tubulaires (ISO 15614-
8:2016)

Anforderung und Qualifizierung von Schweißverfahren
für metallische Werkstoffe -
Schweißverfahrensprüfung - Teil 8: Einschweißen von
Rohren in Rohrböden (ISO 15614-8:2016)

This European Standard was approved by CEN on 2 January 2016.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN-CENELEC Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

CEN-CENELEC Management Centre: Avenue Marnix 17, B-1000 Brussels

European foreword

This document (EN ISO 15614-8:2016) has been prepared by Technical Committee ISO/TC 44 "Welding and allied processes" in collaboration with Technical Committee CEN/TC 121 "Welding" the secretariat of which is held by DIN.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by October 2016, and conflicting national standards shall be withdrawn at the latest by October 2016.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN [and/or CENELEC] shall not be held responsible for identifying any or all such patent rights.

This document supersedes EN ISO 15614-8:2002.

This document has been prepared under a mandate given to CEN by the European Commission and the European Free Trade Association, and supports essential requirements of EU Directive(s).

For relationship with EU Directive(s), see informative Annex ZA, which is an integral part of this document.

According to the CEN-CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and the United Kingdom.

Endorsement notice

The text of ISO 15614-8:2016 has been approved by CEN as EN ISO 15614-8:2016 without any modification.

Annex ZA
 (informative)

Relationship between this European Standard and the Essential Requirements of EU Directive 97/23/EC — Pressure Equipment

This European Standard has been prepared under a mandate given to CEN by the European Commission and the European Free Trade Association to provide a means of conforming to Essential Requirements of the New Approach Directive 97/23/EC.

Once this standard is cited in the Official Journal of the European Union under that Directive and has been implemented as a national standard in at least one Member State, compliance with the clauses of this standard given in Table ZA confers, within the limits of the scope of this standard, a presumption of conformity with the corresponding Essential Requirements of that Directive and associated EFTA regulations.

Table ZA — Correspondence between this European Standard and Directive 97/23/EC

Clause(s)/subclause(s) of this EN	Essential Requirements (ERs) of Directive 97/23/EC	Qualifying remarks/Notes
Clauses 5, 6, 7, 8, 9	Annex I, 3.1.2	Permanent joining

WARNING — Other requirements and other EU Directives may be applicable to the product(s) falling within the scope of this part of ISO 15614.

Contents

	Page
Foreword	v
Introduction	vii
1 Scope	1
2 Normative references	1
3 Terms and definitions	2
4 Symbols and abbreviated terms	2
5 Preliminary welding procedure specification (pWPS)	3
5.1 General	3
5.2 Parameters for all welding process	3
5.3 Parameters for particular welding processes	4
6 Qualification of welding procedure	5
7 Welding of test pieces	5
7.1 General	5
7.2 Type of test piece	5
7.2.1 Joint preparation and joint construction	5
7.2.2 Tube ends welded on triangular pitch	5
7.2.3 Tube ends welded on square pitch	6
8 Examination and testing	7
8.1 Performance	7
8.1.1 General	7
8.1.2 Visual testing	7
8.1.3 Penetrant testing	8
8.1.4 Radiographic testing	8
8.1.5 Macroscopic examination	8
8.1.6 Hardness test	8
8.1.7 Push-out or pull-out test	8
8.2 Acceptance levels	9
8.2.1 General	9
8.2.2 Visual testing	9
8.2.3 Penetrant testing	9
8.2.4 Radiographic testing	9
8.2.5 Macroscopic examination	10
8.2.6 Hardness values	10
8.2.7 Push-out or pull-out load	10
8.3 Re-test	10
9 Range of qualification	11
9.1 General	11
9.2 Related to the manufacturer	11
9.3 Related to the material	11
9.3.1 Parent metal	11
9.3.2 Tube-plate and tube dimensions	11
9.3.3 Tube pitch	11
9.4 Common to all welding procedures	11
9.4.1 Welding process	11
9.4.2 Welding position of tube-plate	11
9.4.3 Type of joint	11
9.4.4 Filler metal, classification	12
9.4.5 Filler metal, dimensions	12
9.4.6 Type of current	12
9.4.7 Arc energy (heat input)	12
9.4.8 Pre-heat temperature	12

9.4.9	Interpass temperature.....	12
9.4.10	Post-weld heat treatment.....	12
9.4.11	Shielding gas.....	12
10	Welding procedure qualification record form (WPQR).....	12
Annex A	(informative) Welding procedure qualification record form for tube to tube-plate joints (WPQR).....	14
Bibliography		18

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the WTO principles in the Technical Barriers to Trade (TBT) see the following URL: [Foreword - Supplementary information](#)

The committee responsible for this document is ISO/TC 44, *Welding and allied processes*, Subcommittee SC 10, *Quality management in the field of welding*.

This second edition cancels and replaces the first edition (ISO 15614-8:2002), which has been technically revised.

ISO 15614 consists of the following parts, under the general title *Specification and qualification of welding procedures for metallic materials — Welding procedure test*:

- *Part 1: Arc and gas welding of steels and arc welding of nickel and nickel alloys*
- *Part 2: Arc welding of aluminium and its alloys*
- *Part 3: Fusion welding of non-alloyed and low-alloyed cast irons*
- *Part 4: Finishing welding of aluminium castings*
- *Part 5: Arc welding of titanium, zirconium and their alloys*
- *Part 6: Arc and gas welding of copper and its alloys*
- *Part 7: Overlay welding*
- *Part 8: Welding of tubes to tube-plate joints*
- *Part 9: Underwater hyperbaric wet welding*
- *Part 10: Hyperbaric dry welding*
- *Part 11: Electron and laser beam welding*
- *Part 12: Spot, seam and projection welding*
- *Part 13: Upset (resistance butt) and flash welding*

— *Part 14: Laser-arc hybrid welding of steels, nickel and nickel alloys*

Requests for official interpretations of any aspect of this International Standard should be directed to the Secretariat of ISO/TC 44/SC 10 via your national standards body. A complete listing of these bodies can be found at www.iso.org.

Introduction

All new welding procedure tests are to be carried out in accordance with this part of ISO 15614 from the date of its issue. However, this part of ISO 15614 does not invalidate previous welding procedure tests made to former national standards or specifications or previous issues of this part of ISO 15614.

Specification and qualification of welding procedures for metallic materials — Welding procedure test —

Part 8: Welding of tubes to tube-plate joints

1 Scope

This part of ISO 15614 specifies requirements for the qualification testing of welding procedures for the arc welding of tube to tube-plate joints in metallic materials by manual, partly mechanized, fully mechanized, or automatic processes.

This part of ISO 15614 is a part of a series of standards. Details of this series are given in ISO 15607, Annex A.

Qualification by tube to tube-plate joint tests can be used for all joints even if they are fully loaded or only seal welded as required in application standards.

This part of ISO 15614 applies to fusion welding of metallic materials for tube to tube-plate joints with a remaining gap between the tube and the tube-plate for some length of the tube-plate thickness. This part of ISO 15614 does not apply to tube-sheets with forged end connections with welded tubes (external/internal bore welds).

For welding of tube to tube-plate joints with mechanical expansion which is load bearing, welding procedure test is to be defined.

For other applications and/or requirements, this part of ISO 15614 can be used if required by the specification.

Repair welding is to be considered in the welding procedure test.

2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 3452-1, *Non-destructive testing — Penetrant testing — Part 1: General principles*

ISO 4063, *Welding and allied processes — Nomenclature of processes and reference numbers*

ISO 6520-1, *Welding and allied processes — Classification of geometric imperfections in metallic materials — Part 1: Fusion welding*

ISO 9015-1, *Destructive tests on welds in metallic materials — Hardness testing — Part 1: Hardness test on arc welded joints*

ISO 9606-1, *Qualification testing of welders — Fusion welding — Part 1: Steels*

ISO 9606-2, *Qualification test of welders — Fusion welding — Part 2: Aluminium and aluminium alloys*

ISO 9606-3, *Approval testing of welders — Fusion welding — Part 3: Copper and copper alloys*

ISO 9606-4, *Approval testing of welders — Fusion welding — Part 4: Nickel and nickel alloys*

ISO 9606-5, *Approval testing of welders — Fusion welding — Part 5: Titanium and titanium alloys, zirconium and zirconium alloys*

ISO 9692-1, *Welding and allied processes — Types of joint preparation — Part 1: Manual metal arc welding, gas-shielded metal arc welding, gas welding, TIG welding and beam welding of steels*

ISO 14175, *Welding consumables — Gases and gas mixtures for fusion welding and allied processes*

ISO 14732, *Welding personnel — Qualification testing of welding operators and weld setters for mechanized and automatic welding of metallic materials*

ISO 15607:2003, *Specification and qualification of welding procedures for metallic materials — General rules*

ISO 15609-1, *Specification and qualification of welding procedures for metallic materials — Welding procedure specification — Part 1: Arc welding*

ISO 15614-1, *Specification and qualification of welding procedures for metallic materials — Welding procedure test — Part 1: Arc and gas welding of steels and arc welding of nickel and nickel alloys*

ISO 17636-1, *Non-destructive testing of welds — Radiographic testing — Part 1: X- and gamma-ray techniques with film*

ISO 17637, *Non-destructive testing of welds — Visual testing of fusion-welded joints*

ISO 17639, *Destructive tests on welds in metallic materials — Macroscopic and microscopic examination of welds*

ISO/TR 15608, *Welding — Guidelines for a metallic materials grouping system*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 15607 apply.

4 Symbols and abbreviated terms

a	throat thickness (mm) (in this case, the minimal distance between root point and weld surface)
b	width of the weld reinforcement (mm)
d_p	pore size (mm)
d_a	tube-outside diameter (mm)
d_l	minimum distance between two pipes (mm)
g	gap between tube and tube plate (mm)
h	height or width of imperfection (mm)
s_p	starting point of the root run
t	tube-wall thickness (mm)
t_1	cladding thickness (mm)
t_2	tube-plate thickness (mm)
x	overlap (mm)

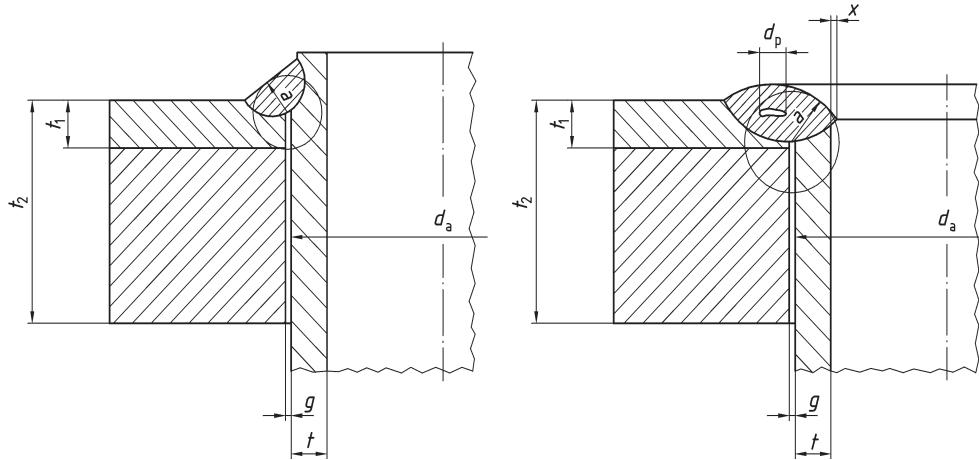


Figure 1 — Presentation of symbols in an example

5 Preliminary welding procedure specification (pWPS)

5.1 General

The qualification for tube to tube-plate welding tests shall be based on a pWPS in accordance with ISO 15609-1. It shall specify the relevant parameters listed in [5.2](#) and [5.3](#).

5.2 Parameters for all welding process

Details relating to the following parameters shall be recorded for all welding processes:

- a) welding process, or processes, when more than one is used in making a complete joint;
- b) tube-plate specification and thickness and details of any cladding and its thickness;
- c) tube specification, thickness, and outside diameter;
- d) pitch type (square or triangular) and distance between pipes;
- e) joint geometry, actual borehole, diameter and fit-up tolerances (sketch);
- f) cleaning and degreasing (time during the fabrication steps and type);
- g) jigging or tacking, tacking position, and expansion (before welding);
- h) tube-plate and welding position;
- i) type and/or trade name of welding consumables;
- j) size (diameter) and wire feed speed or rate of wire addition per run;
- k) pre-heating and interpass temperature, including method of control;
- l) if necessary, travel speed;
- m) number and arrangement of runs, starting points of runs, and weld dimensions (sketch);
- n) welding sequence;
- o) post-weld heat treatment, including method of control;

- p) if necessary, the temperature and time recommended for drying/backing of welding consumables before use;
- q) any special features, including heat input control requirements, any heat sinks effects.

5.3 Parameters for particular welding processes

Details relating to the following parameters given in [5.3 a\)](#) to [5.3 d\)](#) shall be recorded for these particular processes, in addition to the parameters given in [5.2](#). The reference numbers of welding processes relate to ISO 4063.

- a) Manual metal arc welding (111)
 - alternating or direct current and polarity
 - current
- b) MIG welding, MAG welding, solid wire, or cored wire with or without separate gas shield (114), (131), (132), (133), (135), (136), (138)
 - manufacturer of the power source, type (analogue, digital, electronically regulated)
 - shielding gas designation in accordance with ISO 14175 and flow rate
 - arc voltage
 - nozzle size/diameter
 - wire feed speed or current
 - for pulsed welding: the pulse time and frequency, pulsed current, and background current
- c) TIG welding (141)
 - manufacturer of the power source, type (analogue, digital, electronically regulated)
 - shielding gas designation in accordance with ISO 14175 and flow rate
 - alternating current (AC) or direct current (DC) and polarity
 - current
 - nozzle size/diameter
 - shape of the end of tungsten electrode
 - for pulsed welding: the pulse time and frequency, pulsed current, and background current
 - whether filler metal is used
- d) Mechanized or automatic welding
 - All parameters detailed in b) or c) and the following parameters if necessary:
 - arc length or arc voltage;
 - where filler metal is used, wire feed speed, wire diameter;
 - other pre-programmed welding variables such as the following:
 - pre- and post-gas purge times;
 - changes in current level;

- current slope up and down rates;
- welding travel speed and degree of overlap;
- when considering front face welding, the following additional information:
 - radius of electrode rotation;
 - electrode angle relative to the tube axis;
 - distance between the work piece and the electrode.

For all other welding processes, the welding parameters shall be specified.

6 Qualification of welding procedure

The qualification of welding procedure for the tube to tube-plate welding shall be carried out by an examiner or examining body related to the appropriate application standard or specification.

7 Welding of test pieces

7.1 General

Procedure test pieces shall be produced in accordance with [7.2](#) and shall simulate the joint geometry to be used in production or a similar geometry within the requirements of the pWPS. Welders shall be qualified in accordance with ISO 9606-1, ISO 9606-2, ISO 9606-3, ISO 9606-4, or ISO 9606-5. For welding operators and weld setters, the qualification can be carried out during the tests in accordance with ISO 14732.

7.2 Type of test piece


7.2.1 Joint preparation and joint construction

For examples of joint preparation based on ISO 9692-1 and joint construction, see EN 1708-1 [\[1\]](#).

7.2.2 Tube ends welded on triangular pitch

Where tube end welds are involved on a triangular pitch, a minimum of 10 tube ends with an outside diameter smaller than 40 mm (<40 mm) or a minimum of seven tube ends (area A) with an outside diameter greater than or equal to 40 mm (≥ 40 mm) shall be welded as shown in [Figure 2](#).

Dimensions in millimetres

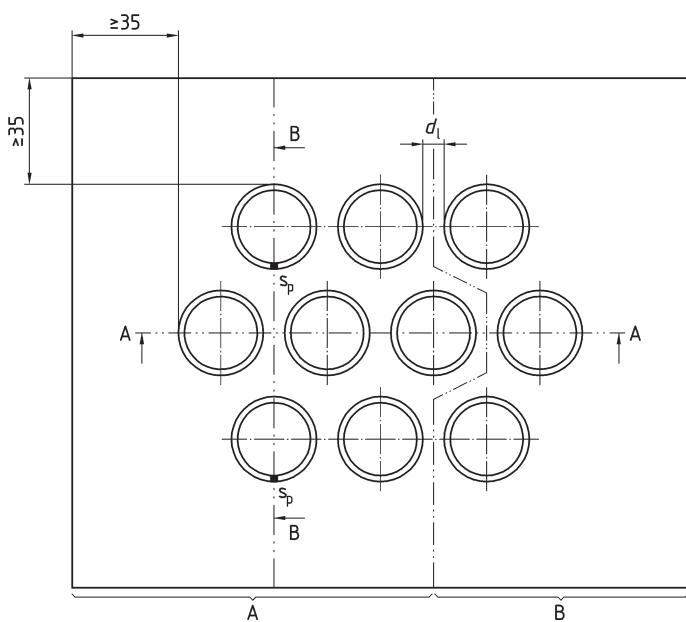

Key


A-A/B-B ground sections of a test specimen (examples for the location of the cut lines)

Figure 2 — Test piece for tube ends on triangular pitch

7.2.3 Tube ends welded on square pitch

Where tube end welds are involved on a square pitch, a minimum of 12 tube ends with an outside diameter smaller than 40 mm (<40 mm) or a minimum of nine tube ends (area A) with an outside diameter greater than or equal to 40 mm (≥ 40 mm) shall be welded as shown in [Figure 3](#).

Dimension in millimetres

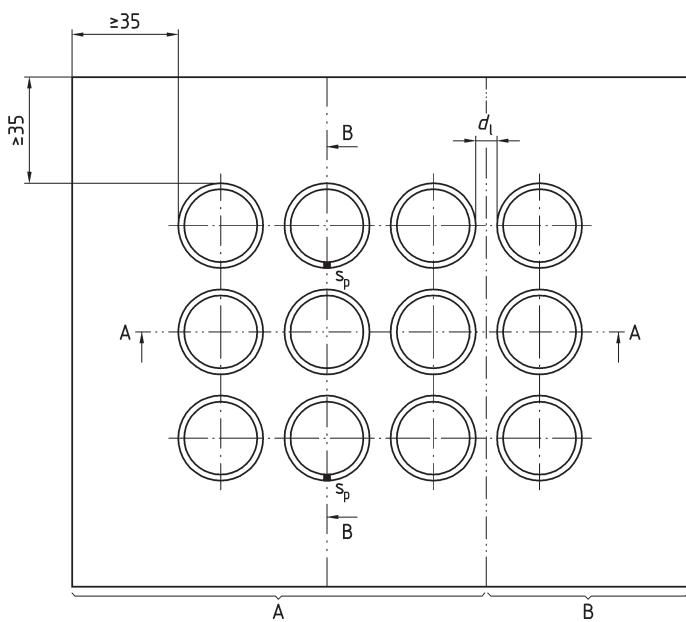

Key

A-A/B-B ground sections of a test specimen (examples for the location of the cut lines)

Figure 3 — Test piece for tube ends on square pitch

8 Examination and testing

8.1 Performance

8.1.1 General

For a welding procedure to be qualified, the same test piece representing the welding procedure test shall comply with 8.1.2 to 8.1.6 and, when specified, with the push-out tests described in 8.1.7.

Table 1 — Examination and testing of the test pieces

Tube arrangement in the tube plate	Number of welds and type of test	Extent of testing
Triangular pitch (see Figure 2)	<ul style="list-style-type: none"> — $d_a < 40$ mm (10 tube ends) — $d_a \geq 40$ mm (seven tube ends) — Visual testing — Penetrant testing — Radiographic testing^a — Macroscopic examination — Hardness test (row)^{b, c} — Push-out or pull-out test 	<p>100 %</p> <p>100 %</p> <p>100 %</p> <p>Six specimens ($d_a < 40$ mm) Five specimens ($d_a \geq 40$ mm)</p> <p>One specimen at the first tube end which was welded</p> <p>If required by specification</p>
Square pitch (see Figure 3)	<ul style="list-style-type: none"> — $d_a < 40$ mm (12 tube ends) — $d_a \geq 40$ mm (nine tube ends) — Visual testing — Penetrant testing — Radiographic testing — Macroscopic examination — Hardness test (row)^{b, c} — Push-out or pull-out test 	<p>100 %</p> <p>100 %</p> <p>100 %</p> <p>Seven specimens ($d_a < 40$ mm) Six specimens ($d_a \geq 40$ mm)</p> <p>One specimen at the first tube end which was welded</p> <p>If required by specification</p>

^a Except those for push-out or pull-out test.

^b Not required for steel sub-group 1.1 and 7.1, groups 8, 10, and 41 to 48 except for dissimilar joints between subgroup 1.1 and group 8.

^c For cladded tube ends, the hardness test shall also cover the area of the parent material under the cladding.

8.1.2 Visual testing

After appropriate cleaning and if required, any post-weld heat treatment and prior to the cutting of test specimens, the test piece shall be tested visually according to ISO 17637.


The welds shall show uniform contour without excessive reinforcement with the bores of the tube free from any spatter and shall be in accordance with Table 2.

8.1.3 Penetrant testing

The external surfaces of all welds shall be subjected to penetrant examination in accordance with ISO 3452-1.

8.1.4 Radiographic testing

All test welds, except those for push-out tests, shall be radiographed in accordance with ISO 17636-1. An example is given in [Figure 4](#). In the case of push out tests, the tube-plate shall be reduced in thickness to between 5 mm and 12 mm.

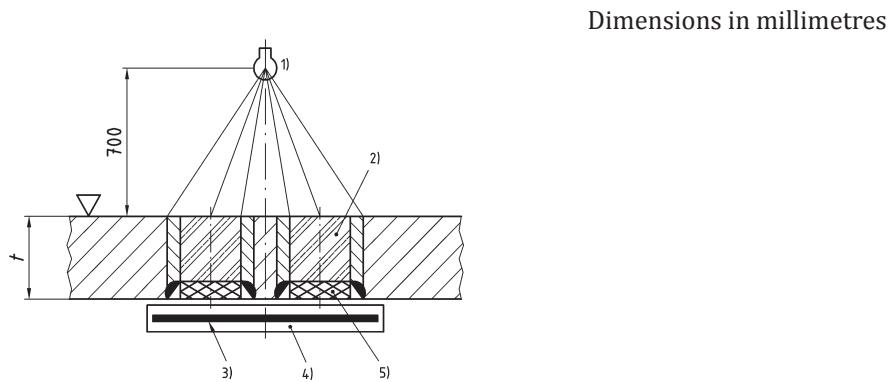

Key

- 1) ray source
- 2) radiated marcasite (steel/lead)
- 3) film
- 4) film cassette
- 5) stopper

Figure 4 — Performance of the radiographic testing

8.1.5 Macroscopic examination

After visual and non-destructive testing, the test piece shall be sectioned as shown in [Figures 2](#) and [3](#) by sawing or machining and exposing two starting points of the root runs. The macroscopic examination specimens shall be prepared and examined in accordance with ISO 17639.

Macroscopic examinations of additional sections to assess compliance with the acceptance levels in [8.2](#) shall be carried out where radiography reveals imperfections other than gas pores.

8.1.6 Hardness test

A hardness row, normally HV 10 in accordance with ISO 9015-1, shall be carried out for the cases identified in [Table 1](#). The hardness shall be recorded for the weld metal, both parent metals and the heat-affected zones. The hardness values under cladding shall be recorded, if applicable.

8.1.7 Push-out or pull-out test

The requirements should be defined in the specification.


8.2 Acceptance levels

8.2.1 General

The following details are to be used for the qualification testing of welding procedures and as such, may be different from those specified for a particular application.

8.2.2 Visual testing

Table 2 — Visual testing

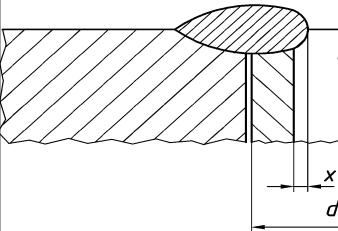No.	Imperfection/ designation	ISO 6520-1 reference no.	Remarks	Limits for imperfections
1	Cracks	100	All types of cracks	Not permitted
2	Crater crack	104		Not permitted
3	Surface pore open end crater pipe	2017 2024	All types of pores, they are visible on the surface	Not permitted
4	Burn through of tube wall			Not permitted
5	Overlap	506		$x \leq 0,5 \text{ mm}$ for tubes, $d_a \leq 25 \text{ mm}$ outside diameter and $x \leq 1 \text{ mm}$ for tubes, $d_a > 25 \text{ mm}$ outside diameter
6	Burn down of tube end (only fillet welds)			Not permitted, where it reduces the weld below its required dimensions
7	Undercut	5011		0,1 t
8	Excess weld metal	502		$h \leq 1 \text{ mm} + 0,1 b$ Where b is the width of the weld reinforcement

8.2.3 Penetrant testing


Any indication of dimensions in the weld metal or heat-affected zone is not acceptable.

8.2.4 Radiographic testing

Table 3 — Radiographic testing


No.	Imperfection/ designation	ISO 6520-1 reference no.	Remarks	Limits for imperfections
9	Cracks	100	All types of cracks	Not permitted
		1001	In case of micro cracks, the dimensions and frequency of the cracks should be agreed.	
10	Elongated cavities, wormholes	2015 2016		Not permitted
11	Clustered (localized) cavities	2013		Not permitted

Table 3 (continued)

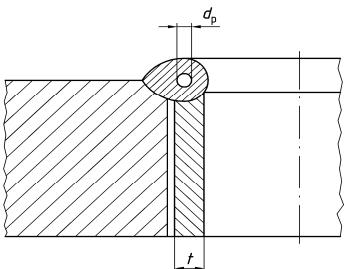No.	Imperfection/ designation	ISO 6520-1 reference no.	Remarks	Limits for imperfections
12	Gas pores uniformly distributed, porosity, linear porosity	2011 2012 2014	 <ul style="list-style-type: none"> — Per tube joint max. two pores with pore size d_p permitted as measured on the image — Distance between two pores min. distance $2 \times d_p$ around the circumference 	$d_p \leq 0,25 t$ max. 1 mm
13	Solid inclusions	300		Not permitted
14	Lack of fusion	401		Not permitted
15	Lack of penetra- tion	402		Not permitted

8.2.5 Macroscopic examination

Table 4 — Macroscopic examination

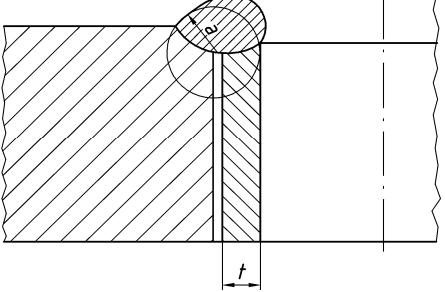No.	Imperfection/ designation	ISO 6520-1 reference no.	Remarks	Limits for imperfections
9 to 15	see Table 3			
16	Weld thickness		 <p>The throat dimension, a, is equal to the radius of the largest circle totally inscribed in the weld whose centre is situated in the root of weld</p>	$a \geq 0,9 t$

8.2.6 Hardness values

The results from the hardness test shall meet the requirements given in ISO 15614-1.

8.2.7 Push-out or pull-out load

The requirements should be defined in the specification.

8.3 Re-test

If the test piece fails to comply with any of the requirements for examination and testing specified in [8.1](#), one further test piece shall be welded and subjected to the same examination/testing. If this additional test piece does not comply with the requirements, the welding procedure test has failed.

9 Range of qualification

9.1 General

All the conditions of validity stated below shall be met independently of each other. Changes outside of the ranges specified shall require a new welding procedure test.

9.2 Related to the manufacturer

A qualification of a WPS obtained by a manufacturer is valid for welding in workshops and sites under the same technical conditions and quality control of that manufacturer.

9.3 Related to the material

9.3.1 Parent metal

For the purposes of this part of ISO 15614, the groups of materials listed in ISO/TR 15608 shall apply. Only those materials groups according to ISO/TR 15608 used in this qualification test in combination with each other are qualified.

9.3.2 Tube-plate and tube dimensions

For all geometrical details, the ranges of qualification are given in [Table 5](#).

Table 5 — Range of qualification for geometrical details

Designation	Test piece mm	Range of qualification mm
Cladding thickness	$t_1 < 3$ $t_1 \geq 3$	$\geq t_1$ ≥ 3
Tube-plate thickness	$t_2 < 35$ $t_2 \geq 35$	$\geq t_2$ ≥ 35
Tube-wall thickness	t	0,5 t to 2 t
Tube-outside diameter	d_a	$\geq d_a$

9.3.3 Tube pitch

The qualification of a welding procedure using a particular pitch of tubes shall include qualification for any other type of pitch provided that the minimum distance between two pipes, d_l (see [Figures 2](#) and [3](#)), is not reduced to below that used in the qualified welding procedure.

9.4 Common to all welding procedures

9.4.1 Welding process

The qualification is valid only for the welding process used in the welding procedure test.

Qualification in a multi-process procedure test is only valid for that multi-process procedure.

9.4.2 Welding position of tube-plate

The qualification is only valid for the welding position used in the welding procedure test.

9.4.3 Type of joint

The qualification is only valid for the type of welded joints used in the welding procedure test.

9.4.4 Filler metal, classification

The qualification range of filler metals covers other filler metals as long as they are

- either in the same group of tensile properties. Change in the type of a covered electrode or a change in a type of electrode core requires a new welding procedure qualification, or
- within the same nominal chemical composition.

9.4.5 Filler metal, dimensions

The qualification given is for the diameters of electrodes or for the diameters of wires or for special consumables, e.g. inserts, used in the welding procedure test.

9.4.6 Type of current

The qualification given is for the type of current (alternating, direct, or pulsed current) and polarity used in the welding procedure test.

9.4.7 Arc energy (heat input)

The requirements of this subclause apply in case of welding without filler material or in other cases when the control of heat input is specified.

The lowest limit of heat input is that used in welding procedure test or may be 25 % greater than that used in welding the test piece.

9.4.8 Pre-heat temperature

The lower limit of qualification is the pre-heat temperature used at the start of the welding procedure test.

9.4.9 Interpass temperature

The upper limit of qualification is the nominal interpass temperature reached in the welding procedure test.

9.4.10 Post-weld heat treatment

Welding procedure test with heat treatment does not include welding procedure test without heat treatment and vice versa. The temperature range used for the welding procedure test is the range qualified. Where required, heating rates, cooling rates, and holding time shall be related to the production component.

9.4.11 Shielding gas

The qualification given to the shielding gas is restricted to the type of gas (nominal composition) in accordance with ISO 14175 used in the welding procedure test.

10 Welding procedure qualification record form (WPQR)

A welding procedure qualification record (WPQR) is a statement of the results of assessment of each test piece including re-tests. The relevant parameters listed for the WPS in [Clause 5](#) shall be included together with details of any features that would be rejectable by the requirements of [Clause 8](#).

If no rejectable features or unacceptable test results are found, a WPQR detailing the welding procedure test piece results is qualified and shall be signed and dated by the examiner or examining body.

A WPQR format shall be used to record details for the welding procedure and the test results in order to facilitate uniform presentation and assessment of the parameters.

An example of the WPQR form is shown in Annex A.

Annex A
(informative)

Welding procedure qualification record form for tube to tube-plate joints (WPQR)

Welding procedure qualification - Test certificate

Manufacturer's welding procedure

Examiner or examining body

Reference no. :

Reference no. :

Manufacturer :

Address :

Code/Testing standard :

Date of welding :

Extent of qualification

Welding process :

Joint type :

Parent metal (s) : tube plate : Cladding : Tube :

Thickness of tube plate (mm) : Cladding (mm) : Tube (mm) :

Tube outside diameter (mm) : Gap (g)(mm) :

Filler metal type :

Shielding gas :

Type of welding current :

Welding positions :

Pre-heat :

Post-weld heat treatment :

Other information :

.....

.....

Certified that test welds prepared, welded and tested satisfactorily in accordance with the requirements of the code/testing standard indicated above

.....
Location

.....
Date of issued

.....
Examiner or examining body

.....
Name, date and signature

Details of tube-to-tube plate joint tests

Location:
 Manufacturer's welding procedure
 Reference no. :
 WPQR no. :

Examiner or examining body:

Method of preparation and cleaning:

Parent material specification: - tube-plate:
 - cladding:
 - tube:
 Material thickness (mm) : - tube-plate :
 - cladding:
 - tube:

Manufacturer:

Welder's name:
 Welding process:
 Joint type:

Tube outside diameter (mm):
 Welding position:

Sketch of test piece in accordance with Clause 7	Sketch of the joint preparation

Welding details

Run	Process	Size of filler metal mm	Current A	Voltage V	Type of current/polarity	Wire feed speed m/min	Travel speed ¹⁾ cm/min	Heat input ¹⁾ kJ/cm

Cleaning and degreasing:

Filler metal classification and trade name:

Any special baking or drying:

Gas shielding:

Gas flow rate – shielding:

Tungsten electrode type/size:

Details of fastening of tubes before welding:

Preheat temperature:

Interpass temperature:

Post-weld heat treatment and/or ageing:

Time, temperature, method:

Heating and cooling rates¹⁾:

Remarks:

Further information¹⁾:

(see on a separate sheet)

Manufacturer

Examiner or examining body

.....
 Name, date, and signature

.....
 Name, date, and signature

1) If required.

Further information

Oscillation (amplitude, frequency):

Distance contact tube/ workpiece:

Torch angle:

Current increase (A) from to: in: (s)

Pool formation (A): Time (s):

Wire rate (mm/s):
for 1st run²⁾: for 2nd run²⁾:

Min. current (A):
for 1st run²⁾: for 2nd run²⁾:

Max. current (A):
for 1st run²⁾: for 2nd run²⁾:

Pulse frequency:

Circulation time (s):
for 1st run²⁾: for 2nd run²⁾:

Current decrease (A) from: to: in: (s)

Pulse, wire: yes no

Pulse, rotary: yes no

Manufacturer of weld machine: ²⁾

.....

.....

.....

Current:²⁾

Polarity:²⁾

Test results

Manufacturer's welding procedure
Reference no. :

Examiner or examining body
Reference no. :

Visual testing

without objections <input type="checkbox"/>	with objections <input type="checkbox"/>	Remarks
---	--	---------

Penetrant testing

without objections <input type="checkbox"/>	with objections <input type="checkbox"/>	Remarks
---	--	---------

Radiographic testing

without objections <input type="checkbox"/>	with objections <input type="checkbox"/>	Remarks
---	--	---------

2) Welding data for automatic welding.

Macroscopic examination

Weld thickness		Assessment	Remarks
required	measured min. (mm) max. (mm)	without objections <input type="checkbox"/> with objections <input type="checkbox"/>	
acceptable	yes <input type="checkbox"/> no <input type="checkbox"/>		

Hardness test³⁾

Type/load:

Parent metal:

HAZ:

Weld metal:

Push-out or pull-out test³⁾

	Re (N/mm ²)	Rm (N/mm ²)	Fracture location	Remarks
Requirements				

Other tests:

Remarks:

.....

Tests carried out in accordance with the requirements of:

Laboratory report reference no.:

The test results are - acceptable not acceptable

Test carried out in the presence of Examiner or examining body

..... Name, date, and signature

3) If required.

Bibliography

- [1] EN 1708-1, *Welding — Basic weld joint details in steel — Part 1: Pressurized components*

This page deliberately left blank

British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at bsigroup.com/standards or contacting our Customer Services team or Knowledge Centre.

Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at bsigroup.com/shop, where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to bsigroup.com/subscriptions.

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

PLUS is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit bsigroup.com/shop.

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email bsmusales@bsigroup.com.

BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK

Rewvisions

Our British Standards and other publications are updated by amendment or revision. We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

Copyright

All the data, software and documentation set out in all British Standards and other BSI publications are the property of and copyrighted by BSI, or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI. Details and advice can be obtained from the Copyright & Licensing Department.

Useful Contacts:

Customer Services

Tel: +44 845 086 9001

Email (orders): orders@bsigroup.com

Email (enquiries): cservices@bsigroup.com

Subscriptions

Tel: +44 845 086 9001

Email: subscriptions@bsigroup.com

Knowledge Centre

Tel: +44 20 8996 7004

Email: knowledgecentre@bsigroup.com

Copyright & Licensing

Tel: +44 20 8996 7070

Email: copyright@bsigroup.com

