

BS EN ISO 17653:2012



BSI Standards Publication

**Resistance welding —  
Destructive tests on welds in  
metallic materials — Torsion  
test of resistance spot welds  
(ISO 17653:2012)**

**bsi.**

...making excellence a habit.™

**National foreword**

This British Standard is the UK implementation of EN ISO 17653:2012. It supersedes BS EN ISO 17653:2003 which is withdrawn.

The UK participation in its preparation was entrusted to Technical Committee WEE/29, Resistance welding.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© The British Standards Institution 2012. Published by BSI Standards Limited 2012

ISBN 978 0 580 70474 1

ICS 25.160.40

**Compliance with a British Standard cannot confer immunity from legal obligations.**

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 31 May 2012.

**Amendments issued since publication**

Date	Text affected
------	---------------

---

English Version

## Resistance welding - Destructive tests on welds in metallic materials - Torsion test of resistance spot welds (ISO 17653:2012)

Soudage par résistance - Essais destructifs des soudures sur matériaux métalliques - Essai de torsion de soudure par résistance par points (ISO 17653:2012)

Widerstandsschweißen - Zerstörende Prüfung von Schweißverbindungen an metallischen Werkstoffen - Torsionsversuch an Widerstandspunktschweißverbindungen (ISO 17653:2012)

This European Standard was approved by CEN on 20 April 2012.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN-CENELEC Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION  
COMITÉ EUROPÉEN DE NORMALISATION  
EUROPÄISCHES KOMITEE FÜR NORMUNG

Management Centre: Avenue Marnix 17, B-1000 Brussels

## Foreword

This document (EN ISO 17653:2012) has been prepared by Technical Committee ISO/TC 44 "Welding and allied processes" in collaboration with Technical Committee CEN/TC 121 "Welding" the secretariat of which is held by DIN.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by November 2012, and conflicting national standards shall be withdrawn at the latest by November 2012.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN [and/or CENELEC] shall not be held responsible for identifying any or all such patent rights.

This document supersedes EN ISO 17653:2003.

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and the United Kingdom.

### Endorsement notice

The text of ISO 17653:2012 has been approved by CEN as a EN ISO 17653:2012 without any modification.

## Contents

Page

Foreword .....	iv
<b>1 Scope .....</b>	<b>1</b>
<b>2 Normative references .....</b>	<b>1</b>
<b>3 Terms and definitions .....</b>	<b>1</b>
<b>4 Specimens .....</b>	<b>1</b>
<b>5 Testing equipment and testing procedure .....</b>	<b>2</b>
<b>5.1 Non-instrumented torsion test (workshop test) .....</b>	<b>2</b>
<b>5.2 Instrumented torsion test .....</b>	<b>3</b>
<b>6 Evaluation of test results whenever applying the instrumented torsion tests .....</b>	<b>4</b>
<b>7 Test report .....</b>	<b>5</b>

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 17653 was prepared by Technical Committee ISO/TC 44, *Welding and allied processes*, Subcommittee SC 6, *Resistance welding and allied mechanical joining*.

This second edition cancels and replaces the first edition (ISO 17653:2003), which has been technically revised.

# Resistance welding — Destructive tests on welds in metallic materials — Torsion test of resistance spot welds

## 1 Scope

This International Standard specifies specimen dimensions, testing equipment and the procedure for torsion testing of resistance spot welds with single sheet thicknesses ranging from 0,5 mm to 6,0 mm in steels. It can be used for non-ferrous materials in certain circumstances.

The aim of this International Standard is to determine the weld diameter and the failure type of fractured specimens, and to evaluate the influence of different steel types, welding parameters and other factors on the deformation characteristics of a resistance spot weld.

## 2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 14329, *Resistance welding — Destructive tests of welds — Failure types and geometric measurements for resistance spot, seam and projection welds*

ISO 17677-1, *Resistance welding — Vocabulary — Part 1: Spot, projection and seam welding*

## 3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 14329 and ISO 17677-1 and the following apply.

### 3.1

#### **non-instrumented torsion test**

test used to determine weld diameter and failure type of welds without measuring torque or torsion angle


### 3.2

#### **instrumented torsion test**

torsion test with measuring instruments for torque or torsion angle to evaluate the mechanical properties of welds as well as the weld diameter and failure type

## 4 Specimens

Specimens for torsion testing are welded individually. The two coupons with a minimum width of 40 mm and a minimum length of 60 mm shall be welded together such that they can be rotated relative to each other (see Figure 1). The distance of the centre of the spot weld from outer edge in longitudinal direction shall be minimum 20 mm.

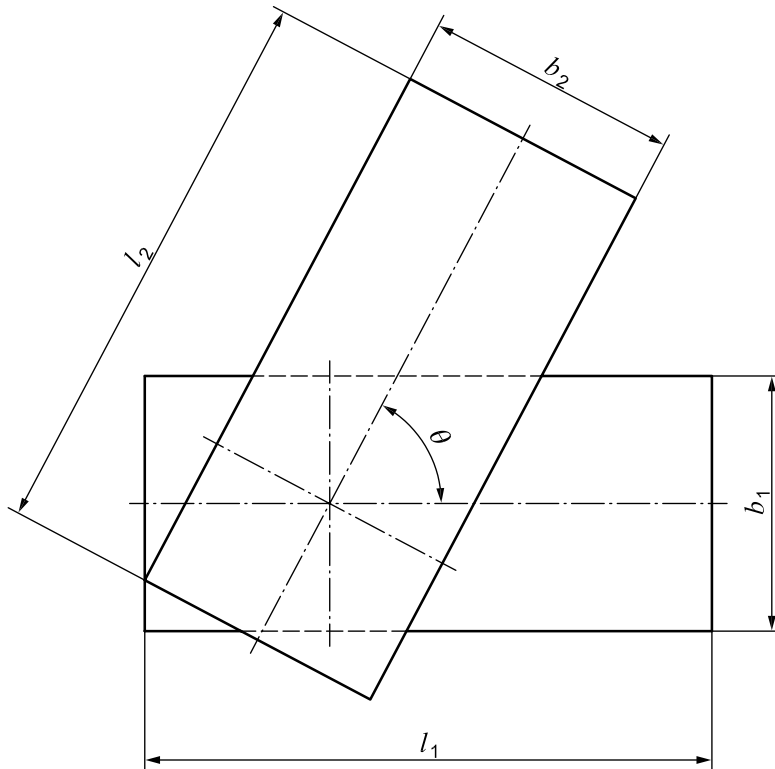

**Key**

$l_1, l_2$  length of coupons ( $\geq 60$  mm)

$b_1, b_2$  width of coupons ( $\geq 40$  mm)

$\theta$  stacking angle between both coupons before testing

The distance of the centre of the spot weld from outer edge of the coupon in longitudinal direction shall be  $\geq 20$  mm.

**Figure 1 — Specimen**


## 5 Testing equipment and testing procedure

### 5.1 Non-instrumented torsion test (workshop test)

For the non-instrumented torsion test (workshop test), the lower sheet of the specimen is gripped as shown in Figure 2. The upper sheet of the specimen is held in a plier or flattened end pipe as shown in Figure 2 a), and rotated steadily in one direction until failure of the spot weld. The testing device shall be designed to minimize the bending of the two sheets of the specimen during testing in order to maintain pure torsional loading of the spot weld. This is necessary to increase the comparability of the test results. This test method determines the weld diameter and the failure type.

NOTE In the case of sheet material thicker than 2,0 mm the other sheet of the specimen can be gripped with the movable specimen gripper, and rotated until failure.



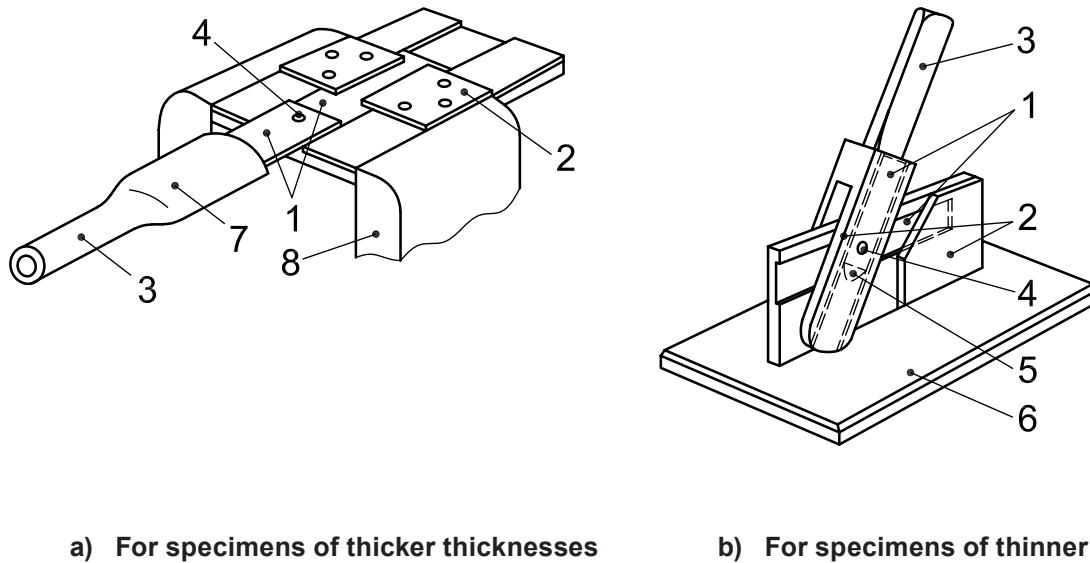


**Key**

- 1 specimen
- 2 specimen gripper
- 3 handle
- 4 spot weld
- 5 notch to stop slipping of specimen
- 6 fixed specimen gripper mounting
- 7 flattened part of pipe as specimen gripper
- 8 vice

**Figure 2 — Examples of torsion testing devices used only to determine weld diameter and failure type**

**5.2 Instrumented torsion test**

The device used for the instrumented torsion test shall be constructed such that the clearance between the edge of the specimen and the tooling does not exceed 0,3 mm. The specimen shall be positioned such that the interface between the two sheets corresponds to the torsional plane of the device. Shims or an adjusting mechanism may be used for this purpose. Torque shall be applied to the longer sides of the specimen. Rotation of the specimen shall be possible without tilting the specimen sheets or the gripper.

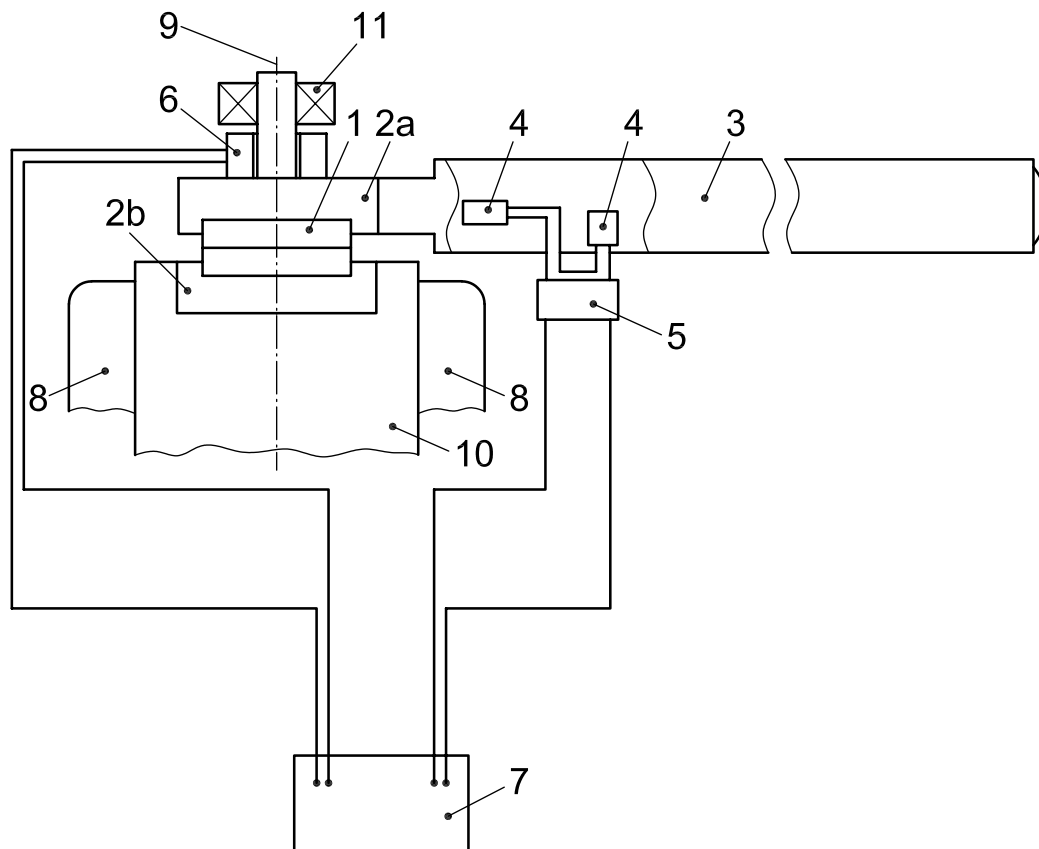

**Key**

- 1 specimen
- 2a specimen grip (rotatable)
- 2b specimen grip (fixed)
- 3 torque bar
- 4 strain gauge
- 5 strain gauge amplifier
- 6 torsion angle sensor
- 7 data recorder
- 8 grips of clamping device for holding testing jig
- 9 rotation axis
- 10 housing for specimen grippers 2a and 2b with common rotation axis and bearing
- 11 bearing

**Figure 3 — Example of measuring equipment for instrumented torsion test**


The torque is applied manually using a lever or a mechanized drive on the rotating part of the testing device (upper part). During testing, the lever is moved steadily through 90° in approximately 5 s.

Torque and torsion angle are measured during testing, using measuring equipment as shown in Figure 3, for example. The values should be recorded using a suitable instrument, for example a data recorder.

The centre of electrode indentation shall not deviate by more than 0,5 mm from the axis of rotation.

**6 Evaluation of test results whenever applying the instrumented torsion tests**

A torque,  $T$ , torsion angle,  $\varphi$ , curve is used to determine the maximum torque,  $T_{max}$ , and the corresponding torsion angle (see Figure 4).

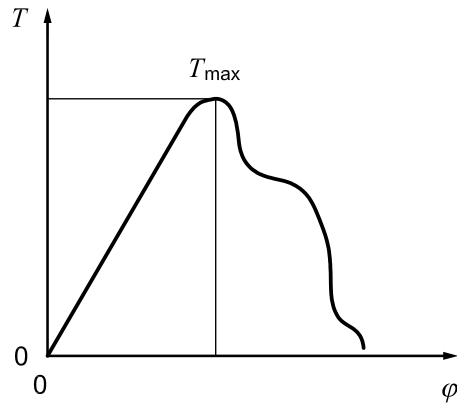

**Key**

- $T$  torque  
 $T_{\max}$  maximum torque  
 $\varphi$  torsion angle

**Figure 4 — Example of a torque vs. torsion angle curve recorded in a torsion test**

The weld diameter and failure type shall be determined from the fractured specimens in accordance with ISO 14329.

NOTE Torque, torsion angle and failure type are dependent on the sheet thickness, the weld diameter and the mechanical characteristics of the weld nugget, heat-affected zone and parent metal.

## 7 Test report

The test report shall include at least the following information:

- a) reference to this International Standard, i.e. ISO 17653:2012;
- b) welding equipment used;
- c) welding conditions;
- d) designation of the materials and sheet thicknesses;
- e) weld diameter,  $d$ ;
- f) maximum torque and corresponding torsion angle, if applicable;
- g) failure type, appearance of the fractured surface (spatter or weld splash, pores, lack of fusion);
- h) details of the test procedure and measuring equipment used;
- i) any deviations from this International Standard.





# British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

## About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

## Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at [bsigroup.com/standards](http://bsigroup.com/standards) or contacting our Customer Services team or Knowledge Centre.

## Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at [bsigroup.com/shop](http://bsigroup.com/shop), where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

## Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to [bsigroup.com/subscriptions](http://bsigroup.com/subscriptions).

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

**PLUS** is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit [bsigroup.com/shop](http://bsigroup.com/shop).

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email [bsmusales@bsigroup.com](mailto:bsmusales@bsigroup.com).

## BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK

## Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

## Copyright

All the data, software and documentation set out in all British Standards and other BSI publications are the property of and copyrighted by BSI, or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI. Details and advice can be obtained from the Copyright & Licensing Department.

## Useful Contacts:

### Customer Services

**Tel:** +44 845 086 9001

**Email (orders):** [orders@bsigroup.com](mailto:orders@bsigroup.com)

**Email (enquiries):** [cservices@bsigroup.com](mailto:cservices@bsigroup.com)

### Subscriptions

**Tel:** +44 845 086 9001

**Email:** [subscriptions@bsigroup.com](mailto:subscriptions@bsigroup.com)

### Knowledge Centre

**Tel:** +44 20 8996 7004

**Email:** [knowledgecentre@bsigroup.com](mailto:knowledgecentre@bsigroup.com)

### Copyright & Licensing

**Tel:** +44 20 8996 7070

**Email:** [copyright@bsigroup.com](mailto:copyright@bsigroup.com)



...making excellence a habit.™