

**BS EN ISO 17828:2015**



**BSI Standards Publication**

# **Solid biofuels — Determination of bulk density**

**bsi.**

...making excellence a habit.™

**National foreword**

This British Standard is the UK implementation of EN ISO 17828:2015. It supersedes BS EN 15103:2009 which is withdrawn.

The UK participation in its preparation was entrusted to Technical Committee PTI/17, Solid biofuels.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© The British Standards Institution 2016.

Published by BSI Standards Limited 2016

ISBN 978 0 580 81421 1

ICS 27.190; 75.160.10

**Compliance with a British Standard cannot confer immunity from legal obligations.**

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 31 January 2016.

**Amendments/corrigenda issued since publication**

Date	Text affected
------	---------------

---

EUROPEAN STANDARD

**EN ISO 17828**

NORME EUROPÉENNE

EUROPÄISCHE NORM

December 2015

ICS 75.160.10; 27.190

Supersedes EN 15103:2009

English Version

## Solid biofuels - Determination of bulk density (ISO 17828:2015)

Biocombustibles solides - Détermination de la masse volumique apparente (ISO 17828:2015)

Biogene Festbrennstoffe - Bestimmung der Schüttdichte (ISO 17828:2015)

This European Standard was approved by CEN on 17 October 2015.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN-CENELEC Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION  
COMITÉ EUROPÉEN DE NORMALISATION  
EUROPÄISCHES KOMITEE FÜR NORMUNG

**CEN-CENELEC Management Centre: Avenue Marnix 17, B-1000 Brussels**

## **European foreword**

This document (EN ISO 17828:2015) has been prepared by Technical Committee ISO/TC 238 "Solid biofuels" in collaboration with Technical Committee CEN/TC 335 "Solid biofuels" the secretariat of which is held by SIS.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by June 2016, and conflicting national standards shall be withdrawn at the latest by June 2016.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN [and/or CENELEC] shall not be held responsible for identifying any or all such patent rights.

This document supersedes EN 15103:2009.

This document has been prepared under a mandate given to CEN by the European Commission and the European Free Trade Association.

According to the CEN-CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and the United Kingdom.

### **Endorsement notice**

The text of ISO 17828:2015 has been approved by CEN as EN ISO 17828:2015 without any modification.

# Contents

Page

<b>Foreword</b> .....	<b>iv</b>
<b>Introduction</b> .....	<b>v</b>
<b>1 Scope</b> .....	<b>1</b>
<b>2 Normative references</b> .....	<b>1</b>
<b>3 Terms and definitions</b> .....	<b>1</b>
<b>4 Principle</b> .....	<b>1</b>
<b>5 Apparatus</b> .....	<b>1</b>
5.1 Measuring containers.....	1
5.1.1 General.....	1
5.1.2 Large container.....	2
5.1.3 Small container.....	2
5.2 Balances.....	3
5.2.1 Balance 1.....	3
5.2.2 Balance 2.....	3
5.3 Scantlings.....	3
5.4 Wooden board.....	3
<b>6 Sample preparation</b> .....	<b>3</b>
<b>7 Procedure</b> .....	<b>3</b>
7.1 Determination of the container volume.....	3
7.2 Container selection.....	3
7.3 Measurement procedure.....	3
<b>8 Calculation</b> .....	<b>4</b>
8.1 Calculation of bulk density as received.....	4
8.2 Calculation of bulk density on dry basis.....	5
<b>9 Performance characteristics</b> .....	<b>5</b>
9.1 General.....	5
9.2 Repeatability.....	5
9.3 Reproducibility.....	5
<b>10 Test report</b> .....	<b>5</b>
<b>Annex A (informative) Measuring differences of sample treatment with and without shock impact</b> .....	<b>7</b>
<b>Bibliography</b> .....	<b>8</b>

## Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see [www.iso.org/directives](http://www.iso.org/directives)).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see [www.iso.org/patents](http://www.iso.org/patents)).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation on the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the WTO principles in the Technical Barriers to Trade (TBT) see the following URL: [Foreword - Supplementary information](#)

The committee responsible for this document is ISO/TC 238, *Solid biofuels*.

## Introduction

Bulk density is an important parameter for fuel deliveries on volume basis, and together with the net calorific value, it determines the energy density. It also facilitates the estimation of space requirements for transport and storage. This International Standard describes the determination of the bulk density of pourable solid biofuels, which can be conveyed in a continuous material flow.

For practical reasons, two standard measuring containers with a volume of 5 l or 50 l were chosen for the determination. Due to the limited volume of these containers, some fuels are therefore excluded from the scope of this International Standard. This, for example, applies for chunk wood, non-comminuted bark, baled material and larger briquettes. The bulk density of such fuels can be calculated from their mass and the volume of the container or lorry used for transportation.

To decide on the actual storage volume requirement of a solid biofuel the different storage conditions, which usually differ largely from the conditions of sample analysis (e.g. height of heap versus volume of the standard measuring container, moisture content) also have to be taken into account.

The described method herein includes a defined shock exposure of the bulk material for several reasons. A shock leads to a certain volume reduction, which accounts for compaction effects occurring during the production chain. These compaction effects are mainly due the fact, that the fuel is usually transported and/or stored in containers or silos that are much larger than the measuring container as chosen for the described method. Thus, in practice, the higher mass load leads to an increased load pressure and to settling of the material, which can also be additionally enhanced by the vibrations during transportation. Furthermore, filling or unloading operations in practice usually apply a higher falling depth than the one chosen for the performed test. This will also result in a respectively higher compaction due to the increased kinetic energy of the particles falling. A procedure which applies a controlled shock to the sample was thus believed to reflect the practically prevailing bulk density in a better way than a method without shock. This is particularly true when the mass of a delivered fuel has to be estimated from the volume load of a transporting vehicle, which is a common procedure in many countries. For a rough estimation on how susceptible the different solid biofuels are towards the shock exposure, some research data are given in Annex A. The data show a compaction effect between 6 % and 18 % for biomass fuels.





# Solid biofuels — Determination of bulk density

## 1 Scope

This International Standard defines a method of determining bulk density of solid biofuels by the use of a standard measuring container. This method is applicable to all pourable solid biofuels with a nominal top size of maximum 100 mm.

Bulk density is not an absolute value; therefore, conditions for its determination have to be standardized in order to gain comparative measuring results.

**NOTE** Bulk density of solid biofuels is subject to variation due to several factors such as vibration, shock, pressure, biodegradation, drying, and wetting. Measured bulk density can therefore deviate from actual conditions during transportation, storage, or transshipment.

## 2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 14780, *Solid biofuels — Sample preparation*<sup>1)</sup>

ISO 16559, *Solid biofuels — Terminology, definitions and descriptions*

ISO 18134-1, *Solid biofuels — Determination of moisture content — Oven dry method, Part 1: Total moisture — Reference method*

ISO 18134-2, *Solid biofuels — Determination of moisture content — Oven dry method, Part 2: Total moisture — Simplified procedure*

ISO 18135, *Solid biofuels — Sampling*<sup>1)</sup>

## 3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 16559 apply.

## 4 Principle

A standard container is filled with the test portion of a given size and shape, densified by defined shock exposure and weighed afterwards. The bulk density is calculated from the net weight per standard volume and reported with the determined moisture content.

## 5 Apparatus

### 5.1 Measuring containers


#### 5.1.1 General

The container shall be cylindrically shaped and manufactured of a shock resistant, smooth-surfaced material. The container shall be resistant to deformation in order to prevent any variation in shape

---

1) In preparation.

and volume. The container has to be waterproof. For easier handling, grips can be fixed externally. The height-diameter-ratio shall be within 1,25 and 1,50.

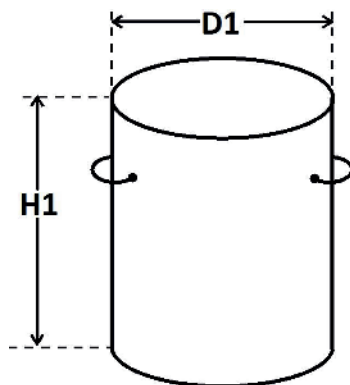


**Key**

D1 = 360 mm

H1 = 491 mm

**Figure 1 — Large measuring container**

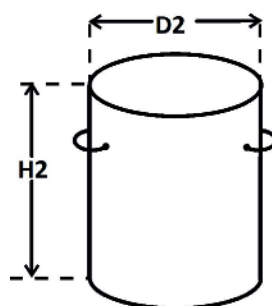

**Key**

D2 = 167 mm

H2 = 228 mm

**Figure 2 — Small measuring container**

**5.1.2 Large container**

The large measuring container (see [Figure 1](#)) has a filling volume of 50 l (0,05 m<sup>3</sup>) volume. The volume can deviate by 1 l (= 2 %). It shall have an effective (inner) diameter of 360 mm and an effective (inner) height of 491 mm (see [Figure 1](#)). Deviations from these dimensions are tolerable, if the height-diameter-ratio remains as given in [5.1.1](#).

**5.1.3 Small container**

The small measuring container (see [Figure 2](#)) has a filling volume of 5 l (0,005 m<sup>3</sup>) volume. The volume can deviate by 0,1 l (= 2 %). It shall have an effective (inner) diameter of 167 mm and an effective (inner) height of 228 mm (see [Figure 2](#)). Deviations from these dimensions are tolerable, if the height-diameter-ratio remains as given in [5.1.1](#).

## 5.2 Balances

### 5.2.1 Balance 1

A balance shall be capable of reading to the nearest 10 g. This balance shall be used for measurements with the large container.

### 5.2.2 Balance 2

A balance shall be capable of reading to the nearest 1 g. This balance shall be used for measurements with the small container.

## 5.3 Scantlings

A rigid scantling with a length exceeding the diameter of the container in [5.1.1](#) shall be used for levelling the material in the measuring container by lateral movements of the scantling across the rim of the measuring container.

NOTE It is advisable to use a second scantling or other device for spacing the dropping height of 150 mm between the measuring container and the wooden board in [5.4](#).

## 5.4 Wooden board

A flat wooden board [e.g. oriented strand board (OSB)] with a thickness of approximately 15 mm and sufficient in size for dropping the container during shock exposure.

## 6 Sample preparation

Sampling shall be carried out in accordance with ISO 18135. If necessary, the sample can be divided in to test portions in accordance with ISO 14780. The test portion volume shall exceed the volume of the container measures by minimum of 30 %.

NOTE Precautions should be taken to ensure that the moisture is evenly distributed within the sample.

## 7 Procedure

### 7.1 Determination of the container volume

Before use, the mass and filling volume of the container shall be determined. Weigh the empty, clean, and dry container on the balance ([5.2.1](#) or [5.2.2](#)). Then fill the container with water and a few drops of wetting agent (e.g. liquid soap) until maximum capacity; then weigh it again. The water should be at a temperature between 10 °C and 20 °C. Calculate the volume (V) of the container from the net weight of water and the density of the water (1 kg/dm<sup>3</sup>) and record the result rounded to the nearest 0,01 l (0,000 01 m<sup>3</sup>) for the large container or 0,001 l (0,000 001 m<sup>3</sup>) for the small container.

NOTE 1 The effect of temperature on the density of water is negligible.

NOTE 2 The container should be cleaned regularly and its volume should be checked regularly.

### 7.2 Container selection

The large container ([5.2.1](#)) can be used for larger materials within the scope of this International Standard. For materials with a nominal top size up to 12 mm and for pellets with a diameter equal or below 12 mm the small container ([5.2.2](#)) can be used (optional).

### 7.3 Measurement procedure

- a) Fill the container by pouring the sample material from a height of 200 mm to 300 mm above the upper rim until a cone of maximum possible height is formed.

NOTE Make sure that the container is dry and clean before being (re)filled.

- b) The filled container is then shock exposed to allow settling. This shall be done by dropping it freely from 150 mm height onto a wooden board (5.4). Before shock exposure, remove particles from the wooden board within the dropping area. Make sure that the container hits the board in a vertical position. Repeat the shock exposure two more times to apply a total of three shock exposures. Then refill the resulting empty space at the top of the container in accordance with 7.3 a).

NOTE The second scantling or device referred to in 5.3 can be used for spacing of the distance between the measuring container and the wooden board before dropping. Also, other mechanisms to create a comparable shock impact can be suitable.

- c) Remove surplus material by using a scantling (5.3), which is shuffled over the container's edge in oscillating movements. When the test portion contains coarse material, all particles preventing the free passage of the scantling have to be removed by hand. If the removal of larger particles tears bigger holes into the leveled surface, the cavities shall be refilled and the removal procedure is repeated.
- d) Weigh the container with the remaining sample material.
- e) Unify the used sample material with the unused sample material and repeat the procedure from 7.3 a) to 7.3 d) at least once in order to get duplicate determinations.
- f) Determine moisture content of the test sample material as received according to ISO 18134-1 or ISO 18134-2 immediately after bulk density determination.

## 8 Calculation

### 8.1 Calculation of bulk density as received

Calculate the bulk density of the sample as received ( $BD_{ar}$ ) according to Formula (1):

$$BD_{ar} = \frac{(m_2 - m_1)}{V} \quad (1)$$

where

$BD_{ar}$  is the bulk density as received in  $\text{kg}/\text{m}^3$ ;

$BD_d$  is the bulk density of the sample on dry basis in  $\text{kg}/\text{m}^3$ ;

$m_1$  is the mass of the empty container in kg;

$m_2$  is the mass of the filled container in kg;

$V$  is the net volume of the measuring container in  $\text{m}^3$ .

The result for each individual determination shall be calculated to 0,1 decimal place and for reporting purposes the mean value of the individual results shall be calculated and rounded to the nearest  $10 \text{ kg}/\text{m}^3$ .

## 8.2 Calculation of bulk density on dry basis

Calculate the bulk density of the test portion mass on dry basis ( $BD_d$ ) in accordance with Formula (2):

$$BD_d = BD_{ar} \times \frac{(100 - M_{ar})}{100} \quad (2)$$

NOTE Formula (2) in 8.2 disregards shrinkage or expansion, which usually causes significant deviations when the test portion is measured at different drying stages. For wood fuels, these phenomena usually occur at a moisture content below the fibre saturation point, which is at around 25 % moisture content, depending on the wood species. A true comparison between material samples is therefore only possible when bulk density is measured at similar moisture contents. If material samples with different moisture content shall be compared and at least one sample is below the fibre saturation point, the usual effect of swelling or shrinkage is in the order of around 0,7 % volume change per percentage point of moisture difference below the fibre saturation point (see Reference [1]). For a comparison of measurements based on materials with similar moisture content, the application of this correction factor can be useful.

## 9 Performance characteristics

### 9.1 General

**Table 1 — Repeatability and reproducibility limits**

Bulk density	Maximum acceptable differences between results obtained	
	Repeatability limits	Reproducibility limits
Bulk density below 300 kg/m <sup>3</sup>	3,0 %	6,0 %
Bulk density equal or above 300 kg/m <sup>3</sup>	2,0 %	4,0 %

### 9.2 Repeatability

The results obtained for bulk density as received ( $BD_{ar}$ ) of the duplicate determinations (see 7.3), performed within a short period of time by the same operator using the same apparatus in the same laboratory shall not differ by more than the values in Table 1 (see Reference [2]).

### 9.3 Reproducibility

The mean values of the results of duplicate determinations (see 7.3) for bulk density as received ( $BD_{ar}$ ), performed in each of two different laboratories on representative test portions taken from the same sample material shall not differ by more than the values in Table 1 (see Reference [2]).

## 10 Test report


The test report shall include at least the following information:

- identification of laboratory performing the test and the date of the test;
- identification of the product (or sample) tested;
- a reference to this International Standard, i.e. ISO 17828;
- specification of the applied container size;
- result of the test at moisture content as received according to 8.1 (required) or according to 8.2 (optional), expressed with relevant symbols;

- f) any unusual features noted during the determination, which can affect the result;
- g) any deviation from this International Standard or operations regarded as optional.

## Annex A (informative)

### Measuring differences of sample treatment with and without shock impact

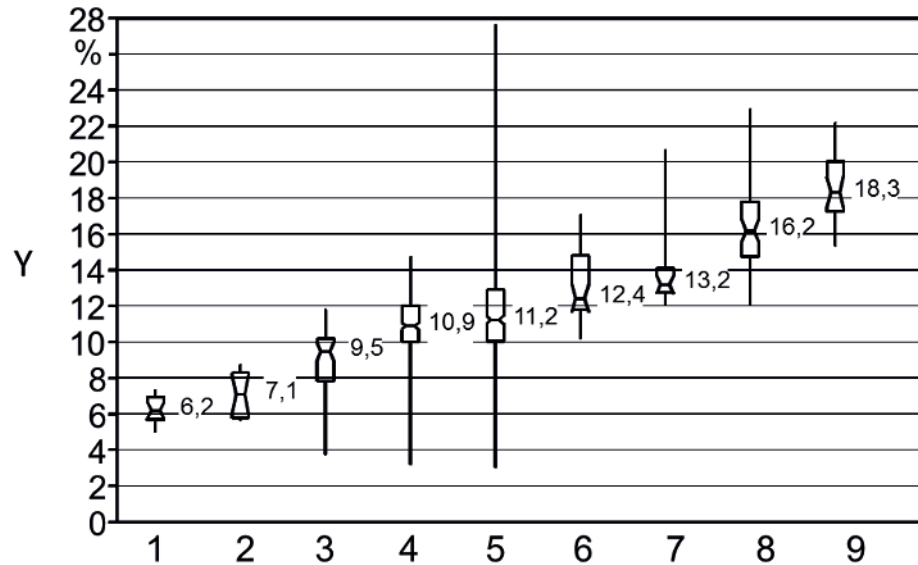

Legend		
Y Relative deviation in % to non-shock application	Number of replications	
1 Wood pellets	21	
2 Grain kernels	12	
3 Herbaceous pellets	42	
4 High density wood chips	312	
5 Low density wood chips	492	
6 Sawdust	39	
7 Peat	18	
8 Bark	63	
9 Chopped miscanthus	24	

**Figure A.1**

Representation of the relative effect of shock impact compared to a non-shock application for bulk density determination, here given for the 50-l-container dropped three times before re-filling, surface levelling and weighing. The boundary value for high or low bulk density grouping of wood chips was 180 kg/m<sup>3</sup> (see Reference [1]).

## Bibliography

- [1] HARTMANN H., BÖHM T., DAUGBJERG JENSEN P. Temmerman, M.; Rabier, F.; Jirjis, R. Hersener, J.-L.; Rathbauer, J.: Methods for Bulk Density Determination of Solid Biofuels. In: Van Swaaij, W. P. M.; Fjällström, T.; Helm, P.; Grassi, A. (Eds.): 2nd World Conference and Technology Exhibition on Biomass for Energy, Industry and Climate Protection, Rome, 10-14 May 2004, pp. 662-665
- [2] BÖHM T., & HARTMANN H. Guidelines for bulk density determination – European project “Pre-normative work on sampling and testing of solid biofuels for the development of quality assurance systems” (BioNorm) ENK6-CT-2001-00556, Deliverable D4 Part 2, Technology and Support Centre of Renewable Raw Materials. TFZ, Straubing, Germany, 2004









# British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

## About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

## Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at [bsigroup.com/standards](http://bsigroup.com/standards) or contacting our Customer Services team or Knowledge Centre.

## Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at [bsigroup.com/shop](http://bsigroup.com/shop), where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

## Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to [bsigroup.com/subscriptions](http://bsigroup.com/subscriptions).

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

**PLUS** is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit [bsigroup.com/shop](http://bsigroup.com/shop).

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email [bsmusales@bsigroup.com](mailto:bsmusales@bsigroup.com).

## BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK

## Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

## Copyright

All the data, software and documentation set out in all British Standards and other BSI publications are the property of and copyrighted by BSI, or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI. Details and advice can be obtained from the Copyright & Licensing Department.

## Useful Contacts:

### Customer Services

**Tel:** +44 845 086 9001

**Email (orders):** [orders@bsigroup.com](mailto:orders@bsigroup.com)

**Email (enquiries):** [cservices@bsigroup.com](mailto:cservices@bsigroup.com)

### Subscriptions

**Tel:** +44 845 086 9001

**Email:** [subscriptions@bsigroup.com](mailto:subscriptions@bsigroup.com)

### Knowledge Centre

**Tel:** +44 20 8996 7004

**Email:** [knowledgecentre@bsigroup.com](mailto:knowledgecentre@bsigroup.com)

### Copyright & Licensing

**Tel:** +44 20 8996 7070

**Email:** [copyright@bsigroup.com](mailto:copyright@bsigroup.com)



...making excellence a habit.™