

Advanced technical ceramics — Methods of test for ceramic powders

Part 8. Determination of tapped bulk density

The European Standard EN 725-8 : 1997 has the status of a
British Standard

ICS 81.060.99

Committees responsible for this British Standard

The preparation of this British Standard was entrusted to Technical Committee RPI/13, Advanced technical ceramics, upon which the following bodies were represented:

AEA Technology
Aluminium Federation
British Ceramic Research Ltd.
British Industrial Ceramic Manufacturers' Association
Department of Trade and Industry (National Physical Laboratory)
Flat Glass Manufacturers' Association
GAMBICA (BEAMA Ltd.)
Institute of Refractories Engineers
Ministry of Defence
Refractories Association of Great Britain
Society of British Aerospace Companies Ltd.
University of Manchester

This British Standard, having been prepared under the direction of the Sector Board for Materials and Chemicals, was published under the authority of the Standards Board and comes into effect on 15 July 1997

© BSI 1997

Amendments issued since publication

Amd. No.	Date	Text affected

The following BSI references relate to the work on this standard:
Committee reference RPI/13
Draft for comment 93/301337 DC

ISBN 0 580 27908 1

Contents

	Page
Committees responsible	Inside front cover
National foreword	ii
Foreword	2
Text of EN 725-8	3

National foreword

This British Standard has been prepared by Technical Committee RPI/13 and is the English language version of EN 725-8 : 1997 *Advanced technical ceramics — Methods of test for ceramic powders — Part 8: Determination of tapped bulk density*, published by the European Committee for Standardization (CEN).

EN 725-8 : 1997 was produced as a result of international discussions in which the United Kingdom took an active part.

EN 725-8 : 1997 has been approved by CEN member bodies under the weighted voting procedures introduced in 1988 to coincide with the introduction of 'New Approach' Directives from the Commission of the European Community.

NOTE. International and European Standards as well as overseas standards, are available from Customer Services, BSI, 389 Chiswick High Road, London, W4 4AL.

Compliance with a British Standard does not of itself confer immunity from legal obligations.

Summary of pages

This document comprises a front cover, an inside front cover, pages i and ii, the EN title page, pages 2 to 4, an inside back cover and a back cover.

ICS 81.060.99

Descriptors: Ceramics, powdery materials, tests, determination, bulk density, setting

English version

Advanced technical ceramics — Methods of test for ceramic
powders —
Part 8: Determination of tapped bulk density

Céramiques techniques avancées — Méthodes
d'essai pour poudres céramiques —
Partie 8: Détermination de la masse volumique
après tassement

Hochleistungskeramik — Prüfverfahren für
keramische Pulver —
Teil 8: Bestimmung der Klopfichte

This European Standard was approved by CEN on 1996-12-22. CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration.

Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Central Secretariat or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Central Secretariat has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and United Kingdom.

CEN

European Committee for Standardization
Comité Européen de Normalisation
Europäisches Komitee für Normung

Central Secretariat: rue de Stassart 36, B-1050 Brussels

Foreword

This European Standard has been prepared by Technical Committee CEN/TC184, Advanced technical ceramics, the secretariat of which is held by BSI.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by September 1997, and conflicting national standards shall be withdrawn at the latest by September 1997.

EN 725 consists of 11 parts:

- Part 1 : *Determination of impurities in alumina*
- Part 2 : *Determination of impurities in barium titanate (ENV)*
- Part 3 : *Determination of oxygen content of non-oxides by thermal extraction*
- Part 4 : *Determination of oxygen content of non-oxides by XRF analysis (ENV)*
- Part 5 : *Determination of particle size distribution*
- Part 6 : *Determination of specific area*
- Part 7 : *Determination of absolute density*
- Part 8 : *Determination of tapped bulk density*
- Part 9 : *Determination of untamped bulk density*
- Part 10 : *Determination of compaction properties*
- Part 11 : *Determination of reactivity on sintering (ENV)*

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and the United Kingdom.

Contents

	Page
Foreword	2
1 Scope	3
2 Principle	3
3 Apparatus	3
4 Procedure	3
5 Expression of results	3
6 Test report	3
7 Repeatability and reproducibility	4

1 Scope

This part of EN 725 describes a method for the determination of the tapped bulk density of ceramic powders.

2 Principle

The mass of a known volume of the powder is determined after allowing it to fall freely into a stationary container and then tapping it under specified conditions.

The tapped bulk density is expressed by division of this mass by the volume of the container.

3 Apparatus (see figure 1)

3.1 *Stainless steel cylindrical container*, of volume approximately 100 cm³ and a diameter to height ratio of 1.

3.2 *24 mesh (710 μm) sieve*, with a typical diameter of 80 mm.

3.3 *Balance*, with a precision of 0,01 g.

3.4 *Tray*, to collect the powder during the filling of the container.

3.5 *Suitable apparatus for the powder sieve assembly*, including a fixing system for the sieve with a cone in its lower part to allow the sieve and the cone to be set to a predetermined height above the top level of the ring (see 3.6), and an electric system to regulate the vibration of the sieve.

3.6 *Ring*, height 50 mm, which can be fitted to the top of the stainless steel cylindrical container to increase its height.

3.7 *Tapping system*, which permits the tapping of the cylinder and its ring. The stroke shall be 20 mm and the tapping frequency shall be 50 taps per minute.

4 Procedure

4.1 Sample treatment

If there is any treatment of the sample of powder before measurement (e.g. drying), this shall be recorded in the test report.

4.2 Measurement

Weigh the cylindrical container (see 3.1). Place the plastic ring (see 3.6) on the top of the cylindrical container (see 3.1). Set the cylindrical container with its ring in the tray (see 3.4) so that its axis coincides with that of the cone, with the level of the sieve at a height of 190 mm above the top of the container.

Fill the sieve with the sample. If necessary start the vibration system (see 3.5) and regulate it to allow the powder to flow evenly. Fill the cylindrical container and its ring in between 40 s and 60 s. Stop the feed when the powder has formed a cone above the top of the plastic ring and is spilling over.

Place the cylindrical container with its ring, filled with the powder, on the tapping device. Start the tapping at a rate of 50 taps/min and maintain for 180 s. Remove the cylindrical container and its ring from the tapping device without vibration. Carefully remove the ring from the cylindrical container.

Remove the cone of surplus powder by gently drawing a straight edge across the top rim of the cylindrical container, without communicating any vibration to the latter.

Weigh the cylindrical container and its contents.

5 Expression of results

The tapped bulk density ρ_b is given by the formula:

$$\rho_b = \frac{m_1 - m_0}{V}$$

where

m_0 is the mass, in grams, of the empty cylindrical container;

m_1 is the mass, in grams, of the cylindrical container full of powder after tapping;

V is the volume, in cubic centimetres, of the cylindrical container.

Calculate the density in grams per cubic centimetre and then convert the answer to kilograms per cubic metre, to the nearest 5 kg/m³.

6 Test report


The test report shall include the following information:

- the name of the testing establishment;
- date of the test, report identification and number, operator, signatory;
- a reference to this standard, i.e. determined in accordance with EN 725-8;
- a description of the powder (material type, manufacturer, batch or code number);
- any pre-treatment of the powder such as drying;
- the results;
- any unusual features noted during the determination;
- comments about the test or test results.

7 Repeatability and reproducibility

The experience of three laboratories indicates that the method is capable, for an alumina powder with a tapped bulk density of $1\,526\text{ kg/m}^3$, of achieving:

- a) a standard deviation of repeatability of 8 kg/m^3 ;
- b) a standard deviation of reproducibility of 13 kg/m^3 .

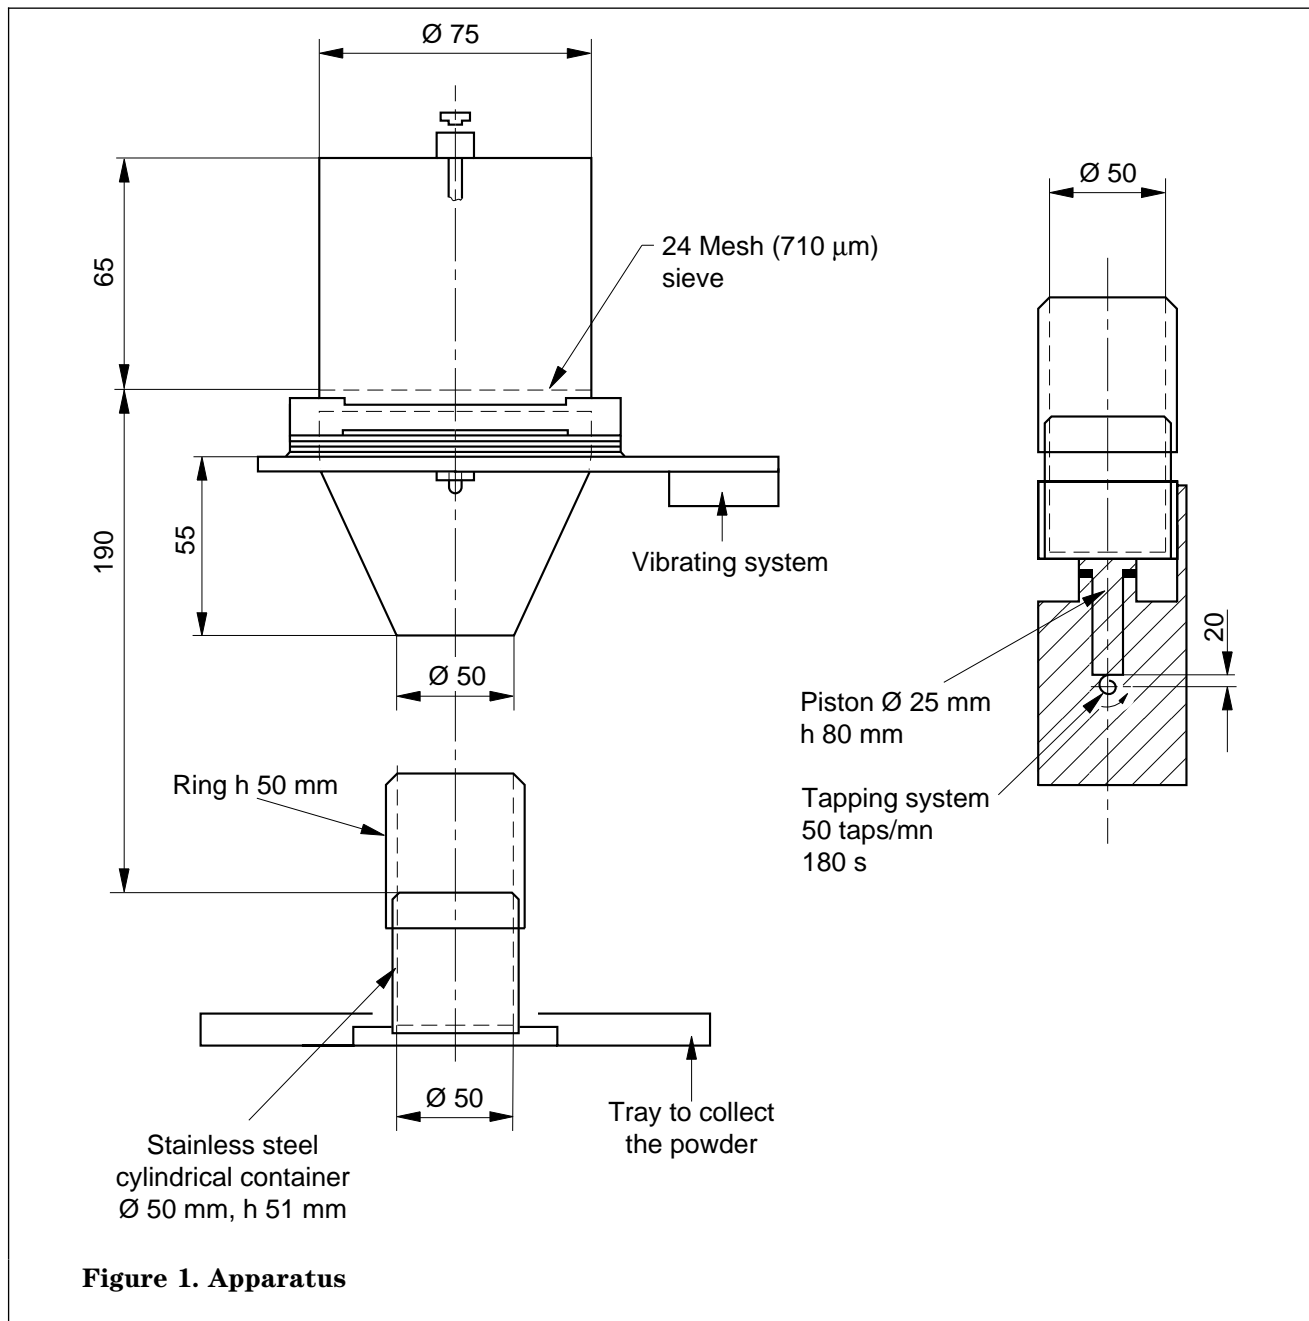

BSI — British Standards Institution

BSI is the independent national body responsible for preparing British Standards. It presents the UK view on standards in Europe and at the international level. It is incorporated by Royal Charter.

Revisions

British Standards are updated by amendment or revision. Users of British Standards should make sure that they possess the latest amendments or editions.

It is the constant aim of BSI to improve the quality of our products and services. We would be grateful if anyone finding an inaccuracy or ambiguity while using this British Standard would inform the Secretary of the technical committee responsible, the identity of which can be found on the inside front cover. Tel: 020 8996 9000. Fax: 020 8996 7400.

BSI offers members an individual updating service called PLUS which ensures that subscribers automatically receive the latest editions of standards.

Buying standards

Orders for all BSI, international and foreign standards publications should be addressed to Customer Services. Tel: 020 8996 9001. Fax: 020 8996 7001.

In response to orders for international standards, it is BSI policy to supply the BSI implementation of those that have been published as British Standards, unless otherwise requested.

Information on standards

BSI provides a wide range of information on national, European and international standards through its Library and its Technical Help to Exporters Service. Various BSI electronic information services are also available which give details on all its products and services. Contact the Information Centre. Tel: 020 8996 7111. Fax: 020 8996 7048.

Subscribing members of BSI are kept up to date with standards developments and receive substantial discounts on the purchase price of standards. For details of these and other benefits contact Membership Administration. Tel: 020 8996 7002. Fax: 020 8996 7001.

Copyright

Copyright subsists in all BSI publications. BSI also holds the copyright, in the UK, of the publications of the international standardization bodies. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI.

This does not preclude the free use, in the course of implementing the standard, of necessary details such as symbols, and size, type or grade designations. If these details are to be used for any other purpose than implementation then the prior written permission of BSI must be obtained.

If permission is granted, the terms may include royalty payments or a licensing agreement. Details and advice can be obtained from the Copyright Manager. Tel: 020 8996 7070.