

# Advanced technical ceramics — Methods of testing monolithic ceramics — Thermo-mechanical properties —

## Part 2: Determination of self-loaded deformation

The European Standard EN 820-2:2003 has the status of a  
British Standard

ICS 81.060.30

## National foreword

This British Standard is the official English language version of EN 820-2:2003. It supersedes DD ENV 820-2:1992 which is withdrawn.

The UK participation in its preparation was entrusted to Technical Committee RPI/13, Advanced technical ceramics, which has the responsibility to:

- aid enquirers to understand the text;
- present to the responsible international/European committee any enquiries on the interpretation, or proposals for change, and keep the UK interests informed;
- monitor related international and European developments and promulgate them in the UK.

A list of organizations represented on this committee can be obtained on request to its secretary.

### Cross-references

The British Standards which implement international or European publications referred to in this document may be found in the *BSI Catalogue* under the section entitled “International Standards Correspondence Index”, or by using the “Search” facility of the *BSI Electronic Catalogue* or of British Standards Online.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

**Compliance with a British Standard does not of itself confer immunity from legal obligations.**

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 22 April 2003

### Summary of pages

This document comprises a front cover, an inside front cover, the EN title page, pages 2 to 11 and a back cover.

The BSI copyright date displayed in this document indicates when the document was last issued.

### Amendments issued since publication

Amd. No.	Date	Comments

© BSI 22 April 2003

ISBN 0 580 41604 6

English version

**Advanced technical ceramics - Methods of testing monolithic  
ceramics - Thermo-mechanical properties - Part 2:  
Determination of self-loaded deformation**

Céramiques techniques avancées - Méthodes d'essai pour  
céramiques monolithiques - Propriétés thermo-mécaniques  
- Partie 2: Détermination de la déformation sous son propre  
poids

Hochleistungskeramik - Prüfverfahren für monolithische  
Keramik - Thermomechanische Eigenschaften - Teil 2:  
Bestimmung der Verformung unter Eigengewicht

This European Standard was approved by CEN on 2 January 2003.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Luxembourg, Malta, Netherlands, Norway, Portugal, Slovakia, Spain, Sweden, Switzerland and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION  
COMITÉ EUROPÉEN DE NORMALISATION  
EUROPÄISCHES KOMITEE FÜR NORMUNG

**Management Centre: rue de Stassart, 36 B-1050 Brussels**

# Contents

	page
Foreword.....	3
1 Scope .....	4
2 Normative references .....	4
3 Term and definition.....	4
4 Principle .....	4
5 Apparatus .....	4
6 Test pieces.....	5
7 Procedure .....	5
7.1 Setting up of measurement gauge .....	5
7.2 Marking of the test pieces.....	5
7.3 Measurement of test pieces before heat treatment.....	5
7.4 Heat treatment of test pieces.....	5
7.5 Measurement of the test pieces after heat treatment .....	6
7.6 Calculation of deformation .....	6
8 Determination of the temperature of commencement of self-loaded deformation.....	6
8.1 Determination.....	6
8.2 Limits.....	6
9 Interferences.....	7
10 Test report .....	7

## Foreword

This document (EN 820-2:2003) has been prepared by Technical Committee CEN/TC 184 "Advanced technical ceramics", the secretariat of which is held by BSI.

This document shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by October 2003, and conflicting national standards shall be withdrawn at the latest by October 2003.

This document supersedes ENV 820-2:1992.

EN 820 *Advanced technical ceramics – Methods of testing monolithic ceramics – Thermo-mechanical properties* consists of four parts:

- Part 1: *Determination of flexural strength at elevated temperatures*
- Part 2: *Determination of self-loaded deformation*
- Part 3: *Determination resistance to thermal shock by water quenching*
- Part 4: *Determination of flexural creep deformation at elevated temperatures*

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Luxembourg, Malta, Netherlands, Norway, Portugal, Slovakia, Spain, Sweden, Switzerland and the United Kingdom.

## 1 Scope

This European Standard specifies a method for the determination of the temperature at which the self-loaded deformation of a ceramic test piece commences and the extent of this deformation.

## 2 Normative references

This European Standard incorporates by dated or undated reference, provisions from other publications. These normative references are cited at the appropriate places in the text, and the publications are listed hereafter. For dated references, subsequent amendments to or revisions of any of these publications apply to this European Standard only when incorporated in it by amendment or revision. For undated references the latest edition of the publication referred to applies (including amendments).

EN 60584-1, *Thermocouples - Part 1: Reference tables (IEC 60584-1:1995)*.

EN ISO/IEC 17025, *General requirements for the competence of testing and calibration laboratories (ISO/IEC 17025:1999)*.

ENV 1006, *Advanced technical ceramics - Methods of testing monolithic ceramics - Guidance on the sampling and selection of test pieces*.

## 3 Term and definition

For the purposes of this European Standard the following term and definition applies.

**3.1 self-loaded deformation**  
the property induced by heat, which results in a ceramic body being readily deformed under its own weight

## 4 Principle

The method involves determining whether or not test bars supported only at their ends deform at a series of temperatures, recording any self-loaded deformation observed, and recording the results graphically. The temperature of commencement of self-loaded deformation, taken from the graph, is reported.

This test is intended as a simple method of determining the upper use temperature of ceramic components in a self-loaded condition. The criterion is an upper limit of flexural distortion. The test is suitable for use on furnace construction materials and on any ceramic materials, from which components are subjected to further processing at high temperatures.

## 5 Apparatus

**5.1** Measurement apparatus, of the type shown in Figure 1. The distance between the knife edge supports shall be  $160 \text{ mm} \pm 0,5 \text{ mm}$ . The gauge for measuring deformation (sag or bow) shall be accurate to  $0,01 \text{ mm}$ .

NOTE The dial gauge shown in Figure 1 is an example only.

**5.2** Steel bar, of dimensions as shown in Figure 2, with the top surface flat to  $\pm 0,01 \text{ mm}$  and parallel, to  $\pm 0,01 \text{ mm}$ , to the under surfaces in the regions of reduced thicknesses.

**5.3** Laboratory furnace, capable of achieving  $1600 \text{ }^\circ\text{C}$ , and of holding the temperature uniformly over the area occupied by the test pieces (see Figure 3) to within  $\pm 5 \text{ }^\circ\text{C}$ . A controlled atmosphere, other than air, may be used if required. This shall be reported (see clause 10).

**5.4** Two refractory supports, with square cross-section of approximately 12 mm (see Figure 3), made of material which is compatible with the test material at the test temperature. The supports shall be inspected after each firing and where there is evidence of reaction with the test pieces, the supports shall be replaced.

**5.5** Thermocouples (two), one to control the furnace and one to measure the temperature of the test pieces. The thermocouples shall be either type R, type S or type B in accordance with EN 60584-1.

## 6 Test pieces

Materials for testing shall be selected in accordance with the guidance given in ENV 1006. Test pieces shall be rectangular bars, within the following range of dimensions:

- a) length: 173 mm to 177 mm;
- b) width: 11,5 mm to 12,5 mm;
- c) thickness: 3,9 mm to 4,1 mm.

The test pieces shall be ground flat and parallel so that the thickness tolerance of a set of test pieces shall be  $\pm 0,02$  mm.

**NOTE 1** A set is the number of test pieces which are required for the determination of the temperature of commencement of self-loaded deformation.

Two pieces are required for each determination at a single temperature. Test pieces may be either cut from fired ceramic products or may be prepared especially for this method of test.

**NOTE 2** In the latter case they should be fired before testing in a manner comparable to production firing.

## 7 Procedure

### 1.1 Setting up of measurement gauge

Check that the measurement gauge (see 5.1) probe is positioned at the mid-point between the two knife edges, as shown in Figure 1. Place the steel bar (see 5.2) on the knife edges and adjust the gauge to read zero.

### 7.2 Marking of the test pieces

Mark the upper face of one end of the test piece with refractory paint, as the reference end. Draw a pencil line 8 mm from this reference end, across the top surface of the test piece, to act as a reference marker to be aligned with the knife edge of the reference gauge (see 7.3). Repeat the above procedure for the second test piece.

### 7.3 Measurement of test pieces before heat treatment

Place the test bar in the gauge, reference face uppermost so that the line across the width of the top surface (see 7.2) lies over a knife edge. Record the initial gauge reading ( $M_1$ ) to the nearest 0,01 mm and whether it is positive or negative. Repeat for the second test piece to be included in the heat treatment (see 7.4).

### 7.4 Heat treatment of test pieces

Support the two test pieces, approximately 6 mm apart, on the two square cross-section refractory supports (see 5.4), which are positioned  $160 \text{ mm} \pm 0,5 \text{ mm}$  apart on a refractory batt (see Figure 3). Place the test pieces so that the pencil lines marked across the width of the test pieces are facing upwards and lie over the inside edge of one of the square cross-section supports (see Figure 3). Place the refractory batt with the test pieces in the furnace and position the measuring thermocouple (see 5.5) adjacent to the test pieces. Raise the temperature of the test pieces in the furnace by  $300 \text{ }^\circ\text{C/h}$  to the test temperature without exceeding it, and then maintain that temperature for 1 h. Cool the furnace to room temperature and remove the test pieces.

## EN 820-2:2003 (E)

NOTE The final test temperature should be agreed between the interested parties before the test (see clause 8).

### 7.5 Measurement of the test pieces after heat treatment

Remeasure the test pieces in accordance with the procedure given in 7.2 and 7.3 to obtain the final gauge reading ( $M_2$ ).

### 7.6 Calculation of deformation

The self-loaded deformation, sag or bow, for each temperature tested is calculated from the following expression:

$$\text{Deformation} = M_1 - M_2$$

where

$M_1$  is the initial dial gauge reading (see 7.3);

$M_2$  is the final dial gauge reading (see 7.5).

The deformation shall be expressed in millimetres and the numerical mean of the deformation of both test bars subjected to the same heat treatment temperature shall be determined.

Report the deformation to the nearest 0,01 mm and the test temperatures to the nearest 5 °C.

## 8 Determination of the temperature of commencement of self-loaded deformation

### 8.1 Determination

**8.1.1** Where deformation does not occur at the first test temperature, repeat the test described in clause 7 at a temperature approximately 100 K higher, using two new test pieces taken from the same set, and where necessary carry out further tests at intervals of 100 °C until deformation occurs. When a range of 100 °C over which deformation occurs has been established, carry out further tests at intervals of approximately 50 °C, 25 °C and 12,5 °C until the interval between the observation of 'no deformation' and 'deformation' (see 8.2) is between 10 °C and 15 °C.

**8.1.2** Where deformation occurs at the first test temperature, repeat the test described in clause 7 at a temperature approximately 100 K lower, using two new test pieces taken from the same set, and where necessary carry out further tests at intervals of 100 °C until no deformation occurs. Establish the interval between 'no deformation' and 'deformation' as described in 8.1.1.

### 8.2 Limits

Draw a graph (see Figure 4) to show the deformation of the test pieces against temperature. Use this graph to determine any permanent deformation, as shown in Figure 4.

NOTE Such permanent deformation can be due to irreversible expansion, oxidation, or relief of residual stress and is not due to the load of the test piece (see 9).

For the purpose of this test, the state of 'no deformation' described in 8.1.1 and 8.1.2 occurs when the deformation is 0,03 mm or less, excluding the permanent deformation.

Report the temperature of commencement of self-loaded deformation, taken from the graph as shown in Figure 4.




## 9 Interferences

Other changes can occur during this test which lead to apparent permanent deformation, including permanent density changes, interval stress relief and oxidation. If oxidation or permanent density changes are suspected, checks shall be made on test-piece dimensions and reported in the test report (see 10 i). Residual stress relief may show variable positive or negative apparent deformation. If this is suspected, ensure sufficient testing is undertaken to distinguish the correct onset of permanent plastic deformation.

## 10 Test report

The results shall be reported in accordance with EN ISO/IEC 17025, and the test report shall include the following information:

- a) name and address of the testing laboratory;
- b) date of the tests, report identification, signatory;
- c) reference to this method of test, i.e. 'determined in accordance with EN 820-2';
- d) description of the test material (manufacturer, type, batch number);
- e) method of preparation of the test pieces (see clause 6);
- f) atmosphere of the furnace used;
- g) for each test temperature, the individual values of the deformation and the mean value (see 7.6);
- h) test temperatures for the series of tests, the temperature at which self-loaded deformation commenced (see clause 8 and Figure 4), and the graph showing the results;
- i) comments about the test or the test results.

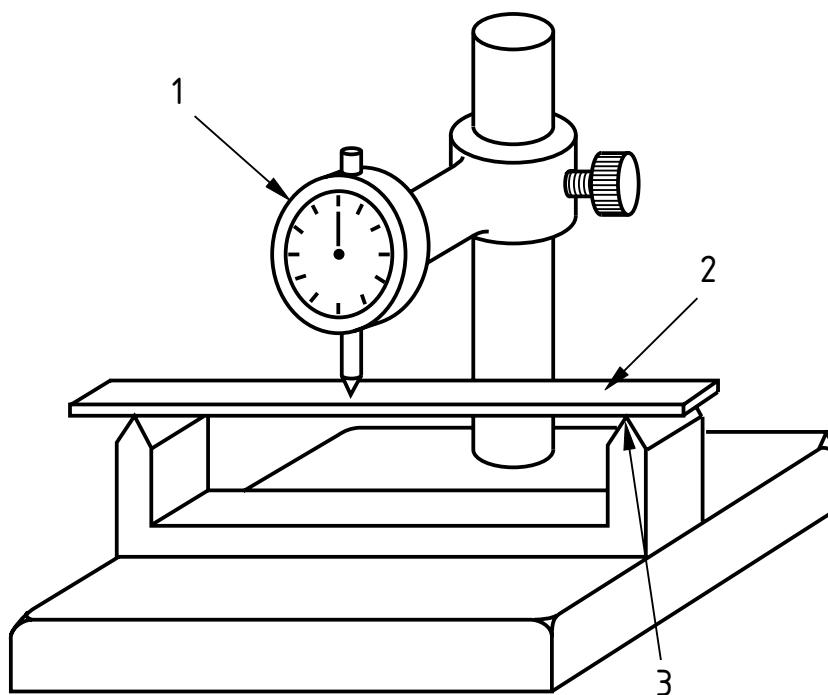

**Key**

- 1 Dial gauge
- 2 Test bar
- 3 Knife edge support

**Figure 1 - Measurement apparatus**

Dimensions in millimetres


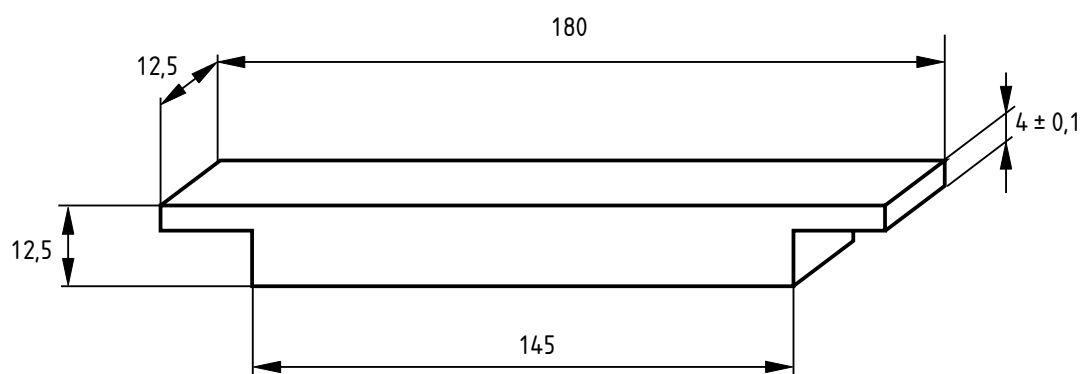


Figure 2 - Steel bar


Dimensions in millimetres

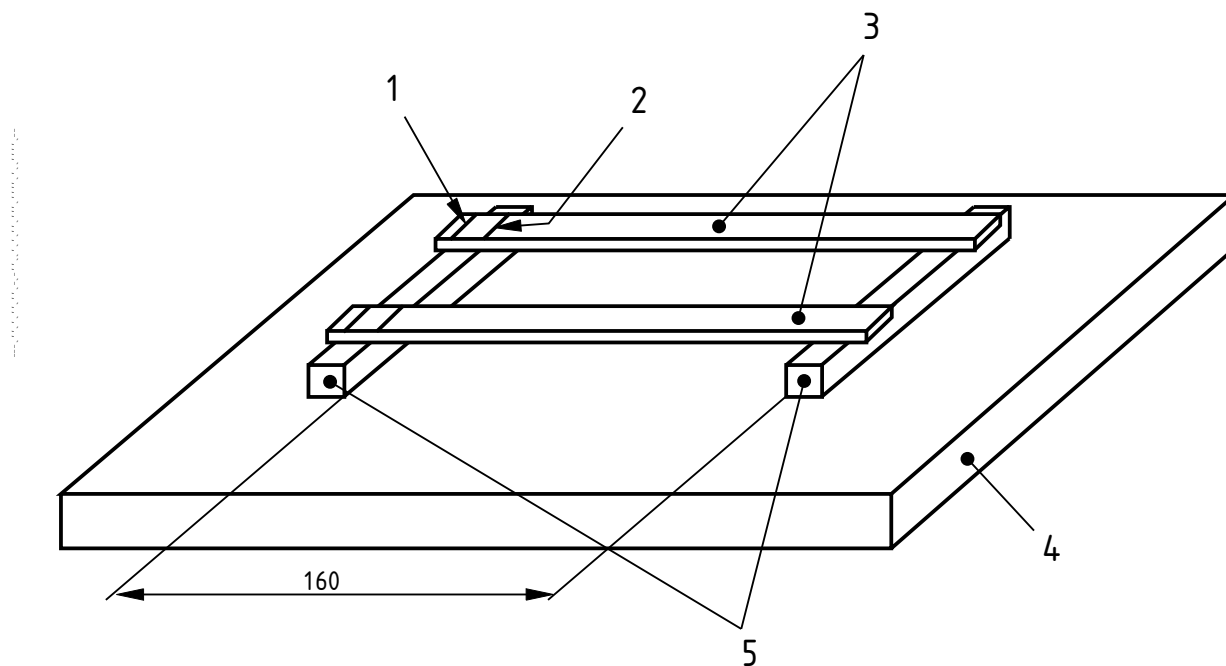

**Key**

- 1 Permanent mark for reference end
- 2 Pencil line (see 7.2)
- 3 Test bars
- 4 Refractory batt
- 5 Square-section refractory bars

**Figure 3 - Arrangement of test pieces for firing**

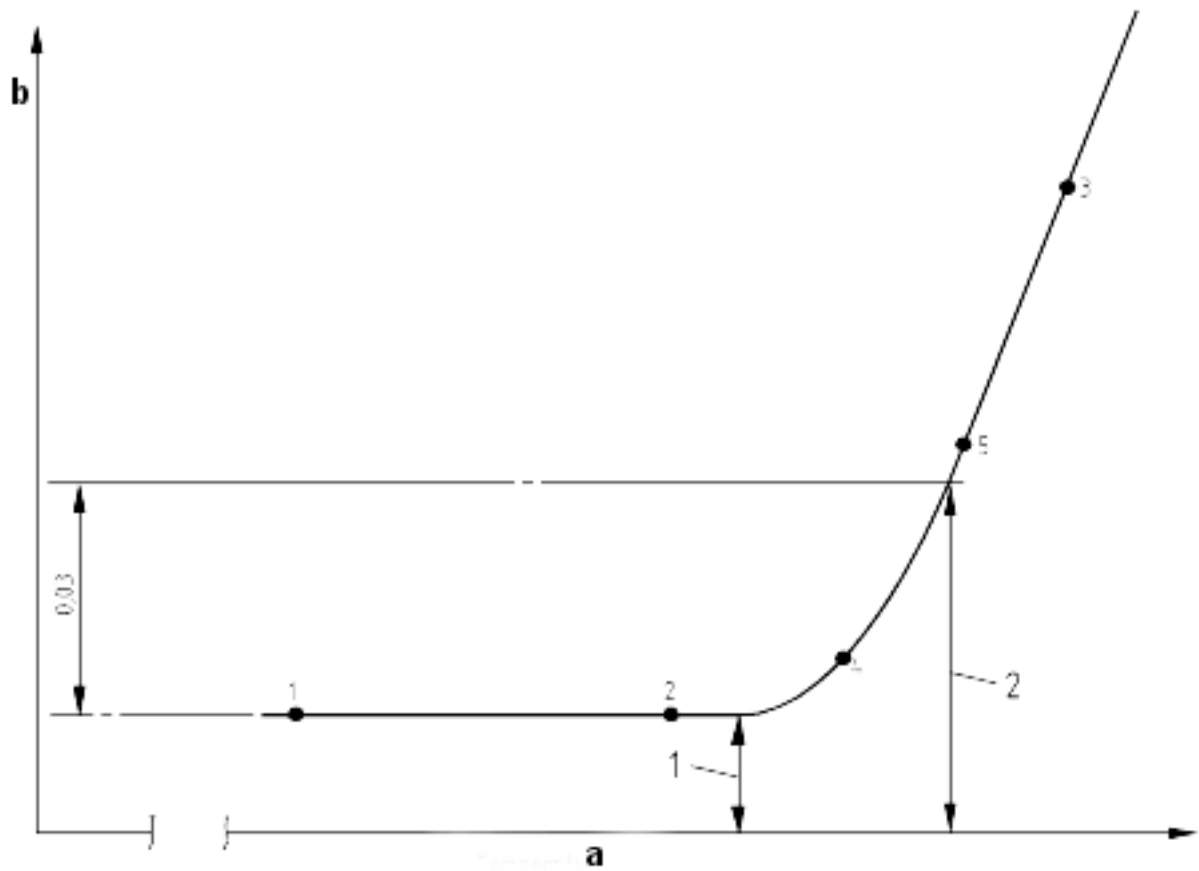

### Key

a Temperature, °C  
b Deformation, mm

- 1 Permanent deformation
- 2 Temperature of onset of self-loaded deformation

**Figure 4 - Determination of onset of self-loaded deformation, showing sequence of determinations**

---

---

## BSI — British Standards Institution

BSI is the independent national body responsible for preparing British Standards. It presents the UK view on standards in Europe and at the international level. It is incorporated by Royal Charter.

### Revisions

British Standards are updated by amendment or revision. Users of British Standards should make sure that they possess the latest amendments or editions.

It is the constant aim of BSI to improve the quality of our products and services. We would be grateful if anyone finding an inaccuracy or ambiguity while using this British Standard would inform the Secretary of the technical committee responsible, the identity of which can be found on the inside front cover. Tel: +44 (0)20 8996 9000. Fax: +44 (0)20 8996 7400.

BSI offers members an individual updating service called PLUS which ensures that subscribers automatically receive the latest editions of standards.

### Buying standards

Orders for all BSI, international and foreign standards publications should be addressed to Customer Services. Tel: +44 (0)20 8996 9001. Fax: +44 (0)20 8996 7001. Email: [orders@bsi-global.com](mailto:orders@bsi-global.com). Standards are also available from the BSI website at <http://www.bsi-global.com>.

In response to orders for international standards, it is BSI policy to supply the BSI implementation of those that have been published as British Standards, unless otherwise requested.

### Information on standards

BSI provides a wide range of information on national, European and international standards through its Library and its Technical Help to Exporters Service. Various BSI electronic information services are also available which give details on all its products and services. Contact the Information Centre. Tel: +44 (0)20 8996 7111. Fax: +44 (0)20 8996 7048. Email: [info@bsi-global.com](mailto:info@bsi-global.com).

Subscribing members of BSI are kept up to date with standards developments and receive substantial discounts on the purchase price of standards. For details of these and other benefits contact Membership Administration. Tel: +44 (0)20 8996 7002. Fax: +44 (0)20 8996 7001. Email: [membership@bsi-global.com](mailto:membership@bsi-global.com).

Information regarding online access to British Standards via British Standards Online can be found at <http://www.bsi-global.com/bsonline>.

Further information about BSI is available on the BSI website at <http://www.bsi-global.com>.

### Copyright

Copyright subsists in all BSI publications. BSI also holds the copyright, in the UK, of the publications of the international standardization bodies. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI.

This does not preclude the free use, in the course of implementing the standard, of necessary details such as symbols, and size, type or grade designations. If these details are to be used for any other purpose than implementation then the prior written permission of BSI must be obtained.

Details and advice can be obtained from the Copyright & Licensing Manager. Tel: +44 (0)20 8996 7070. Fax: +44 (0)20 8996 7553. Email: [copyright@bsi-global.com](mailto:copyright@bsi-global.com).

BSI  
389 Chiswick High Road  
London  
W4 4AL