

BS EN 941:2014



BSI Standards Publication

Aluminium and aluminium alloys — Circle and circle stock for the production of general applications — Specifications

bsi.

...making excellence a habit.™

National foreword

This British Standard is the UK implementation of EN 941:2014. It supersedes BS EN 941:1996 which is withdrawn.

The UK participation in its preparation was entrusted to Technical Committee NFE/35, Light metals and their alloys.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© The British Standards Institution 2014. Published by BSI Standards Limited 2014

ISBN 978 0 580 83720 3

ICS 77.150.10

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 31 May 2014.

Amendments issued since publication

Date	Text affected
------	---------------

English Version

Aluminium and aluminium alloys - Circle and circle stock for the production of general applications - Specifications

Aluminium et alliages d'aluminium - Disques et ébauches pour disques pour applications générales - Spécifications

Aluminium und Aluminiumlegierungen - Ronden und Rondenvormaterial für allgemeine Anwendungen - Spezifikationen

This European Standard was approved by CEN on 13 March 2014.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN-CENELEC Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

CEN-CENELEC Management Centre: Avenue Marnix 17, B-1000 Brussels

Contents		Page
Foreword		3
1	Scope	4
2	Normative references	4
3	Terms and definitions	4
4	Technical conditions for inspection and delivery	5
4.1	General	5
4.2	Orders or tenders	5
5	Mechanical properties	6
6	Tolerances on dimensions and form	6
6.1	General	6
6.2	Diameter	6
6.3	Thickness	6
6.4	Tolerances on flatness for circles	6

Foreword

This document (EN 941:2014) has been prepared by Technical Committee CEN/TC 132 "Aluminium and aluminium alloys", the secretariat of which is held by AFNOR.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by October 2014 and conflicting national standards shall be withdrawn at the latest by October 2014.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN [and/or CENELEC] shall not be held responsible for identifying any or all such patent rights.

This document supersedes EN 941:1995.

With regard the previous version, Clause 2 Normative references was updated; no new alloys were added.

According to the CEN-CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and the United Kingdom.

1 Scope

This European Standard specifies the particular requirements for wrought aluminium and aluminium alloys in the form of circle or circle stock for general applications.

It applies to:

- Circles made out of hot or cold rolled circles stock by:
 - Blanking: thickness 0,2 mm up to including 12 mm and with a diameter up to 1 000 mm;
 - Sawing or shearing: thickness 0,2 mm up to and including 200 mm with a diameter up to 3 500 mm;
- Hot or cold rolled circle stock with a thickness from 0,2 mm up to and including 200 mm and with a width up to 3 500 mm.

It does not apply to slugs for impact extrusions or to circle and circle stock for culinary utensils applications which are dealt with in other European Standards.

2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

EN 485-1:2008+A1:2009, *Aluminium and aluminium alloys - Sheet, strip, and plate - Part 1: Technical conditions for inspection and delivery*

EN 485-2, *Aluminium and aluminium alloys - Sheet, strip and plate - Part 2: Mechanical properties*

EN 485-3:2003, *Aluminium and aluminium alloys - Sheet, strip and plate - Part 3: Tolerances on dimensions and form for hot-rolled products*

EN 485-4:1993, *Aluminium and aluminium alloys - Sheet, strip and plate - Part 4: Tolerances on shape and dimensions for cold-rolled products*

EN 515, *Aluminium and aluminium alloys - Wrought products - Temper designations*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

3.1

circle

circular flat product obtained by circular sawing or shearing, or by blanking of a flat rolled product with a uniform thickness over 0,20 mm

3.2

circle stock

flat rolled product of rectangular cross-section with uniform thickness over 0,20 mm, supplied in coils, sheets, or plates, usually with sheared or sawn edges, and intended to be sawn, sheared or blanked into flat shapes to be subsequently formed, drawn, etc.

Note 1 to entry: The thickness does not exceed one tenth of the width.

3.3

hot rolled circle and circle stock

circle or circle stock whose final thickness is obtained by hot rolling

3.4

cold rolled circle and circle stock

circle or circle stock whose final thickness is obtained by cold rolling

4 Technical conditions for inspection and delivery

4.1 General

All the provisions of EN 485-1 shall apply, except Clause 4 (orders and tenders) which is modified as follows:

4.2 Orders or tenders

The order or tender shall define the product required and shall contain the following information:

- a) the form and the type of product:
 - 1) the form of the product (circle and circle stock);
 - 2) the designation of the aluminium or aluminium alloy;
 - 3) the customer application,
- b) the metallurgical temper of the material for delivery according to EN 515 (degree of hardness or heat treatment condition) and, if different, the metallurgical temper for use;
- c) the number of this European Standard or Specification number, or where none exists, the properties agreed between purchaser and supplier;
- d) the dimensions and shape of the product as applicable:
 - 1) thickness;
 - 2) diameter of the circle;
 - 3) width of the strip, sheet, or plate;
 - 4) length of the sheet or plate;
 - 5) internal and external diameters of the coil;
- e) whether hot rolled or cold rolled tolerances apply;
- f) quantity:

- 1) mass or number of pieces;
- 2) tolerances on quantity if required;
- g) any requirements for certificates of conformity, test and/or analysis reports or inspection certificates;
- h) any special requirements agreed between purchaser and supplier :
 - 1) marking of products;
 - 2) references to drawings, etc.

5 Mechanical properties

The mechanical properties shall conform to the requirements specified in EN 485-2.

6 Tolerances on dimensions and form

6.1 General

All provisions of EN 485-3 and EN 485-4 shall apply with the following amendments and additions.

6.2 Diameter

Tolerances on diameters for circle shall conform to Table 1. These tolerances include the tolerances on roundness.

NOTE For circle obtained by blanking the recommended standard diameters are:

- From 100 mm up to 500 mm nominal diameter: every multiple of 5;
- Over 500 mm up to 1 000 mm nominal diameter: every multiple of 10.

6.3 Thickness

Tolerances on thickness for hot rolled circle and circle stock shall conform to Table 2. They are identical to those specified in Table 1 of EN 485-3:2003 and are reproduced here for convenience.

The tolerances on thickness for cold rolled circle and circle stock shall conform to Table 3. They are identical to those specified in Table 1 of EN 485-4:1993 and are reproduced here for convenience. The partition into group I and group II of most common materials which may be used for the present application shall be as shown in Table 4.

6.4 Tolerances on flatness for circles

Tolerances on flatness for circles, expressed as a percentage of the diameter D and/or the measured chord length L , shall conform to Table 5.

Deviation from flatness d , resulting from arching or buckling, shall be measured as shown in Figures 1 and 2, using a lightweight straightedge and a feeler gauge, dial gauge or scale, while the circle is resting on a horizontal base plate, concave side upwards.

Two measurements shall be carried out with the straight edge respectively parallel and perpendicular to the rolling direction.

These tolerances do not apply to circles supplied in O or F tempers except for special agreement between supplier and purchaser.

Table 1 — Tolerances on diameter

Dimensions in millimetres

Specified thickness		Method of production	Diameter tolerances for specified diameter ^a				
over	up to		up to 600	over 600 up to 1 000	over 1 000 up to 1 600	over 1 600 up to 3 000	over 3 000 up to 3 500
0,2	4	Blanking	± 0,5	± 0,5	-	-	-
		circular sawing or shearing	+ 3 0	+ 4 0	+ 7 0	+ 9 0	+ 11 0
4	6	Blanking	± 0,7	± 0,7	-	-	-
		circular sawing or shearing	+ 4 0	+ 5 0	+ 8 0	+ 9 0	+ 11 0
6	12	Blanking	± 1	± 1	-	-	-
		circular sawing or shearing	+ 4 0	+ 5 0	+ 8 0	+ 10 0	+ 12 0
12	50	circular sawing or shearing	+ 7 0	+ 7 0	+ 9 0	+ 12 0	+ 14 0
50	200	circular sawing or shearing	+ 10 0	+ 10 0	+ 12 0	+ 14 0	+ 16 0

^a These tolerances include the tolerances on roundness.

Table 2 — Thickness tolerances for hot rolled circle and circle stock

Dimensions in millimetres

Specified thickness		Thickness tolerance for specified diameter or width				
over	up to	up to 1 250	over 1 250 up to 1 600	over 1 600 up to 2 000	over 2 000 up to 2 500	over 2 500 up to 3 500
2,5	4,0	± 0,28	± 0,28	± 0,32	± 0,35	± 0,40
4,0	5,0	± 0,30	± 0,30	± 0,35	± 0,40	± 0,45
5,0	6,0	± 0,32	± 0,32	± 0,40	± 0,45	± 0,50
6,0	8,0	± 0,35	± 0,40	± 0,40	± 0,50	± 0,55
8,0	10	± 0,45	± 0,50	± 0,50	± 0,55	± 0,60
10	15	± 0,50	± 0,60	± 0,65	± 0,65	± 0,80
15	20	± 0,60	± 0,70	± 0,75	± 0,80	± 0,90
20	30	± 0,65	± 0,75	± 0,85	± 0,90	± 1,0
30	40	± 0,75	± 0,85	± 1,0	± 1,1	± 1,2
40	50	± 0,90	± 1,0	± 1,1	± 1,2	± 1,5
50	60	± 1,1	± 1,2	± 1,4	± 1,5	± 1,7
60	80	± 1,4	± 1,5	± 1,7	± 1,9	± 2,0
80	100	± 1,7	± 1,8	± 1,9	± 2,1	± 2,2
100	150	± 2,2	± 2,2	± 2,7	± 2,8	-
150	200	± 2,8	± 2,8	± 3,3	± 3,3	-

Table 3 — Thickness tolerances for cold-rolled circle and circle stock

Dimensions in millimetres

Specified thickness		Thickness tolerances ^a for specified diameter or width													
		up to 1 000		over 1 000 up to 1 250		over 1 250 up to 1 600		over 1 600 up to 2 000		over 2 000 up to 2 500		over 2 500 up to 3 000		over 3 000 up to 3 500	
		Material Group		Material Group		Material Group		Material Group		Material Group		Material Group		Material Group	
over	Up to	Group I	Group II	Group I	Group II	Group I	Group II	Group I	Group II	Group I	Group II	Group I	Group II	Group I	Group II
0,2	0,4	± 0,02	± 0,03	± 0,04	± 0,05	± 0,05	± 0,06	-	-	-	-	-	-	-	-
0,4	0,5	± 0,03	± 0,03	± 0,04	± 0,05	± 0,05	± 0,06	± 0,06	± 0,07	± 0,10	-	-	-	-	-
0,5	0,6	± 0,03	± 0,04	± 0,05	± 0,06	± 0,06	± 0,07	± 0,07	± 0,08	± 0,11	-	-	-	-	-
0,6	0,8	± 0,03	± 0,04	± 0,06	± 0,07	± 0,07	± 0,08	± 0,08	± 0,09	± 0,12	-	-	-	-	-
0,8	1	± 0,04	± 0,05	± 0,06	± 0,08	± 0,08	± 0,09	± 0,09	± 0,10	± 0,13	-	-	-	-	-
1,0	1,2	± 0,04	± 0,05	± 0,07	± 0,09	± 0,09	± 0,10	± 0,10	± 0,12	± 0,14	-	-	-	-	-
1,2	1,5	± 0,05	± 0,07	± 0,09	± 0,11	± 0,10	± 0,12	± 0,11	± 0,14	± 0,16	-	-	-	-	-
1,5	1,8	± 0,06	± 0,08	± 0,10	± 0,12	± 0,11	± 0,13	± 0,12	± 0,15	± 0,17	-	-	-	-	-
1,8	2	± 0,06	± 0,09	± 0,11	± 0,13	± 0,12	± 0,14	± 0,14	± 0,16	± 0,19	-	-	-	-	-
2,0	2,5	± 0,07	± 0,10	± 0,12	± 0,14	± 0,13	± 0,15	± 0,15	± 0,17	± 0,20	-	-	-	-	-
2,5	3	± 0,08	± 0,11	± 0,13	± 0,15	± 0,15	± 0,17	± 0,17	± 0,19	± 0,23	-	-	-	-	-
3,0	3,5	± 0,10	± 0,12	± 0,15	± 0,17	± 0,17	± 0,19	± 0,18	± 0,20	± 0,24	-	-	-	-	-
3,5	4	± 0,15		± 0,20		± 0,22		± 0,23		± 0,25	± 0,34		± 0,38		
4,0	5	± 0,18		± 0,22		± 0,24		± 0,25		± 0,29	± 0,36		± 0,42		
5,0	6	± 0,20		± 0,24		± 0,25		± 0,26		± 0,32	± 0,40		± 0,46		
6,0	8	± 0,24		± 0,30		± 0,31		± 0,32		± 0,38	± 0,44		± 0,50		
8	10	± 0,27		± 0,33		± 0,36		± 0,38		± 0,44	± 0,50		± 0,56		
10	12	± 0,32		± 0,38		± 0,40		± 0,41		± 0,47	± 0,53		± 0,59		
12	15	± 0,36		± 0,42		± 0,43		± 0,45		± 0,51	± 0,57		± 0,63		
15	20	± 0,38		± 0,44		± 0,46		± 0,48		± 0,54	± 0,60		± 0,66		
20	25	± 0,40		± 0,46		± 0,48		± 0,50		± 0,56	± 0,62		± 0,68		
25	30	± 0,45		± 0,50		± 0,53		± 0,55		± 0,60	± 0,65		± 0,70		
30	40	± 0,50		± 0,55		± 0,58		± 0,60		± 0,65	± 0,70		± 0,75		
40	50	± 0,55		± 0,60		± 0,63		± 0,65		± 0,70	± 0,75		± 0,80		

^a When measuring the thickness, a zone 10 mm wide from the edges of the product shall be disregarded.


Table 4 — Material groups

Group I	EN AW-1080A, EN AW-1070A, EN AW-1050A, EN AW-1200 EN AW-3003, EN AW-3103, EN AW-3005; EN AW-3105 EN AW-4006, EN AW-4007 EN AW-5005, EN AW-5305, EN AW-5505, EN AW-5605, EN AW-5110, EN AW-5210, EN AW-5310, EN AW5050 EN AW-8011A
Group II	EN AW-2014, EN AW-2017A, EN AW-2024 EN AW-3004, EN AW-5040, EN AW-5049, EN AW-5251, EN AW-5052, EN AW-5154A, EN AW-5454, EN AW-5754, EN AW-5182 EN AW-5083, EN AW5086 EN AW-6061, EN AW-6082 EN AW-7020, EN AW-7021, EN AW-7022, EN AW-7075

Table 5 — Circle - Flatness tolerances

Specified thickness mm		Maximum total deviation ^a d_{\max}/D
over	up to	%
6,5	50	0,4
50	150	0,3

^a These tolerances only apply to circles with a diameter greater than 1 000 mm. Tolerances for other dimensions are to be agreed.

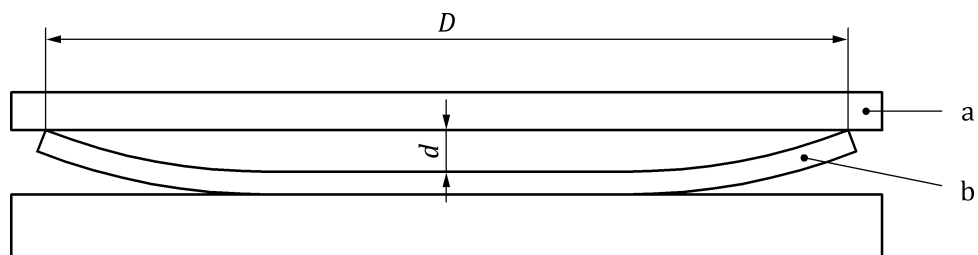


Key

- a** straightedge
- b** circle
- d* deviation from flatness
- D* diameter of circle

For further details see 6.4.

Figure 1 — Arch

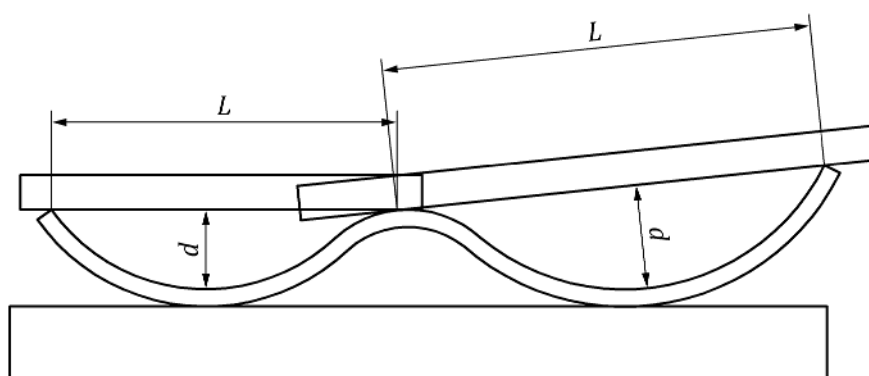

Key

- d* deviation from flatness
- L* length of buckle (chord)

For further details see 6.4.

Figure 2 — Buckle

British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at bsigroup.com/standards or contacting our Customer Services team or Knowledge Centre.

Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at bsigroup.com/shop, where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to bsigroup.com/subscriptions.

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

PLUS is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit bsigroup.com/shop.

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email bsmusales@bsigroup.com.

BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK

Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

Copyright

All the data, software and documentation set out in all British Standards and other BSI publications are the property of and copyrighted by BSI, or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI. Details and advice can be obtained from the Copyright & Licensing Department.

Useful Contacts:

Customer Services

Tel: +44 845 086 9001

Email (orders): orders@bsigroup.com

Email (enquiries): cservices@bsigroup.com

Subscriptions

Tel: +44 845 086 9001

Email: subscriptions@bsigroup.com

Knowledge Centre

Tel: +44 20 8996 7004

Email: knowledgecentre@bsigroup.com

Copyright & Licensing

Tel: +44 20 8996 7070

Email: copyright@bsigroup.com



...making excellence a habit.™