



Welding — Recommendations for welding of metallic materials —

Part 7: Electron beam welding

The European Standard EN 1011-7:2004 has the status of a
British Standard

ICS 25.160.10

National foreword

This British Standard is the official English language version of EN 1011-7:2004.

The UK participation in its preparation was entrusted to Technical Committee WEE/-/1, Briefing committee for welding, which has the responsibility to:

- aid enquirers to understand the text;
- present to the responsible international/European committee any enquiries on the interpretation, or proposals for change, and keep the UK interests informed;
- monitor related international and European developments and promulgate them in the UK.

A list of organizations represented on this committee can be obtained on request to its secretary.

Cross-references

The British Standards which implement international or European publications referred to in this document may be found in the *BSI Catalogue* under the section entitled “International Standards Correspondence Index”, or by using the “Search” facility of the *BSI Electronic Catalogue* or of British Standards Online.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

Compliance with a British Standard does not of itself confer immunity from legal obligations.

Summary of pages

This document comprises a front cover, an inside front cover, the EN title page, pages 2 to 41 and a back cover.

The BSI copyright notice displayed in this document indicates when the document was last issued.

Amendments issued since publication

Amd. No.	Date	Comments

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 4 August 2004

© BSI 4 August 2004

ISBN 0 580 44198 9

ICS 25.160.10

English version

Welding - Recommendations for welding of metallic materials - Part 7: Electron beam welding

Soudage - Recommandations pour le soudage des
matériaux métalliques - Partie 7 : Soudage par faisceau
d'électrons

Schweißen - Empfehlungen zum Schweißen metallischer
Werkstoffe - Teil 7: Elektronenstrahlschweißen

This European Standard was approved by CEN on 30 April 2004.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Central Secretariat or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Central Secretariat has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Slovakia, Slovenia, Spain, Sweden, Switzerland and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

Management Centre: rue de Stassart, 36 B-1050 Brussels

Contents

	page
Foreword.....	5
Introduction.....	6
1 Scope.....	7
2 Normative references.....	7
3 Terms and definitions.....	7
4 Quality requirements.....	12
5 Storage and handling of parent metals and consumables.....	12
6 Welding facilities.....	12
7 Qualification of the welding personnel.....	13
8 Welding procedure specification.....	13
9 Welding procedure test.....	14
10 Joint preparation.....	14
10.1 Machining.....	14
10.2 Demagnetisation.....	14
10.3 Cleaning.....	14
10.4 Assembly.....	15
11 Joint design.....	15
11.1 Longitudinal seams.....	15
11.2 Circular seams.....	16
12 Evacuation holes.....	17
13 Tack welds, cosmetic passes.....	17
14 Thermal pre- and post heat treatment.....	18
15 Documentation.....	18
Annex A (informative) Information about weldability of metallic materials.....	19
A.1 General.....	19
A.2 Steels and iron alloys.....	19
A.3 Nickel and nickel alloys.....	20
A.4 Aluminium and magnesium alloys.....	20
A.5 Copper and copper alloys.....	20
A.6 Refractory and reactive metals.....	21
A.7 Dissimilar metals.....	21
A.8 Non-metals.....	21
Annex B (informative) Information about causes of weld imperfections and prevention.....	23
Annex C (informative) Summary of electron beam weldability of metals with reference to CR ISO 15608:2000 groups.....	26
C.1 Grouping system for steels.....	26
C.2 Grouping system for aluminium and aluminium alloys.....	30
C.3 Grouping system for copper and copper alloys.....	31
C.4 Grouping system for nickel and nickel alloys.....	31
C.5 Grouping system for titanium and titanium alloys.....	32
C.6 Grouping system for zirconium and zirconium alloys.....	32
C.7 Grouping system for cast iron.....	33

Annex D (informative) Examples of preparation of circular joints	34
Bibliography	41

Figures

Figure 1 — Terms of electron beam oscillation	8
Figure 2 — Definition of working distance and focusing distance	9
Figure 3 — Definition for termination of circular seams	10
Figure 4 — Welding with interlayer material	11
Figure 5 — Welding of dissimilar metals with transition material	12
Figure 6 — Example of preparation of surface treated work pieces	14
Figure 7 — Normal square butt weld	15
Figure 8 — Square butt weld with spigot or integral backing	16
Figure 9 — Square butt weld with detached backing	16
Figure 10 — Work piece with run-on and run-off plate for separating the weld start and weld end	16
Figure 11 — Machining-related cavities	17
Figure 12 — Weldment with additional hole for evacuating the cavity	17
Figure A.1 — Sensitivity of hot cracks depending of alloy contents in aluminium	22
Figure D.1 — Various types of radial joints with centring	34
Figure D.2 — Work piece with radial joint, centred using a welding jig	35
Figure D.3 — Work pieces with unsuitable and better positions for radial weld	35
Figure D.4 — Various types of axial joints	36
Figure D.5 — Example of an axial weld with a depth of fusion zone adapted to suit the strength requirement (not welded through the full thickness of the joint)	36
Figure D.6 — Improved joint detail for axial welds with reduced stress concentration	37
Figure D.7 — Deterioration of joint fit-up that occurs when welding axial joints assembled with a clearance fit	37
Figure D.8 — Effect of the method of manufacture on the dimensions of gear wheels	38
Figure D.9 — Example of a gear wheel with an unsuitable located axial joint. The joint is too close to the central bore.	38
Figure D.10 — Better positioned axial joint compared with figure D.9. The joint is further from the central bore and the wall thickness has been adapted to suit the required weld strength	39
Figure D.11 — Better positioned axial joint compared with figure D.9. The slot has been included to accommodate radial shrinkage	39
Figure D.12 — Example of a difficult to access electron beam weld	39

Figure D.13 — Relative tendency of axial and radial welds to cause deformation.....40

Tables

Table B.1 — Causes of weld imperfections and prevention23

Table C.1 — Grouping system for steels.....27

Table C.2 — Grouping system for aluminium and aluminium alloys30

Table C.3 — Grouping system for copper and copper alloys31

Table C.4 — Grouping system for nickel and nickel alloys.....31

Table C.5 — Grouping system for titanium and titanium alloys32

Table C.6 — Grouping system for zirconium and zirconium alloys32

Table C.7 — Grouping system for cast irons.....33

Foreword

This document (EN 1011-7:2004) has been prepared by Technical Committee CEN/TC 121 "Welding", the secretariat of which is held by DIN.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by January 2005, and conflicting national standards shall be withdrawn at the latest by January 2005.

This document has been prepared under a mandate given to CEN by the European Commission and the European Free Trade Association, and supports essential requirements of EU Directive(s).

This European Standard is composed of the following parts:

- Part 1: General guidance for arc welding
- Part 2: Arc welding of ferritic steels
- Part 3: Arc welding of stainless steels
- Part 4: Arc welding of aluminium and aluminium alloys
- Part 5: Welding of clad steel
- Part 7: Electron beam welding
- Part 8: Welding of cast irons

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Slovakia, Slovenia, Spain, Sweden, Switzerland and United Kingdom.

Introduction

This document contains special recommendations for the electron beam welding of metallic materials and should be observed in connection with the general recommendations for welding according to EN 1011-1. It includes details on quality requirements, production welding facilities as well as the weldability of some materials and informs about welding procedures.

The special properties of electron beam welding derive from the high power and power density possible in the beam spot, the resulting "deep welding effect" and the unique controllability of the process.

Electron beam welding is recommended for welding metallic materials which require low heat input, low shrinkage, low distortion, and for welding dissimilar or reactive metals. It allows high welding speeds and flexibility of design by joining simple components. The electron beam is able to join very thin and very thick sections and the combination of both. It is also suited to automation and quality control.

1 Scope

This document may be used for the electron beam welding (process no. 51 according to EN ISO 4063) of weldable metallic materials according to CR ISO 15608. It does not contain data on permissible stresses on weld seams or on the testing and evaluation of weld seams. Such data can either be seen from the relevant application standards or should be separately agreed between the contracting parties.

A requirement for the application of this document is that the recommendations should be used by appropriately trained and experienced personnel.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

EN 1011-1, *Welding — Recommendations for welding of metallic materials — Part 1: General guidance for arc welding*

EN ISO 13919-1:1996, *Welding — Electron and laser beam welded joints — Guidance on quality levels for imperfections — Part 1: Steel (ISO 13919-1:1996)*

EN ISO 13919-2:2001, *Welding — Electron and laser beam welded joints — Guidance on quality levels for imperfections — Part 2: Aluminium and its weldable alloys (ISO 13919-2:2001)*

EN ISO 14744-1:2000, *Welding — Acceptance inspection of electron beam welding machines — Part 1: Principles and acceptance conditions (ISO 14744-1:2000)*

EN ISO 14744-2, *Welding — Acceptance inspection of electron beam welding machines — Part 2: Measurement of accelerating voltage characteristics (ISO 14744-2:2000)*

EN ISO 14744-3, *Welding — Acceptance inspection of electron beam welding machines — Part 3: Measurement of beam current characteristics (ISO 14744-3:2000)*

EN ISO 14744-4, *Welding — Acceptance inspection of electron beam welding machines — Part 4: Measurement of welding speed (ISO 14744-4:2000)*

EN ISO 14744-5, *Welding — Acceptance inspection of electron beam welding machines — Part 5: Measurement of run-out accuracy (ISO 14744-5:2000)*

EN ISO 14744-6, *Welding — Acceptance inspection of electron beam welding machines — Part 6: Measurement of stability of spot position (ISO 14744-6:2000)*

EN ISO 15614-11:2002, *Specification and qualification of welding procedures for metallic materials — Welding procedure test — Part 11: Electron and laser beam welding (ISO 15614-11:2002)*

EN ISO 15609-3:2004, *Specification and qualification of welding procedures for metallic materials — Welding procedure specification — Part 3: Electron beam welding (ISO 15609-3:2004)*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in EN ISO 15609-3:2004, EN ISO 13919-1:1996, EN ISO 13919-2:2003, EN ISO 14744-1:2000, and EN ISO 15614-11:2002 and the following apply.

**3.1
accelerating voltage**

electric potential difference U_A between cathode and anode


**3.2
beam current**

value of the electric current in the beam I_B

**3.3
beam oscillation**

periodic deflection of the electron beam from the initial position defined in terms of pattern, dimensions and frequency

NOTE See Figure 1.

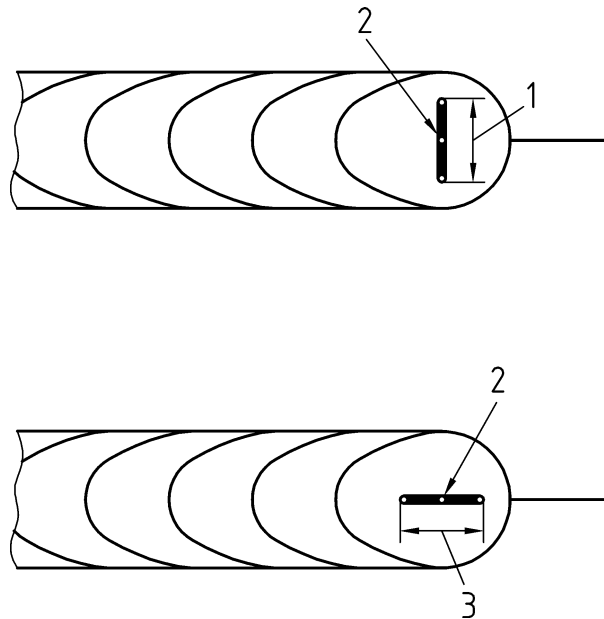

Key

- 1 Oscillation width
- 2 Initial position of the beam
- 3 Oscillation length

Figure 1 — Terms of electron beam oscillation

**3.4
cosmetic pass**

superficial remelting of the weld in order to enhance its appearance

NOTE This pass is usually made with a defocused or oscillating beam.


**3.5
defocusing**

deviation from the normal focus position (e. g. focus on work piece surface)

**3.6
focusing distance**

distance between the focusing lens plane and beam focus position

NOTE See Figure 2.

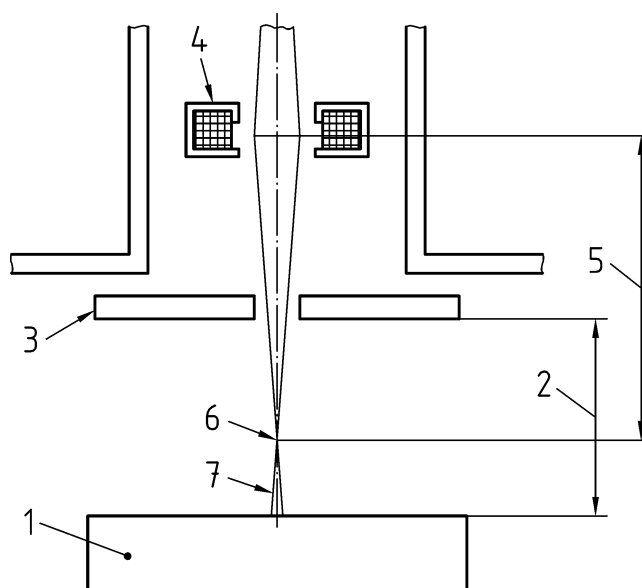

Key

1	Work piece	5	Focusing distance
2	Working distance	6	Beam focus
3	Heat protection	7	Beam spot
4	Focusing lens		

Figure 2 — Definition of working distance and focusing distance

3.7

working distance

distance between the surface of the work piece and a standard reference point on the equipment which is traceable to the true focusing lens plane

NOTE See Figure 2.

3.8

lens current

current I_L which flows through the electromagnetic focusing lens


3.9

slope down


controlled decrease of the beam power at the end of welding. The slope down region is the region on the work piece in which the effects of slope down occur

NOTE See Figure 3. The slope down region can consist of one or two areas, depending on the selected welding mode:


- a) in partial penetration welding:
 - a region where penetration decreases continuously.
- b) in full penetration welding:
 - a region where beam penetration is still complete;
 - a region where penetration is partial or decreasing.

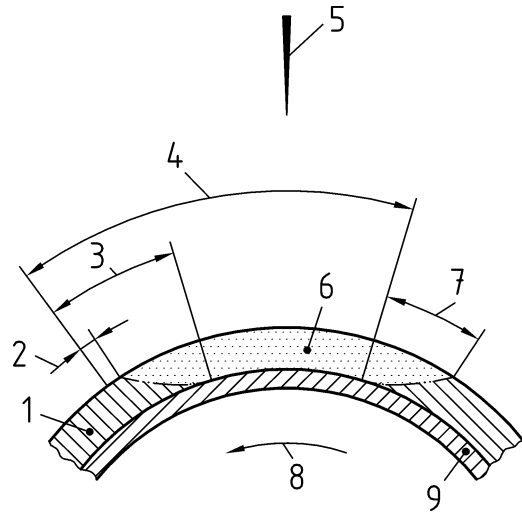

a) Partial penetration welding (with overlap)

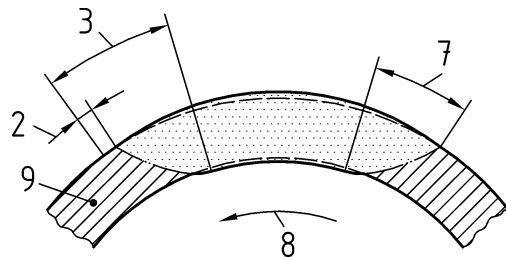

b) Full penetration welding (without overlap)

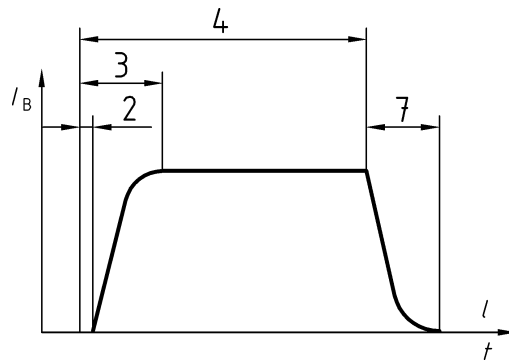

c) Typical beam current I_B profile for a circular weld with overlap

Key

- | | |
|---|----------------------------------|
| 1 Work piece (welded zone) | 7 Slope-down region |
| 2 Delay between control starting and weld beginning | 8 Direction of work piece motion |
| 3 Slope-up region | 9 Work piece (unwelded zone) |
| 4 Overlapping region | I_B Beam current |
| 5 Electron beam | l Weld length |
| 6 Remelted zone | t Weld time |

Figure 3 — Definition for termination of circular seams

3.10**slope-up**

controlled increase of the beam power at the beginning of welding

NOTE See Figure 3.

3.11**spiking**

locally variation of fusion zone depths as a consequence of instabilities in the beam penetration mechanism

3.12**evacuation hole**

hole for evacuating cavities in work pieces

NOTE See Figure 12.


3.13**working pressure**

pressure measured in the welding enclosure in the vicinity of the work piece

3.14**interlayer material**

alloy addition introduced by means of pre-placed foil at the joint interface to modify the weld fusion zone composition to improve weldability or weld performance

NOTE See Figure 4.

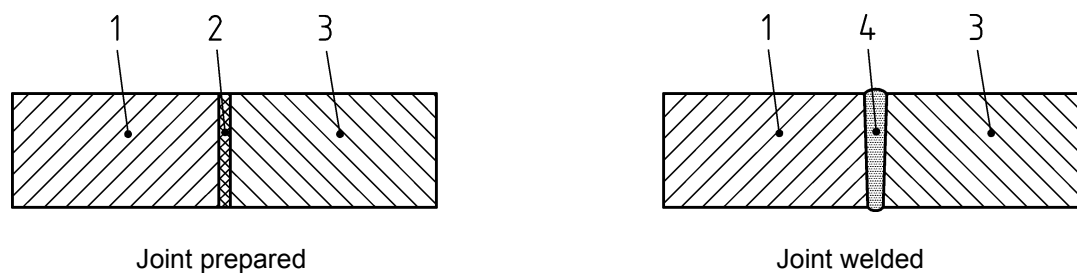**Key**


- 1 Parent material A
- 2 Interlayer material
- 3 Parent material A or B
- 4 Fusion zone

Figure 4 — Welding with interlayer material

3.15**transition material**

buffer material insert employed to allow welding of metallurgically incompatible materials

NOTE See Figure 5.

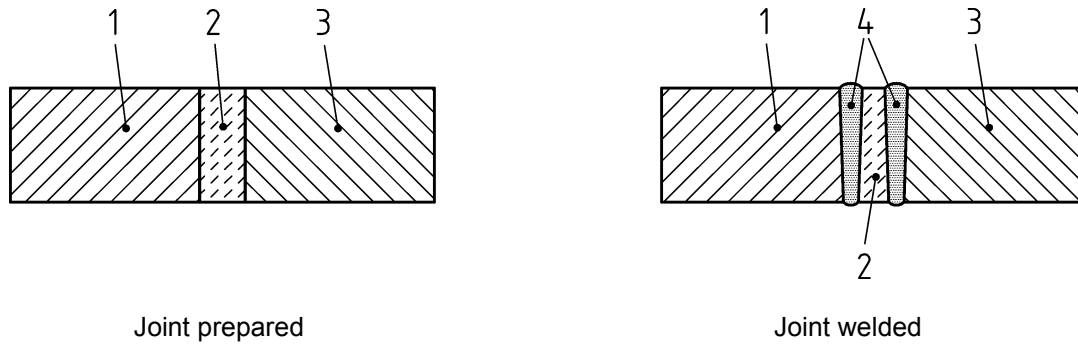

Key

- 1 Parent material A
- 2 Transition material
- 3 Parent material B
- 4 Fusion zone

Figure 5 — Welding of dissimilar metals with transition material

4 Quality requirements

The quality requirements should be given in the design specification prior to the beginning of welding work. They should be based on EN 729-1 and EN 729-2 or EN 729-3 or EN 729-4 and EN ISO 13919-1 or EN ISO 13919-2, unless relevant application standards are available.

5 Storage and handling of parent metals and consumables

In order to avoid contact corrosion, foreign metal inclusions etc., parent metals and consumables of dissimilar classes of materials (according to CR ISO 15608) should not be stored and processed jointly.

6 Welding facilities

Welding facilities include the electron beam-welding machine, workshop, tools, clamping devices, demagnetisation devices, and cleaning facilities. In the following, only those facilities, which are of particular significance for electron beam welding, will be described in more detail.

The electron beam welding machine should be installed so that environmental conditions, such as mechanical vibrations, noise and dirt from neighbouring machines, electric and magnetic fields do not influence the quality of welds. Moreover, noise control regulations pursuant to the equipment safety act should be observed for the vacuum pumps. In larger workshops, the machine operators' and machine setters' workplace should be shielded against disturbances from manufacturing operations (e.g. by means of partition walls). The exhaust gases generated during evacuation of the working chamber shall only be released into the environment in accordance with the relevant emission regulations. Where particularly high demands are placed, on weld quality it is recommended that filtered air or inert gas be used to vent the working chamber.

The supply voltage for the electron beam welding machine shall not vary by more than $\pm 10\%$ and care should be taken to ensure that the welding machine has a satisfactory earth connection.

The electron beam welding machine shall be subjected to an acceptance inspection according to EN ISO 14744-1 to EN ISO 14744-6 as part of an internal quality management upon commissioning or in the case of displacement, modifications and repairs of major welding machine components. In this acceptance inspection the short and long-term consistency as well as the reproducibility of the most important welding parameters and compliance with particular characteristic data deviations will be measured and verified according to given deviation limits.

It is possible using special equipment that electron beam welding can be carried out at atmospheric pressure. In this case, attention is drawn to the need for providing appropriate fume extraction.

Electron beam welding machines are operated at different accelerating voltages: up to 150 kV for vacuum equipment and up to 200 kV for non-vacuum equipment. The accelerating voltage dictates the design of the X-ray shielding.

All measures to fulfil the applicable radiation protection rules are to be implemented, complied with and supervised by a radiological inspection officer.

Normally, the electron beam generator is fixed to the working chamber. Alternatively the electron beam generator can be arranged to move with respect to the work piece mounted either external to the work chamber or internally. Consequently, the relative motion between electron beam and work piece can be performed by work piece or generator motion, by beam deflection or by simultaneous motion of both.

7 Qualification of the welding personnel

The requirements for the qualification of personnel for fully mechanised and automatic welding equipment are laid down in EN 1418. Among the different procedures specified in this document, the functional test is particularly suitable as a basis for the recognition of personnel responsible for the operation and set-up of electron beam welding machines as part of an internal quality management system. In a functional test, the operator or setter demonstrates his knowledge of working with a welding procedure specification and of setting, supervising and checking the electron beam-welding machine.

8 Welding procedure specification

All details for the electron beam welding of components are to be recorded in a welding procedure specification (WPS) according to EN ISO 15609-3. This includes, for example:

- work piece specification;
- material specification;
- work piece demagnetisation;
- joint design;
- joint preparation;
- thermal pre-treatment;
- weld sequence (tacking, welding, cosmetic pass);
- clamping device;
- work chamber pressure;
- working distance;
- welding data;
- mechanical and thermal post-treatment.

9 Welding procedure test


The successful completion of a procedure test according to EN ISO 15614-11 records that the manufacturer has performed electron beam welding including the preceding and subsequent machining with his operating facilities and personnel according to a recognised welding instruction. EN ISO 15614-11 contains data on the dimensions of test pieces for longitudinal and circular butt welds, for fillet and stake welds and describes the type and scope of weld tests required as a function of the quality levels of imperfections according to EN ISO 13919-1 or EN ISO 13919-2¹⁾.

10 Joint preparation

10.1 Machining

It is recommended that all joint preparations be produced by machining or high precision cutting. The objective is to prepare clean metal surfaces with a minimum gap when assembled.

Where components have surface layers produced by carburising, anodising, cadmium plating, nitriding, phosphating, galvanising etc. these are to be removed preferentially by machining in and adjacent to the weld joint region as shown in Figure 6.

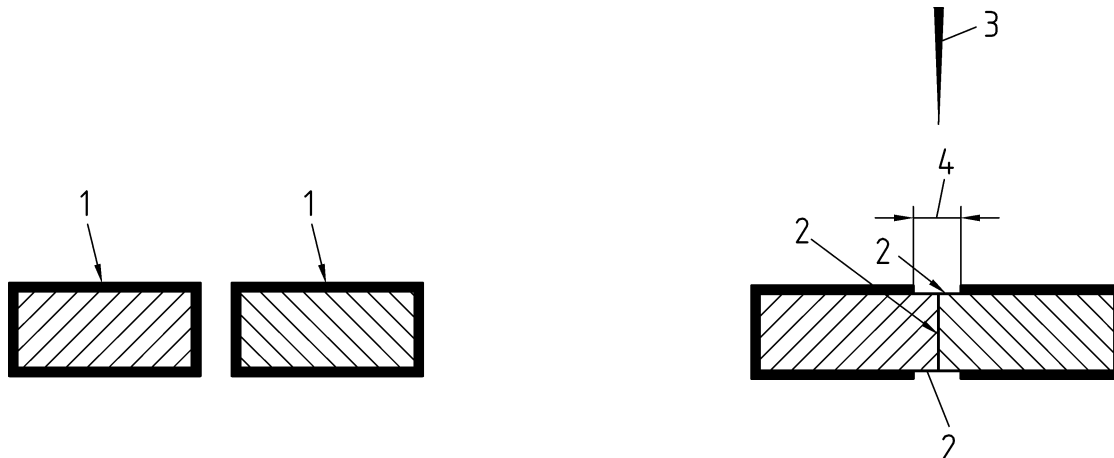

Key

- 1 Boundary-layer-treated work piece
- 2 Boundary-layer removed for welding
- 3 Electron beam
- 4 3 x upper bead width

Figure 6 — Example of preparation of surface treated work pieces

10.2 Demagnetisation

Components containing ferromagnetic materials should be checked for residual magnetism and demagnetised if necessary.

10.3 Cleaning

The quality of electron beam welding relies on accuracy and cleanliness of the joint preparation.

1) EN ISO 13919-1 and EN ISO 13919-2 are covered steel and aluminium. For other materials these standards can be used, if possible.

Attention should be paid to the resulting surface condition and compatibility of any coolant used.

Cleaning of weld joint surfaces should be carried out to remove all contaminants such as oxides, oil, grease, coolant and paint.

The specific cleaning method used will be dependent on the material type, component size and the quality requirements as well as the operational circumstances. The following treatments can be used:

- a) manual degreasing with a solvent;
- b) cleaning in a closed solvent vapour unit or in a ultrasonic bath;
- c) pre-treatment by steam cleaning with a slightly alkaline additive, following by drying;
- d) acid pickling neutralisation, washing in distilled water, drying, short-term storage.

10.4 Assembly

Following cleaning the components to be welded should be assembled taking care to avoid recontamination and magnetisation.

11 Joint design

11.1 Longitudinal seams

If the components to be joined can be clamped, a simple square butt joint is preferred (see Figure 7). For accuracy a spigot preparation can be used for location of the components (see Figure 8). Tack welding is always recommended for large components.

Electron beam welding with root backing can be employed if spatter and undercut are to be avoided (see Figures 8 and 9).


If the component cannot be machined in the weld start and finish regions to remove the end crater, run-on or run-off plates should be used (see Figure 10). These run-on/ run-off plates also suppress heat accumulation at the workpiece ends. The run-on/run-off plates should be attached to the work piece by clamping or welding to achieve good thermal contact and will be subsequently removed.



Key

t Work piece thickness


Figure 7 — Normal square butt weld

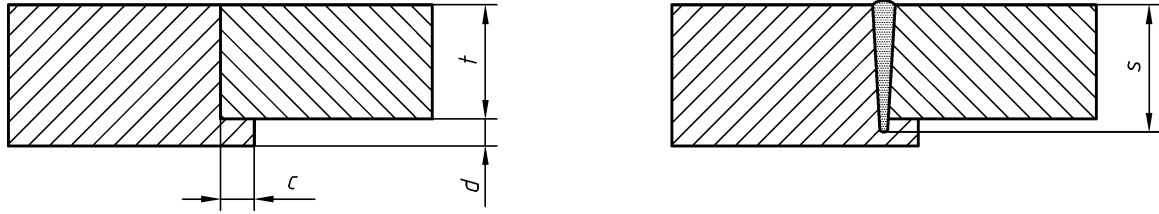

Key

- t Work piece thickness
- s Weld penetration
- c and d Lengths to be defined


Figure 8 — Square butt weld with spigot or integral backing

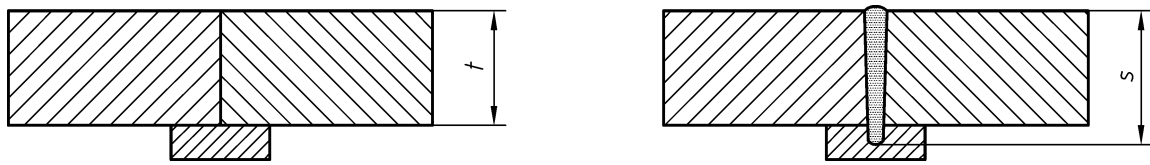

Key

- t Work piece thickness
- s Weld penetration

Figure 9 — Square butt weld with detached backing

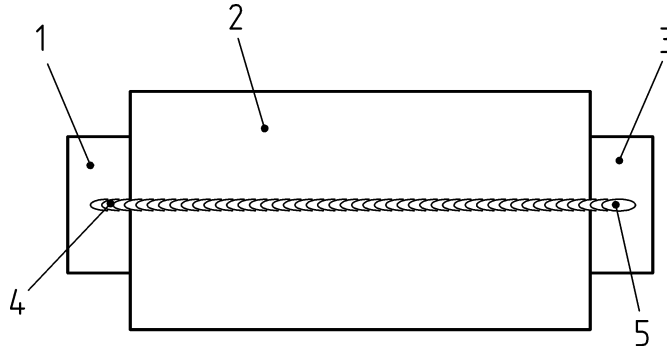

Key

- 1 Run-on plate
- 2 Work piece
- 3 Run-off plate
- 4 Start of weld
- 5 End of weld

Figure 10 — Work piece with run-on and run-off plate for separating the weld start and weld end

11.2 Circular seams

For welding circular components a spigot preparation, which facilitates alignment positioning of the components, can be used.

Rotation-angle- or time-dependent control of the beam power and possibly other parameters (e.g. lens current) is required. Particular difficulties can be encountered due to occurrence of spiking in the weld slope-down. Depending on the type of materials and welding speed, spiking can be prevented in many cases by the control of beam focus

and beam oscillation parameters (shape, direction, frequency and dimensions) during slope-down. When possible, circular welds should be designed to be located in regions of low applied stress or else special consideration should be given to the permissible level of imperfections in the slope down region. For axial circular welds on components with narrow dimensional tolerances, a press fit (e.g. H7/r6 to H7/n6) is recommended. For circular welds with a clearance fit, tacking is essential.

Examples of typical joint preparations for electron beam welding are given in Annex D.

12 Evacuation holes

Component design or machining details can lead to the presence of trapped volumes or cavities in the assembled joint, which are closed and cannot be evacuated to the working pressure. These can lead to anomalies during welding and therefore should be kept to a minimum volume (see Figure 11), or else should be vented by means of an evacuating hole (see Figure 12).


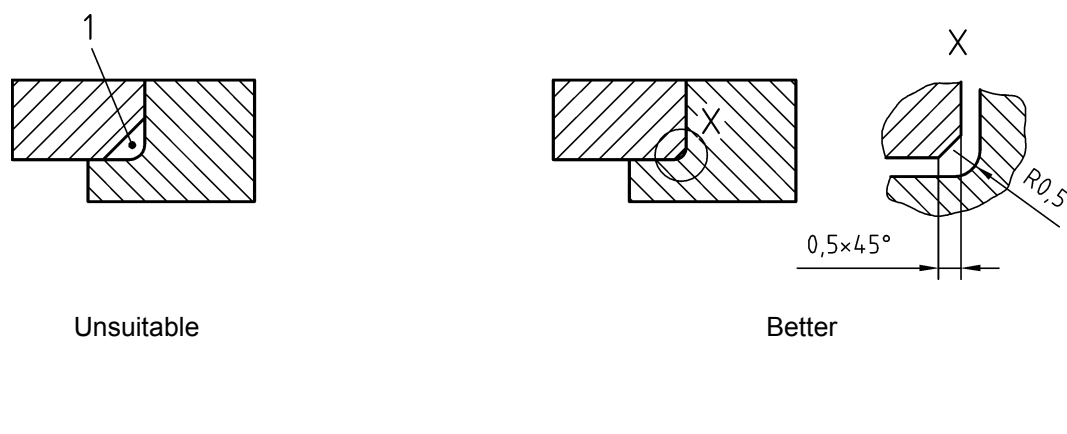


Figure 11 — Machining-related cavities

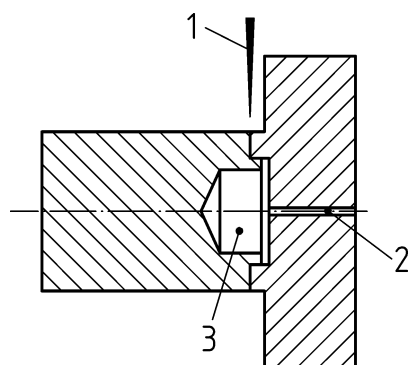

Key

- 1 Electron beam
- 2 Evacuation hole
- 3 Cavity

Figure 12 — Weldment with additional hole for evacuating the cavity

13 Tack welds, cosmetic passes

Prior to full current welding, components can be secured by tack welding. This can be done using the electron beam process or another welding process.

Weld bead appearance can be improved by means of a cosmetic pass. In this case, it should be checked whether renewed fusion of the weld seam impairs the weld properties.

14 Thermal pre- and post heat treatment

If a thermal treatment of the weld before and/or after welding is required for metallurgical reasons, the electron beam can also be used for this purpose.

15 Documentation

In electron beam welding most of the machine and parameters are of an electrical nature. Therefore it is possible to monitor and record all welding data with which a component has been manufactured. Within the framework of quality assurance, this information can be complemented by monitoring the welding machine condition as well as the dimensional tolerances of the work piece.

Annex A (informative)

Information about weldability of metallic materials

A.1 General

All metallic materials can be melted using a focussed electron beam and, in consequence, most pure metals and alloys can be successfully welded. In its most simple form, electron beam welding is carried out by translating the beam, with respect to a close fitting joint, and locally melting the material. No filler metal or consumable is usually necessary and welding is achieved in a single pass almost irrespective of the material thickness. Even weld depth of > 100 mm can be performed without the need for a groove preparation. Consequently the weld quality and properties achievable are controlled by the composition of the material alone. When considering weldability metallic materials are divided into discrete groups based on the elements present in most abundance as follows.

A.2 Steels and iron alloys

A.2.1 General

Most steels and iron alloys that are weldable by conventional fusion welding processes can be successfully joined using the electron beam process. Also, because of the narrow electron beam weld profile and the absence of hydrogen; many steels, which are otherwise considered difficult or impossible to fusion weld, can be joined using electron beam welding. Special consumables or preheating are not normally necessary. It is important, however, for electron beam welding, that steels are specified with low levels of impurities such as sulphur and phosphorus to prevent solidification cracking and that materials are sufficiently well de-oxidised, i.e. degassed or aluminium treated, to minimise the risk of weld porosity.

A.2.2 C-Mn and structural steels

C-Mn and structural steels can be joined in a single pass in thicknesses ranging from less than 1 mm to in excess of 200 mm and provided that certain composition controls are recognised, good weld quality can be consistently achieved.

The rapid thermal cycle associated with the electron beam process invariably results in welds in steels with overmatched tensile strength and hardness. Thus, it is sometimes necessary to add material to modify the weld metal composition or perform a post weld heat treatment operation if high levels of fracture toughness or low hardness are required.

Ideally, for C-Mn steels the carbon content should be $\leq 0,2\%$ to minimise the risk of high hardness levels. Electron beam welding is not recommended for the group of free machining steels.

A.2.3 Quenched and tempered and alloy steels

In many applications including aero-engine and automobile transmission parts, components are electron beam welded in high strength alloy steels and are frequently used in the as-welded condition. NiCrMo steels, for example, and high alloy creep resistant steels can be welded in substantial thicknesses, without preheat. Again low impurity levels are beneficial particularly if toughness properties are important. The tendency for cold cracking is increased with thickness and C-content. Alloy steels containing nickel are more sensitive to hot cracking.

A.2.4 Stainless steels

Most common types of stainless steel are readily weldable using the electron beam process including austenitic grades, ferritic, duplex and precipitation hardening martensitic stainless steels. The duplex and some austenitic materials are commonly alloyed with nitrogen and thus welding procedures should be developed which minimise

the risk of porosity formation due to nitrogen outgassing and which compensate for the detrimental effect of nitrogen loss on phase balance and stability. For the majority of austenitic-ferritic steels (duplex stainless steels) a low welding speed is recommended and a post-weld solution heat treatment is necessary to guarantee development of sufficient austenite in the weldment. For thick materials, e.g. >25 mm, the use of nickel alloy addition is recommended. This is best achieved by means of an interlayer.

The precipitation hardening grades show a slight degradation in tensile strength when electron beam welded which can be restored, if required, by a post-weld ageing operation.

A.2.5 Cast irons

Cast irons are not generally considered to be readily electron beam weldable predominantly for metallurgical reasons. With the exception perhaps of ductile and spheroidal graphite irons electron beam welding is not recommended as a joining process for cast irons.

A.2.6 Soft iron

Soft iron and silicon iron, used in transformer and electric motor manufacture, are electron beam welded successfully in a variety of industrial applications.

A.3 Nickel and nickel alloys

Many of the popular nickel alloys used in welded fabrication can be joined satisfactorily using the electron beam welding process. Pure nickel, nickel/copper, nickel/chromium, nickel/beryllium alloys and many nickel/iron alloys can be welded without difficulty. It should be noted, however, that pure nickel and some nickel alloys are ferromagnetic and the necessary precautions are taken. The complex high temperature alloys, designed to have good creep resistance at high temperature, can be welded using electron beam welding often in preference to arc welding because of the minimal metallurgical disturbance and low thermal strains induced by the electron beam process. Care should be taken however to prevent HAZ liquation cracking during welding and to avoid cracking during post weld heat treatment of the more complex super alloys.

A.4 Aluminium and magnesium alloys

The majority of wrought aluminium and magnesium alloys, available commercially, can be welded satisfactorily using the electron beam process. Most Al-Mn alloys (3xxx type) are considered to be readily weldable. Care should be taken when welding Al-Si-Mg alloys (6xxx type) and dissimilar metal combinations to avoid hot cracking (Figure A.1). Some of the heat treatable Al-Cu-Mg alloys (e.g. 2014 and 2219 type) have better electron beam weldability than the common non-heat treatable grades although will require post weld ageing to restore strength properties. Evaporation of volatile constituents during welding, particularly in the 7xxx and 5xxx series Al alloys (according to EN 573-1), can cause difficulties due to gun flash-over, loss of alloy content and subsequent degradation of properties. Cleaning prior to welding is especially important and the majority of weld defects that occur are often a consequence of poor cleaning practice. Many of the cast alloys can also be electron beam welded although the weld quality achievable depends heavily on the quality of the casting and, in particular the residual gas content.

A.5 Copper and copper alloys

Unlike many of the other thermal processes used for joining pure copper, electron beam welding can be carried out without the need for any pre-heating operation and can join components in excess of 150 mm thickness in a single pass. So-called 'pure' copper may contain impurities such as oxygen, sulphur and carbon, which can compromise its weldability due to the formation of porosity (e.g. Cu-ETP). Oxygen free, high conductivity copper (OFHC, ISO 1190-1) or phosphorus de-oxidised grades (e.g. EN 1173 Cu-DPH or Cu-DLP) are preferred.

The majority of copper alloys, with the marked exception of the brasses (Cu-Zn alloys), can be welded but again, cast materials can be problematic if the parent material quality is poor and residual gas content is high. Some high strength materials, e.g. those alloyed with zirconium, can suffer from cracking problems.

A.6 Refractory and reactive metals

The ability to work in a vacuum environment make it possible to use the process for joining metals which not only have high melting points but also those which are extremely reactive when hot or molten. Titanium and many of its alloys can be welded readily using the electron beam process without the danger of oxidation and hydrogen embrittlement and subsequent undetectable degradation of ductility. For this reason the process is used widely in the aero engine industry for welding safety critical titanium alloy parts. Similarly Zirconium alloys, which are also extremely reactive, can be welded without difficulty under vacuum. Likewise tantalum, niobium, vanadium and their alloys can be joined successfully using electron beam welding but again impurity levels can profoundly influence the weld quality and properties achievable.

Tungsten, molybdenum and their alloys can be joined, but consideration should be given to joint details to take account of the poor ductility of the resulting welds.


A.7 Dissimilar metals

One of the particular advantages offered by the electron beam process is that the beam intensity is such that dissimilar metals with vastly different thermal conductivities and melting points can be welded successfully without preferential melting of the lower melting point material. Although not all combinations are possible due to metallurgical incompatibility and the formation of undesirable intermetallic compounds, many dissimilar combinations are possible. It should be noted that thermo-electric currents would be generated (due to the couple thermal effects) whilst welding dissimilar metal combinations, which can give rise to strong magnetic fields and deflection of the electron beam. The severity of this phenomenon is very dependent on the material combination, their magnetic and electrical properties and the component geometry.

Where the combination of materials gives rise to embrittlement it is often possible to introduce a mutually compatible transition material or to employ an electron beam brazing/diffusion bonding approach with an appropriate interlayer (see Figures 4 and 5).

A.8 Non-metals

Whilst welding of non-metals using the electron beam process is generally not possible, drilling, cutting and engraving can sometimes be performed.

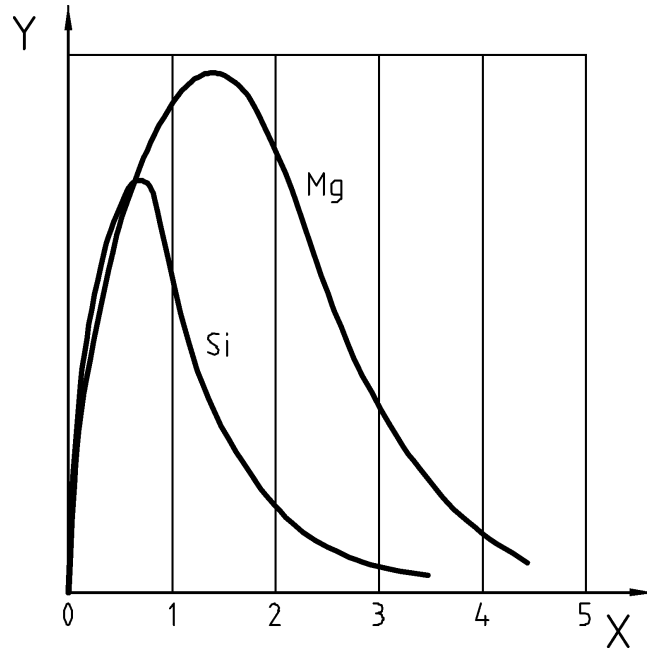

Key

X Alloy contents [%]

Y Tendency to hot cracks

Figure A.1 — Sensitivity of hot cracks depending of alloy contents in aluminium

Annex B (informative)

Information about causes of weld imperfections and prevention

The choice of preventions as well as the way and scope of eliminating undue weld imperfections should be in conformity with the application standards or specifically agreed between the contracting parties.

Table B.1 — Causes of weld imperfections and prevention

Weld imperfection (ref. no. according to EN ISO 6520-1)	Possible cause	Proposed prevention
crack (100)	cause for a quench crack is an excessively high carbon content (in the case of carbon steels), cooling rate too high	thermal treatment immediately before and/or after welding (e.g. with defocused electron beam), decreasing the welding speed; constructional provision to avoid shrinkage constraints
crater crack (104)	cause for a liquidation crack is the precipitation of low-melting eutectics at the grain boundaries and shrinkage stresses during cooling	changing the welding speed; modifying the weld geometry to reduce residual welding stresses, e.g. radial instead of axial circular weld and/or constructional provision to avoid shrinkage constraints; welding with a special filler metal to influence the weld pool metallurgically
porosity and gas pores (200)	contamination of the weld joint	cleaning the weld joints
	incomplete degasification of trace and alloying elements due to excessively fast solidification of the weld pool	beam defocusing, beam oscillation; reduction of the welding speed
	instability of the vapour cavity	beam defocusing, beam oscillation; reduction of the welding speed
localised and linear porosity	Joint contamination material composition	proper cleaning change material specification or adjust welding procedure
	spiking porosity in partially penetrating welds	adjust welding procedure to minimise spiking
	slope-down spiking porosity	adjust slope-down procedure
shrinkage, cavity and crater pipe	unintentional interruption of the weld process, e.g. gun discharge or metal ejection	appropriate equipment design and maintenance attention to joint design details

Table B.1 (continued)

Weld imperfection (ref. no. according to EN ISO 6520-1)	Possible cause	Proposed prevention
lack of fusion (401)	<p>incomplete fusion of the weld joint as a consequence of beam misalignments, magnetic deflection or insufficient weld width</p> <p>incomplete fusion of the weld joint side walls as a consequence of incorrect positioning of the filler metal or insufficient weld width</p> <p>beam deflection due to residual magnetism or electrostatic effects in the working chamber</p> <p>beam deflection when welding dissimilar materials as a consequence of magnetic fields (thermal couple effects)</p>	<p>checking and correcting the beam; increasing the weld width</p> <p>checking and correcting the positioning of the filler metal; increasing the weld width</p> <p>demagnetising the work piece and tooling; removal or shielding of equipment causing electromagnetic fields (e.g. electric motors); elimination of electrostatic effects; magnet screening</p> <p>magnetic screening or measuring the beam deflection in a test seam and compensation during welding</p>
incomplete penetration	<p>insufficient beam power excessive welding speed appropriate focus setting</p> <p>equipment malfunction</p>	<p>select appropriate welding parameters</p> <p>isolate fault and rectify equipment</p>
undercut (5011, 5012)	<p>for vertical beam axis: interaction of molten pool agitation, surface tension and surface viscosity</p> <p>for horizontal beam axis: interaction of molten pool agitation, gravitation, surface tension and surface viscosity</p>	<p>beam oscillation, beam defocusing, changing the welding speed, cosmetic pass</p> <p>beam oscillation, beam defocusing, changing the welding speed, cosmetic pass</p>
excess weld metal (502)	<p>as a consequence of transverse shrinkage especially for partially penetrated welds</p> <p>as a consequence of material transport opposite to the welding direction</p>	<p>cosmetic weld, chamfering the weld preparation</p> <p>for longitudinal seams, displace weld start to run-on plate for circular seams, controlled increase of the beam power (slope-up)</p>
excessive penetration (504)	consequence of transverse shrinkage and gravity effects	adjust the welding procedure, joint preparation detail, cosmetic pass, welding on backing
linear misalignment (507)	<p>inadequate tacking and/or tooling</p> <p>incorrect machining</p>	<p>change assembly procedure</p> <p>check joint details</p>
sagging	due to gravity in flat position	change welding position or adjust welding procedure

Table B.1 (continued)

Weld imperfection (ref. no. according to EN ISO 6520-1)	Possible cause	Proposed prevention
incompletely filled groove (511) root concavity (515)	material is ejected due to the combined effect of gravitation, vapour pressure in the weld cavity and excess through current	adjust the welding to procedure, cosmetic pass, weld on to backing, welding with horizontal beam axis
weld spatter (602)	molten droplets ejected from the weld caps and root	adjust the welding procedure; weld on to backing; weld with a spatters protection shield or use a spatter release agent so that the spatter does not adhere to the work piece and can be easily removed

Annex C (informative)

Summary of electron beam weldability of metals with reference to CR ISO 15608:2000 groups

C.1 Grouping system for steels

Steels are grouped as shown in Table C.1. Only those elements that are specified in material standards or specifications will be considered. The figures given in group 1 and 11 are referring to the ladle analysis of the materials. The figures given in groups 4 to 10 are based on the element content used in the designation of the alloys.

The following grouping of weldability classes (WCL) is used in Table C.1 to Table C.7:

- I Weldable:
Welds with good quality can be produced reliably without difficulty. Mechanical properties achievable will depend on precise welding procedures and material composition details.
- II Weldable with caution:
Some materials in this group can be welded although special techniques and restrictions on material composition may be required. Special techniques include pre-and post weld heat treatment and the use of alloy additions.
- III Limited weldability:
Materials in this group are known to cause difficulties with electron beam welding. In extreme circumstances it can be possible to develop welding procedures to produce joints for limited application.

Table C.1 — Grouping system for steels

Group	Sub-group	Type of steel	Weldability class
1		Steels with a specified minimum yield strength $R_{eH} \leq 460 \text{ N/mm}^2$ ^a and with analysis in %: $C \leq 0,25$ $Si \leq 0,60$ $Mn \leq 1,70$ $Mo \leq 0,70$ ^b $S \leq 0,045$ $P \leq 0,045$ $Cu \leq 0,40$ ^b $Ni \leq 0,5$ ^b $Cr \leq 0,3$ (0,4 for castings) ^b $Nb \leq 0,05$ $V \leq 0,12$ ^b $Ti \leq 0,05$	I

Table C.1 (continued)

Group	Sub-group	Type of steel	Weldability class
1	1.1	Steels with a specified minimum specified yield strength $R_{eH} \leq 275 \text{ N/mm}^2$	I
	1.2	Steels with a specified minimum yield strength $275 \text{ N/mm}^2 < R_{eH} \leq 360 \text{ N/mm}^2$	I
	1.3	Normalized fine grain steels with a specified minimum yield strength $R_{eH} > 360 \text{ N/mm}^2$	I
	1.4	Steels with improved atmospheric corrosion resistance whose analysis may exceed the requirements for the single elements as indicated under 1	II
2		Thermo mechanically treated fine grain steels and cast steels with a specified minimum yield strength $R_{eH} > 360 \text{ N/mm}^2$	
	2.1	Thermomechanically treated fine grain steels and cast steels with a specified minimum yield strength $360 \text{ N/mm}^2 < R_{eH} \leq 460 \text{ N/mm}^2$	I
	2.2	Thermo mechanically treated fine grain steels and cast steels with a specified minimum yield strength $R_{eH} > 460 \text{ N/mm}^2$	I
3		Quenched and tempered steels and precipitation hardened steels except stainless steels with a specified minimum yield strength $R_{eH} > 360 \text{ N/mm}^2$	
	3.1	Quenched and tempered steels with a specified minimum yield strength $360 \text{ N/mm}^2 < R_{eH} \leq 690 \text{ N/mm}^2$	I
	3.2	Quenched and tempered steels with a specified minimum yield strength $R_{eH} > 690 \text{ N/mm}^2$	II
	3.3	Precipitation hardened steels except stainless steels	II
4		Low vanadium alloyed Cr-Mo- (Ni) steels with $\text{Mo} \leq 0,7 \%$ and $\text{V} \leq 0,1 \%$	
	4.1	Steels with $\text{Cr} \leq 0,3 \%$ and $\text{Ni} \leq 0,7 \%$	II
	4.2	Steels with $\text{Cr} \leq 0,7 \%$ and $\text{Ni} \leq 1,5 \%$	II
5		Cr-Mo steels free of vanadium with $\text{C} \leq 0,35 \%$ ^c	
	5.1	Steels with $0,75 \% \leq \text{Cr} \leq 1,5 \%$ and $\text{Mo} \leq 0,7 \%$	II
	5.2	Steels with $1,5 \% < \text{Cr} \leq 3,5 \%$ and $0,7 \% < \text{Mo} \leq 1,2 \%$	II
	5.3	Steels with $3,5 \% < \text{Cr} \leq 7,0 \%$ and $0,4 \% < \text{Mo} \leq 0,7 \%$	II
	5.4	Steels with $7,0 \% < \text{Cr} \leq 10,0 \%$ and $0,7 \% < \text{Mo} \leq 1,2 \%$	II

Table C.1 (continued)

Group	Sub-group	Type of steel	Weldability class
6		High vanadium alloyed Cr-Mo- (Ni) steels	
	6.1	Steels with $0,3 \% \leq Cr \leq 0,75 \%$, $Mo \leq 0,7 \%$ and $V \leq 0,35 \%$	II
	6.2	Steels with $0,75 \% < Cr \leq 3,5 \%$, $0,7 \% < Mo \leq 1,2 \%$ and $V \leq 0,35 \%$	II
	6.3	Steels with $3,5 \% < Cr \leq 7,0 \%$, $Mo \leq 0,7 \%$ and $0,45 \% \leq V \leq 0,55 \%$	II
	6.4	Steels with $7,0 \% < Cr \leq 12,5 \%$, $0,7 \% < Mo \leq 1,2 \%$ and $V \leq 0,35 \%$	II
7		Ferritic, martensitic or precipitation hardened stainless steels with $C \leq 0,35 \%$ and $10,5 \% \leq Cr \leq 30 \%$	
	7.1	Ferritic stainless steels	I
	7.2	Martensitic stainless steels	II
	7.3	Precipitation hardened stainless steels	I
8		Austenitic steels	
	8.1	Austenitic stainless steels with $Cr \leq 19 \%$	I
	8.2	Austenitic stainless steels with $Cr > 19 \%$	II
	8.3	Manganese austenitic stainless steels with $4 \% < Mn \leq 12 \%$	II
9		Nickel alloyed steels with $Ni \leq 10,0 \%$	
	9.1	Nickel alloyed steels with $Ni \leq 3,0 \%$	II
	9.2	Nickel alloyed steels with $3,0 \% < Ni \leq 8,0 \%$	II
	9.3	Nickel alloyed steels with $8,0 \% < Ni \leq 10,0 \%$	II
10		Austenitic ferritic stainless steels (duplex)	
	10.1	Austenitic ferritic stainless steels with $Cr \leq 24 \%$	II
	10.2	Austenitic ferritic stainless steels with $Cr > 24 \%$	II
11		Steels covered by group 1 ^d except $0,25 \% < C \leq 0,5 \%$	
	11.1	Steels as indicated under 11 with $0,25 \% < C \leq 0,35 \%$	II
	11.2	Steels as indicated under 11 with $0,35 \% < C \leq 0,5 \%$	II
a	In accordance with the specification of the steel product standards, R_{eH} may be replaced by $R_{p0,2}$ or $R_{t0,5}$.		
b	A higher value is accepted provided that $Cr + Mo + Ni + Cu + V \leq 0,75 \%$.		
c	"Free of vanadium" means not deliberately added to the material.		
d	A higher value is accepted provided that $Cr + Mo + Ni + Cu + V \leq 1 \%$.		

C.2 Grouping system for aluminium and aluminium alloys

Aluminium and aluminium alloys are grouped as shown in Table C.2. The figures given are based on the element content used in the designation of the alloys.

Table C.2 — Grouping system for aluminium and aluminium alloys

Group	Sub-group	Type of aluminium and aluminium alloys	Weldability class
21		Pure aluminium ≤ 1 % impurities or alloy content	I
22		Non heat treatable alloys	
	22.1	Aluminium-manganese alloys	I
	22.2	Aluminium-magnesium alloys with Mg $\leq 1,5$ %	I
	22.3	Aluminium-magnesium alloys with $1,5\% < \text{Mg} \leq 3,5$ %	II
	22.4	Aluminium-magnesium alloys with Mg $> 3,5$ %	I
23		Heat treatable alloys	
	23.1	Aluminium-magnesium-silicon alloys	II
	23.2	Aluminium-zinc-magnesium alloys	II
24		Aluminium-silicon alloys with Cu ≤ 1 %	
	24.1	Aluminium-silicon alloys with Cu ≤ 1 % and $5\% < \text{Si} \leq 15$ %	I
	24.2	Aluminium-silicon-magnesium alloys with Cu ≤ 1 % ; $5\% < \text{Si} \leq 15$ % and $0,1\% < \text{Mg} \leq 0,80$ %	II
25	—	Aluminium-silicon-copper alloys with $5\% < \text{Si} \leq 14$ %; $1\% < \text{Cu} \leq 5$ % and Mg $\leq 0,8$ %	II
26	—	Aluminium-copper alloys with $2\% < \text{Cu} \leq 6$ %	II

Groups 21 to 23 are generally for wrought materials and groups 24 to 26 are generally for cast materials.

C.3 Grouping system for copper and copper alloys

Copper and copper alloys are grouped as indicated in Table C.3.

Table C.3 — Grouping system for copper and copper alloys

Group	Sub-group	Type of copper and copper alloys	Weldability class
31		Pure copper	II
32		Copper-zinc alloys	
	32.1	Copper-zinc alloys, binary	III
	32.2	Copper-zinc alloys, complex	III
33		Copper-tin alloys	I
34		Copper-nickel alloys	I
35		Copper-aluminium alloys	I
36		Copper-nickel-zinc alloys	III
37		Copper alloys, low alloyed (less than 5 % other elements) not covered by groups 31 to 36	II
38		Other copper alloys (5 % or more other elements) not covered by groups 31 to 36	II

C.4 Grouping system for nickel and nickel alloys

Nickel and nickel alloys are grouped as indicated in Table C.4. The figures given are based on the element content used in the designation of the alloys. It is recognised, however, that the weldability of the alloy groups 43 to 48 is heavily dependent on minor alloy additions such as Al, Ti, Nb etc.

Table C.4 — Grouping system for nickel and nickel alloys

Group	Type of nickel and nickel alloys	Weldability class
41	Pure nickel	I
42	Nickel-copper alloys (Ni/Cu) Ni \geq 45 %, Cu \geq 10 %	I
43	Nickel-chromium alloys (Ni/Cr/Fe/Mo) Ni \geq 40 %	II
44	Nickel-molybdenum alloys (Ni/Mo) Ni \geq 45 %, Mo \leq 32 %	II
45	Nickel-iron-chromium alloys (Ni/Fe/Cr) Ni \geq 30 %	II
46	Nickel-chromium-cobalt alloys (Ni/Cr/Co) Ni \geq 45 %, Co \geq 10 %	II
47	Nickel-iron-chromium alloys (Ni/Fe/Cr/Cu) Ni \geq 45 %	II
48	Nickel-iron-cobalt alloys (Ni/Fe/Co/Cr/Mo/Cu) 25 % \leq Ni \leq 45 % and Fe \geq 20 %	II

C.5 Grouping system for titanium and titanium alloys

Titanium and titanium alloys are grouped as indicated in Table C.5.

Table C.5 — Grouping system for titanium and titanium alloys

Group	Sub-group	Type of titanium and titanium alloys	Weldability class
51		Pure titanium	II
	51.1	Titanium with $O_2 < 0,20 \%$	I
	51.2	Titanium with $O_2 \leq 0,20 \%$	I
	51.3	Titanium with $0,25 \% < O_2 \leq 0,35 \%$	I
	51.4	Titanium with $0,35 \% < O_2 \leq 0,40 \%$	I
52		Alpha alloys ^a	II
53		Alpha-beta alloys ^b	II
54		Near beta and beta alloys ^c	N

^a Alloys covered by group 52 are : Ti-0,2Pd ; Ti-2,5Cu ; Ti-5Al-2,5Sn ; Ti-8Al-1Mo-1V ; Ti-6Al-2Sn-4Zr-2Mo ; Ti-6Al-2Nb-1Ta-0,8Mo.
^b Alloys covered by group 53 are : Ti-3Al-2,5V (WCL II); Ti-6Al-4V (WCL I); Ti-6Al-6V-2Sn (WCL II); Ti-7Al-4Mo (WCL II).
^c Alloys covered by group 54 are : Ti-10V-2Fe-3Al ; Ti-13V-11Cr-3Al ; Ti-11,5Mo-6Zr-4,5Sn ; Ti-3Al-8V-6Cr-4Zr-4Mo.
 N insufficiency experience

C.6 Grouping system for zirconium and zirconium alloys

Zirconium and zirconium alloys are grouped as indicated in Table C.6.

Table C.6 — Grouping system for zirconium and zirconium alloys

Group	Type of zirconium and zirconium alloys	Weldability class
61	Pure zirconium	I
62	Zirconium with 2,5 % Nb	I

C.7 Grouping system for cast iron

Cast irons are grouped as indicated in Table C.7.

Table C.7 — Grouping system for cast irons

Group	Sub-group	Type of cast iron	Weldability class
71		Grey cast irons with specified tensile strength or Brinell hardness	III
72		Spheroidal graphite cast irons with specified mechanical properties	
	72.1	Spheroidal graphite cast irons with specified tensile strength, 0,2 % proof stress and elongation or specified Brinell hardness	II
	72.2	Spheroidal graphite cast irons (like 72.1) with specified impact resistance values	II
73		Malleable cast irons	
	73.1	Whiteheart malleable (decarburized) cast irons most suitable for welding	I
	73.2	Whiteheart malleable (decarburized) cast irons	II
	73.3	Blackheart malleable (non-decarburized) cast irons	III
74		Austempered ductile cast irons	N
75		Austenitic cast irons	
	75.1	Austenitic spheroidal graphite cast irons with specified element content	II
	75.2	Austenitic spheroidal graphite cast irons	II
	75.3	Austenitic grey cast irons	N
76		Cast irons excepting 71 to 75	
	76.1	Abrasion resistant cast irons	III
N insufficiency experience			

Annex D (informative)

Examples of preparation of circular joints

For better clarity in all figures the various items are not always reproduced to scale.

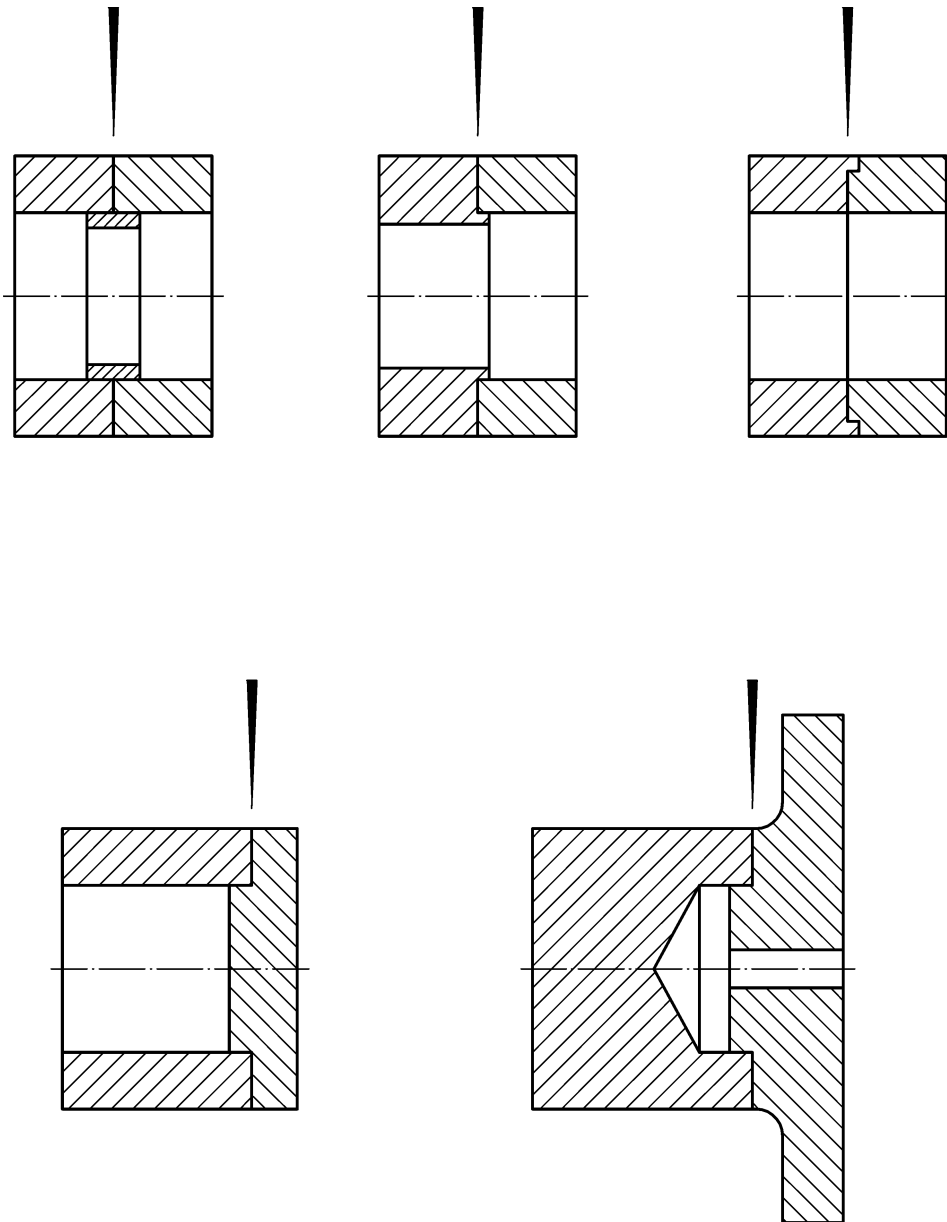



Figure D.1 — Various types of radial joints with centring

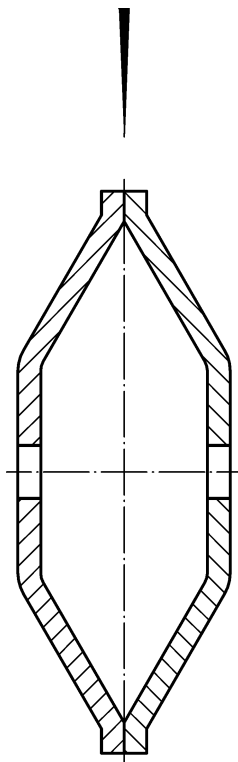


Figure D.2 — Work piece with radial joint, centred using a welding jig

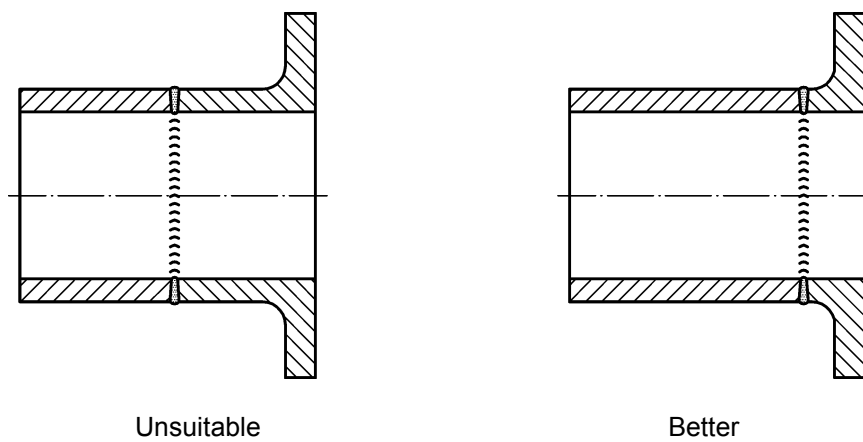


Figure D.3 — Work pieces with unsuitable and better positions for radial weld

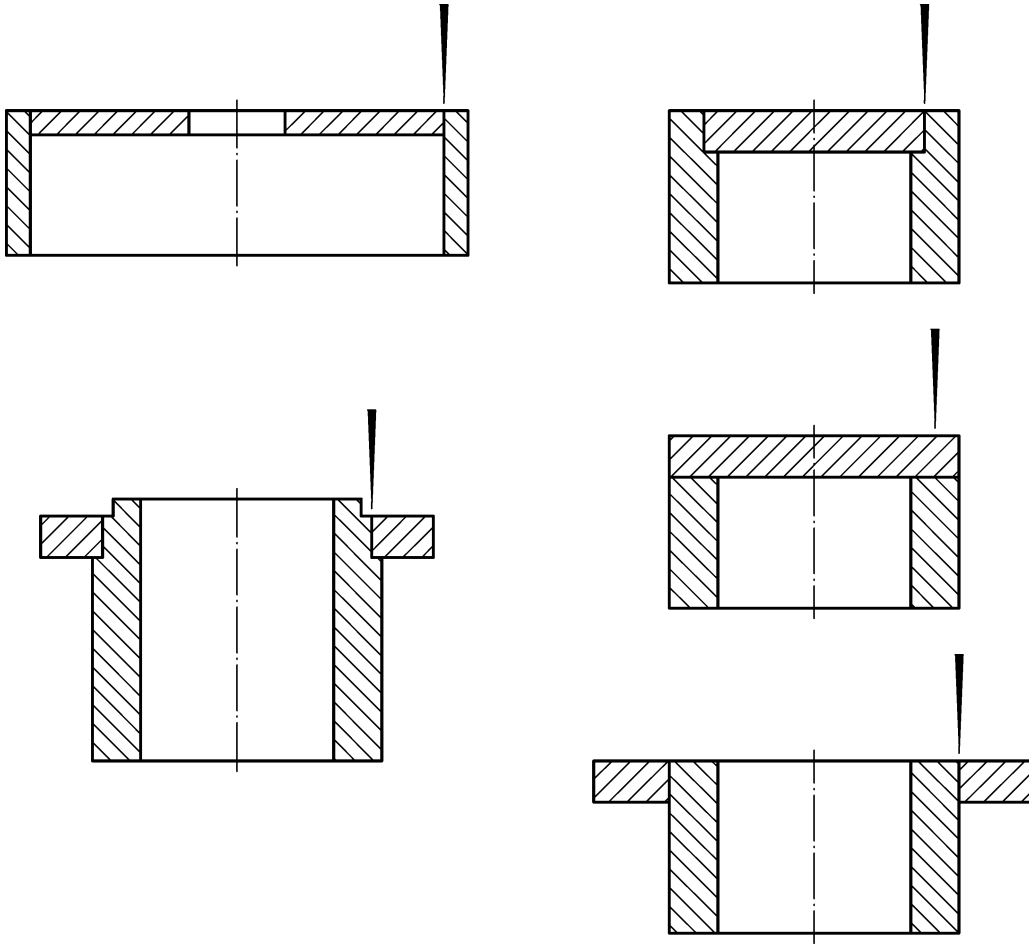


Figure D.4 — Various types of axial joints

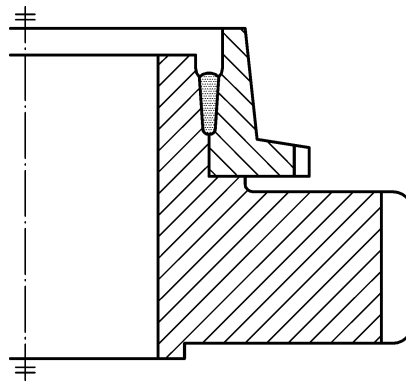


Figure D.5 — Example of an axial weld with a depth of fusion zone adapted to suit the strength requirement (not welded through the full thickness of the joint)



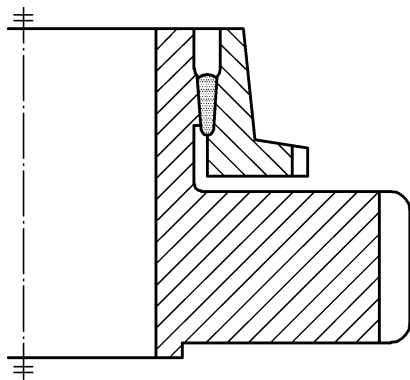


Figure D.6 — Improved joint detail for axial welds with reduced stress concentration

A-A

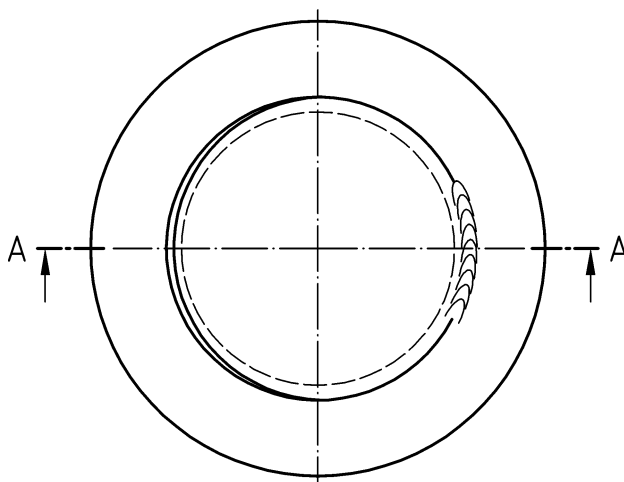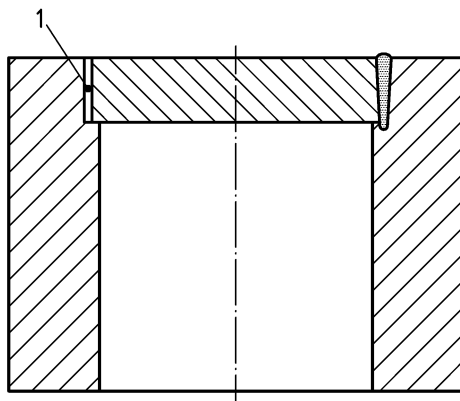

Key

1 Gap

Figure D.7 — Deterioration of joint fit-up that occurs when welding axial joints assembled with a clearance fit

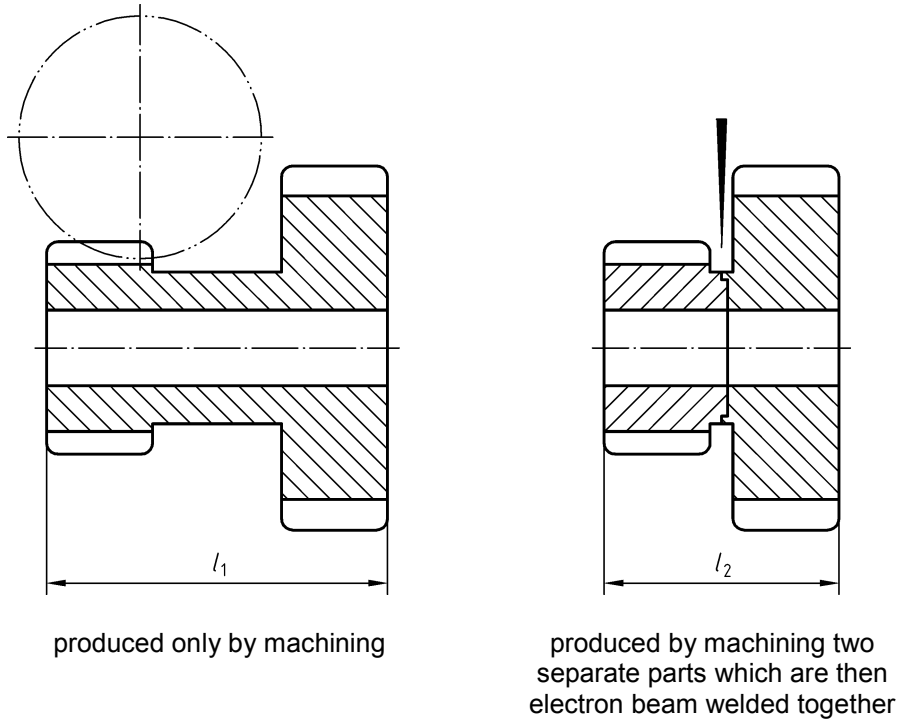


Figure D.8 — Effect of the method of manufacture on the dimensions of gear wheels

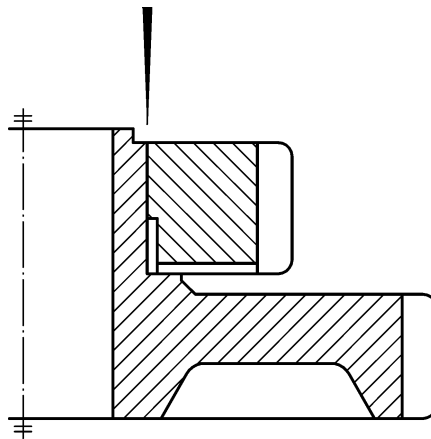


Figure D.9 — Example of a gear wheel with an unsuitable located axial joint. The joint is too close to the central bore

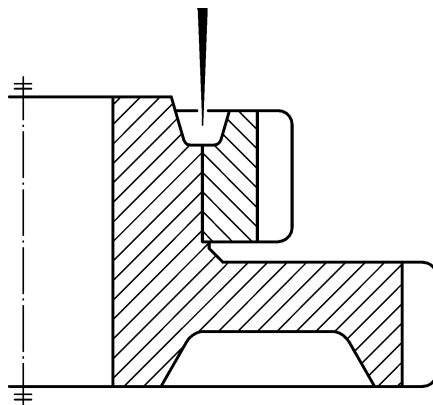


Figure D.10 — Better positioned axial joint compared with Figure D.9. The joint is further from the central bore and the wall thickness has been adapted to suit the required weld strength

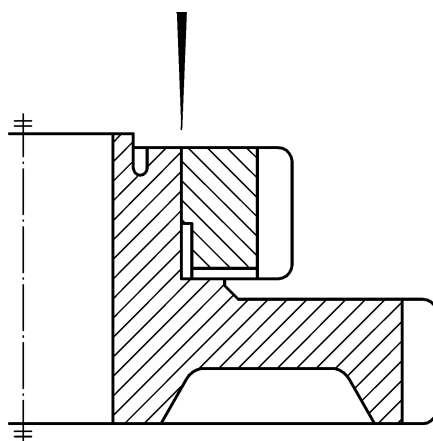


Figure D.11 — Better positioned axial joint compared with Figure D.9. The slot has been included to accommodate radial shrinkage


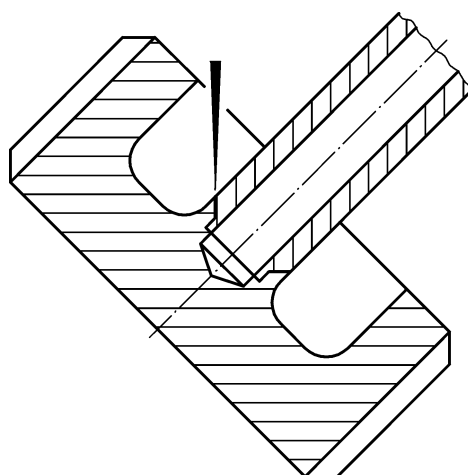


Figure D.12 — Example of a difficult to access electron beam weld

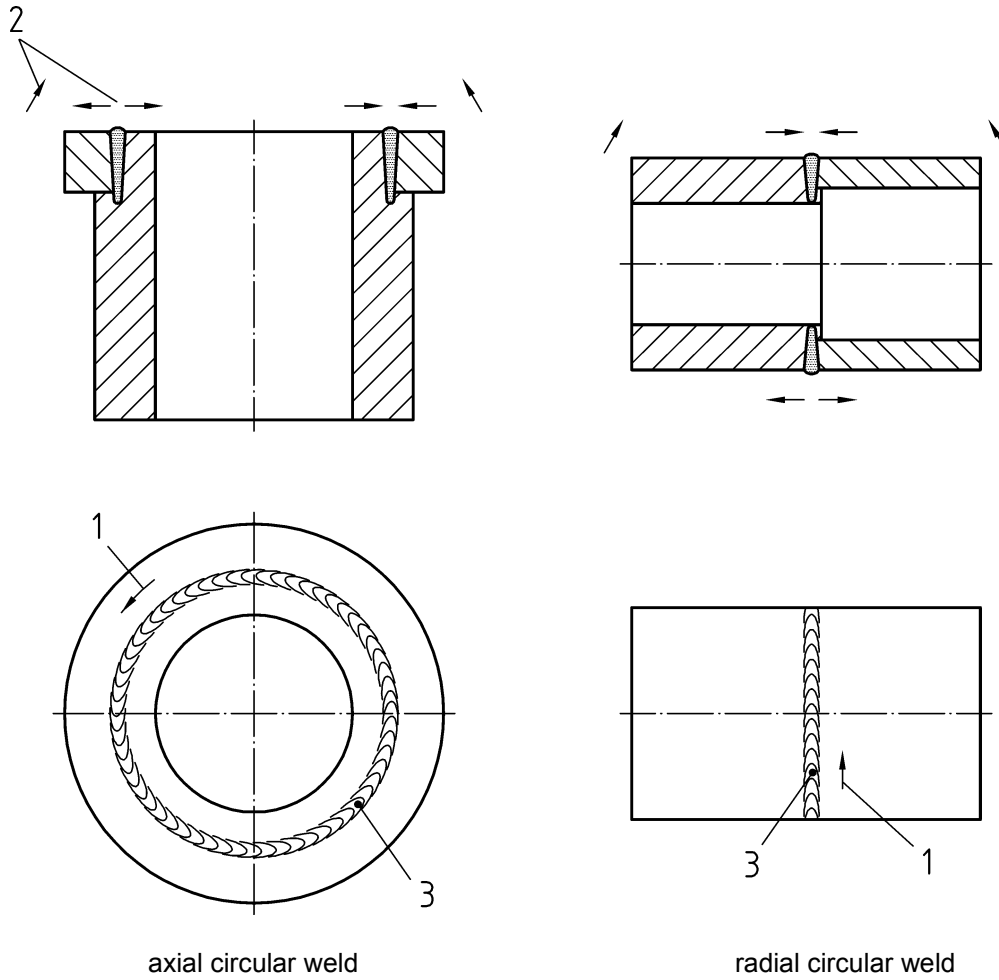

Key

- 1 Work piece moving direction
- 2 Tendency of deformation
- 3 Welding start

Figure D.13 — Relative tendency of axial and radial welds to cause deformation

Bibliography

- [1] EN 573-1, *Aluminium and aluminium alloys — Chemical composition and form of wrought products — Part 1: Numerical designation system*
- [2] EN 729-1, *Quality requirements for welding — Fusion welding of metallic materials — Part 1: Guidelines for selection and use*
- [3] EN 729-2, *Quality requirements for welding — Fusion welding of metallic materials — Part 2: Comprehensive quality requirements*
- [4] EN 729-3, *Quality requirements for welding — Fusion welding of metallic materials — Part 3: Standard quality requirements*
- [5] EN 729-4, *Quality requirements for welding — Fusion welding of metallic materials — Part 4: Elementary quality requirements*
- [6] EN 1011-1, *Welding — Recommendations for welding of metallic materials — Part 1: General guidance for arc welding*
- [7] EN 1173, *Copper and copper alloys — Material condition or temper designation*
- [8] EN 1418, *Welding personnel — Approval testing of welding operators for fusion welding and resistance weld setters for fully mechanized and automatic welding of metallic materials*
- [9] EN ISO 4063, *Welding and allied processes — Nomenclature of processes and reference numbers (ISO 4063:1998)*
- [10] EN ISO 6520-1, *Welding and allied processes — Classification of geometric imperfections in metallic materials — Part 1: Fusion welding (ISO 6520-1:1998)*
- [11] ISO 1190-1, *Copper and copper alloys — Code of designation — Part 1: Designation of materials*
- [12] CR ISO 15608:2000, *Welding — Guidelines for a metallic materials grouping system (ISO/TR 15608:2000)*

BSI — British Standards Institution

BSI is the independent national body responsible for preparing British Standards. It presents the UK view on standards in Europe and at the international level. It is incorporated by Royal Charter.

Revisions

British Standards are updated by amendment or revision. Users of British Standards should make sure that they possess the latest amendments or editions.

It is the constant aim of BSI to improve the quality of our products and services. We would be grateful if anyone finding an inaccuracy or ambiguity while using this British Standard would inform the Secretary of the technical committee responsible, the identity of which can be found on the inside front cover. Tel: +44 (0)20 8996 9000. Fax: +44 (0)20 8996 7400.

BSI offers members an individual updating service called PLUS which ensures that subscribers automatically receive the latest editions of standards.

Buying standards

Orders for all BSI, international and foreign standards publications should be addressed to Customer Services. Tel: +44 (0)20 8996 9001. Fax: +44 (0)20 8996 7001. Email: orders@bsi-global.com. Standards are also available from the BSI website at <http://www.bsi-global.com>.

In response to orders for international standards, it is BSI policy to supply the BSI implementation of those that have been published as British Standards, unless otherwise requested.

Information on standards

BSI provides a wide range of information on national, European and international standards through its Library and its Technical Help to Exporters Service. Various BSI electronic information services are also available which give details on all its products and services. Contact the Information Centre. Tel: +44 (0)20 8996 7111. Fax: +44 (0)20 8996 7048. Email: info@bsi-global.com.

Subscribing members of BSI are kept up to date with standards developments and receive substantial discounts on the purchase price of standards. For details of these and other benefits contact Membership Administration. Tel: +44 (0)20 8996 7002. Fax: +44 (0)20 8996 7001. Email: membership@bsi-global.com.

Information regarding online access to British Standards via British Standards Online can be found at <http://www.bsi-global.com/bsonline>.

Further information about BSI is available on the BSI website at <http://www.bsi-global.com>.

Copyright

Copyright subsists in all BSI publications. BSI also holds the copyright, in the UK, of the publications of the international standardization bodies. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI.

This does not preclude the free use, in the course of implementing the standard, of necessary details such as symbols, and size, type or grade designations. If these details are to be used for any other purpose than implementation then the prior written permission of BSI must be obtained.

Details and advice can be obtained from the Copyright & Licensing Manager. Tel: +44 (0)20 8996 7070. Fax: +44 (0)20 8996 7553. Email: copyright@bsi-global.com.