

Sports mats —

Part 6: Determination of the top friction

The European Standard EN 12503-6:2001 has the status of a British Standard

ICS 97.220.30

National foreword

This British Standard is the official English language version of EN 12503-6:2001. Together with BS EN 12503-1:2001, BS EN 12503-2:2001, BS EN 12503-3:2001, BS EN 12503-4:2001, BS EN 12503-5:2001 and BS EN 12503-7:2001, it supersedes BS 1892-2.10:1990 which will be withdrawn on 15 August 2001.

The UK participation in its preparation was entrusted to Technical Committee SW/14, Gymnasium and sports equipment, which has the responsibility to:

- aid enquirers to understand the text;
- present to the responsible European committee any enquiries on the interpretation, or proposals for change, and keep the UK interests informed;
- monitor related international and European developments and promulgate them in the UK.

A list of organizations represented on this committee can be obtained on request to its secretary.

Cross-references

The British Standards which implement international or European publications referred to in this document may be found in the BSI Standards Catalogue under the section entitled “International Standards Correspondence Index”, or by using the “Find” facility of the BSI Standards Electronic Catalogue.

A British Standard does not purport to include all the necessary provisions of a contract. Users of British Standards are responsible for their correct application.

Compliance with a British Standard does not of itself confer immunity from legal obligations.

This British Standard, having been prepared under the direction of the Consumer Products and Services Sector Committee, was published under the authority of the Standards Committee and comes into effect on 15 June 2001

Summary of pages

This document comprises a front cover, an inside front cover, the EN title page, pages 2 to 6, an inside back cover and a back cover.

The BSI copyright date displayed in this document indicates when the document was last issued.

Amendments issued since publication

Amd. No.	Date	Comments

ICS 97.220.30

English version

Sports mats - Part 6: Determination of the top friction

Tapis de sport - Partie 6: Détermination des caractéristiques antidérapantes de la face supérieure

Sportmatten - Teil 6: Bestimmung der Reibungseigenschaften der Oberseite

This European Standard was approved by CEN on 21 January 2001.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

Management Centre: rue de Stassart, 36 B-1050 Brussels

Contents

	Page
Foreword	2
1 Scope	3
2 Normative references	3
3 Principle	3
4 Apparatus	3
5 Test piece	5
6 Conditioning and test temperature	5
7 Procedure	5
8 Expression of results	5
9 Test report	6

Foreword

This European Standard has been prepared by Technical Committee CEN/TC 136 "Sports, playground and other recreational equipment", the secretariat of which is held by DIN.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by October 2001, and conflicting national standards shall be withdrawn at the latest by October 2001.

This standard EN 12503 "Sports mats" consists of:

Part 1:

Gymnastic mats, safety requirements

Part 2:

Pole vault and high jump mats, safety requirements

Part 3:

Judo mats, safety requirements

Part 4:

Determination of shock absorption

Part 5:

Determination of the base friction

Part 6:

Determination of the top friction

Part 7:

Determination of static stiffness

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and the United Kingdom.

1 Scope

This European Standard specifies a method of test for the determination of the top friction of sports mats types 1 to 8 of EN 12503-1:2001 and type 12 of EN 12503-3:2001.

2 Normative references

This European Standard incorporates, by dated or undated reference, provisions from other publications. These normative references are cited at the appropriate places in the text and the publications are listed hereafter. For dated references, subsequent amendments to or revisions of any of these publications apply to this European Standard only when incorporated in it by amendment or revision. For undated references, the latest edition of the publication referred to applies (including amendments).

EN 12503-1:2001

Sports mats – Part 1: Gymnastic mats, safety requirements

EN 12503-3:2001

Sports mats – Part 3: Judo mats, safety requirements

ISO 48

Rubber, vulcanized or thermoplastic – Determination of hardness (Hardness between 10 IRHD and 100 IRHD)

ISO 4662

Rubber – Determination of rebound resilience of vulcanizates

3 Principle

A gradually increasing torque is applied to a motionless weighted foot positioned on a mat and the torque required to cause initial movement is measured.

4 Apparatus

A rigid disc of diameter (150 ± 2) mm with a central shaft concentrically loaded with annular weights to give a total mass, including the torque wrench of (46 ± 2) kg. To the bottom of the disc is bonded a rubber test sole of diameter (150 ± 2) mm complying with the requirements of table 1.

A rigid stabilising frame with bearings or bushes for the shaft such that the sole remains in the plane of the surface during test and the legs of the frame do not contact the mat.

Dial indicating torque wrench, calibrated in maximum increments of 2,0 Nm with a maximum indicating pointer.

The apparatus is shown schematically in figure 1.

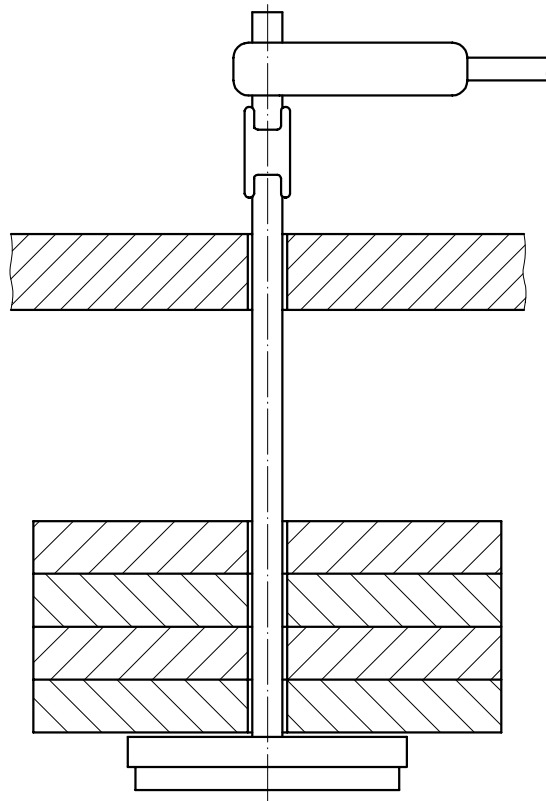


Figure 1 - Apparatus

Table 1 - Properties of rubber sole

Property	Test procedure	Requirement
Resilience	ISO 4662	(21 ± 2) % at 5 °C (24 ± 2) % at 23 °C (28 ± 2) % at 40 °C
Hardness	ISO 48	(96 ± 2) IRHD at (23 ± 2) °C

5 Test piece

The test piece shall be the complete mat.

6 Conditioning and test temperature

Condition the test piece for a minimum of 24 h at (21 ± 3) °C immediately before the test and carry out the test at the same temperature.

7 Procedure

Position the apparatus over the test piece. Place the weighted disc on the test piece and gradually and smoothly apply an increasing rotational force to the torque wrench at a nominal speed of 12 min⁻¹ such that the disc rotates between 90° and 120°.

Repeat the test to obtain eight readings of torque in the same position and note the maximum torque for the last five readings.

Repeat the test to obtain readings at four positions on the mat.

NOTE Processing agents on new materials or particulate materials may contaminate the test sole material and affect the results. It is recommended that the sole be cleaned to remove contamination between each test or new test soles be used.

8 Expression of results

Calculate the mean static rotational friction for the five readings in each position from:

$$\text{Mean static rotational friction} = \frac{3 T}{w D}$$

where:

T is the mean value of torque, in Nm;

w is the vertical force applied to the surface, in N;

D is the diameter of disc, in m.

Determine the static rotational friction as the lowest mean value of the four positions.

9 Test report

The test report shall include the following information:

- a) reference to this test method, i.e. EN 12503-6;
- b) complete identification of the mat tested including type, manufacturer's reference and previous history;
- c) the temperature at which the test was carried out;
- d) the static rotational friction value;
- e) the individual test results if required;
- f) details of any deviation from the procedure.

BSI — British Standards Institution

BSI is the independent national body responsible for preparing British Standards. It presents the UK view on standards in Europe and at the international level. It is incorporated by Royal Charter.

Revisions

British Standards are updated by amendment or revision. Users of British Standards should make sure that they possess the latest amendments or editions.

It is the constant aim of BSI to improve the quality of our products and services. We would be grateful if anyone finding an inaccuracy or ambiguity while using this British Standard would inform the Secretary of the technical committee responsible, the identity of which can be found on the inside front cover. Tel: 020 8996 9000. Fax: 020 8996 7400.

BSI offers members an individual updating service called PLUS which ensures that subscribers automatically receive the latest editions of standards.

Buying standards

Orders for all BSI, international and foreign standards publications should be addressed to Customer Services. Tel: 020 8996 9001. Fax: 020 8996 7001. Standards are also available from the BSI website at <http://www.bsi-global.com>.

In response to orders for international standards, it is BSI policy to supply the BSI implementation of those that have been published as British Standards, unless otherwise requested.

Information on standards

BSI provides a wide range of information on national, European and international standards through its Library and its Technical Help to Exporters Service. Various BSI electronic information services are also available which give details on all its products and services. Contact the Information Centre. Tel: 020 8996 7111. Fax: 020 8996 7048.

Subscribing members of BSI are kept up to date with standards developments and receive substantial discounts on the purchase price of standards. For details of these and other benefits contact Membership Administration. Tel: 020 8996 7002. Fax: 020 8996 7001. Further information about BSI is available on the BSI website at <http://www.bsi-global.com>.

Copyright

Copyright subsists in all BSI publications. BSI also holds the copyright, in the UK, of the publications of the international standardization bodies. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI.

This does not preclude the free use, in the course of implementing the standard, of necessary details such as symbols, and size, type or grade designations. If these details are to be used for any other purpose than implementation then the prior written permission of BSI must be obtained.

If permission is granted, the terms may include royalty payments or a licensing agreement. Details and advice can be obtained from the Copyright Manager. Tel: 020 8996 7070.