

Footwear — Test methods for outsoles — Needle tear strength

The European Standard EN 12773:1999 has the status of a
British Standard

ICS 61.060

National foreword

This British Standard is the official English language version of EN 12773:1999.

The UK participation in its preparation was entrusted to Technical Committee TCI/69, Footwear and leather, which has the responsibility to:

- aid enquirers to understand the text;
- present to the responsible European committee any enquiries on the interpretation, or proposals for change, and keep the UK interests informed;
- monitor related international and European developments and promulgate them in the UK.

A list of organizations represented on this committee can be obtained on request to its secretary.

Cross-references

The British Standards which implement international or European publications referred to in this document may be found in the BSI Standards Catalogue under the section entitled “International Standards Correspondence Index”, or by using the “Find” facility of the BSI Standards Electronic Catalogue.

A British Standard does not purport to include all the necessary provisions of a contract. Users of British Standards are responsible for their correct application.

Compliance with a British Standard does not of itself confer immunity from legal obligations.

Summary of pages

This document comprises a front cover, an inside front cover, the EN title page, pages 2 to 7 and a back cover.

The BSI copyright notice displayed in this document indicates when the document was last issued.

Amendments issued since publication

Amd. No.	Date	Comments

This British Standard, having been prepared under the direction of the Sector Committee for Materials and Chemicals, was published under the authority of the Standards Committee and comes into effect on 15 February 2000

© BSI 02-2000

ISBN 0 580 35616 7

EUROPEAN STANDARD

EN 12773

NORME EUROPÉENNE

EUROPÄISCHE NORM

November 1999

ICS 61.060

English version

Footwear - Test methods for outsoles - Needle tear strength

Chaussures - Méthodes d'essai applicables aux semelles
d'usure - Résistance du point de couture

Schuhwerk - Prüfverfahren für Laufsohlen -
Nadelausreißfestigkeit

This European Standard was approved by CEN on 17 September 1999.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Central Secretariat or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Central Secretariat has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

Central Secretariat: rue de Stassart, 36 B-1050 Brussels

Contents

	Page
Foreword	3
1 Scope.....	4
2 Normative references.....	4
3 Definitions	4
4 Apparatus and material.....	4
5 Sampling and conditioning.....	5
6 Test method.....	6
7 Expression of results.....	6
8 Test report	6

Foreword

This European Standard has been prepared by Technical Committee CEN/TC 309, Footwear, the Secretariat of which is held by AENOR.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by May 2000, and conflicting national standards shall be withdrawn at the latest by May 2000.

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Greece, Iceland, Ireland, Italy, Luxembourg, Netherlands, Norway, Portugal, Spain, Sweden, Switzerland and the United Kingdom.

1 Scope

This European Standard specifies a method for the determination of the needle tear strength for outsoles, irrespective of the material.

2 Normative references

This European Standard incorporates by dated or undated reference, provisions from other publications. These normative references are cited at the appropriate places in the text and the publications are listed hereafter. For dated references, subsequent amendments to or revisions of any of these publications apply to this European Standard only when incorporated in it by amendment or revision. For undated references the latest edition of the publication referred to applies.

EN 10002-2 Metallic materials. Tensile testing - Part 2: Verification of the force measuring system of the tensile testing machines.

EN 12222 Footwear - Standard atmospheres for conditioning and testing of footwear and components for footwear.

prEN 13400:1998 Footwear - Sampling location of components for footwear.

3 Definitions

For the purposes of this standard the following definition applies:

3.1

needle tear strength

the quotient by division of the maximum force, occurring during tearing-out of the needle, by the thickness of the test piece

4 Apparatus and material

The following apparatus and material shall be used:

4.1 Tensile-testing machine

The tensile-testing machine shall comply with the requirements of EN 10002-2, to an accuracy corresponding to grade B, with a constant rate of traverse of 100 mm/min \pm 10 mm/min. Autographic recording of force or a maximum force pointer is recommended.

4.2 Needle

Either a smooth-surfaced steel needle of $1 \text{ mm} \pm 0,01 \text{ mm}$ diameter or a corresponding piece of spring steel wire, ground to a point.

4.3 Clamping device

Figure 1 shows an example of a clamping device. The distance between the support links for the needle shall be adjustable, so that it can be adjusted to the thickness of the specimen. The clamping device shall be equipped with a suitable protective device to prevent the needle from jumping out.

4.4 Thickness gauge

Thickness gauge, standing on a firm base and loaded with a dead weight such that the presser foot applies a pressure of $10 \text{ kPa} \pm 3 \text{ kPa}$. The gauge has a presser foot which is flat, circular and $10 \text{ mm} \pm 0,1 \text{ mm}$ in diameter.

The gauge has a scale division of $0,01 \text{ mm}$.

5 Sampling and conditioning

The test pieces to be tested are taken in accordance with prEN 13400:1998. All test pieces shall be conditioned according to EN 12222 before testing for a minimum of 24 h.

Test pieces are strips of $50 \text{ mm} \pm 1 \text{ mm}$ length and $20 \text{ mm} \pm 1 \text{ mm}$ width. The thickness of the test piece shall be preferably:

- $2,0 \text{ mm} \pm 0,2 \text{ mm}$ for polymeric and elastomeric compact outsoles;
- $4,0 \text{ mm} \pm 0,2 \text{ mm}$ for semi-expanded and cellular outsoles;
- for leather outsoles the original thickness shall be tested.

The test is being performed with at least three specimens. Their uniform thickness (see specification below) shall be obtained by means of an appropriate splitting machine. If feasible, smooth original "skin" surfaces of the sample shall remain unchanged in the specimens. This leads to three possible types of specimen:

- Specimen with 2 original "skins" - S 2
- Specimen with 1 original "skin" - S 1
- Specimen with no original "skin" - S O

The final result shall be based only on specimens of the same type, which shall be stated in the report.

6 Test method

Measure the thickness of the test piece, using the thickness gauge (see 4.4). Pierce the piece with a needle of 1 mm diameter (see 4.2), 5 mm from the edge at the centre of the narrow side (see Figure 1), as nearly perpendicular as possible with the aid of a template. The piece shall not have been previously bored or punched. Place the needle, which is now stuck in the piece, in the clamping device (see 4.3). The distance between the support links shall be adjusted so that they just touch the piece. Clamp the lower end of the piece in the lower grip (shown in Figure 1 as a scissors-clamp). Stress the piece with a feed-rate of 100 mm/min \pm 10 mm/min on the clamps. Read off the maximum strength in newtons which occurs during the tearing-out of the needle.

7 Expression of results

The needle tear strength S_s expressed in newtons per millimetres of thickness is given by the formula

$$S_s = F/d$$

where

F is the maximum force in newtons
 d is the thickness in millimetres

The result will be the average of the three determinations.

8 Test report

The test report shall include the following information:

- a) results, expressed in accordance with clause 7;
- b) thickness of the test pieces;
- c) full description of the samples tested including commercial styles, codes, colours, nature, etc.;
- d) reference to this method of test;
- e) date of testing;
- f) any deviation from this test method.

Dimensions in mm

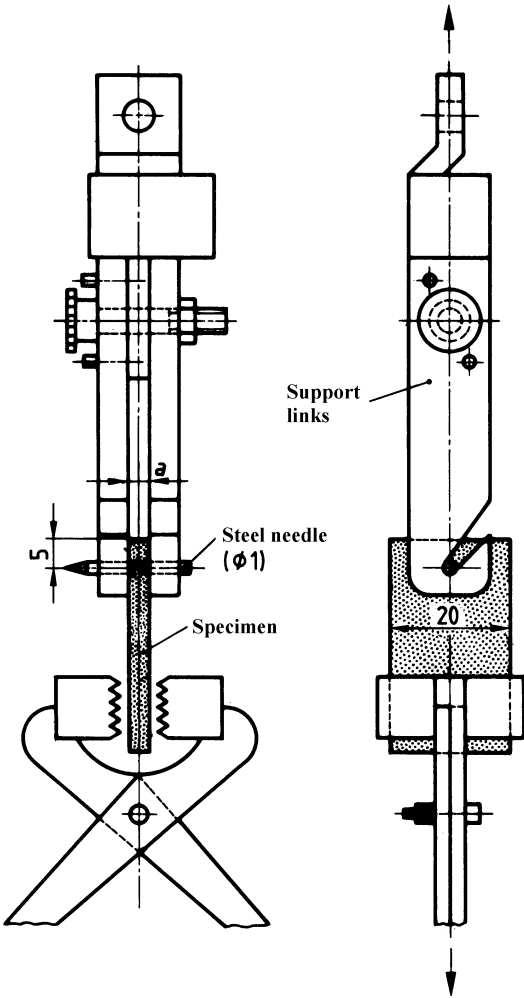


Figure 1 - Example of clamping device

BSI — British Standards Institution

BSI is the independent national body responsible for preparing British Standards. It presents the UK view on standards in Europe and at the international level. It is incorporated by Royal Charter.

Revisions

British Standards are updated by amendment or revision. Users of British Standards should make sure that they possess the latest amendments or editions.

It is the constant aim of BSI to improve the quality of our products and services. We would be grateful if anyone finding an inaccuracy or ambiguity while using this British Standard would inform the Secretary of the technical committee responsible, the identity of which can be found on the inside front cover. Tel: 020 8996 9000. Fax: 020 8996 7400.

BSI offers members an individual updating service called PLUS which ensures that subscribers automatically receive the latest editions of standards.

Buying standards

Orders for all BSI, international and foreign standards publications should be addressed to Customer Services. Tel: 020 8996 9001. Fax: 020 8996 7001.

In response to orders for international standards, it is BSI policy to supply the BSI implementation of those that have been published as British Standards, unless otherwise requested.

Information on standards

BSI provides a wide range of information on national, European and international standards through its Library and its Technical Help to Exporters Service. Various BSI electronic information services are also available which give details on all its products and services. Contact the Information Centre. Tel: 020 8996 7111. Fax: 020 8996 7048.

Subscribing members of BSI are kept up to date with standards developments and receive substantial discounts on the purchase price of standards. For details of these and other benefits contact Membership Administration. Tel: 020 8996 7002. Fax: 020 8996 7001.

Copyright

Copyright subsists in all BSI publications. BSI also holds the copyright, in the UK, of the publications of the international standardization bodies. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI.

This does not preclude the free use, in the course of implementing the standard, of necessary details such as symbols, and size, type or grade designations. If these details are to be used for any other purpose than implementation then the prior written permission of BSI must be obtained.

If permission is granted, the terms may include royalty payments or a licensing agreement. Details and advice can be obtained from the Copyright Manager. Tel: 020 8996 7070.